



Approval body for construction products and types of construction

Bautechnisches Prüfamt

An institution established by the Federal and Laender Governments



European Technical Assessment

ETA-15/0890 of 14 December 2015

English translation prepared by DIBt - Original version in German language

General Part

Technical Assessment Body issuing the European Technical Assessment:

Trade name of the construction product

Product family to which the construction product belongs

Manufacturer

Manufacturing plant

This European Technical Assessment contains

This European Technical Assessment is issued in accordance with Regulation (EU) No 305/2011, on the basis of

Deutsches Institut für Bautechnik

BTV injection system KM for masonry

Injection system for use in masonry

BTV Bautechnik Vertriebs-GmbH Gartenstraße 43/1 72764 Reutlingen DEUTSCHLAND

BTV Werk 1

26 pages including 3 annexes which form an integral part of this assessment

Guideline for European technical approval of "Metal Injection Anchors for Use in Masonry", ETAG 029, April 2013,

used as European Assessment Document (EAD) according to Article 66 Paragraph 3 of Regulation (EU) No 305/2011.



European Technical Assessment ETA-15/0890

Page 2 of 26 | 14 December 2015

English translation prepared by DIBt

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.



European Technical Assessment ETA-15/0890 English translation prepared by DIBt

Page 3 of 26 | 14 December 2015

Specific Part

1 Technical description of the product

The BTV injection system KM for masonry is a bonded anchor (injection type) consisting of a mortar cartridge with injection mortar KM Winter, KM and KM Summer, a perforated sieve sleeve and an anchor rod with hexagon nut and washer or an internal threaded rod. The steel elements are made of zinc coated steel, stainless steel or high corrosion resistant steel.

The anchor rod is placed into a drilled hole filled with injection mortar and is anchored via the bond between steel element, injection mortar and masonry and mechanical interlock.

The product description is given in Annex A.

2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment

3.1 Mechanical resistance and stability (BWR 1)

Essential characteristic	Performance
Characteristic resistance for tension and shear loads	See Annex C 1 – C 4
Characteristic resistance for bending moments	See Annex C 5
Displacements under shear and tension loads	See Annex C 5
Reduction Factor for job site tests (β-Factor)	See Annex C 6
Edge distances and spacing	See Annex C 7 – C8

3.2 Safety in case of fire (BWR 2)

Essential characteristic	Performance
Reaction to fire	Anchorages satisfy requirements for Class A1
Resistance to fire	No performance assessed

3.3 Hygiene, health and the environment (BWR 3)

Regarding dangerous substances there may be requirements (e.g. transposed European legislation and national laws, regulations and administrative provisions) applicable to the products falling within the scope of this European Technical Assessment. In order to meet the provisions of Regulation (EU) No 305/2011, these requirements need also to be complied with, when and where they apply.





European Technical Assessment ETA-15/0890

Page 4 of 26 | 14 December 2015

English translation prepared by DIBt

3.4 Safety in use (BWR 4)

The essential characteristics regarding Safety in use are included under the Basic Works Requirement Mechanical resistance and stability.

4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with guideline for European technical approval ETAG 029, April 2013 used as European Assessment Document (EAD) according to Article 66 Paragraph 3 of Regulation (EU) No 305/2011 the applicable European legal act is: [97/177/EC].

The system to be applied is: 1

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Deutsches Institut für Bautechnik.


Issued in Berlin on 14 December 2015 by Deutsches Institut für Bautechnik

Uwe Benderbeglaubigt:Head of DepartmentWittstock



Installation conditions part 1;


Threaded rods with perforated sleeve; Installation in perforated and solid brick masonry

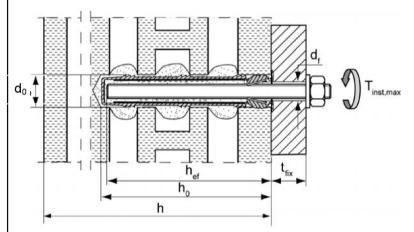

Pre-positioned installation

perforated sleeve 12x85 perforated sleeve 16x85 perforated sleeve 16x130 perforated sleeve 20x85 perforated sleeve 20x130 perforated sleeve 20x200

Internal threaded anchors with perforated sleeve; Installation in perforated and solid brick masonry

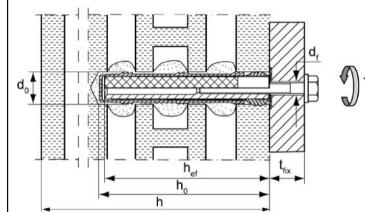

Pre-positioned installation

perforated sleeve 16x85 –
Internal threaded anchors 11x85 M6 and M8
perforated sleeve 20x85Internal threaded anchors 15x85 M10 and M12

h_{ef} = effective anchorage depth

h₀ = depth of drill hole t_{fix} = thickness of fixture h = thickness of masonry d₀= nominal drill bit diameter

d_f= diameter of clearance hole in the fixture

 $\Gamma_{\text{inst.max}} = \text{maximum torque moment}$

BTV injection system KM for masonry

Product description

Installation condition, part 1: in perforated and solid brick masonry


Annex A 1




Installation conditions part 2;

Threaded rods without perforated sleeve; Installation in solid brick masonry and autoclaved aerated concrete


Pre-positioned installation

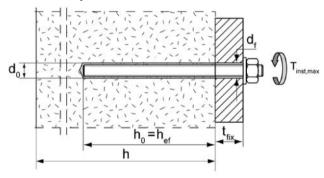

Push through installation

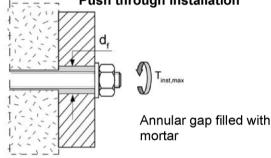

Internal threaded anchors without perforated sleeve; Installation in solid brick masonry and autoclaved aerated concrete

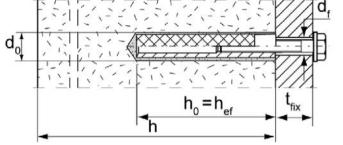



Pre-positioned installation

Internal threaded anchors 11x85 M6 Internal threaded anchors 11x85 M8 Internal threaded anchors 15x85 M10 Internal threaded anchors 15x85 M12

 h_{ef} = effective anchorage depth

 $h_0 =$ depth of drill hole $t_{fix} =$ thickness of fixture

h = thickness of masonry

 $\mathsf{T}_{\mathsf{inst}}$

d₀= nominal drill bit diameter

d_f= diameter of clearance hole in the fixture

_{inst.max} = maximum torque moment

BTV injection system KM for masonry

Product description

Installation condition, part 2: in solid brick masonry and autoclaved aerated concrete

Annex A 2



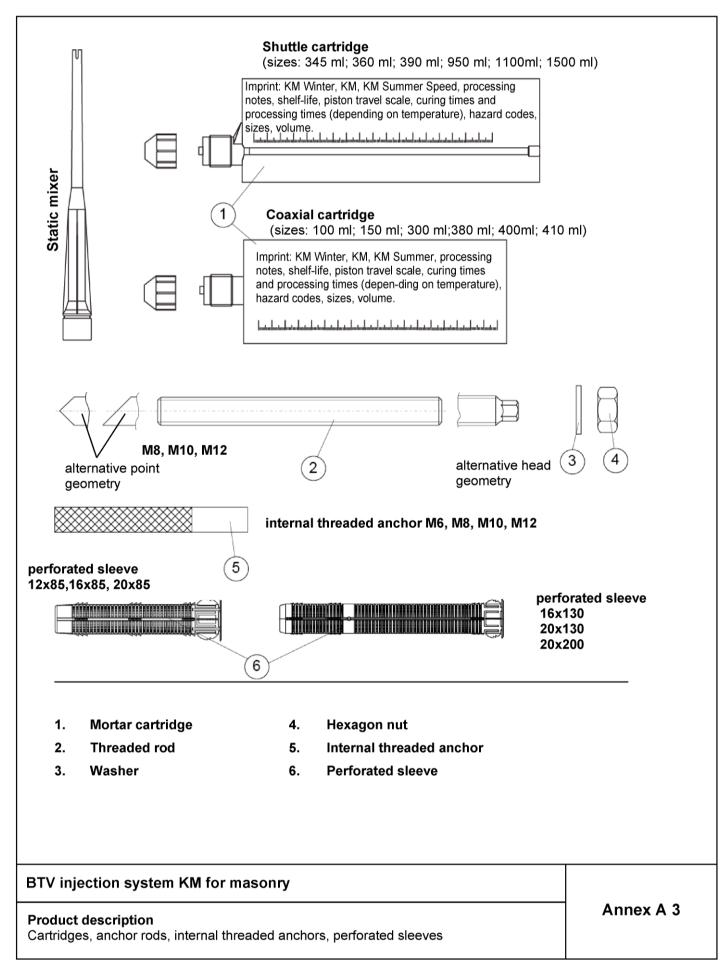




Table A1: Materials

Part	Designation	Material						
1	Mortar cartridge	r	nortar, hardener; filler					
		Steel, zinc plated Stainless steel A4		High corrosion- resistant steel C				
2	Threaded rod	Property class 5.8 or 8.8; EN ISO 898-1:2013 zinc plated \geq 5 μ m, EN ISO 4042:1999 A2K or hot-dip galvanised EN ISO 10684:2004 $f_{uk} \leq$ 1000 N/mm ² $A_5 > 8\%$	Property class 50, 70 or 80 EN ISO 3506:2009 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362; 1.4062 EN 10088-1:2014 $f_{uk} \le 1000 \text{ N/mm}^2$ $A_5 > 8\%$	Property class 50 or 80 EN ISO 3506:2009 or property class 70 with f_{yk} = 560 N/mm ² 1.4565; 1.4529 EN 10088-1:2014 $f_{uk} \le 1000$ N/mm ² $A_5 > 8\%$				
3	Washer ISO 7089:2000	zinc plated ≥ 5µm, EN ISO 4042:1999 A2K or hot-dip galvanised ISO 10684:2004	1.4401; 1.4404; 1.4578;1.4571; 1.4439; 1.4362 EN 10088-1:2014	1.4565;1.4529 EN 10088-1:2014				
4	Hexagon nut	Property class 5 or 8; EN ISO 898-2:2013 zinc plated ≥ 5µm, ISO 4042:1999 A2K or hot-dip galvanised ISO 10684:2004	Property class 50, 70 or 80 ISO 3506:2009 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362 EN 10088-1:2014	Property class 50, 70 or 80 ISO 3506:2009 1.4565; 1.4529 EN 10088-1:2014				
5	Internal threaded anchor	Property class 5.8; EN 10277-1:2008 zinc plated ≥ 5µm, EN ISO 4042:1999 A2K	Property class 70 EN ISO 3506:2009 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362 EN 10088-1:2014	Property class 70 EN ISO 3506-1:2009 1.4565; 1.4529 EN 10088-1:2014				
	Screw or threaded rod for internal threaded anchor	Property class 5.8 or 8.8; EN ISO 898-1:2013 zinc plated ≥ 5µm, ISO 4042:1999 A2K	Property class 70 EN ISO 3506:2009 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362 EN 10088-1:2014	Property class 70 EN ISO 3506-1:2009 1.4565; 1.4529 EN 10088-1:2014				
6	Perforated sleeve		PP / PE					

BTV injection system KM for masonry	
Product description Materials	Annex A 4



Specifications of intended use part 1

Anchorages subject to:

Static and quasi-static loads

Base materials:

- Solid brick masonry (Use category b) and autoclaved aerated concrete (Use category d), acc. to Annex B8.
 Note: The characteristic resistance is also valid for larger brick sizes and higher compressive strength of the masonry unit.
- · Hollow brick masonry (use category c), according to Annex B8
- Mortar strength class of the masonry M2,5 at minimum according to EN 998-2:2010
- For other bricks in solid masonry, hollow or perforated masonry and autoclaved aerated concrete, the characteristic resistance of the anchor may be determined by job site tests according to ETAG 029, Annex B under consideration of the β-factor according to Annex C6, Table C4

Temperature Range:

• I: From - 40°C to +80°C (max. short term temperature +80°C and max. long term temperature +50°C)

Use conditions (Environmental conditions):

- Dry and wet structure (regarding injection mortar)
- Structures subject to dry internal conditions exist (zinc coated steel, stainless steel or high corrosion resistant steel)
- Structures subject to external atmospheric exposure including industrial and marine environment or exposure to permanently damp internal condition, if no particular aggressive conditions exist (stainless steel or high corrosion resistant steel)
- Structures subject to external atmospheric exposure and to permanently damp internal condition, if other particular aggressive conditions exist (high corrosion resistant steel)
 - Note: Particular aggressive conditions are e.g. permanent, alternating immersion in seawater or the splash zone of seawater, chloride atmosphere of indoor swimming pools or atmosphere with extreme chemical pollution (e.g. in desulphurization plants or road tunnels where de-icing materials are used)

BTV injection system KM for masonry	
Intended Use Specifications part 1	Annex B 1



Specifications of intended use part 2

Design:

- The anchorages have to be designed in accordance with the ETAG 029, Annex C, Design method A under the responsibility of an engineer experienced in anchorages and masonry work
 - Applies to all bricks, if no other values are specified:

$$N_{Rk} = N_{Rk,s} = N_{Rk,p} = N_{Rk,b} = N_{Rk,pb}$$

$$V_{Rk} = V_{Rk,s} = V_{Rk,b} = V_{Rk,c} = V_{Rk,pb}$$

Verifiable calculation notes and drawings have to be prepared taking account the relevant masonry in the
region of the anchorage, the loads to be transmitted and their transmission to the supports of the structure. The
position of the anchor is indicated on the design drawings

Installation:

- Category d/d: -Installation and use in dry structures
- · Category w/w: -Installation and use in dry and wet structures
- Hole drilling by hammer drill mode
- · In case of aborted hole: The hole shall be filled with mortar
- Bridging of unbearing layer (e.g. plaster) see Annex B 4 (Table B1.3)
- Anchor installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site
- Fastening screws or threaded rods (including nut and washer) must comply with the appropriate material and property class of the internal threaded anchor
- minimum curing time see Annex B5. Table B3
- Commercial standard threaded rods, washers and hexagon nuts may also be used if the following requirements are fulfilled:


Material dimensions and mechanical properties of the metal parts according to the specifications are given in Annex A4, Table A1

Conformation of material and mechanical properties of the metal parts by inspection certificate 3.1 according to EN 10204:2004, the documents shall be stored

Marking of the threaded rod with the envisage embedment depth. This may be done by the manufacturer of the rod or by a person on job site

BTV injection system KM for masonry	
Intended Use Specifications part 2	Annex B 2



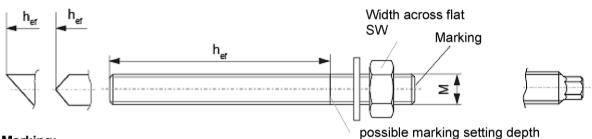

Marking:

Property class 8.8 or high corrosion-resistant steel C, property class 80: •

Stainless steel A4, property class 50 and high corrosion-resistant steel C, property class 50: ••

Table B1.1: Installation parameters for threaded rod without perforated sleeve

Size	•			M8	M10	M12		
Nominal drill hole diame	eter	$d_{nom}=d_0$	[mm]	10	12 14			
Width across flat		SW	[mm]	13	17	19		
Effective anchorage dep	oth ¹⁾	$h_{\rm ef,min}$	[mm]		50			
Depth of drill hole $h_0 = h$	n _{ef}	h _{ef,max}	[mm]	h-30 and ≤ 200 mm				
Effective anchorage depth AAC		$h_{ m ef,min}$	mm]	100				
Ellective afficilitiage dep	DIIIAAC	h _{ef,max}	[mm]	120				
Maximum torque mome	nt	$T_{inst,max}$	[Nm]	10				
Max. torque moment for	autoclaved aerated concrete	$T_{inst,max}$	[Nm]	1	1 2			
Diameter of clearance	Pre-position anchorage	d _f ≤	[mm]	9	12	14		
hole in the fixture	Push through anchorage	d _f ≤	[mm]	11	14	16		

¹⁾ $h_{ef,min} \le h_{ef} \le h_{ef,max}$ is possible.

internal threaded anchor

Marking: size, e.g. M8 stainless steel A4: e.g. M8 A4 high corrosion-resistant steel C: e.g. M8 C

Table B1.2: Installation parameters for internal threaded anchor without perforated sleeve

Size			M6	M8	M10	M12	
diameter of internal threaded anchor	d_H	[mm]	1	1	1	5	
Nominal drill hole diameter	$d_{nom}=d_0$	[mm]	1	4	1	8	
Depth of drill hole	h_0	[mm]			85		
Effective anchorage depth	$L_H=h_{ef}$	[mm]	85				
Maximum torque moment	T _{inst, max}	[Nm]	4	4 10			
Max. torque moment for	т	[Nm]	,	1		2	
autoclaved aerated concrete	$T_{inst,\;max}$	נואוון		'	2		
Diameter of clearance hole in the	d₅≤	[mm]	7	9	12	14	
fixture	u _f ≥	[mm]	,		12	14	
Screw-in depth	$L_{E,min}$	[mm]	6	8	10	12	

BTV injection system KM for masonry	
Intended Use Installation parameters, part 1	Annex B 3



Perforated sleeves 12x85; 16x85; 16x130; 20x85; 20x130; 20x200

Marking:size $D_{Sleeve} \times L_{Sleeve}$ e.g. 16x85






Table B1.3: Installation parameters (threaded rod and internal threaded anchor with perforated sleeve; only pre-positioned anchorage)

Size Perforated sleeves	;		12x85	16x85	16x130 ²⁾	20x85	20x130 ²⁾	20x200 ²⁾
Nominal drill hole diameter (d ₀ = D _{Sleeve})	$d_{nom}=d_0$	[mm]	12	,	16		20	
Depth of drill hole	h_0	[mm]	90	90	135	90	135	205
Effective anchorage depth ¹⁾	$h_{\text{ef},\text{min}}$	[mm]	85	85	110	85	110	180
	h _{ef,max}	[mm]	85	85	130	85	130	200
Size of threaded rod		[-]	M8	М8	, M 10		M12	
Size of internal threaded anchor		[-]		11x85 M6/M8		11x85 M10/M12		
Maximum torque moment threaded rod and internal threaded anchor	$T_{inst,max}$	[mm]				2		

BTV injection system KM for masonry	
Intended Use Installation parameters, part 2.	Annex B 4

 $^{^{1)}}$ $h_{ef,min} \le h_{ef} \le h_{ef,max}$ is possible. $^{2)}$ Bridging of unbearing layer (e.g. plaster) possible



Steel brush BS



Only for solid bricks and aerated concrete

Table B2: Parameters of steel brush

Drill hole diameter	do	[mm]	10	12	14	16	18	20
Brush diameter	$d_{b,nom}$	[mm]	11	14	16	20	20	25

Table B3: Maximum processing time of the mortar and minimum curing time (During the curing time of the mortar the masonry temperature may not fall below the listed minimum temperature).

			Minimum curing time ¹⁾ t _{cure} [minutes]				
Temperature at anchoring base [°C]		KM Winter	КМ	KM Summer ²⁾			
-10	to	-5	12 hours	-	-		
>-5	to	±0	3 hours	24 hours	-		
>±0	to	+5	90	3 hours	6 hours		
>+5	to	+10	45	90	3 hours		
>+10	to	+20	30	60	2 hours		
>+20	to	+30	-	45	60		
>+30	to	+40	-	35	30		

System-	Maximum processing time t _{work} [minutes]					
temperature (mortar) [°C]	KM Winter ³⁾	KM ²⁾	KM Summer			
-	-	-	-			
±0	5	-	-			
+5	5	13	20			
+10	3	9	20			
+20	1	5	10			
+30	-	4	6			
+40	-	2	4			

BTV injection system KM for masonry	
Intended Use Steel brush	Annex B 5
Processing times and curing times	


¹⁾ For wet bricks the curing time must be doubled ²⁾ Minimum cartridge temperature +5°C

³⁾ Minimum cartridge temperature ±0°C




Installation instructions part 1


Installation and Preparing the cartridge in solid brick and autoclaved aerated concrete (without perforated sleeve)



Drill the hole. Depth of drill hole h₀ and drill hole diameter d₀ see Table **B1.1** or **B1.2**

2








Blow out the drill hole two times by hand. Brush the drill hole two times using an adequate steel brush (see Table B2) and blow out two times again

3




Remove the sealing cap



Screw on the static mixer (the spiral in the static mixer must be clearly visible)

4




Place the cartridge into a suitable dispenser.




Press out approximately 10 cm of material until the mortar is permanently grey in colour. Mortar which is not grey in colour will not cure and must be disposed off.

5




Fill approximately 2/3 of the drill hole with mortar Always begin from the bottom of the hole to eliminate voids¹⁾.



For push through installation (not internal threaded anchor) fill the annular gap also with mortar.

6




Only use clean and oil-free anchor elements. Mark the threaded rod for setting depth. Press the threaded rod or internal threaded anchor down to the bottom of the hole, turning it slightly by hand while doing. After inserting the anchor element, excess mortar must emerge around the anchor element.

7



Wait for the specified curing time t_{cure} see Table ${f B3}$



Mounting the fixture
T_{inst.max} see Table **B1.1** or **B1.2**

BTV injection system KM for masonry Intended Use Installation instructions part 1 in solid brick and autoclaved aerated concrete Annex B 6

¹⁾ For the exact quantity of mortar see manufacturer`s specification.

Installation instructions part 2

Installation in perforated or solid brick with perforated sleeve (pre-positioned anchorage)

2

Drill the hole. Depth of drill hole h₀ and drill hole diameter d₀ see Table **B1.3**

When install perforated sleeves in solid bricks or solid areas of hollow bricks, also clean the hole by blowing out and brushing




Remove the sealing cap



Screw on the static mixer (the spiral in the static mixer must be clearly visible)

3




Place the cartridge into a suitable dispenser



Press out approximately 10 cm of material until the mortar is permanent-ly grey in colour. Mortar which is not grey in colour will not cure and must be disposed




Insert the perforated sleeve flush with the surface of the masonry or plaster



Fill the perforated sleeve completely with mortar beginning from the bottom of the hole¹⁾.

5





Only use clean and oil-free anchor elements. Mark the threaded rod for setting depth. Insert the threaded rod or the internal threaded anchor by hand using light turning motions until reaching the setting depth marking (threaded rod) or flush with the surface (internal threaded anchor).



Wait for the specified curing time t_{cure} see Table ${\bf B3}$



Mounting the fixture.
T_{inst,max} see Table B1.3

BTV injection system KM for masonry

Intended Use

Installation instructions part 2 in hollow brick masonry

Annex B 7

electronic copy of the eta by dibt: eta-15/0890

¹⁾ For the exact quantity of mortar see manufacturer's specification.

English translation prepared by DIBt

electronic copy of the eta by dibt: eta-15/0890



Table B 4: Summary of bricks and blocks

Brick No. 1 Solid brick Mz according to EN 771-2 $\rho \ge 1.8 \text{ [kg/dm}^3\text{]}$ fb $\ge 10 \text{ or } 20 \text{ [N/mm}^2\text{]}$	115		Brick No. 6 Perforated brick HLz according to EN 771-1 ρ≥ 1,4 [kg/dm³] fb≥ 20 [N/mm²]		8 + 14 + 8 + 28 + 28 + 28 + 28 + 28 + 28 + 28
Brick No. 2 Solid sand-lime brick according to EN 771-2 $\rho \ge 1.8$ [kg/dm ³] fb ≥ 10 or 20 [N/mm ²]	118		Brick No. 7 Perforated brick HLz according to EN 771-1 ρ≥ 1,0 [kg/dm³] fb≥ 10 [N/mm²]	TO DESIGNATION OF THE PARTY OF	
Brick No. 3 Solid sand-lime brick according to EN 771-2 $\rho \ge 1.8 \text{ [kg/dm}^3\text{]}$ fb $\ge 10 \text{ or } 20$ [N/mm ²]	\$ 8 S S S S S S S S S S S S S S S S S S		Brick No. 8 Perforated brick HLz filled with mineral wool according to EN 771-1 ρ≥ 0,6 [kg/dm³] fb≥ 8 [N/mm²]	3	¥ 10 112 55
Brick No. 4 Sand-lime hollow brick according to EN 771-2 ρ≥ 1,4 [kg/dm³] fb≥ 12 or 20 [N/mm²]	115	21 9 14 42 71 14 142 17 17 18 18 18 18 18 18 18 18 18 18 18 18 18	Brick-No. 9 Light-weight concrete hollow block HbI according to EN 771-1 ρ≥ 1,0 [kg/dm³] fb≥ 4 [N/mm²]	DE THE THE THE THE THE THE THE THE THE TH	8 2 76 1 76 1 76 1 76 1 76 1 76 1 76 1 76
Brick No. 5 Perforated brick HLz according to EN 771-1 ρ ≥ 0,9 [kg/dm³] fb ≥ 10 [N/mm²]	THE STATE OF THE S	9. 12. 12. 10.	Brick No. 10 Autoclaved aerated concrete block $\rho \ge 350, 500 \text{ or } 650$ [kg/dm³] fb $\ge 2, 4 \text{ or } 6$ [N/mm²]		

Imaging of the bricks are not scaled

BTV injection system KM for masonry	
Intended Use Types and dimensions of blocks and bricks	Annex B 8



Table B5.1: Allocation of threaded rods¹⁾, perforated sleeves¹⁾²⁾ and solid bricks

Kind of masonry Brick		Valid anchor rods, perforated sleeves and internal threaded anchor			
Brick No. 1 Solid brick Mz according to EN 771-2 $\rho \ge 1.8$ [kg/dm ³] fb ≥ 10 or 20 [N/mm ²]	110		M8; M10; M12 internal threaded anchor 11x85 M6, M8		
Brick No. 2 Solid sand-lime brick according to EN 771-2 $\rho \ge 1.8$ [kg/dm ³] fb ≥ 10 or 20 [N/mm ²]	a _b		M8; M10; M12 internal threaded anchor 11x85 M6, M8		
Brick No. 3 Solid sand-lime brick according to EN 771-2 ρ≥ 1,8 [kg/dm³] fb ≥ 10 or 20 [N/mm²]	36 S		perforated sleeves 12x85 16x85 20x85 16x130 20x130		
Brick No. 4 Sand-lime hollow brick according to EN 771-2 ρ≥1,4 [kg/dm³] fb≥12 or 20 [N/mm²]	SEL - AND -		perforated sleeves 12x85 16x85 20x85 16x130 20x130		
Brick No. 5 Perforated brick HLz according to EN 771-1 ρ ≥ 0,9 [kg/dm³] fb ≥ 10 [N/mm²]	113 113 115		perforated sleeves 12x85 16x85 20x85 16x130 20x130		
Brick No. 6 Perforated brick HLz according to EN 771-1 ρ≥1,4 [kg/dm³] fb≥20 [N/mm²]			perforated sleeves 12x85 16x85 20x85		

¹⁾ Other combinations can be used after job site tests acc. to ETAG 029, Annex B. ²⁾ Sleeve/anchor rod combination see table B1.3

The β - factor for this job site tests are given in Table C4

Imaging of the bricks are not scaled

BTV injection system KM for masonry	
Intended Use Allocation of threaded rods, perforated sleeves, internal threaded anchor and bricks, part 1	Annex B 9



Table B5.2: Allocation of threaded rods¹⁾, perforated sleeves¹⁾²⁾ and perforated or solid bricks

Kind of masonry	Brick	Valid anchor rods, perforated sleeves and internal threaded anchor				
Brick No. 7 Perforated brick HLz according to EN 771-1 ρ≥ 1,0 [kg/dm³] fb≥ 10 [N/mm²]	1000 ORE 0.55 (ED)		perforated sleeves 12x85 16x85 20x85 20x130			
Brick No. 8 Perforated brick HLz filled with mineral wool according to EN 771-1 ρ≥ 0,6 [kg/dm³] fb≥ 8 [N/mm²]			12x85 16x85 20x85 16x130 20x130 20x200			
Brick-No. 9 Light-weight concrete hollow block Hbl according to EN 771-1 $\rho \ge 1,0$ [kg/dm ³] fb ≥ 4 [N/mm ²]	100		perforated sleeves 12x85 16x85 20x85 16x130 20x130			
Brick No. 10 Autoclaved aerated concrete block $\rho \ge 350, 500 \text{ or } 650$ [kg/dm³] fb $\ge 2, 4 \text{ or } 6$ [N/mm²]	R		M8; M10; M12 internal threaded anchor 11x85 M6 11x85 M8 15x85 M10 15x85 M12			

¹⁾ Other combinations can be used after job site tests acc. to ETAG 029, Annex B.

The β - factor for this job site tests are given in Table C4

Imaging of the bricks are not scaled

BTV injection system KM for masonry	
Intended Use Allocation of threaded rods, perforated sleeves, internal threaded anchor and bricks, part 2	Annex B 10

²⁾Sleeve/anchor rod combination see table B1.3



Table C1.1: Characteristic values of resistance under tension loads and under shear loads

	Density ρ			Effec		Characteristic resistance [kN]						
Brick	[kg/dm ³]	Perforated	Anchor size or screw	ancho dep		N _{Rk}		V _{Rk}				
Brick	Compressive strength f _b	sleeve	size in internal threaded anchor	h _{ef,min} h _{ef,max}		Temp.		All categories				
	[N/mm ²]			[mm]	[mm]	d/d	w/w	Ű				
			M8	50	200	4,0	2,5	2,5				
			M10	50	79	3,5	2,0	4,0				
			M10	80	199	5,0	3,0					
	ρ≥ 1,8		M10	200	200	8,5	7,5	8,5				
	f _b ≥ 10		M12	50	79	3,0	2,0	4,0				
116			M12	80	199	5,5	3,5	4,0				
E			M12	200	200	8,0	5,0	8,5				
E .			11x85 M6/ M8	85	85	5,5	3,5	2,5				
* 340		without	M8	50	200	5,5	3,5	4,0				
No.1			M10	50	79	5,0	3,0	6.0				
Solid brick Mz	ρ≥ 1,8 f _b ≥ 20		M10	80	199	7,0	4,5	6,0				
			M10	200	200	8,5	8,5	8,5				
			M12	50	79	4,5	3,0	5,5				
			M12	80	199	8,0	5,0					
			M12	200	200	8,5	7,0	8,5				
			11x85 M6/ M8	85	85	8,0	5,0	4,0				
			M8	50	200	2,5 1,5						
			M10	50	79		1,5	4.0				
			M10	80	199			4,0				
	ρ≥ 1,8		M10	200	200	8,5	6,0					
	f _b ≥ 10		M12	50	79	2,5	1,5					
115			M12	80	199	2,5	1,5	5,0				
E C			M12	200	200	8,5	6,5					
		without	11x85 M6/ M8	85	85	2,5	1,5	3,0				
240			M8	50	200							
No.2			M10	50	79	3,5	2,0	5,5				
Solid sand-lime brick			M10	80	199] 3,5				
	ρ≥ 1,8 f _b ≥ 20		M10	200	200	8,5	8,5					
	1b = 20		M12	50	79	3,5	2,0					
			M12	80	199	3,5	2,0	7,0				
			M12	200	200	8,5	8,5					
							11x85 M6/ M8	85	85	3,5	2,0	4,0

Imaging of the bricks are not scaled

BTV injection system KM for masonry	
Performances Characteristic values of resistance under tension loads and under shear loads, part 1	Annex C 1



Characteristic values of resistance under tension loads and under

	Density ρ		Anchor size or		Effective anchorage		Characteristic resistance [kN]					
Brick	[kg/dm³] - Compressive strength f _b	[kg/am]	[kg/am] -	[kg/am] -	[kg/am] -	Perforated sleeve	screw size in	d€	epth	N	Rk	V_{Rk}
		Sieeve	internal threaded		h _{ef,max}	Te: 50/8	mp. 30°C	All categories				
	[N/mm ²]			h _{ef,min} [mm]	[mm]	d/d	w/w					
		12x85	M8	85	85	6,0	3,5	3,0				
		16x85	11x85 M6	85	85	3,5	2,0	3,0				
	ρ ≥ 1,8 f _b ≥ 10	16x85	M8/M10, 11x85 M8	85	85	3,5	2,0					
E 18	1 ₀ = 10	20x85	M12, 15x85 M10/M12	85	85	8,5	6,5	3,5				
= 1.30.		16x130	M8/M10	110	130	3,5	2,0					
34		20x130	M12	110	130	7,0	4,5					
**	ρ≥ 1,8	12x85	M8	85	85	8,5	5,0	4,5				
No.3	f _b ≥ 20	16x85	11x85 M6	85	85	5,5	3,0	4,5				
Solid sand-lime brick		16x85	M8/M10, 11x85 M8	85	85	5,5	3,0					
		20x85	M12, 15x85 M10/M12	85	85	8,5	8,5	5,5				
		16x130	M8/M10	110	130	5,0	3,0					
		20x130	M12	110	130	8,5	6,0					
	ρ≥ 1,4	12x85	M8	85	85	2,5	2,5	2,5				
		16x85	11x85 M6	85	85	3,0	2,5	2,5				
		16x85	M8/M10, 11x85 M8	85	85	3,0	2,5	4,5				
175	f _b ≥ 12	20x85	M12, 15x85 M10/M12	85	85							
E 65.50		16x130	M8/M10	110	130	3,5	3,0	4,5				
		20x130	M12	110	130]						
340		12x85	M8	85	85	4,5	4,0	4,5				
No.4		16x85	11x85 M6	85	85	5,0	4,0	4,0				
Sand-lime hollow brick	ρ≥ 1,4	16x85	M8/M10, 11x85 M8	85	85	5,0	4,5	7,5				
	f _b ≥ 20	20x85	M12, 15x85 M10/M12	85	85							
		16x130	M8/M10	110	130	6,0	6,0 5,5	7,5				
		20x130	M12	110	130]						

Imaging of the bricks are not scaled

electronic copy of the eta by dibt: eta-15/0890

BTV injection system KM for masonry	
Performances Characteristic values of resistance under tension loads and under shear loads, part 2	Annex C 2

electronic copy of the eta by dibt: eta-15/0890



Table C1.3: Characteristic values of resistance under tension loads and under shear loads

	Donoity				ctive	Characteristic				
	Density ρ [kg/dm³]	Perfor-		anche	orage pth	resistance [kN]				
Brick	-	ated	Anchor size or screw size in internal threaded	u o		N	Rk	V_{Rk}		
Briok	Compressive	sleeve	anchor			Ter				
	strength f _b [N/mm ²]			h _{ef,min}	h _{ef,max}	50/8		All		
	[[mm]	[mm]	d/d	w/w	categories		
175		12x85	M8	85	85	4,0	3,5	4,0		
E. C.		16x85	11x85 M6	85	85	3,5	3,5	4,0		
	ρ≥0,9	16x85	M8/M10, 11x85 M8	85	85	3,5	3,5	5,5		
40	f _b ≥ 10	20x85	M12, 15x85 M10/M12	85	85	5,0	4,5	6,0		
		16x130	M8/M10	130	130	5,0	4,5	5,5		
No.5 Perforated brick HLz		20x130	M12	110	130	5,0	4,5	6,0		
* >		12x85	M8	85	85	4,0	3,5	7,5 (5,5) ¹⁾		
2 4	->44	16x85	11x85 M6	85	85	2	,5	4,0		
	$\rho \ge 1.4$ $f_b \ge 20$	16x85	M8/M10, 11x85 M8	85	85	2,5		4,5		
No.6 Perforated brick HLz		20x85	M12, 15x85 M10/M12	85	85	3,0		3,0		8,5 (5,5) ¹⁾
Te Carol		12x85	M8	85	85	0	9	1,2		
one.	ρ≥ 1,0 f _b ≥ 10	16x85	M8/M10, 11x85 M6/M8	85	85					
		20x85	M12, 15x85 M10/M12	85 85 2,5			,5			
375 (BB)		16x130	M8/M10	110	130			1,5		
No.7 Perforated brick HLz		20x130	M12	110	130	3,5	3,0	1,5		
370		12x85	M8	85	85	2,0	2,0	2,5		
The state of the s		16x85	11x85 M6	85	85	2,0	1,5	2,5		
38	ρ≥ 0,6	16x85	M8/M10, 11x85 M8	85	85	2,0	1,5	3,0		
130	f _b ≥ 8	20x85	M12, 15x85 M10/M12	85	85	2,0	2,0	1,5		
		16x130	M8/M10	130	130	3,0	2,5	3,0		
		20x130	M12	110	130	2,0	2,0	1,5		
No.8 Perforated brick HLz		20x200	M12	180	200	3,0	3,0	1,5		
10		12x85	М8	85	85					
DE .	ρ≥ 1,0	16x85	M8/M10, 11x85 M6/M8	85	85	3,0		2,0		
*	f _b ≥ 4	20x85	M12, 15x85 M10/M12	85	85		, -	_,-		
No.9 Light-weight		16x130	M8/M10	130	130					
concrete hollow block		20x130	M12	110	130					

 $^{^{1)}}$ Characteristic value of pushing out of one brick $V_{\rm Rk,pb}$ = 5,5 kN Imaging of the bricks are not scaled

BTV injection system KM for masonry	
Performances Characteristic values of resistance under tension loads and under shear loads, part 3	Annex C 3



Table C1.4: Characteristic values of resistance under tension loads and under shear loads

	Density ₃ p			anch	ctive orage pth	Chara		ic resistance N]
Brick	[kg/dm ³]	Perforated	Anchor size or screw size in			N_{Rk}		V_{Rk}
Blick	Compressive strength f _b	sleeve	internal threaded anchor				mp. 80°C	ΔΙΙ
	[N/mm ²]			h _{ef,min} [mm]	h _{ef,max} [mm]	d/d	w/w	All categories
			M8	100	120			1,2
	ρ ≥ 350 f _b ≥ 2	without	M10	100	120	1,5		1,2
			M12	100	120			1,5
700			11x85 M6/M8 15x85 M10/M12	8	5			1,2
88	0 > 500	without	M8	100	120	2,0		2,5
			M10	100	120	2,5		2,0
40	ρ≥ 500 f _b ≥ 4		M12	100	120			2,5
	-		11x85 M6/M8 15x85 M10/M12	85		2	,0	2,0
No.10 Aerated concrete block			M8	100	120	3,5	3,0	3,0
DIOGR	ρ≥650		M10	100	120	5,0	4,5	3,0
	p ≥ 650 f _b ≥ 6	without	M12	100	120	3,0	4,5	3,5
			11x85 M6/M8 15x85 M10/M12	85		3,5		2,5

Imaging of the bricks are not scaled

BTV injection system KM for masonry	
Performances Characteristic values of resistance under tension loads and under shear loads, p	Annex C 4

English translation prepared by DIBt



Table C2: Characteristic bending moments

Size					M8	M10	M12
		Zinc-plated steel	Property class	5.8 [Nm]	19	37	65
g			Property class	8.8 [Nm]	30	60	105
bending		Stainless steel A4	Dranarty alasa	50 [Nm]	19	37	65
þe	$M_{Rk,s}$		Property class	70 [Nm]	26	52	92
stic	Σ			80[Nm]	30	60	105
teri	!	High corrosion-resistant steel C		50 [Nm]	19	37	65
Characteristic moment			Property class	70 ¹⁾ [Nm]	26	52	92
မှိ မို	2			80 [Nm]	30	60	105

 $^{^{1)}}$ f_{uk}= 700 N/mm²; f_{yk}=560 N/mm²

Table C2.1: Characteristic bending moments for internal threaded anchors

Size				М6	M8	M10	M12
	zinc plated steel,	Property	5.8 [Nm]	8	19	37	65
bending M _{Rk,s}		class of screw	8.8 [Nm]	12	30	60	105
rracteristic b moments M	stainless steel A4	Property class of screw	70 [Nm]	11	26	52	92
Characteristic moments N	high corrosion resistant steel C	Property class of screw	70 [Nm]	11	26	52	92

Tabelle C3: Displacements under tension loads and shear loads

Material	N [kN]	δN ₀ [mm]	δN∞ [mm]	∨ [kN]	δV_0 [mm]	δV∞ [mm]
solid units and autoclaved aerated concrete	N _{Rk}	0,03	0,06	V _{Rk} 1,4 * γ _M	0,59	0,88
hollow units	N _{Rk} 1,4 * γ _M	0,03	0,06	V _{Rk}	1,71	2,56

BTV injection system KM for masonry	
Performances Characteristic bending moments; displacements	Annex C 5



Table C4: β- factor for job site tests according to ETAG 029, Annex B

Using categories		w/w	d/d		
Temperature range	[°C]	50/80	50/80		
Brick	Size ¹⁾				
	M8	0,57			
	M10	0,59	1		
Solid brick	M12 internal threaded anchor 11x85 M6 / M8 15x85 M10 / M12	0,60	0,96		
Hollow brick	All sizes	0,86	0,96		
Autoclaved aerated concrete	All size	0,73	0,81		

BTV injection system KM for masonry

Performances
β- factors for job site tests

Annex C 6




Edge distance and spacing (installation with and without sleeves) Table C5:

Direction to bed joint						Group factor				Min. thickness			
Brick No.	h_{ef}	c _{cr} =c _{min}	S _{min}	s _{cr}	S _{min}	S _{cr}			Τ		of the masonry members		
Briok 140.	[mm]	[mm]	[mm]	[mm]	[mm]	[mm]	$\alpha_{\text{g},\text{N}}$	$\alpha_{\text{g,V}}$	$\alpha_{\text{g},\text{N}}$	$\alpha_{g,V}$	[mm]		
	50	100	7	5	60 ¹⁾	150	2	2	1,5	1,4			
1	80	100	7	5	60 ¹⁾	240	2	2	1,5	1,4			
	200	150	7	5	2	40			2				
	50	100	7	5	2	40			2				
2	80	100	7	75		240			2				
	200	150	7	75		240		2					
3	85	100	1	15	2	40			2				
	130	100	115		2	40		2			h _{ef} + 30		
4	all sizes	100	1	15	100	240	2	2	1,5	1,5	(≥ 80)		
5	all sizes	100	115		2	40		2					
6	all sizes	100	1	15	2	40	2		2		2		
7	all sizes	100	100	240	100	375 (500) ²⁾	1	1	1	1			
8	all sizes	120	24	1 5	2	:50	2						
9	all sizes	80	24	40	3	65	2						
10	all sizes	100	2	50	3	00	2						

BTV injection system KM for masonry	
Performances Edge distance and spacing	Annex C 7

 $^{^{1)}}$ only valid for tension loads, for shear loads $s_{min}\|=s_{cr}\|$ spacing for alternative brick dimension, see table B4, brick 7



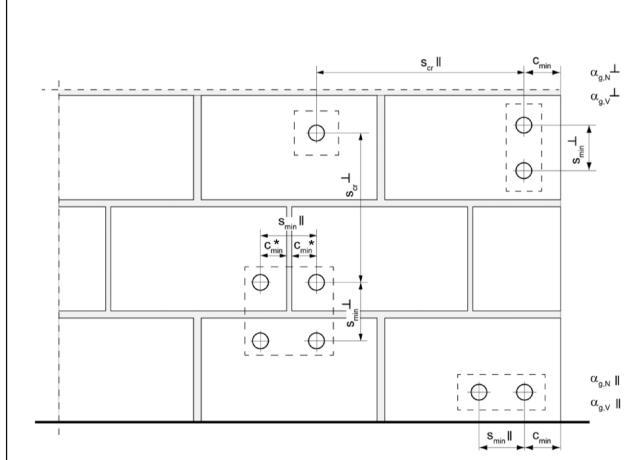

* Only, if joints are visible and/or vertical joints are not filled with mortar

 $s_{min} II = Minimum spacing parallel to bed joint$

 s_{min}^{\perp} = Minimum spacing vertical to bed joint

s_{cr} II = Characteristic spacing parallel to bed joint

 s_{c_1} = Characteristic spacing vertical to bed joint

 $c_{cr} = c_{min}$ = Edge distance

 $\alpha_{a,N}II$ = Group factor for tension load parallel to bed joint

 $\alpha_{q} \vee II$ = Group factor for shear load parallel to bed joint

 $\alpha_{a,N}\bot$ = Group factor for tension load vertical to bed joint

 $\alpha_{a,v}\bot$ = Group factor for shear load vertical to bed joint

For s > s_{cr} $\alpha_g = 2$

For $s_{\text{min}} \le s \le s_{\text{cr}}$ α_g according to table C5 $N_{Rk}^g = \alpha_{g,N} \cdot N_{Rk}$; $V_{Rk}^g = \alpha_{g,V} \cdot V_{Rk}$ (Group of 2 anchors) $N_{Rk}^g = \alpha_{g,N} \cdot N_{Rk} \cdot N_{Rk}$ (Group of 4 anchors)

BTV injection system KM for masonry

Performance

Definition of minimum edge distance, minimum spacing and group factors

Annex C 8