

Approval body for construction products  
and types of construction

Bautechnisches Prüfamt

An institution established by the Federal and  
Laender Governments



## European Technical Assessment

ETA-11/0257  
of 23 March 2017

English translation prepared by DIBt - Original version in German language

### General Part

Technical Assessment Body issuing the  
European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

DHTherm Wärmedämmverbundsystem

Product family  
to which the construction product belongs

Product area code 4  
External Thermal Insulation Composite System with  
rendering on expanded polystyrene for the use as  
external insulation of building walls

Manufacturer

DHT Dämmstoffhandel + Technik GmbH  
Hafenstraße 38  
31137 Hildesheim  
DEUTSCHLAND

Manufacturing plant

DHT Dämmstoffhandel + Technik GmbH  
Hafenstraße 38  
31137 Hildesheim  
DEUTSCHLAND

This European Technical Assessment  
contains

19 pages including 4 annexes which form an integral part  
of this assessment

Annex 5 Control Plan contains confidential information  
and is not included in the European Technical  
Assessment when that assessment is publicly available

This European Technical Assessment is  
issued in accordance with Regulation (EU)  
No 305/2011, on the basis of

Guideline for European technical approval of "External  
Thermal Insulation Composite Systems with Rendering",  
ETAG 004, edition 2000, amended 2013,  
used as European Assessment Document (EAD)  
according to Article 66 Paragraph 3 of Regulation (EU)  
No 305/2011.

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

## Specific part

### 1 Technical description of the product

#### 1.1 Definition and composition of the kit

This product is an ETICS (External Thermal Insulation Composite System) with rendering - a kit comprising components which are factory-produced by the manufacturer or component suppliers. It's made up on site from these. The ETICS manufacturer is ultimately responsible for all components of the ETICS specified in this ETA.

The ETICS kit comprises a prefabricated insulation product of expanded mineral wool (MW) to be bonded and if it necessary additionally mechanically fixed onto a wall. The methods of fixing and the relevant components are specified in the table below.

The insulation product is faced with a rendering system consisting of one or more layers (site applied), one of which contains reinforcement. The rendering is applied directly to the insulating panels, without any air gap or disconnecting layer.

The ETICS may include special fittings (e.g. base profiles, corner profiles ...) for connection to adjacent building elements (apertures, corners, parapets...).

Assessment and performance of these components is not addressed in this ETA, however the ETICS manufacturer is responsible for adequate compatibility and performance within the ETICS when the components are delivered as a part of the kit.

#### 1.2 Composition of the ETICS

	Components National application documents shall be taken into account	Coverage [kg/m <sup>2</sup> ]	Thickness [mm]
Insulation material with associated method of fixing	<b>Bonded ETICS:</b> <ul style="list-style-type: none"> <li> <b>Insulation product</b>                      (see annex 1 for product characteristics)                      factory-prefabricated expanded polystyrene (EPS)                      - standard EPS                 </li> <li> <b>Adhesives</b> (minimum bonded surface 40 %)                     <ul style="list-style-type: none"> <li>DHTherm Klebe- und Armierungsmörtel weiß</li> <li>DHTherm Klebe- und Armierungsmörtel weiß</li> <li>DHTherm Klebe- und Armierungsmörtel grau</li> <li>DHTherm Klebe- und Armierungsmörtel leicht</li> <li>DHTherm Baukleber</li> </ul> </li> </ul>	–  4.0 to 5.0 4.0 to 5.0 4.0 to 5.0 3.0 to 4.0 about 4.0 (prepared)	≤ 400  – – – – –
	<b>Mechanically fixed ETICS with profiles and supplementary adhesive:</b> <ul style="list-style-type: none"> <li> <b>Insulation product</b>                      (see annex 1 for product characteristics)                      factory-prefabricated expanded polystyrene (EPS)                      - standard EPS                 </li> <li> <b>Supplementary adhesive</b>                      (equal to bonded ETICS)                 </li> </ul>	–	60 to 200

	<b>Components</b> National application documents shall be taken into account	<b>Coverage</b> [kg/m <sup>2</sup> ]	<b>Thickness</b> [mm]
<b>Insulation material with associated method of fixing</b>	<ul style="list-style-type: none"> <li>• <b>Profiles</b> (see annex 3 for product characteristics) <ul style="list-style-type: none"> <li>- DHTherm Halteschiene</li> <li>- DHTherm Verbindungsschiene</li> </ul> </li> <li>Polyvinyl chloride (PVC) profiles</li> <li>• <b>Anchors for profiles</b> (see annex 2 for product characteristics) <ul style="list-style-type: none"> <li>- WS 8 L</li> <li>- WS 8 N</li> <li>- ejothem SDK U</li> <li>- SDF-K plus</li> <li>- ejothem NK U</li> </ul> </li> </ul>		
	<p><b>Mechanically fixed ETICS with anchors and supplementary adhesive:</b></p> <ul style="list-style-type: none"> <li>• <b>Insulation product</b> (see annex 1 for product characteristics) factory-prefabricated expanded polystyrene (EPS) <ul style="list-style-type: none"> <li>- standard EPS</li> </ul> </li> <li>• <b>Supplementary adhesive</b> (equal to bonded ETICS)</li> <li>• <b>Anchors for insulation product</b> (see annex 2 for product characteristics) all anchors with ETA according to ETAG 014<sup>1</sup> with characteristics defined in annex 2</li> </ul>	–  4.0 to 5.0	60 to 400
<b>Base coat</b>	<p><b>DHTherm Klebe- und Armierungsmörtel weiß</b> <b>DHTherm Klebe- und Armierungsmörtel grau</b> <b>DHTherm Klebe- und Armierungsmörtel leicht</b> Identical with the equally named adhesives given above.</p>	6.0 to 10.0 6.0 to 10.0 4.5 to 7.0 (prepared)	3.5 – 6.0 3.5 – 6.0 3.5 – 6.0
<b>Glass fibre mesh</b>	<p><b>DHTherm Armierungsgewebe</b> Alkali- and slide-resistant glass fibre mesh with mass per unit area of about 160 g/m<sup>2</sup> and mesh size of about 4.0 mm x 4.0 mm. (see annex 4 for product characteristics)</p>	–	–
<b>Key coat</b>	<p><b>DHTherm Putzgrund</b> Ready to use pigmented acrylic-resin dispersion liquid For the compatibility with the finishing coats see below.</p>	about 0.15	–

<sup>1</sup> ETAG 014

Plastic anchors for fixing of external thermal insulation composite systems with rendering

	Components National application documents shall be taken into account	Coverage [kg/m <sup>2</sup> ]	Thickness [mm]
<b>Finishing coat</b>	<p><b>To use with key coat "DHTherm Putzgrund" if applicable:</b></p> <ul style="list-style-type: none"> <li>Ready to use pastes – acrylic binder: <ul style="list-style-type: none"> <li><b>DHTherm Kunstharzputz</b> <ul style="list-style-type: none"> <li>Rillen-Reibputz (R) (particle size 1.5 – 2 and 3 mm)</li> <li>Kratzputzstruktur (K) (particle size 1.5 – 2 and 3 mm)</li> </ul> </li> </ul> </li> <li>Ready to use pastes – acrylosioxane binder: <ul style="list-style-type: none"> <li><b>DHTherm Silikonharzputz</b> <ul style="list-style-type: none"> <li>Rillen-Reibputz (R) (particle size 1.5 – 2 and 3 mm)</li> <li>Kratzputzstruktur (K) (particle size 1.5 – 2 and 3 mm)</li> </ul> </li> </ul> </li> <li>Ready to use paste – acrylic-silicate binder: <ul style="list-style-type: none"> <li><b>DHTherm Silikatputz</b> <ul style="list-style-type: none"> <li>Rillen-Reibputz (R) (particle size 1.5 – 2 and 3 mm)</li> <li>Kratzputzstruktur (K) (particle size 1.5 – 2 and 3 mm)</li> </ul> </li> </ul> </li> <li>Thin layered cement based powder requiring addition of about 25 % of water: <ul style="list-style-type: none"> <li><b>DHTherm Modellierputz</b> (particle size 1 and 2 mm)</li> <li><b>DHTherm Scheibenputz</b> (particle size 2 – 3 and 5 mm)</li> <li><b>DHTherm Edelleichtputz</b> <ul style="list-style-type: none"> <li>Rillenputzstruktur (R) (particle size 2 and 3 mm)</li> <li>Scheibenputz-Struktur (K) (particle size 2 and 3 mm)</li> </ul> </li> <li><b>DHTherm Münchner Rauputz</b> (particle size 2 – 3 and 5 mm)</li> <li><b>DHTherm Klebe- und Armierungsmörtel weiß**</b></li> </ul> </li> <li>Thick layered cement based powder requiring addition of about 25 % of water: <ul style="list-style-type: none"> <li><b>DHTherm Kratzputz</b> (particle size 3 mm)</li> </ul> </li> </ul>	<p>2.5 to 4.3 2.3 to 3.8</p> <p>2.3 to 4.2 2.4 to 4.2</p> <p>2.5 to 4.5 2.5 to 4.5</p> <p>3.0 to 6.0 (prepared) 2.7 to 5.5 (prepared)</p> <p>2.3 to 3.3 1.8 to 2.5 2.7 to 6.0 (prepared) 2.5 to 3.0</p> <p>22.5 (prepared before scraping) about 14.0 (finished)</p>	<p>regulated by particle size</p> <p>regulated by particle size</p> <p>1.5 to 2.5</p> <p>15 mm</p> <p>8 to 12 mm</p>
<b>Ancillary material</b>	Remains the responsibility of the manufacturer.		
<p>*The instruction to the installer concerning the use of a key coat remains the responsibility of the ETA-holder. **The finishing coat "DHTherm Klebe- und Armierungsmörtel weiß" has to be used with the equally named base coat exclusively</p>			

## 2. Specification of the intended use in accordance with the applicable European assessment Document (hereinafter called EAD)

### 2.1 Intended use

This ETICS is intended to be used as external insulation to the walls of buildings made of masonry (bricks, blocks, stones ...) or concrete (cast on site or as prefabricated panels) with and without rendering. The characteristics of the walls shall be verified prior to use of the ETICS, especially regarding conditions for reaction to fire classification and for fixing of the ETICS either by bonding or mechanically. It shall be designed to give the wall to which it is applied satisfactory thermal insulation.

The ETICS is non load-bearing construction element. It does not contribute directly to the stability of the wall on which it is installed, but it can contribute to durability by providing enhanced protection from the effects of weathering.

The ETICS can be used on new or existing (retrofit) vertical walls.

The ETICS is not intended to ensure the air tightness of the building structure.

The choice of the method of fixing depends on the characteristics of the substrate, which could need preparation (see clause 7.2.1 of ETAG 004) and on the national instruction

The verifications and assessment methods on which this European Technical Assessment (hereinafter called ETA) is based lead to the assumption of a working life of the ETICS "DHTherm Wärmedämmverbundsystem" of at least 25 years. The indications given on the working life cannot be interpreted as a guarantee given by the manufacturer, but are to be regarded only as a means for choosing the right products in relation to the assumed economically reasonable working life of the works

### 2.2 Manufacturing

The ETA is issued for the ETICS on the basis of agreed data/information, deposited with the DIBt, which identifies the ETICS that has been assessed and judged. Changes to the ETICS or the components or their production process, which could result in this deposited data/information being incorrect, should be notified to the DIBt before the changes are introduced. The DIBt will decide whether or not such changes affect the approval and consequently the validity of the CE marking on the basis of the approval and if so whether further assessment or alterations to the approval shall be necessary.

### 2.3 Design and installation

The installation instructions including special installation techniques and provisions for the qualification of the personnel are given in the manufacturer's technical documentation.

Design, installation and execution of ETICS are to be in conformity with national documents. Such documents and the level of their implementation in Member States' legislation are different. Therefore, the assessment and declaration of performance are done taking into account general assumptions introduced in the chapters 7.1 and 7.2 of ETAG 004 used as EAD, which summarize how information introduced in the ETA and related documents is intended to be used in the construction process and gives advice to all parties interested when normative documents are missing.

#### **2.4 Packing, transport and storage**

The information on packaging, transport and storage is given in the manufacturer's technical documentation. It is the responsibility of the manufacturer to ensure that this information is made known to the concerned people.

#### **2.5 Use, maintenance, repair**

The finishing coat shall normally be maintained in order to fully preserve the ETICS performance. Maintenance includes at least:

- visual inspection of the ETICS
- the repairing of localised damaged areas due to accidents,
- the aspect maintenance with products adapted and compatible with the ETICS (possibly after washing or ad hoc preparation).

Only products which are compatible with the ETICS shall be used.

Necessary repairs should be performed as soon as the need has been identified.

The information on use, maintenance and repair is given in the manufacturer's technical documentation. It is the responsibility of the manufacturer to ensure that this information is made known to the concerned people.

### **3 Characteristics of products and methods of verification**

#### **3.0 General**

The performances of the kit as described in this chapter are valid provided that the components of the kit comply with Annexes 1- 4.

#### **3.1 Mechanical resistance and stability (BWR 1)**

not relevant

### 3.2 Safety in case of fire (BWR 2)

#### Reaction to fire (BWR 2) (ETAG 004 - clause 5.1.2)

Configurations	Organic content	Flame retardant content	Euroclass according to EN 13501-1
Base coat	max. 2.4 %	no flame retardant	
EPS	In quantity ensuring Euroclass E according to EN 13501-1	In quantity ensuring Euroclass E according to EN 13501-1	
Profile	-	-	
Anchors	-	-	
<b>rendering system :</b> Base coat with finishing coat and compatible key coat in clause 1.2:			
<b>rendering system consisting of:</b> DHTherm Modellierputz, DHTherm Scheibenputz, DHTherm Edelleichtputz, DHTherm Münchner Rauputz, DHTherm Kratzputz	max. 1.1 %	no flame retardant	B – s1,d0
DHTherm Silikatputz	max. 5.0%		
DHTherm Kunsthatzputz, DHTherm Silikonharzputz, DHTherm Klebe- und Armierungsmörtel weiß	max. 7.8%		B – s2,d0

### 3.3 Hygiene, health and environment (BWR 3)

#### 3.3.1 Water absorption (capillarity test) (ETAG 004 - clause 5.1.3.1)

Base coat	Water absorption after 1 h < 1 kg/m <sup>2</sup>	Water absorption after 24 h < 0.5 kg/m <sup>2</sup>
DHTherm Klebe- und Armierungsmörtel weiß	x	x
DHTherm Klebe- und Armierungsmörtel grau	x	x
DHTherm Klebe- und Armierungsmörtel leicht	x	x



English translation prepared by DIBt

- **Rendering system:**

		Water absorption after 24 hours	
		< 0.5 kg/m <sup>2</sup>	< 0.5 kg/m <sup>2</sup>
<b>Rendering system:</b> all base coats with finishing coat indicated hereafter:	DHTherm Kunstharzputz	x	
	DHTherm Silikonharzputz	x	
	DHTherm Silikatputz	x	
	DHTherm Modellierputz	x	
	DHTherm Scheibenputz	x	
	DHTherm Edelleichtputz	x	
	DHTherm Münchner Rauputz	x	
	DHTherm Klebe- und Armierungsmörtel weiß	x	
	DHTherm Kratzputz	x	

### 3.3.2 Hygrothermal behaviour (ETAG 004 - clause 5.1.3.2)

Pass (without defects)

### 3.3.3 Impact resistance (ETAG 004 – clause 5.1.3.3)

The verified resistance to hard body impact of the ETICS results in the classification into categories listed below.

<b>Rendering system:</b> Base coat "DHTherm Klebe- und Armierungsmörtel weiß" or "DHTherm Klebe- und Armierungsmörtel grau" with finishing coat indicated hereafter:	<b>Single standard mesh:</b> " DHTherm Armierungsgewebe "
DHTherm Kunstharzputz (3 mm)	category II
DHTherm Silikonharzputz (3 mm)	category II
DHTherm Silikatputz (2 mm)	category I
DHTherm Modellierputz (3 mm)	category II
DHTherm Scheibenputz (3 mm)	category II
DHTherm Edelleichtputz (3 mm)	category II
DHTherm Münchner Rauputz (3 mm)	category II
DHTherm Kratzputz (10 mm)	category II

<b>Rendering system:</b> Base coat "DHTherm Klebe- und Armierungsmörtel leicht" with finishing coat indicated hereafter:	<b>Single standard mesh:</b> " DHTherm Armierungsgewebe "
DHTherm Kunstharzputz (3 mm)	category I
DHTherm Silikonharzputz (3 mm)	category I
DHTherm Silikatputz (2 mm)	category I
DHTherm Modellierputz (3 mm)	category III
DHTherm Scheibenputz (3 mm)	category III
DHTherm Edelleichtputz (3 mm)	category III
DHTherm Münchner Rauputz (3 mm)	category III
DHTherm Kratzputz (10 mm)	category I

### 3.3.4 Water vapour permeability (ETAG 004 – clause 5.1.3.4)

<b>Rendering system:</b> all base coats with finishing coat and compatible key coat indicated hereafter:	<b>Equivalent air thickness <math>s_d</math></b>
DHTherm Modellierputz DHTherm Scheibenputz DHTherm Edelleichtputz DHTherm Münchner Rauputz DHTherm Klebe- und Armierungsmörtel weiß DHTherm Kratzputz	$\leq 1.0$ m (Test result obtained with DHTherm Kratzputz 10 mm: 0.1 m)
DHTherm Silikonharzputz	$\leq 1.0$ m (Test result obtained with a layer thickness 3 mm: 0.3 m)
DHTherm Silikatputz	$\leq 1.0$ m (Test result obtained with a layer thickness 3 mm: 0.1 m)
DHTherm Kunstharzputz	$\leq 1.0$ m (Test result obtained with a layer thickness 3 mm: 0.4 m)

### 3.3.5 Release of dangerous substances (ETAG 004 - clause 5.1.3.5, EOTA TR 034)

<b>Essential characteristic</b>	<b>Performance</b>
Release of dangerous substances	no performance assessed

English translation prepared by DIBt

**3.4 Safety and accessibility in use (BWR 4)**

**3.4.1 Bond strength between base coat and insulation product (EPS) (ETAG 004 - clause 5.1.4.1.1)**

Base coat	Conditioning		
	Initial state	After hygrothermal cycles	After freeze/thaw test
DHTherm Klebe- und Armierungsmörtel weiß	≥ 0.08 MPa	≥ 0.08 MPa	Test not required because freeze/thaw cycles not necessary
DHTherm Klebe- und Armierungsmörtel grau	≥ 0.08 MPa	≥ 0.08 MPa	
DHTherm Klebe- und Armierungsmörtel leicht	≥ 0.08 MPa	≥ 0.08 MPa	

**3.4.2 Bond strength between base coat and substrate resp. insulation product (EPS) (ETAG 004 - clauses 5.1.4.1.2 and 5.1.4.1.3)**

		Conditioning		
		Initial state	2 d immersion in water and 2 h drying	2 d immersion in water and 7 d drying
DHTherm Klebe- und Armierungsmörtel weiß	Concrete	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	EPS	≥ 0.08 MPa	≥ 0.03 MPa	≥ 0.08 MPa
DHTherm Klebe- und Armierungsmörtel grau	Concrete	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	EPS	≥ 0.08 MPa	≥ 0.03 MPa	≥ 0.08 MPa
DHTherm Klebe- und Armierungsmörtel leicht	Concrete	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	EPS	≥ 0.08 MPa	≥ 0.03 MPa	≥ 0.08 MPa
DHTherm Baukleber	Concrete	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	EPS	≥ 0.08 MPa	≥ 0.03 MPa	≥ 0.08 MPa

Bonded surface:

For bonded ETICS the calculated minimal bonded surface area, according to ETAG 004, clause 6.1.4.1.3 is 40 %.

**3.4.3 Bond strength after ageing (ETAG 004 - clause 5.1.7.1)**

<b>Rendering system:</b> All base coats with finishing coat indicated hereafter	DHTherm Kunstharzputz	≥ 0.08 MPa
	DHTherm Silikonharzputz	
	DHTherm Silikatputz	
	DHTherm Modellierputz	
	DHTherm Scheibenputz	
	DHTherm Edelleichtputz	
	DHTherm Münchner Rauputz	
	DHTherm Klebe- und Armierungsmörtel weiß	
	DHTherm Kratzputz	

English translation prepared by DIBt

**3.4.4 Fixing strength (displacement test) (ETAG 004 - clause 5.1.4.2)**

Test not required therefore no limitation of ETICS length required

**3.4.5 Wind load resistance (ETAG 004 - clause 5.1.4.3)**

The following failure loads only apply to the listed combination (EPS panel's characteristics) / (way of fixing the profiles) and the characteristics of the insulation product given in annex 1.

**3.4.5.1 Safety in use of mechanically fixed ETICS using profiles**

Characteristics of the EPS (standard EPS)	Dimensions	500 mm x 500 mm
	Thickness	≥ 60 mm
	<b>Tensile strength perpendicular to the faces</b>	<b>≥ 150 kPa</b>
	Shear modulus	≥ 1.0 N/mm <sup>2</sup>
Failure loads [N / panel] (Static Foam Block Test)	Horizontal profiles fixed every 30 cm and 49.4 cm long vertical connection profiles	Minimal: 950 Average: 1010

**3.4.5.2 Safety in use of mechanically fixed ETICS using anchors**

Failure loads – Table 2

Apply to all anchors listed in clause 1.2 mounted on the insulation panels surface				
Characteristics of the EPS (standard EPS)	Thickness		≥ 60 mm	
	<b>Tensile strength perpendicular to the faces</b>		<b>≥ 100 kPa</b>	
	Shear modulus		≥ 1.0 N/mm <sup>2</sup>	
Plate diameter of anchor			Ø 60 mm	Ø 90 mm
Failure loads [N]	Anchors not placed at the panel joints (Static Foam Block Test)	R <sub>panel</sub>	Minimal: 510 Average: 520	Minimal: 720 Average: 730
	Anchors placed at the panel joints (Pull-through test)	R <sub>joint</sub>	Minimal: 400 Average: 430	Minimal: 430 Average: 470

The failure loads specified above only for a plate diameter of anchor of 60 mm apply to the following anchors with deep mounting but only on the following conditions of installation:

Anchor	Thickness of the EPS [d]	Conditions of installation*
ejothem STR U (ETA-04/0023)	100 mm > d ≥ 80 mm	– Maximum installation depth of the anchor plate: 15 mm (≙ thickness of insulation cover) – Maximum depth of die: 5 mm
	≥ 100 mm	– Maximum installation depth of the anchor plate: 15 mm (≙ thickness of insulation cover) – Maximum depth of die: 20 mm
* according to the appropriate ETA of anchor		

English translation prepared by DIBt

### 3.4.6 Render strip tensile test (ETAG 004 – clause 5.5.4.1)

The average value of crack width of the base coat "DHTherm Klebe- und Armierungsmörtel grau" reinforced with the glass fibre mesh "DHTherm Armierungsgewebe" measured at a render strain value of 0.5 % is about 0.08 mm.

The average value of crack width of the base coat coat "DHTherm Klebe- und Armierungsmörtel leicht" reinforced with the glass fibre mesh "DHTherm Armierungsgewebe" measured at a render strain value of 1.0 % is about 0.11 mm.

For the cracks width of base coat "DHTherm Klebe- und Armierungsmörtel weiß" no performance determined.

### 3.5 Protection against noise (BWR 5)

NPD (no performance determined)

### 3.6 Energy economy and heat retention (BWR 6)

#### 3.6.1 Thermal resistance

The nominal value of the additional thermal resistance  $R$  provided by the ETICS to the substrate wall is calculated in accordance with EN ISO 6946:2007 from the nominal value of the insulation product's thermal resistance  $R_D$  given accompanied to the CE marking and from the thermal resistance of the rendering system  $R_{render}$  which is about  $0.02 \text{ (m}^2 \cdot \text{K)/W}$ .

$$R = R_D + R_{render}$$

The thermal bridges caused by anchors profiles increases the thermal transmittance  $U$ . This influence had to take into account according to EN ISO 6946:2007

$$U_c = U + \chi_p \cdot n$$

Where:  $U_c$ : corrected thermal transmittance [ $\text{W}/(\text{m}^2 \cdot \text{K})$ ]

$n$ : number of anchors per  $\text{m}^2$

$\chi_p$ : local influence of thermal bridge caused by an anchor. The values listed below can be taken into account if not specified in the anchor's ETA:

$\chi_p = 0.004 \text{ W/K}$  for anchors with a galvanized steel screw with the head covered by a plastic material

$\chi_p = 0.002 \text{ W/K}$  for anchors with a stainless steel screw covered by plastic anchors and for anchors with an air gap at the head of the screw

The thermal bridges caused by profiles are negligible.

### 3.7 Sustainable use of natural resources (BWR 7)

For the sustainable use of natural resources no performance was investigated for this product.

**4 Assessment and verification of constancy of performance (hereinafter AVCP) system applied, with reference to its legal base**

According to the European Commission decision 97/556/EC amended by the European Commission decision 2001/596/EC, the assessment and verification of constancy of performance system (AVCP) applies suitable following table (see Annex V to Regulation (EU) No 305/2011).

Product	Intended use	Levels or classes (Reaction to fire)	Systems
"DHTherm Wärmedämmverbundsystem"	in external wall subject to fire regulations	A1 <sup>(1)</sup> , A2 <sup>(1)</sup> , B <sup>(1)</sup> , C <sup>(1)</sup>	1
		A1 <sup>(2)</sup> , A2 <sup>(2)</sup> , B <sup>(2)</sup> , C <sup>(2)</sup> , D, E, (A1 to E) <sup>(3)</sup> , F	2+
	in external wall not subject to fire regulations	any	2+

- (1) Products/materials for which a clearly identifiable stage in the production process results in an improvement of the reaction to fire classification (e.g. an addition of fire retardants or a limiting of organic material)
- (2) Products/materials not covered by footnote (1)
- (3) Products/materials that do not require to be tested for reaction to fire (e.g. products/materials of Classes A1 according to Commission Decision 96/603/EC)

**5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document (EAD)**

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Deutsches Institut für Bautechnik.

Issued in Berlin on 23 March 2017 by Deutsches Institut für Bautechnik

Uwe Bender  
Head of Department

*beglaubigt:*  
Windhorst

**Annexes:**

- Annex 1: Thermal insulation product characteristic
- Annex 2: Anchors
- Annex 3: Profiles
- Annex 4: Reinforcement

**Annex 1: Thermal insulation product characteristic**

Factory-prefabricated, uncoated panels made of expanded polystyrene (EPS) to EN 13163:2015 shall be used, having the description and characteristics defined in the Table below.

Description and characteristics	For bonded ETICS	For mechanically fixed ETICS	
		with anchors and supplementary adhesive	with profiles and supplementary adhesive***
Reaction to fire; EN 13501-1:2007	Class E*		
Thermal resistance [(m <sup>2</sup> ·K)/W]	Defined in the CE marking in reference to EN 13163:2015		
<b>Tolerances</b>			
Length; EN 822:1994	± 0.6 % or ± 3 mm whichever gives the greatest numerical tolerance (class L1 or class L2)		
Width [mm]; EN 822:1994	± 2 (class W2)		
Thickness [mm]; EN 823:1994	± 1 (class T2)		
Squareness [mm/m]; EN 824:1994	± 2 (class S2)		
Flatness [mm/m]; EN 825:1994	5 (class P4)		
<b>Dimensional stability under</b>			
- laboratory conditions [%]; EN 1603:1996	± 0.2 (class DS(N)2)		
- specified temperature and humidity conditions [%]; EN 1604:1996	2 (level DS(70,-)2 or level DS(70,-)1)		
Water absorption (long term partial immersion) [kg/m <sup>2</sup> ]; EN 12087:1997	W <sub>ip</sub> ≤ 0.5		
Water vapour diffusion resistance factor; EN 12086:1997	μ = 20 – 78		
Tensile strength perpendicular to the faces in dry conditions** [kPa]; EN 1607:1996 - standard EPS	σ <sub>mt</sub> ≥ 80	σ <sub>mt</sub> ≥ 100	σ <sub>mt</sub> ≥ 150
Bending strength** [kPa]; EN 12089:1997	σ <sub>b</sub> ≥ 50		
Apparent density [kg/m <sup>3</sup> ]; EN 1602:1996	ρ <sub>a</sub> ≤ 30		
Shear strength** [kPa]; EN 12090:1997	20 ≤ f <sub>tk</sub> ≤ 170		
Shear modulus [MPa]; EN 12090:1997 - standard EPS	1.0 ≤ G <sub>m</sub> ≤ 3.8		
Testing of characteristics see EN 13163:2015.			
* See the conditions of clause 3.2 for the EPS.			
** Minimal value of all single values			
*** Thermal insulation materials for mechanically fixed ETICS with profiles must circumferentially at the edges, 24 mm from the inner surface, get an approx. 3 mm wide and 13 to 18 mm deep groove cut-in at the factory.			



## Annex 2: Anchors

All anchors with ETA according to ETAG 014<sup>1</sup> with characteristics having the description below shall be used in the mechanically fixed ETICS:

- plate diameter of anchor  $\geq 60$  mm resp.  $\geq 90$  mm
- plate stiffness  $\geq 0.3$  kN/mm
- load resistance of the anchor plate  $\geq 1.0$  kN

These characteristics and the characteristic tension resistance of the anchors shall be taken from the corresponding ETA.

The anchors listed in the Table in clause 1.2 with reference to the respective ETA shall be used in the mechanically fixed ETICS with profiles for fixing the horizontal profiles.


Trade name	ETA-number
WS 8 L	ETA-02/0019
WS 8 N	ETA-03/0019
ejotharm SDK U	ETA-04/0023
SDF-K plus,	ETA-04/0064
ejotharm NK U	ETA-05/0009

### Annex 3: Profiles


Polyvinyl chloride (PVC) profiles, PVC-U, EGL, 082-05-T33 to EN ISO 1163-1:1999 are to be used in the mechanically fixed ETICS with profiles.

The Pull-through resistance of fixings from profiles is  $\geq 500$  N.

#### Horizontal profile – "DHTherm Halteschiene" (dimensions in millimetres)

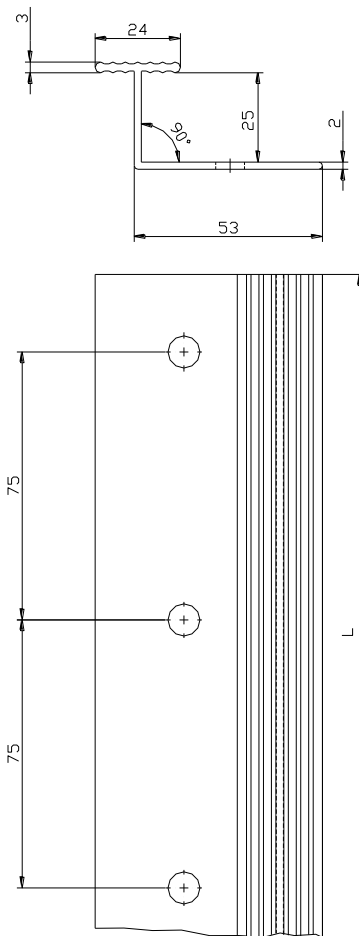

#### Vertical connection profile "DHTherm Verbindungsschiene" (dimensions in millimetres)

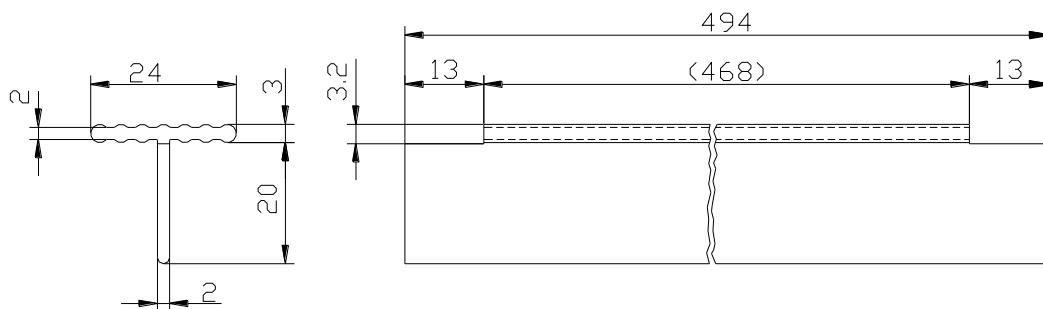

**Annex 4: Reinforcement (glass fibre mesh)**

Characteristics (alkali resistance): Pass

	Description	Residual strength after ageing [N/mm]	Relative residual strength after ageing, of the strength in the as-delivered state [%]
"DHTherm Armierungsge webe"	Alkali- and slide-resistant glass fibre mesh with mass per unit area of about 160 g/m <sup>2</sup> and mesh size of about 4.0 mm x 4.0 mm	≥ 20	≥ 50