

Approval body for construction products
and types of construction

Bautechnisches Prüfamt

An institution established by the Federal and
Laender Governments



European Technical Assessment

ETA-06/0045
of 19 June 2018

English translation prepared by DIBt - Original version in German language

General Part

Technical Assessment Body issuing the
European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

StoTherm Vario 3

Product family
to which the construction product belongs

Product area code:4
External Thermal Insulation Composite System with
rendering on expanded polystyrene for use on building
walls

Manufacturer

Sto SE & Co. KGaA
Ehrenbachstraße 1
79780 Stühlingen
DEUTSCHLAND

Manufacturing plant

Sto SE & Co. KGaA
Ehrenbachstraße 1
79780 Stühlingen
DEUTSCHLAND

This European Technical Assessment
contains

22 pages including 4 annexes which form an integral part
of this assessment

Annex 5 Control Plan contains confidential information
and is not included in the European Technical
Assessment when that assessment is publicly available

This European Technical Assessment is
issued in accordance with Regulation (EU)
No 305/2011, on the basis of

ETAG 004, edition 2000, amended 2013,
used as EAD according to Article 66 Paragraph 3 of
Regulation (EU) No 305/2011.

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

Specific Part

1 Technical description of the product

1.1 Definition of the kit

This product is an External Thermal Insulation Composite System (ETICS) with rendering - a kit comprising components which are factory-produced by the manufacturer or component suppliers. It's made up on site from these. The ETICS manufacturer is ultimately responsible for all components of the ETICS specified in this ETA.

The ETICS kit comprises a prefabricated insulation product of expanded polystyrene (EPS) to be bonded and if it necessary additional mechanically fixed onto a wall. The methods of fixing and the relevant components are specified in the table below.

The insulation product is faced with a rendering system consisting of one base coat and finishing coat (site applied), in which the base coat contains reinforcement. The rendering is applied directly to the insulating panels, without any air gap or disconnecting layer.

The ETICS may include special fittings (e.g. base profiles, corner profiles ...) for connection to adjacent building elements (apertures, corners, parapets ...). Assessment and performance of these components is not addressed in this ETA, however the ETICS manufacturer is responsible for adequate compatibility and performance within the ETICS when the components are delivered as a part of the kit.

1.2 Composition of the ETICS

	Components National application documents shall be taken into account	Coverage [kg/m ²]	Thickness [mm]
Insulation material with associated method of fixing	Bonded ETICS:		
	• Insulation product (see annex 1 for product characteristics) factory-prefabricated expanded polystyrene (EPS)		
	– standard EPS	–	≤ 400
	– elastified EPS		≤ 200
	• Adhesives		–
	– Sto Levell FT (cement based powder requiring addition of 28 % of water)	4.0 to 7.5 (powder)	–
	- StoLevell Novo (cement based powder requiring addition of about 37) % of water)	3.0 to 7.5 (powder)	–
	- StoLevell Uni (cement based powder requiring addition of 24 - 26 % of water)	3.0 to 7.5 (powder)	–
- Sto-Baukleber (cement based powder requiring addition of 21 - 23 % of water)	3.0 to 7.5 (powder)	–	
- Sto-Baukleber QS (cement based powder requiring addition of 21 – 23 of water)	3.0 to 7.5 (powder)	–	
- Sto-Dispersionskleber (organic based ready to use paste)	1.0 to 1.5	–	

	Components National application documents shall be taken into account	Coverage [kg/m ²]	Thickness [mm]
Insulation material with associated method of fixing	Mechanically fixed ETICS with profiles and supplementary adhesive: <ul style="list-style-type: none"> • Insulation product (see annex 1 for product characteristics) factory-prefabricated expanded polystyrene (EPS) <ul style="list-style-type: none"> – standard EPS • Supplementary adhesive (equal to bonded ETICS) • Profiles (see annex 3 for product characteristics) <ul style="list-style-type: none"> – "Sto-Halteleiste PVC" – "Sto-Verbindungsleiste PVC" Polyvinyl chloride (PVC) profiles • Anchors for profiles (see annex 2 for product characteristics) <ul style="list-style-type: none"> – WS 8 L – WS 8 N – ejothem SDK U – SDF-K plus – ejothem NK U 	–	60 to 200
	Mechanically fixed ETICS with anchors and supplementary adhesive: <ul style="list-style-type: none"> • Insulation product (see annex 1 for product characteristics) factory-prefabricated expanded polystyrene (EPS) <ul style="list-style-type: none"> – standard EPS – elastified EPS • Supplementary adhesive (equal to bonded ETICS) • Anchors for insulation product all anchors with ETA according to EAD330196-01-0604¹ with characteristics defined in annex 2 	– –	60 to 400 60 to 200
Base coat	StoLevel Nov Identical with the equally named adhesive given above.	5.0 to 10.0 (powder)	5.0 to 10.0
Glass fibre mesh	<ul style="list-style-type: none"> • Sto-Glasfasergewebe Alkali- and slide-resistant glass fibre mesh with mass per unit area of about 165 g/m² and mesh size of about 6.0 mm x 6.0 mm. (see annex 4 for product characteristics) 	–	–

¹ EAD330196-01-0604 Plastic anchors for fixing of external thermal insulation composite systems with rendering

	Components National application documents shall be taken into account	Coverage [kg/m ²]	Thickness [mm]
Glass fibre mesh	<ul style="list-style-type: none"> • Sto-Glasfasergewebe F Alkali- and slide-resistant glass fibre mesh with mass per unit area of about 165 g/m² and mesh size of about 4.0 mm x 4.0 mm. (see annex 4 for product characteristics) • Sto-Abschirmgewebe AES (special mesh including a thin stainless yarn to reduce radiation of electric fields) Alkali- and slide-resistant glass fibre mesh with mass per unit area of about 165 g/m² and mesh size of about 4.0 mm x 4.0 mm. (see annex 4 for product characteristics) • Sto-Panzergewebe (reinforced mesh implemented in addition to the meshes described above to improve the impact resistance) Alkali- and slide-resistant glass fibre mesh with mass per unit area of about 450 g/m² and mesh size of about 7.5 mm x 7.5 mm. (see annex 4 for product characteristics) 	– – –	– – –
Key coat	StoPrep Miral Sto-Putzgrund Sto-Putzgrund QS StoPrep QS Ready to use pigmented acrylic-resin dispersion liquids. StoPrep Miral with additional potassium silicate binder. For the compatibility with the finishing coats see below.	} about 0.3 l/m ²	–
Finishing coat	To use with key coat "Sto-Putzgrund" if applicable: <ul style="list-style-type: none"> • Ready to use pastes – acrylate binder: <ul style="list-style-type: none"> Stolit K (particle size 1.0 to 6.0 mm) Stolit R (particle size 1.5 to 6.0 mm) Stolit Effect (particle size 3.0 mm) Stolit MP (thin, middle or thick layer) Stolit Milano Stolit K (particle size 1.5 mm) + Stolit Milano StoMarlit K (particle size 1.5 to 3.0 mm) StoMarlit R (particle size 1.5 to 3.0 mm) Sto-Ispolit K (particle size 1.5 to 2.5 and 3.5 mm) StoSuperlit K (particle size 1.5 to 2.0 mm) StoLotusan K (particle size 1.0 to 3.0 mm) StoLotusan MP (thin, middle or thick layer) 	2.0 to 6.5 2.2 to 6.1 4.5 to 5.5 2.2 to 4.7 2.0 to 4.0 about 2.3 + about 3.0 2.6 to 4.9 2.5 to 4.4 2.3 to 4.3 4.5 to 6.0 2.0 to 5.0 2.2 to 4.7	} regulated by particle size 1.5 to 3.5 1.0 to 2.0 2.0 to 3.0 } regulated by particle size 1.5 to 3.5

	Components National application documents shall be taken into account	Coverage [kg/m ²]	Thickness [mm]
Finishing coat	<ul style="list-style-type: none"> Ready to use paste - acrylic binder - associated with a decorative paint: StoNivellit + StoColor Silco (acrylic/siloxane binder) Ready to use paste - acrylic binder - associated with synthetic briquettes Sto-Klebe- und Fugenmörtel + Sto-Flachverblender - size I, II and III Sto-Klebe- und Fugenmörtel + Sto-Ecoshapes Ready to use pastes – acrylic/siloxane binder: Sto-Silkolit K (particle size 1.5 – 2.5 and 3.5 mm) StoSilco K (particle size 1.0 to 3.0 mm) StoSilco R (particle size 1.5 to 3.5 mm) StoSilco MP (thin, middle or thick layer) 	<p>3.0 to 3.5 0.2 to 0.4 l/m²</p> <p>3.0 to 4.0 76, 64 and 48 pieces/m² **</p> <p>3,0 bis 4,0 2,4 bis 11 Stück/m²**</p> <p>2.3 to 4.3 2.0 to 5.0 2.9 to 4.5 2.2 to 4.7</p>	<p>1.0 to 1.5</p> <p>4.0 to 7.0</p> <p>regulated by particle size 1.5 to 3.5</p>
	<p>To use with key coat "Sto-Putzgrund QS"/"StoPrep QS", if applicable: *</p> <ul style="list-style-type: none"> Ready to use paste – acrylic binder: (application between 0 °C and 15 °C): Stolit QS K (particle size 1.0 to 3.0 mm) Stolit QS R (particle size 1.5 to 3.0 mm) Stolit QS MP (thin, middle or thick layer) Ready to use paste – acrylic/siloxane binder (application between 0 °C and 15 °C): StoSilco QS K(particle size 1.0 to 3.0 mm) StoSilco QS R(particle size 1.5 to 3.0 mm) StoSilco QS MP(thin, middle or thick layer) 	<p>2.0 to 4.8 2.2 to 4.5 2.2 to 4.7</p> <p>2.0 to 5.0 2.9 to 4.5 2.2 to 4.7</p>	<p>regulated by particle size 1.5 to 3.5</p> <p>regulated by particle size 1.5 to 3.5</p>
	<p>To use with key coat "StoPrep Miral", if applicable: *</p> <ul style="list-style-type: none"> Ready to use pastes – silicate binder: StoSil K (particle size 1.0 to 3.0 mm) StoSil R (particle size 1.5 to 3.0 mm) StoSil MP (thin, middle or thick layer) Cement based powder requiring addition of about 25 % in weight of water: StoMiral K (particle size 1.5 to 6.0 mm) StoMiral R (particle size 1.5 to 6.0 mm) StoMiral MP (fine structure) 	<p>2.2 to 4.4 2.4 to 3.9 1.5 to 4.0</p> <p>1.7 to 5.0 1.7 to 4.5 1.5 to 4.0</p>	<p>regulated by particle size 1.5 to 3.5</p> <p>regulated by particle size 1.5 to 3.5</p>
	<ul style="list-style-type: none"> Cement based powder requiring addition of about 20 to 23 % of water associated with a decorative paint: StoMiral Nivell F (fine structure) 	<p>3.0 to 4.5</p>	<p>2.0 to 5.0</p>

	Components National application documents shall be taken into account	Coverage [kg/m ²]	Thickness [mm]
Finishing coat	<ul style="list-style-type: none"> • Cement based powder requiring addition of about 30 % of water associated with a decorative paint: Sto-Strukturputz K (particle size 2 and 3 mm) Sto-Strukturputz R (particle size 2 and 3 mm) • Cement based powder requiring addition of about 24 to 32 %: StoMiral EKP (particle size 2.0 to 4.0 mm) 	<p>2.3 to 2.7 2.4 to 2.7</p> <p>15.0 to 25.0</p>	<p>} regulated by particle size</p> <p>8.0.0 to 10 ***</p>
Decorative paint	<ul style="list-style-type: none"> • Ready to use paint with acrylic/siloxane binder: StoSilco Color StoColor Jumbosil StoColor Maxicryl StoColor Crylan Lotusan 	<p>} 0.2 to 0.4 l/m²</p>	
<p>* The instruction to the installer concerning the use of a key coat remains the responsibility of the ETA-holder. ** Depend on the size of the pieces (I, II or III). *** The applied thickness of 10 to 25 mm is reduced to 8 to 10 mm by scraping.</p>			

2. Specification of the intended use in accordance with the applicable European assessment Document (hereinafter called EAD)

2.1 Intended use

This ETICS is intended to be used as external insulation to the walls of buildings made of masonry (bricks, blocks, stones ...) or concrete (cast on site or as prefabricated panels) with and without rendering. The characteristics of the walls shall be verified prior to use of the ETICS, especially regarding conditions for reaction to fire classification and for fixing of the ETICS either by bonding or mechanically. It shall be designed to give the wall to which it is applied satisfactory thermal insulation.

The ETICS is non load-bearing construction element. It does not contribute directly to the stability of the wall on which it is installed, but it can contribute to durability by providing enhanced protection from the effects of weathering.

The ETICS can be used on new or existing (retrofit) vertical walls.

The ETICS is not intended to ensure the air tightness of the building structure.

The choice of the method of fixing depends on the characteristics of the substrate, which could need preparation (see clause 7.2.1 of ETAG 004) and on the national instructions.

The verifications and assessment methods on which this European Technical Assessment (hereinafter called ETA) is based lead to the assumption of a working life of the ETICS "Sto Therm Vario 3" of at least 25 years. The indications given on the working life cannot be interpreted as a guarantee given by the manufacturer, but are to be regarded only as a means for choosing the right products in relation to the assumed economically reasonable working life of the works.

2.2 Manufacturing

The ETA is issued for the ETICS on the basis of agreed data/information, deposited with the DIBt, which identifies the ETICS that has been assessed and judged. Changes to the ETICS or the components or their production process, which could result in this deposited data/information being incorrect, should be notified to the DIBt before the changes are introduced. The DIBt will decide whether such changes affect the approval and consequently the validity of the CE marking on the basis of the approval and if so whether further assessment or alterations to the approval shall be necessary.

2.3 Design and installation

The installation instructions including special installation techniques and provisions for the qualification of the personnel are given in the manufacturer's technical documentation.

Design, installation and execution of ETICS are to be in conformity with national documents. Such documents and the level of their implementation in Member States' legislation are different. Therefore, the assessment and declaration of performance are done taking into account general assumptions introduced in the chapters 7.1 and 7.2 of ETAG 004 used as EAD, which summarize how information introduced in the ETA and related documents is intended to be used in the construction process and gives advice to all parties interested when normative documents are missing.

2.4 Packing, transport and storage

The information on packaging, transport and storage is given in the manufacturer's technical documentation. It is the responsibility of the manufacturer to ensure that this information is made known to the concerned people.

2.5 Use, maintenance, repair

The finishing coat shall normally be maintained in order to fully preserve the ETICS performance. Maintenance includes at least:

- visual inspection of the ETICS
- the repairing of localized damaged areas due to accidents
- the aspect maintenance with products adapted and compatible with the ETICS (possibly after washing or ad hoc preparation)

Only products which are compatible with the ETICS shall be used.

Necessary repairs should be performed as soon as the need has been identified.

The information on use, maintenance and repair is given in the manufacturer's technical documentation.

It is the responsibility of the manufacturer to ensure that this information is made known to the concerned people.

3 Characteristics of products and methods of verification

3.0 General

The performances of the kit as described in this chapter are valid provided that the components of the kit comply with Annexes 1 to 4.

3.1 Mechanical resistance and stability (BWR 1)

not relevant

3.2 Safety in case of fire (BWR 2)
Reaction to fire (ETAG 004 - clause 5.1.2)

Configurations	Organic content	Flame retardant content	Euroclass according to EN 13501-1	
Base coat	max. 3.6 %	no flame retardant		
EPS-insulation product	In quantity ensuring Euroclass E according to EN 13501-1	In quantity ensuring Euroclass E according to EN 13501-1		
Profiles	-	-		
anchors	-	-		
Rendering system: Base coat with finishing coat and compatible key coat indicated hereafter :				
Stolit K/R (particle size 3,5 to 6,0 mm) with key coat "Sto-Putzgrund"	max. 9.6 %	min. 8.0 %	C – s2,d0	
Stolit K/R (particle size 1,0 to 3,0 mm) with key coat "Sto-Putzgrund"		min. 7.8 %	no flame retardant	B – s2,d0
Stolit Effect/MP with key coat "Sto-Putzgrund"				
Stolit Milano with key coat "Sto-Putzgrund"				
Stolit K1,5 + Stolit Milano with key coat "Sto-Putzgrund"				
StoMarlit K/R with key coat "Sto-Putzgrund"				
Sto-Ispolit K with key coat "Sto-Putzgrund"		min. 10.2 %	no flame retardant	
StoLotusan K/MP with key coat "Sto-Putzgrund"				
StoNivellit + StoColor Silco with key coat "Sto-Putzgrund"				
Sto-Silkolit K with key coat "Sto-Putzgrund"		min. 7.6 %	no flame retardant	
StoSilco K/R/MP with key coat "Sto-Putzgrund"				
Stolit QS K/R/MP with key coat "Sto-Putzgrund QS"/"StoPrep QS"				

Configurations	Organic content	Flame retardant content	Euroclass according to EN 13501-1
StoSilco QS K/R/MP with key coat "Sto-Putzgrund QS"/"StoPrep QS"	max. 8.7 %	min. 9.3 %	B – s2,d0
StoSil K/R/MP with key coat "StoPrep Miral"	max. 6.0 %	no flame retardant	B – s1,d0
StoMiral K/R/MP with key coat "StoPrep Miral"	max. 1.6 %		
StoMiral Nivell F with key coat "StoPrep Miral" associated with a decorative paint			
Sto-Strukturputz K/R with key coat "StoPrep Miral", associated with a decorative paint			
StoMiral EKP with key coat "StoPrep Miral"			
Sto-Klebe- und Fugenmörtel + Sto-Flachverblender with key coat "Sto-Putzgrund"	max. 8.0 % max. 7.9 %	min. 15.0% min. 20.0%	B – s2,d0
Sto-Klebe- und Fugenmörtel + Sto-Ecoshapes with key coat "Sto-Putzgrund"	max. 8.0 % max. 7.9 %	min. 15.0% min. 20.0%	
StoSuperlit K with key coat "Sto-Putzgrund"			no performance assessed

3.3 Hygiene, Gesundheit und Umweltschutz (BWR 3)

3.3.1 Wasseraufnahme (Prüfung der Kapillarwirkung) ETAG 004 - Abschnitt 5.1.3.1)

- **Unterputz:**

- Wasseraufnahme nach 1 Stunde < 1.0 kg/m²
- Wasseraufnahme nach 24 Stunden < 0.5 kg/m²

- **Rendering system:**

Rendering system: Base with finishing coat indicated in clause 1.2:		Water absorption after 24 h	
		< 0.5 kg/m ²	≥ 0.5 kg/m ²
	Stolit K/R/Effect/MP	x	
	Stolit Milano	x	
	Stolit K1.5 + Stolit Milano	x	
	StoMarlit K/R	x	
	Sto-Ispolit K	x	
	StoLotusan K/MP	x	
	Sto-Klebe- und Fugenmörtel + Sto-Flachverblender	x	

• Rendering system:		Water absorption after 24 h	
		< 0.5 kg/m ²	≥ 0.5 kg/m ²
Rendering system: Base with finishing coat indicated in clause 1.2:	Sto-Klebe- und Fugenmörtel + Sto-Ecoshapes	x	
	StoSuperlit K	x	
	StoNivellit + StoSilco Color	x	
	Sto-Silkolit K	x	
	StoSilco K/R/MP	x	
	Stolit QS K/R/MP	x	
	StoSilco QS K/R/MP	x	
	StoSil K/R/MP		x
	StoMiral K/R/MP	x	
	StoMiral Nivell F, associated with a decorative paint	x	
	Sto-Strukturputz K/R associated with a decorative paint	x	
	StoMiral EKP		x

3.3.2 Hygrothermal behaviour (ETAG 004 - clause 5.1.3.2)

Pass (without defects)

Freeze/thaw behaviour

The ETICS with the finishing coats "StoSil" and "StoMiral EKP" has been assessed as freeze/thaw resistant according to the simulated method.

3.3.3 Impact resistance (ETAG 004 – clause 5.1.3.3)

Standard mesh: "Sto-Glasfasergewebe" and "Sto-Glasfasergewebe F"

Rendering system: Base coat with finishing coat indicated hereafter	Standard mesh/ Sto-Abschirmgewebe AES	Standard mesh + Sto-Panzergewebe
Stolit K/R/Effect/MP	Category II	Category I
Stolit Milano	Category III	Not determined
Stolit K1.5 + Stolit Milano	Category II	Category II
Sto-Ispolit K		
StoMarlit K/R	Category II	Category I
StoLotusan K/MP		
Sto-Klebe- und Fugenmörtel + Sto-Flachverblender	Category I	Category I
Sto-Klebe- und Fugenmörtel + Sto-Ecoshapes		
StoSuperlit K	Category II	Category I
StoNivellit + StoSilco Color	Category III	Category II
Sto-Silkolit K	Category II	Category II
StoSilco K/R/MP	Category II	Category I
Stolit QS K/R/MP		

Rendering system: Base coat with finishing coat indicated hereafter	Standard mesh/ Sto-Abschirmgewebe AES	Standard mesh + Sto-Panzergewebe
StoSilco QS K/R/MP	Category II	Category I
StoSil K/R/MP		Category II
StoMiral K/R/MP		
StoMiral Nivell F		
Sto-Strukturputz K/R		
StoMiral EKP	Category I	Category I

3.3.4 Water vapour permeability (ETAG004 – clause 5.1.3.4)

Rendering system: Base coat with finishing coat indicated hereafter (evaluated without decorative coating or key coat)	Equivalent air thickness s_d (Test results obtained with a layer thickness of the base coat of 6 mm)
Stolit K/R/Effect/MP	≤ 1.0 m (Test result obtained with Stolit K2: 0.4 m)
Stolit Milano	≤ 1.0 m (Test result obtained with d = 1 mm: 0.6 m)
Stolit K1.5 + Stolit Milano	≤ 1.0 m (Test result obtained with d = 2.5 mm: 0.8 m)
StoMarlit K/R	≤ 1.0 m (Test result obtained with StoMarlit K2: 0.4 m)
Sto-Ispolit K	≤ 1.0 m (Test result obtained with d = 2.5 mm: 0.41 m)
StoLotusan K/MP	≤ 1.0 m (Test result obtained with StoLotusan K2: 0.2 m)
Sto-Klebe- und Fugenmörtel + Sto-Flachverblender	≤ 1.0 m (Test result obtained with size III: 0.6 m)
Sto-Klebe- und Fugenmörtel + Sto-Ecoshapes	≤ 1.0 m (Test result obtained with size III: 0.6 m)
StoSuperlit K	≤ 1.0 m (Test result obtained with "Farbsand" (special colour coated grain) K2: 0.4 m) (Test result obtained with "Silmer" (natural coloured grain) K2: 0.3 m)
StoNivellit + StoSilco Color	≤ 1.0 m (Test result obtained with d = 1 mm: 0.4 m)
Sto-Silkolit K	≤ 1.0 m (Test result obtained with d = 2.5 mm: 0.21 m)
StoSilco K/R/MP	≤ 1.0 m (Test result obtained with StoSilco K2: 0.3 m)
Stolit QS K/R/MP	≤ 1.0 m (Test result obtained with Stolit QS K2: 0.3 m)
StoSilco QS K/R/MP	≤ 1.0 m (Test result obtained with StoSilco QS K2: 0.3 m)
StoSil K/R/MP	≤ 1.0 m (Test result obtained with StoSil K2: 0.2 m)
StoMiral K/R/MP	≤ 1.0 m (Test result obtained with StoMiral K2: 0.1 m)
StoMiral Nivell F associated with a decorative paint	≤ 1.0 m (Test result obtained with d = 2 mm and a double coat of paint "StoSilco Color": 0.2 m) (Test result obtained with d = 2 mm and a double coat of paint "StoColor Jumbosil": 0.2 m)
Sto-Strukturputz K/R associated with a decorative paint	≤ 1.0 m (Test result obtained with Sto-Strukturputz K3 and a double coat of paint "StoSilco Color": 0.2 m) (Test result obtained with Sto-Strukturputz K3 and a double coat of paint "StoColor Jumbosil": 0.3 m)

Rendering system: Base coat with finishing coat indicated hereafter (evaluated without decorative coating or key coat)	Equivalent air thickness s_d (Test results obtained with a layer thickness of the base coat of 6 mm)
StoMiral EKP	≤ 1.0 m (Test result obtained with $d = 11$ mm: 0.4 m)

3.3.5 Release of dangerous substances (ETAG 004 - clause 5.1.3.5, EOTA TR 034)

Essential characteristic	Performance
Release of dangerous substances	no performance assessed

3.4 Safety and accessibility in use (BWR 4)

3.4.1 Bond strength between base coat and insulation product (EPS) (ETAG 004 - clause 5.1.4.1.1)

	Conditioning		
Base coat	After hygrothermal cycles	After freeze/thaw test	Initial state
StoLevell Novo	$\geq 0,08$ MPa	$\geq 0,08$ MPa	$\geq 0,08$ MPa

3.4.2 Bond strength between base coat and adhesive resp. insulation product (EPS) (ETAG 004 - clause 5.1.4.1.2 and 5.1.4.1.3)

		Conditioning		
Adhesive	Substrate resp. insulation product	Initial state	2 d immersion in water and 2 h drying	2 d immersion in water and 7 d drying
StoLevell FT	Concrete	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	EPS	≥ 0.08 MPa	≥ 0.03 MPa	≥ 0.08 MPa
StoLevell Novo	Concrete	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	EPS	≥ 0.08 MPa	≥ 0.03 MPa	≥ 0.08 MPa
StoLevell Uni	Concrete	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	EPS	≥ 0.08 MPa	≥ 0.03 MPa	≥ 0.08 MPa
Sto-Baukleber	Concrete	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	EPS	≥ 0.08 MPa	≥ 0.03 MPa	≥ 0.08 MPa
Sto-Baukleber QS	Concrete	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	EPS	≥ 0.08 MPa	≥ 0.03 MPa	≥ 0.08 MPa
Sto-Dispersionskleber	Concrete	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	Brick	≥ 0.25 MPa	≥ 0.08 MPa	≥ 0.25 MPa
	EPS	≥ 0.08 MPa	≥ 0.03 MPa	≥ 0.08 MPa

Bonded surface:

For bonded ETICS the calculated minimal bonded surface area, according to ETAG 004, clause 6.1.4.1.3 is 40 %

3.4.3 Bond strength after ageing

<p>Rendering system: Base coat with finishing coat and compatible key coat indicated hereafter</p>	Stolit K/R/Effect/MP	<p>≥ 0.08 MPa</p>
	Stolit Milano	
	Stolit K1.5 + Stolit Milano	
	Sto-Ispolit K	
	StoMarlit K/R	
	StoLotusan K/MP	
	Sto-Klebe- und Fugenmörtel + Sto-Flachverblender	
	Sto-Klebe- und Fugenmörtel + Sto-Ecoshapes	
	StoSuperlit K	
	StoNivellit + StoSilco Color	
	Sto-Silkolit K	
	StoSilco K/R/MP	
	Stolit QS K/R/MP	
	StoSilco QS K/R/MP	
	StoSil K/R/MP	
	StoMiral K/R/MP	
StoMiral Nivell F		
Sto-Strukturputz K/R		
StoMiral Edelkratzputz		

3.4.4 Fixing strength (displacement test) (ETAG 004 - clause 5.1.4.2)

Test not required (no limitation of ETICS length)

3.4.5 Wind load resistance (ETAG 004 - clause 5.1.4.3)

The following failure loads only apply to the listed combination (and the characteristics of the insulation product given in annex 1).

3.4.5.1 Safety in use of mechanically fixed ETICS using profiles

<p>Characteristics of the EPS (standard EPS)</p>	Dimensions	500 mm x 500 mm
	Thickness	≥ 60 mm
	Tensile strength perpendicular to the faces	≥ 150 kPa
	Shear modulus	≥ 1.0 N/mm ²
Failure loads [N / panel] (Static Foam Block Test)	Horizontal profiles fixed every 30 cm and 49.4 cm long vertical connection profiles	Minimal: 950 Average: 1010

3.4.5.2 Safety in use of mechanically fixed ETICS using anchors

Apply to all anchors listed in the clause 1.2 mounted on the insulation panels surface				
Characteristics of the EPS (standard EPS)	Thickness		≥ 60 mm	
	Tensile strength perpendicular to the faces		≥ 100 kPa	
	Shear modulus		≥ 1.0 N/mm ²	
Plate diameter of anchor			Ø 60 mm	Ø 90 mm
Failure loads [N]	Anchors not placed at the panel joints (Static Foam Block Test)	R _{panel}	Minimal: 510 Average: 520	Minimal: 720 Average: 730
	Anchors placed at the panel joints (Pull-through test)	R _{joint}	Minimal: 400 Average: 430	Minimal: 430 Average: 470

Apply to all anchors listed in the clause 1.2 mounted on the insulation panels surface				
Characteristics of the EPS (elastified EPS)	Thickness		≥ 60 mm	
	Tensile strength perpendicular to the faces		≥ 80 kPa	
	Shear modulus		≥ 0.3 N/mm ²	
Plate diameter of anchor			Ø 60 mm	
Failure loads [N]	Anchors not placed at the panel joints (Static Foam Block Test)	R _{panel}	Minimal: 350 Average: 360	
	Anchors placed at the panel joints (Pull-through test)	R _{joint}	Minimal: 300 Average: 310	

The failure loads specified above for a plate diameter of anchor of 60 mm apply to the following anchors with deep mounting but only on the following conditions of installation:

Anchor	Thickness of the EPS [d]	Conditions of installation*
ejotherm STR U, ejotherm STR U 2G (ETA-04/0023)	100 mm > d ≥ 80 mm (for standard and elastified EPS)	– Maximum installation depth of the anchor plate: 15 mm (≅ thickness of insulation cover) – Maximum depth of die: 5 mm
	≥ 100 mm (for standard and elastified EPS)	– Maximum installation depth of the anchor plate: 15 mm (≅ thickness of insulation cover) – Maximum depth of die: 20 mm
IsoFux NDT8LZ (ETA-05/0080)	≥ 80 mm (for standard and elastified EPS)	– Maximum depth of countersink: 20 mm
TERMOZ 8 SV (ETA-06/0180)	≥ 80 mm (for standard EPS only)	– Maximum installation depth of the anchor plate: 15 mm (≅ thickness of insulation cover)

* according to the appropriate ETA of anchor

English translation prepared by DIBt

3.4.6 Render strip tensile test (ETAG 004 – clause 5.5.4.1)

The average value of crack width of the base coats reinforced with the different glass fibre meshes measured at a render strain value of 1.0 % is:

StoLevell Novo with the mesh indicated hereafter	Average value of crack width $w_{m(1\%)}$
Sto-Glasfasergewebe	0.09 mm
Sto-Glasfasergewebe F	No performance assessed
Sto-Abschirmgewebe AES	0.06 mm

3.5 Protection against noise (BWR 5)

For the protection against noise no performance was assessed for this product.

3.6 Energy economy and heat retention (BWR 6)

3.6.1 Thermal resistance

The nominal value of the additional thermal resistance R provided by the ETICS to the substrate wall is calculated in accordance with EN ISO 6946:2007 from the nominal value of the insulation product's thermal resistance R_D given accompanied to the CE marking and from the thermal resistance of the rendering system R_{render} which is about $0.02 (m^2 \cdot K)/W$.

$$R = R_D + R_{render}$$

The thermal bridges caused by anchors profiles increases the thermal transmittance U . This influence had to take into account according to EN ISO 6946:2007

$$U_c = U + \chi_p \cdot n \quad \text{corrected thermal transmittance } (W/(m^2 \cdot K)).$$

Where: $\chi_p \cdot n$: influence of thermal bridges

n : number of anchors per m^2

χ_p : local influence of thermal bridge caused by an anchor. The values listed below can be taken into account if not specified in the anchor's ETA:

$\chi_p = 0.002 W/K$ for anchors with a stainless steel screw covered by plastic anchors and for anchors with an air gap at the head of the screw

$\chi_p = 0.004 W/K$ for anchors with a galvanized steel screw with the head covered by a plastic material

U : thermal transmittance

The thermal bridges caused by profiles are negligible.

English translation prepared by DIBt

4 Assessment and verification of constancy of performance (hereinafter AVCP) system applied, with reference to its legal base

According to the European Commission decision 97/556/EC amended by the European Commission decision 2001/596/EC, the assessment and verification of constancy of performance system (AVCP) applies suitable following table (see Annex V to Regulation (EU) No 305/2011).

Product	Intended use	Levels or classes (Reaction to fire)	Systems
"StoTherm Vario 3"	ETICS in external wall subject to fire regulations	A1 ⁽¹⁾ , A2 ⁽¹⁾ , B ⁽¹⁾ , C ⁽¹⁾	1
		A1 ⁽²⁾ , A2 ⁽²⁾ , B ⁽²⁾ , C ⁽²⁾ , D, E, (A1 to E) ⁽³⁾ , F	2+
	ETICS in external wall not subject to fire regulations	any	2+
⁽¹⁾ Products/materials for which a clearly identifiable stage in the production process results in an improvement of the reaction to fire classification (e.g. an addition of fire retardants or a limiting of organic material) ⁽²⁾ Products/materials not covered by footnote (1) ⁽³⁾ Products/materials that do not require to be tested for reaction to fire (e.g. products/materials of Classes A1 according to Commission Decision 96/603/EC)			

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable EAD

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Deutsches Institut für Bautechnik.

Issued in Berlin on 12 July 2018 by Deutsches Institut für Bautechnik

Brigitte Strathmann
p.p. Head of Department

beglaubigt:
Windhorst

Annexes:

- Annex 1: Thermal insulation product characteristic
- Annex 2: Anchors
- Annex 3: Profiles
- Annex 4: Reinforcement

Annex 1: Thermal insulation product characteristic

Factory-prefabricated, uncoated panels made of expanded polystyrene (EPS) to EN 13163:2008 shall be used, having the description and characteristics defined in the Table below.

Description and characteristics	For bonded ETICS	For mechanically fixed ETICS	
		with anchors and supplementary adhesive	with profiles and supplementary adhesive****
Reaction to fire; EN 13501-1:2007	Class E*		
Thermal resistance [(m ² ·K)/W]	Defined in the CE marking in reference to EN 13163:2008		
Tolerances			
Length; EN 822:1994	± 0.6 % or ± 3 mm whichever gives the greatest numerical tolerance (class L1 or class L2)		
Width [mm]; EN 822:1994	± 2 (class W2)		
Thickness [mm]; EN 823:1994	± 1 (class T2)		
Squareness [mm/m]; EN 824:1994	± 2 (class S2)		
Flatness [mm/m]; EN 825:1994	5 (class P4)		
Dimensional stability under			
- laboratory conditions [%]; EN 1603:1996	± 0.2 (class DS(N)2)		
- specified temperature and humidity conditions [%]; EN 1604:1996	2 (level DS(70,-)2 or level DS(70,-)1)		
Water absorption (long term partial immersion) [kg/m ²]; EN 12087:1997	W _{ip} ≤ 0.5		
Water vapour diffusion resistance factor; EN 12086:1997	μ = 20 – 78		
Tensile strength perpendicular to the faces in dry conditions** [kPa]; EN 1607:1996			
- standard EPS	σ _{mt} ≥ 80	σ _{mt} ≥ 100	σ _{mt} ≥ 150
- elastified EPS***	σ _{mt} ≥ 80	σ _{mt} ≥ 80	not used
Bending strength** [kPa]; EN 12089:1997	σ _b ≥ 50		
Apparent density [kg/m ³]; EN 1602:1996	ρ _a ≤ 30		
Shear strength** [kPa]; EN 12090:1997	20 ≤ f _{tk} ≤ 170		
Shear modulus [MPa]; EN 12090:1997			
- standard EPS	1.0 ≤ G _m ≤ 3.8		
- elastified EPS***	0.3 ≤ G _m ≤ 1.0	0.3 ≤ G _m ≤ 1.0	not used
Testing of characteristics see EN 13163:2008.			
* See the conditions of clause 3.2 for the EPS.			
** Minimal value of all single values			
*** Elastified EPS is made from standard EPS by short time high load pressing to reduce the dynamic stiffness. The protection against noise of the entire wall is improved by the use of elastified EPS related to an ETICS with standard EPS.			
**** Thermal insulation materials for mechanically fixed ETICS with profiles must circumferentially at the edges, 24 mm from the inner surface, get an approx. 3 mm wide and 13 to 18 mm deep groove cut-in at the factory.			

English translation prepared by DIBt

Annex 2: Anchors

All anchors with ETA according to EAD330196-01-0604¹ with characteristics having the description below shall be used in the mechanically fixed ETICS:

- plate diameter of anchor ≥ 60 mm resp. ≥ 90 mm
- plate stiffness ≥ 0.3 kN/mm
- load resistance of the anchor plate ≥ 1.0 kN

These characteristics and the characteristic tension resistance of the anchors shall be taken from the corresponding ETA.

The anchors listed in the Table in clause 1.1 with reference to the respective ETA shall be used in the mechanically fixed ETICS with profiles for fixing the horizontal profiles.


Trade name	ETA-number
WS 8 L	ETA-02/0019
WS 8 N	ETA-03/0019
ejothem SDK U	ETA-04/0023
SDF-K plus, SDF-S plus	ETA-04/0064
ejothem NK U	ETA-05/0009

Annex 3: Profiles


Polyvinyl chloride (PVC) profiles, PVC-U, EGL, 082-05-T33 to EN ISO 1163-1:1999, are to be used in the mechanically fixed ETICS with profiles.

The Pull-through resistance of fixings from profiles is ≥ 500 N.

Horizontal profile – "Halteleiste PVC" (dimensions in millimetres)

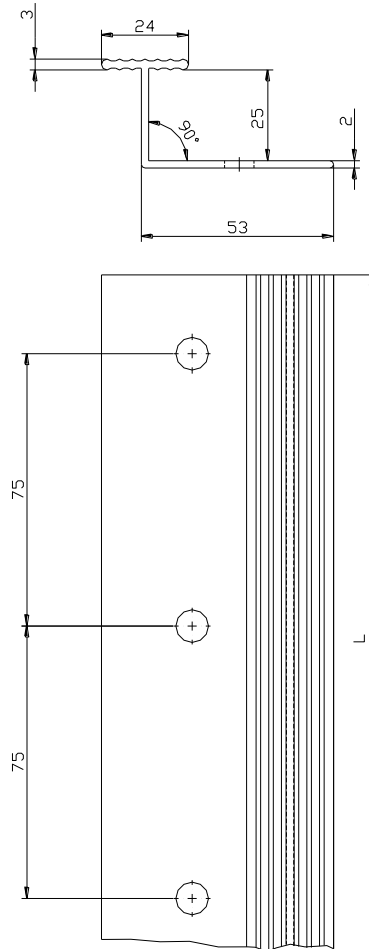

Vertical connection profile "Verbindungsleiste PVC" (dimensions in millimetres)

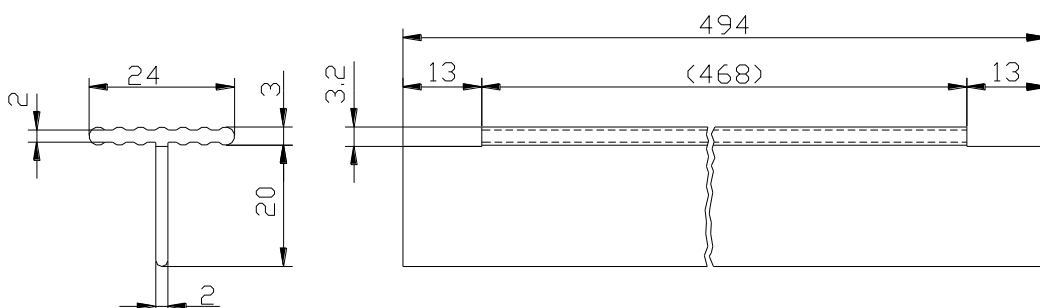

Annex 4: Reinforcement (glass fibre mesh)

Characteristics (alkali resistance): Pass

	Description	Residual strength after ageing [N/mm]	Relative residual strength after ageing, of the strength in the as-delivered state [%]
"Sto-Glasfaserge-webe"	Alkali- and slide-resistant glass fibre mesh with mass per unit area of about 165g/m ² and mesh size of about 6.0 mm x 6.0 mm	≥ 20	≥ 50
"Sto-Glasfaserge-webe F"	Alkali- and slide-resistant glass fibre mesh with mass per unit area of about 165g/m ² and mesh size of about 4.0 mm x 4.0 mm	≥ 20	≥ 50
"Sto-Abschirm-gewebe AES"	Alkali- and slide-resistant glass fibre mesh with mass per unit area of about 165g/m ² and mesh size of about 4.0 mm x 4.0 mm	≥ 20	≥ 50
"Sto-Panzerge-webe"	Alkali- and slide-resistant glass fibre mesh with mass per unit area of about 450g/m ² and mesh size of about 7.5 mm x 7.5 mm	no performance assessed	no performance assessed