



Approval body for construction products and types of construction

#### **Bautechnisches Prüfamt**

An institution established by the Federal and Laender Governments



## European Technical Assessment

### ETA-18/0972 of 10 May 2019

English translation prepared by DIBt - Original version in German language

#### **General Part**

Technical Assessment Body issuing the Deutsches Institut für Bautechnik European Technical Assessment: Injection System Hilti HIT-HY 200 with HAS-D Trade name of the construction product Product family Bonded fastener for use in concrete to which the construction product belongs Manufacturer Hilti Entwicklungsgesellschaft mbH Hiltistraße 6 86916 Kaufering DEUTSCHLAND Manufacturing plant Hilti Werke This European Technical Assessment 21 pages including 3 annexes which form an integral part contains of this assessment EAD 330499-00-0601 This European Technical Assessment is issued in accordance with Regulation (EU) No 305/2011, on the basis of

Deutsches Institut für Bautechnik Kolonnenstraße 30 B | 10829 Berlin | GERMANY | Phone: +49 30 78730-0 | Fax: +49 30 78730-320 | Email: dibt@dibt.de | www.dibt.de



European Technical Assessment ETA-18/0972 English translation prepared by DIBt

Page 2 of 21 | 10 May 2019

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.



Page 3 of 21 | 10 May 2019

European Technical Assessment ETA-18/0972 English translation prepared by DIBt

#### Specific Part

#### 1 Technical description of the product

The "Injection System Hilti HIT-HY 200 with HAS-D" is a bonded anchor consisting of a cartridge with injection mortar Hilti HIT-HY 200-A or Hilti HIT-HY 200-R and a steel element Hilti HAS-D with Hilti sealing washer, a calotte nut and a lock nut in the range of M12, M16 and M20.

The steel element is placed into a drilled hole filled with injection mortar and is anchored via the bond between metal part, injection mortar and concrete.

The product description is given in Annex A.

# 2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

#### 3 Performance of the product and references to the methods used for its assessment

#### 3.1 Mechanical resistance and stability (BWR 1)

| Essential characteristic  | Performance             |
|---|-------------------------|
| Characteristic resistance to static and quasi-static tension load | See Annex C1 and C2     |
| Characteristic resistance to static and quasi-static shear load   | See Annex C3            |
| Displacements for static and quasi-static load                    | See Annex C4            |
| Characteristic resistance for seismic category C1 and C2          | No performance assessed |

#### 3.2 Hygiene, health and the environment (BWR 3)

| Essential characteristic                                 | Performance             |
|--|-------------------------|
| Content, emission and/or release of dangerous substances | No performance assessed |



Page 4 of 21 | 10 May 2019

# European Technical Assessment ETA-18/0972

English translation prepared by DIBt

# 4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with the European Assessment Document EAD 330499-00-0601 the applicable European legal act is: [96/582/EC].

The system to be applied is: 1

# 5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Deutsches Institut für Bautechnik.

Issued in Berlin on 10 May 2019 by Deutsches Institut für Bautechnik

BD Dipl.-Ing. Andreas Kummerow Head of Department *beglaubigt:* Lange

# Page 5 of European Technical Assessment ETA-18/0972 of 10 May 2019

English translation prepared by DIBt




# Installed condition


#### Injection system Hilti HIT-HY 200 with HAS-D

#### Product description Installed condition



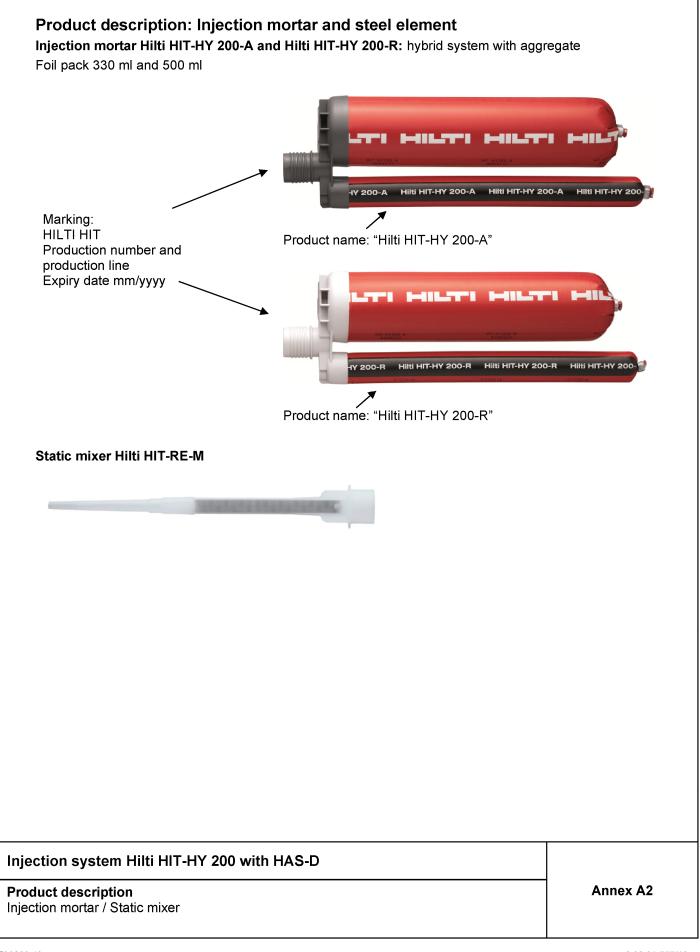



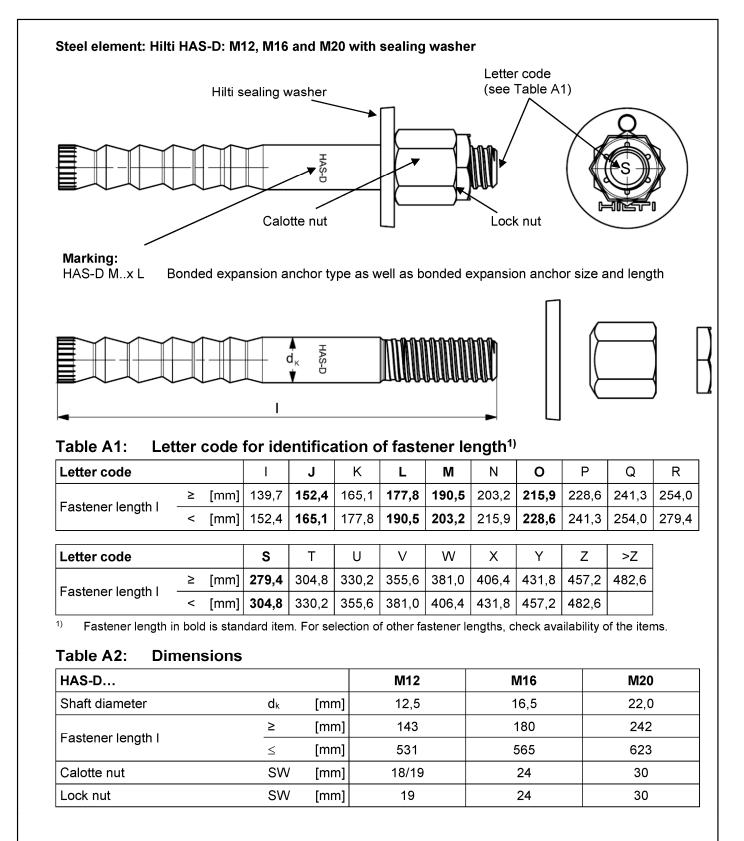


#### Injection system Hilti HIT-HY 200 with HAS-D

#### Product description Steel element



# Hilti sealing washer to fill the annular gap between anchor and fixture



#### Table A3: Geometry of Hilti sealing washer

| Size                              |                    | M12 | M16 M20 |  |
|-----------------------------------|--------------------|-----|---------|--|
| Diameter of sealing washer $d_v$  | <sub>/s</sub> [mm] | 44  | 52 60   |  |
| Thickness of sealing washer $h_v$ | <sub>/s</sub> [mm] | 5   | 6       |  |

#### Injection system Hilti HIT-HY 200 with HAS-D

#### Product description Steel element



| Table A4: Materials |  |  |  |
|---------------------|--|--|--|
| Designation         | Material   |  |  |
| Fastener HAS-D      | Steel acc. to EN 10087:1998, galvanized and coated |  |  |
| Sealing washer      | Steel, electroplated zinc coated $\geq$ 5 $\mu m$  |  |  |
| Calotte nut         | Steel, electroplated zinc coated $\ge$ 5 $\mu$ m   |  |  |
| Lock nut            | Steel, electroplated zinc coated $\ge$ 5 $\mu$ m   |  |  |

#### Injection system Hilti HIT-HY 200 with HAS-D

#### Product description Materials



#### Specifications of intended use

#### Anchorages subject to:

Static and quasi static loading.

#### **Base material:**

- Compacted reinforced or unreinforced normal weight concrete without fibres according to EN 206:2013 + A1:2016.
- Strength classes C20/25 to C50/60 according to EN 206:2013 + A1:2016.
- Cracked and uncracked concrete.

#### Temperature in the base material:

- at installation
- 0 °C to +40 °C
   in-service Temperature range: -40 °C to +80 °C (max. long term temperature +50 °C and max. short term temperature +80 °C)

#### Use conditions (Environmental conditions):

Structures subject to dry internal conditions.

#### **Design:**

- Anchorages are designed under the responsibility of an engineer experienced in anchorages and concrete work.
- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The
  position of the anchor is indicated on the design drawings (e. g. position of the anchor relative to
  reinforcement or to supports, etc.).
- Anchorages under static or quasi-static loading are designed in accordance with: EN 1992-4:2018 and EOTA Technical Report TR 055.

#### Installation:

- Concrete condition I1: dry or wet concrete (not in flooded holes).
- Drilling technique: hammer drilling, hammer drilling with hollow drill bit TE-CD, TE-YD or diamond coring.
- Installation direction D3: downward, horizontal and upwards (e.g. overhead) installation.
- Anchor installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site.

#### Injection system Hilti HIT-HY 200 with HAS-D

#### Intended Use Specifications

#### Deutsches Institut für Bautechnik

| HAS-D  |                       |                     |      | M12              | M16                     | M20                     |
|--|-----------------------|---------------------|------|------------------|-------------------------|-------------------------|
| Diameter of fastener   |                       | $d = d_{nom}$       | [mm] | 12               | 16                      | 20                      |
| Nominal diam   | neter of drill bit    | d₀                  | [mm] | 14               | 18                      | 24                      |
| Effective emb  | pedment depth         | h <sub>ef</sub>     | [mm] | 100              | 125                     | 170                     |
| Minimum drill hole depth   |                       | h₀                  | [mm] | 105              | 133                     | 180                     |
| Minimum thickness of concrete member   |                       | h <sub>min</sub>    | [mm] | 130              | 160 <sup>1)</sup> / 170 | 220 <sup>1)</sup> / 230 |
| <u>Pre-setting:</u><br>Maximum diameter of clearance hole in the fixture     |                       | d <sub>f</sub>      | [mm] | 14               | 18                      | 24                      |
| <u>Through-setting:</u><br>Maximum diameter of clearance hole in the fixture |                       | df                  | [mm] | 16               | 20                      | 26                      |
| Installation torque moment   |                       | T <sub>inst</sub>   | [Nm] | 30               | 50                      | 80                      |
| Uncracked  | Minimum spacing       | Smin,ucr            | [mm] | 80 <sup>2)</sup> | 60                      | 80                      |
| concrete   | Minimum edge distance | <b>C</b> min,ucr    | [mm] | 55 <sup>2)</sup> | 60                      | 80                      |
| Cracked  | Minimum spacing       | Smin,cr             | [mm] | 50               | 60                      | 80                      |
| concrete   | Minimum edge distance | C <sub>min,cr</sub> | [mm] | 50               | 60                      | 80                      |

<sup>1)</sup> The reverse side of the concrete member shall have no break-through after drilling.

 $^{2)}$   $\,$  for min. edge distance  $c_{min} \geq 80$  mm, min. spacing  $s_{min} = 55$  mm

#### Injection system Hilti HIT-HY 200 with HAS-D

Intended Use Installation parameters



| Temperature in the base<br>material T | Maximum working time<br>t <sub>work</sub> | Minimum curing time<br>t <sub>cure</sub> |
|---------------------------------------|---|--|
| ≥ 0 °C to 5 °C                        | 25 min                                    | 2 h                                      |
| > 5 °C to 10 °C                       | 15 min                                    | 75 min                                   |
| > 10 °C to 20 °C                      | 7 min                                     | 45 min                                   |
| > 20 °C to 30 °C                      | 4 min                                     | 30 min                                   |
| > 30 °C to 40 °C                      | 3 min                                     | 30 min                                   |

#### Table B3: Maximum working time and minimum curing time HIT-HY 200-R

| Temperature in the base<br>material T | Maximum working time<br>t <sub>work</sub> | Minimum curing time<br>t <sub>cure</sub> |
|---------------------------------------|---|--|
| ≥ 0 °C to 5 °C                        | 1 h                                       | 4 h                                      |
| > 5 °C to 10 °C                       | 40 min                                    | 2,5 h                                    |
| > 10 °C to 20 °C                      | 15 min                                    | 1,5 h                                    |
| > 20 °C to 30 °C                      | 9 min                                     | 1 h                                      |
| > 30 °C to 40 °C                      | 6 min                                     | 1 h                                      |

#### Injection system Hilti HIT-HY 200 with HAS-D

Intended Use Maximum working time and minimum curing time



| Steel element |        | Drill an                         | id clean       |         | Installation |
|---------------|--------|----------------------------------|----------------|---------|--------------|
|               | Hamme  | er drilling                      |                |         |              |
| HAS-D         |        | Hollow drill bit<br>TE-CD, TE-YD | Diamond coring | Brush   | Piston plug  |
|               |        |                                  | € ⊕)           | ******* |              |
| Size          | d₀[mm] | d₀[mm]                           | d₀[mm]         | HIT-RB  | HIT-SZ       |
| M12           | 14     | 14                               | 14             | 14      | 14           |
| M16           | 18     | 18                               | 18             | 18      | 18           |
| M20           | 24     | 24                               | 24             | 24      | 24           |

#### Table B5: Cleaning alternatives

**Compressed Air Cleaning (CAC):** Air nozzle with an orifice opening of minimum 3,5 mm in diameter.

#### Automatic Cleaning (AC):

Cleaning is performed during drilling with Hilti TE-CD and TE-YD drilling system including vacuum cleaner.



#### Injection system Hilti HIT-HY 200 with HAS-D


Intended Use Drilling, cleaning and setting tools



#### Installation instruction

#### Hole drilling

#### a) Hammer drilling




<u>Through-setting</u>: Drill hole through the clearance hole in the fixture to the required drilling depth with a hammer drill set in rotation-hammer mode using an appropriately sized carbide drill bit.

<u>Pre-setting</u>: Drill hole to the required drilling depth with a hammer drill set in rotationhammer mode using an appropriately sized carbide drill bit.

After drilling is complete, proceed to the "injection preparation" step in the installation instruction.

#### b) Hammer drilling with Hilti hollow drill bit (AC)



<u>Pre- / Through-setting:</u> Drill hole to the required embedment depth with an appropriately sized Hilti TE-CD or TE-YD hollow drill bit with Hilti vacuum attachment. This drilling system removes the dust and cleans the drill hole during drilling when used in accordance with the user's manual. After drilling is completed, proceed to the "injection preparation" step in the installation

After drilling is completed, proceed to the "injection preparation" step in the installation instruction.

#### c) Diamond coring

| drilling depth. | Diamond coring is permissible when suitable diamond core drilling machines and corresponding core bits are used.<br>Through-setting: Drill hole through the clearance hole in the fixture to the required |
|-----------------|---|
|                 |   |

Drill hole cleaning: just before setting an anchor, the drill hole must be free of dust and debris.

a) Compressed Air Cleaning (CAC): for all drill hole diameters do and all drill hole depths ho.

| <b>≠</b> 2x <b>→</b> |   |
|----------------------|---|
|                      |   |
|                      | 5 |
|                      | ] |

Blow 2 times from the back of the hole (if needed with nozzle extension) over the whole length with oil-free compressed air (min. 6 bar at 6 m<sup>3</sup>/h) until return air stream is free of noticeable dust.

| ◆2x→<br>() | Brush 2 times with the specified brush (see Table B4) by inserting the steel brush Hilti<br>HIT-RB to the back of the hole (if needed with extension) in a twisting motion and<br>removing it.<br>The brush must produce natural resistance as it enters the drill hole (brush $\emptyset \ge$<br>drill hole $\emptyset$ ) - if not the brush is too small and must be replaced with the proper brush<br>diameter. |
|------------|--|
|            | Blow again with compressed air 2 times until return air stream is free of noticeable dust.   |

#### Injection system Hilti HIT-HY 200 with HAS-D

#### Intended use Installation instructions




| b) Cleaning of diamon                 | <b>d cored holes:</b> for all drill hole diameters $d_0$ and all drill hole dept   | hs h <sub>0.</sub>   |
|---------------------------------------|--|----------------------|
| <b>◆2x</b> ◆ <b>工</b>                 | Flush 2 times by inserting a water hose (water-line pressure) to until water runs clear.   | the back of the hole |
|                                       | Blow 2 times from the back of the hole (if needed with nozzle ex<br>compressed air (min. 6 bar at 6 m³/h) until return air stream is fr<br>and water.  |                      |
| Injection preparation                 |  |                      |
|                                       | Tightly attach Hilti mixing nozzle HIT-RE-M to foil pack manifold<br>mixing nozzle.<br>Observe the instruction for use of the dispenser.<br>Check foil pack holder for proper function. Insert foil pack into fo<br>put holder into dispenser. |                      |
|                                       | 3 strokes for 500  |                      |
| Inject adhesive from th               | e back of the drill hole without forming air voids.  |                      |
|                                       | Inject the adhesive starting at the back of the hole, slowly withdr each trigger pull.   | awing the mixer with |
| 2/3                                   | Pre-setting: Fill approximately 2/3 of the drill hole.   |                      |
|                                       | <u>Through-setting:</u> Fill 100% of the drill hole.   |                      |
|                                       | After injection is completed, depressurize the dispenser by pres<br>trigger. This will prevent further adhesive discharge from the mix   |                      |
|                                       |  |                      |
| ijection system Hilti H               | HT-HY 200 with HAS-D   |                      |
| tended use<br>stallation instructions |  | Annex B6             |

# Page 16 of European Technical Assessment ETA-18/0972 of 10 May 2019

English translation prepared by DIBt



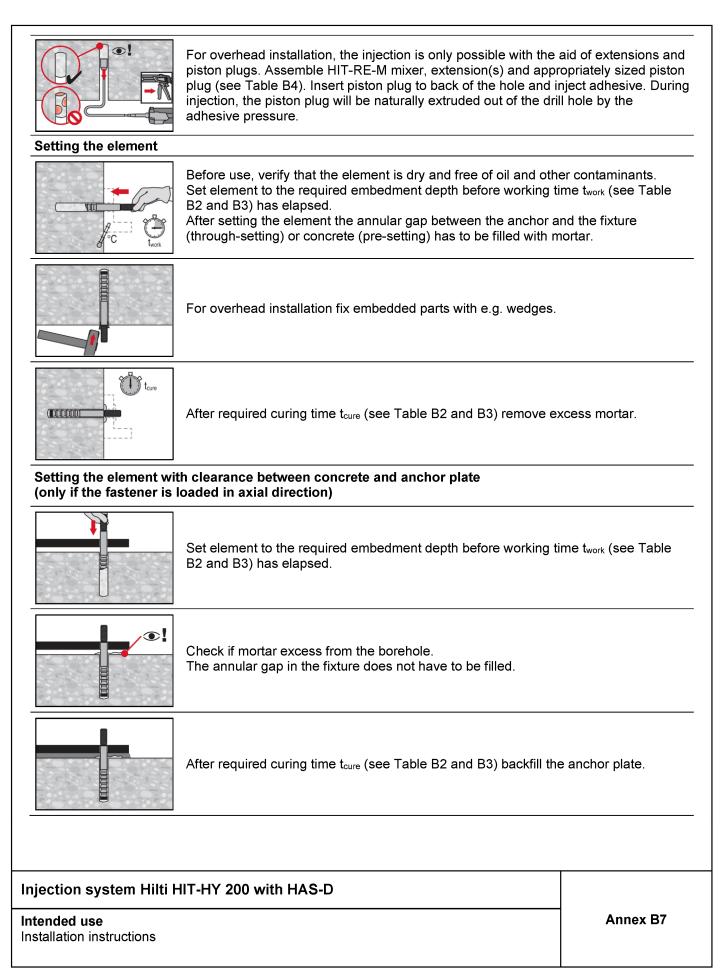

# Page 17 of European Technical Assessment ETA-18/0972 of 10 May 2019

English translation prepared by DIBt



| Orient round part of the calotte nut to the sealing washer and install.   |
|---|
| The required installation torque moment is given in Table B1.   |
| Apply the lock nut and tighten with a $\frac{1}{4}$ to $\frac{1}{2}$ turn.  |
| <u>Pre-setting</u> : Fill the annular gap between the anchor rod and fixture with 1-3 strokes of Hilti injection mortar HIT-HY 200. The static mixer nozzle must be put orthogonally on the filling hole.<br>Follow the installation instructions supplied with the HIT-HY 200 foil pack.<br>After required curing time $t_{cure}$ (see Table B2 and B3), the anchor can be loaded. |

#### Injection system Hilti HIT-HY 200 with HAS-D

Intended use Installation instructions



| HAS-D  |  |                                    |  | M12                    | M16                   | M20                   |
|--|--|------------------------------------|--|------------------------|-----------------------|-----------------------|
| Effective embedment depth                    |  | h <sub>ef</sub>                    | [mm]                                     | 100                    | 125                   | 170                   |
| Installation sensitivity factor              |  | γinst                              | [-]                                      | 1,0                    |                       |                       |
| Steel fail                                   | ure  |                                    | L. L |                        |                       |                       |
| Characteristic resistance                    |  | N <sub>Rk,s</sub>                  | [kN]                                     | 57                     | 111                   | 188                   |
| Partial factor                               |  | γms,n <sup>1)</sup>                | [-]                                      | 1,5                    |                       |                       |
| Pull-out f                                   | ailure   |                                    |  |                        |                       |                       |
| Character                                    | ristic bond resistance in uncrack                                    | ed concrete                        | C20/25                                   |                        |                       |                       |
| Temperature range: 80 °C / 50 °C             |  | <b>N</b> Rk,p,ucr                  | [kN]                                     | 49,2                   | 68,8                  | 109                   |
| Character                                    | ristic resistance in cracked conci                                   | rete C20/25                        |  |                        |                       |                       |
| Temperature range: 80 °C / 50 °C             |  | $\mathbf{N}_{Rk,p,cr}$             | [kN]                                     | 34,4                   | 48,1                  | 76,3                  |
| Increasing factor for $N_{RK,p}$ in concrete |  | _                                  | C30/37                                   | 1,22                   |                       |                       |
|  |  | Ψc                                 | C40/50                                   | 1,41                   |                       |                       |
|  |  | _                                  | C50/60                                   | 1,58                   |                       |                       |
| Concrete                                     | cone failure   |                                    |  |                        |                       |                       |
| Factor for uncracked concrete                |  | $k_1 = k_{ucr,N}$                  | [-]                                      | 11,0                   |                       |                       |
| Factor for cracked concrete                  |  | $\mathbf{k}_1 = \mathbf{k}_{cr,N}$ | [-]                                      | 7,7                    |                       |                       |
| Edge distance                                |  | Ccr,N                              | [mm]                                     | 1,5 · h <sub>ef</sub>  |                       |                       |
| Spacing                                      |  | Scr,N                              | [mm]                                     | 3,0 · h <sub>ef</sub>  |                       |                       |
|  | failure for standard thickness o<br>sistance of case 1 and case 2 ma |                                    |  |                        |                       |                       |
| Standard thickness of concrete member        |  | h                                  | [mm]                                     | 200                    | 250                   | 340                   |
| Case 1                                       | Characteristic resistance in concrete C20/25                         | $N^{0}_{Rk,sp}$                    | [kN]                                     | 40                     | 50                    | 109                   |
|  | Edge distance  | <b>C</b> cr,sp                     | [mm]                                     | 1,5 · h <sub>ef</sub>  |                       |                       |
|  | Spacing  | <b>S</b> cr,sp                     | [mm]                                     | 2 · C <sub>cr,sp</sub> |                       |                       |
| 0  | Edge distance  | <b>C</b> cr,sp                     | [mm]                                     | 2,0 · h <sub>ef</sub>  | 2,0 · h <sub>ef</sub> | 1,5 ⋅ h <sub>ef</sub> |
| Case 2                                       | Spacing  | S <sub>cr,sp</sub>                 | [mm]                                     | 2 · C <sub>cr.sp</sub> |                       |                       |

#### Injection system Hilti HIT-HY 200 with HAS-D

Performances

Essential characteristics under tension load in concrete

Annex C1



|         | failure for minimum thickness of<br>sistance of case 1 and case 2 ma |                    |      |                        |     |                       |
|---------|--|--------------------|------|------------------------|-----|-----------------------|
| Minimum | thickness of concrete member   | h <sub>min</sub>   | [mm] | 130                    | 160 | 220                   |
| Case 1  | Characteristic resistance in concrete C20/25                         | $N^0_{Rk,sp}$      | [kN] | 30                     | 40  | 75                    |
|         | Edge distance  | C <sub>cr,sp</sub> | [mm] | 1,5 · h <sub>ef</sub>  |     |                       |
|         | Spacing  | S <sub>cr,sp</sub> | [mm] | 2 · C <sub>cr,sp</sub> |     |                       |
| Case 2  | Edge distance  | C <sub>cr,sp</sub> | [mm] | 3,0 · h <sub>ef</sub>  |     | 2,6 · h <sub>ef</sub> |
|         | Spacing  | Scr,sp             | [mm] | 2 · C <sub>cr,sp</sub> |     |                       |

<sup>1)</sup> In absence of national regulations.

#### Injection system Hilti HIT-HY 200 with HAS-D

**Performances** Essential characteristics under tension load in concrete Annex C2



| HAS-D                                  |                     |      | M12 | M16  | M20 |
|--|---------------------|------|-----|------|-----|
| Installation sensitivity factor        | γinst               | [-]  |     | 1,0  |     |
| Steel failure without lever arm        |                     |      |     |      |     |
| Characteristic resistance              | V <sub>Rk,s</sub>   | [kN] | 34  | 63   | 149 |
| Partial factor                         | γMs,∨ <sup>1)</sup> | [-]  | ·   | 1,25 |     |
| Ductility factor                       | <b>k</b> 2          |      |     | 1,0  |     |
| Steel failure with lever arm           |                     | ·    |     |      |     |
| Characteristic resistance              | M <sup>0</sup> Rk,s | [Nm] | 105 | 266  | 519 |
| Partial factor                         | γMs,∨ <sup>1)</sup> | [-]  |     | 1,25 |     |
| Concrete pry-out failure               |                     |      |     |      |     |
| Pry-out factor                         | k <sub>8</sub>      | [-]  |     | 2,0  |     |
| Concrete edge failure                  |                     |      |     |      |     |
| Effective length of fastener           | lf                  | [mm] | 100 | 125  | 170 |
| Effective outside diameter of fastener | $d_{nom}$           | [mm] | 14  | 18   | 24  |
| Partial factor                         | γMc <sup>1)</sup>   | [-]  |     | 1,5  | •   |

<sup>1)</sup> In absence of national regulations.

#### Injection system Hilti HIT-HY 200 with HAS-D

**Performances** Essential characteristics under shear load in concrete Annex C3



| HAS-D        |                         |         | M12   | M16   | M20   |
|--------------|-------------------------|---------|-------|-------|-------|
| Uncracked co | ncrete                  |         |       |       |       |
| Displacement | $\delta_{N0}$ -Factor   | [mm/kN] | 0,017 | 0,018 | 0,011 |
| Displacement | δ <sub>N∞</sub> -Factor | [mm/kN] | 0,054 | 0,039 | 0,024 |
| Cracked conc | rete                    |         |       |       |       |
| Displacement | δ <sub>N0</sub> -Factor | [mm/kN] | 0,035 | 0,029 | 0,021 |
| Displacement | δ <sub>N∞</sub> -Factor | [mm/kN] | 0,076 | 0,054 | 0,034 |

<sup>1)</sup> Calculation of the displacement:

 $\delta_{N0} = \delta_{N0}$ -Faktor · N;

(N: applied tension force).

#### Table C4: Displacements under shear load in concrete

 $\delta_{N\infty} = \delta_{N\infty}$ -Faktor · N;

| HAS-D        |                       |         | M12  | M16  | M20   |
|--------------|-----------------------|---------|------|------|-------|
| Displacement | $\delta_{V0}$ -Factor | [mm/kN] | 0,17 | 0,11 | 0,057 |
| Displacement | δv∞-Factor            | [mm/kN] | 0,26 | 0,16 | 0,087 |

<sup>1)</sup> Calculation of the displacement:

 $\delta_{V0} = \delta_{V0}$ -factor · V;  $\delta_{V\infty} = \delta_{V\infty}$ -factor · V;

(V: applied shear force).

#### Injection system Hilti HIT-HY 200 with HAS-D

**Performances** Displacements under tension and shear load in concrete