Deutsches Institut für Bautechnik

Member of EOTA
www.eota.eu

Approval body for construction products and types of construction

Bautechnisches Prüfamt

An institution established by the Federal and Laender Governments

Designated according to Article 29 of Regulation (EU) No 305/2011 and member of EOTA (European Organisation for Technical Assessment)

European Technical Assessment

ETA-11/0079 of 28 July 2020

English translation prepared by DIBt - Original version in German language

General Part

Technical Assessment Body issuing the European Technical Assessment:	Deutsches Institut für Bautechnik
Trade name of the construction product	BERNER multicompound system MCS Uni Plus
Product family to which the construction product belongs	Bonded anchor for use in concrete
Manufacturer	Berner Trading Holding GmbH Bernerstraße 6 74653 Künzelsau DEUTSCHLAND
Manufacturing plant	Berner Herstellwerk 6 Berner manufacturing plant 6
This European Technical Assessment contains	34 pages including 3 annexes which form an integral part of this assessment
This European Technical Assessment is issued in accordance with Regulation (EU) No 305/2011, on the basis of	EAD 330499-01-0601, Edition 04/2020
This version replaces	ETA-11/0079 issued on 20 October 2015

Electronic copy of the ETA by DIBt: ETA-11/0079

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

Electronic copy of the ETA by DIBt: ETA-11/0079

Specific Part

1 Technical description of the product

The "BERNER multicompound system MCS Uni Plus" is a bonded fastener consisting of a cartridge with injection mortar MCS Uni Plus, MCS Uni Plus WE or MCS Uni Plus S and a steel element according to Annex A5.

The steel element is placed into a drilled hole filled with injection mortar and is anchored via the bond between metal part, injection mortar and concrete.

The product description is given in Annex A.

2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment

3.1 Mechanical resistance and stability (BWR 1)

Essential characteristic	Performance
Characteristic resistance to tension load (static and quasi-static loading)	See Annex B 3 to B 6, C 1 to C 8
Characteristic resistance to shear load (static and quasi-static loading)	See Annex C 1 to C 4
Displacements under short-term and long-term loading	See Annex C 9 and C 10
Characteristic resistance and displacements for seismic performance categories C1 and C2	See Annex C 11 to C 14

3.2 Hygiene, health and the environment (BWR 3)

Essential characteristic	Performance
Content, emission and/or release of dangerous substances	No performance assessed

Electronic copy of the ETA by DIBt: ETA-11/0079

4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with the European Assessment Document EAD 330499-01-0601 the applicable European legal act is: [96/582/EC].

The system to be applied is: 1

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Deutsches Institut für Bautechnik.

Issued in Berlin on 28 July 2020 by Deutsches Institut für Bautechnik

BD Dipl.-Ing. Andreas Kummerow
Head of Department

beglaubigt:
Baderschneider

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Installation conditions part 1

BERNER anchor rod

Pre-positioned installation

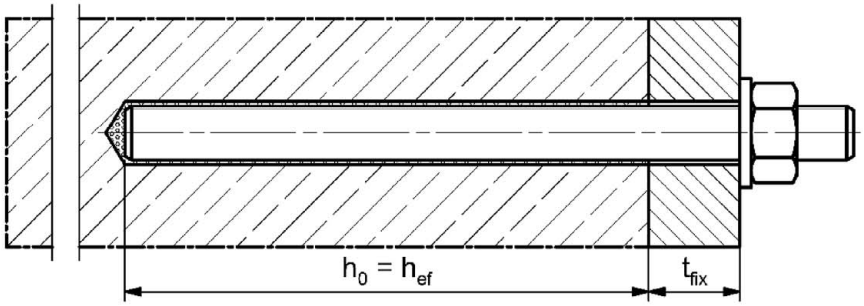

Push through installation (annular gap filled with mortar)

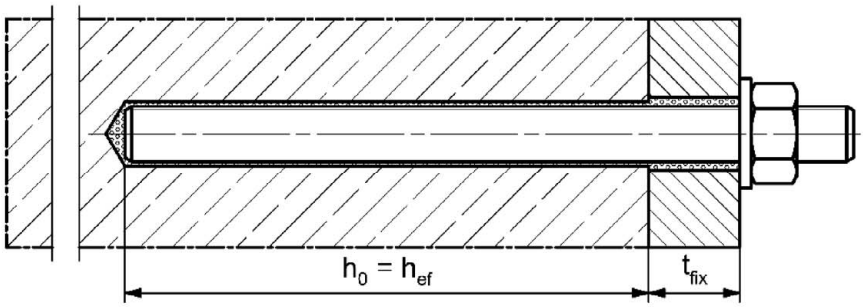

Pre-positioned or push through installation with subsequently injected BERNER filling disc
(annular gap filled with mortar)

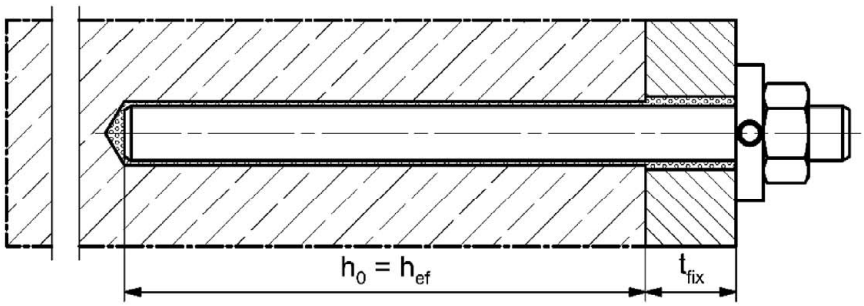

Figures not to scale

h_0 = drill hole depth
h_{ef} = effective embedment depth
t_{fix} = thickness of fixture

BERNER multicompound system MCS Uni Plus

Product description
Installation conditions part 1

Annex A 1

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Installation conditions part 2

BERNER Internal threaded anchor MCS Plus I

Pre-positioned installation

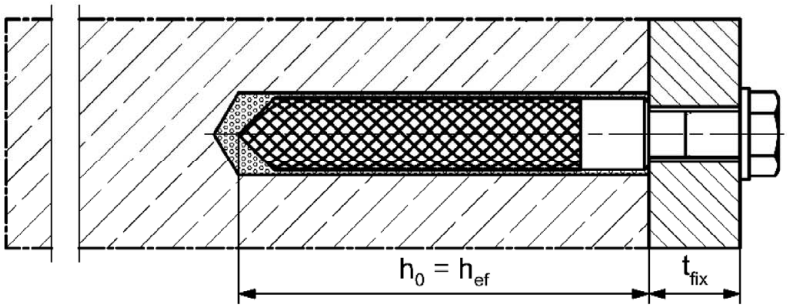

Pre-positioned installation with subsequently injected BERNER filling disc (annular gap filled with mortar)

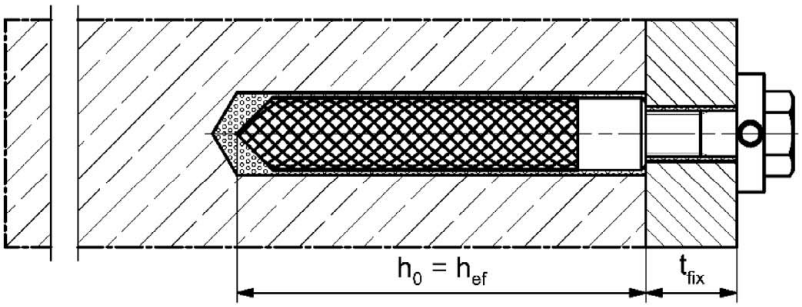

Figures not to scale

h_0 = drill hole depth

h_{ef} = effective embedment depth

t_{fix} = thickness of fixture

BERNER multicompound system MCS Uni Plus

Product description
Installation conditions part 2

Annex A 2

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Installation conditions part 3

Reinforcing bar

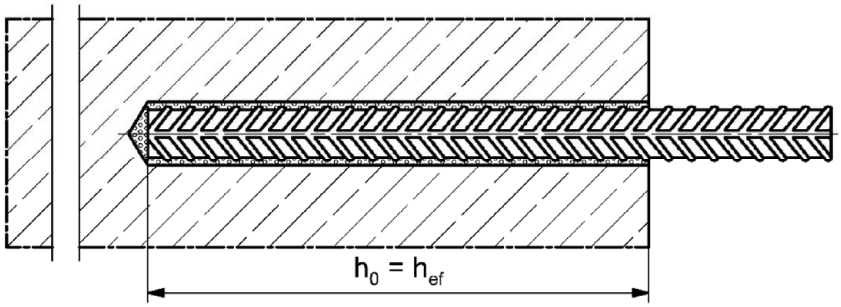

BERNER rebar anchor BRA

Pre-positioned installation

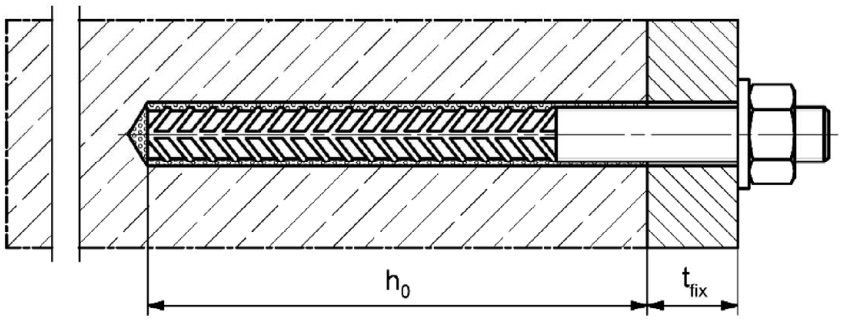

Push through installation (annular gap filled with mortar)

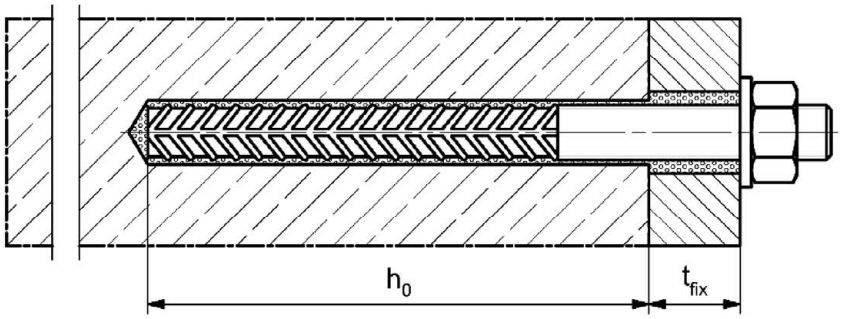

Figures not to scale

h_0 = drill hole depth
h_{ef} = effective embedment depth
t_{fix} = thickness of fixture

BERNER multicompound system MCS Uni Plus

Product description
Installation conditions part 3

Annex A 3

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Overview system components part 1

Injection cartridge (shuttle cartridge) with sealing cap; Sizes: 350 ml, 360 ml, 390 ml, 550 ml, 1100 ml, 1500 ml

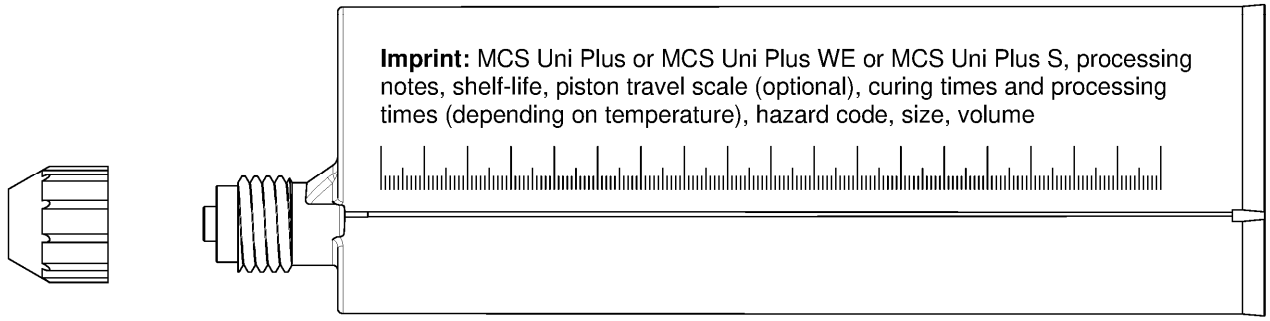

Injection cartridge (coaxial cartridge) with sealing cap; Sizes: 100 ml, 150 ml, 300 ml, 380 ml, 400 ml, 410 ml

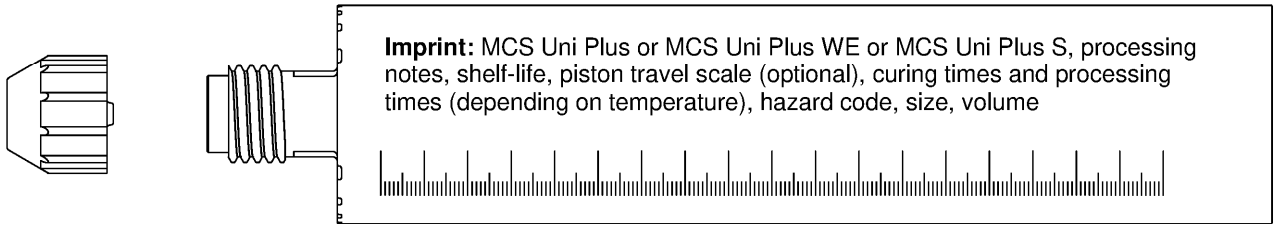

Static mixer MCS Uni Plus

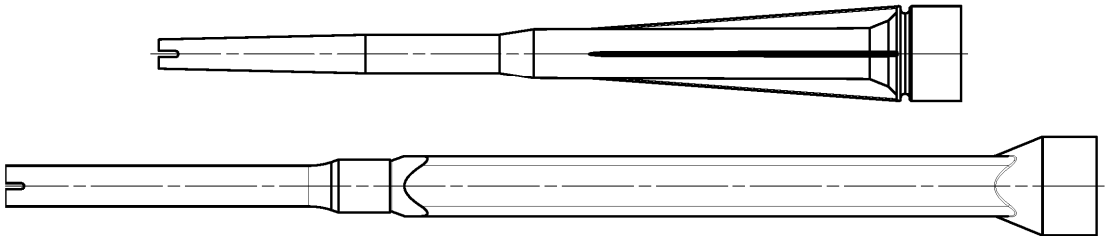

Injection adapter and Extension tube for static mixer



Cleaning brush BERNER

Blow-out pump

Figures not to scale

BERNER multicompound system MCS Uni Plus

Product description
Overview system components part 1;
cartridges / static mixer / accessories

Annex A 4

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Overview system components part 2

BERNER anchor rod

Size: M6, M8, M10, M12, M16, M20, M24, M27, M30



BERNER internal threaded anchor MCS Plus I

Size: M8, M10, M12, M16, M20



Screw / threaded rod / washer / hexagon nut

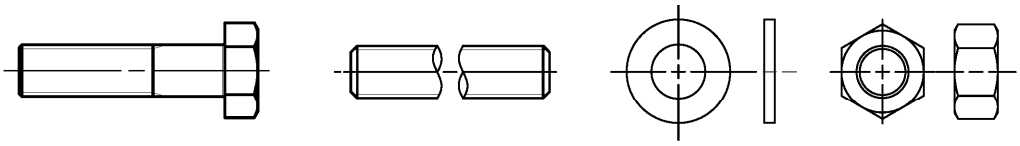

BERNER filling disc BFD with injection adapter

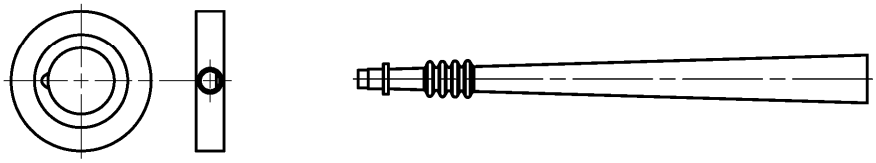

Reinforcing bar

Nominal diameter: ϕ8, ϕ10, ϕ12, ϕ14, ϕ16, ϕ20, ϕ25, ϕ28

BERNER rebar anchor BRA

Size: M12, M16, M20, M24



Figures not to scale

BERNER multicompound system MCS Uni Plus

Product description
Overview system components part 2;
steel components

Annex A 5

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table A6.1: Materials

Part	Designation	Material		
1	Injection cartridge	Mortar, hardener, filler		
	Steel grade	Steel	Stainless steel R	High corrosion resistant steel HCR
		zinc plated	acc. to EN 10088-1:2014 Corrosion resistance class CRC III acc. to EN 1993-1-4:2015	acc. to EN 10088-1:2014 Corrosion resistance class CRC V acc. to EN 1993-1-4:2015
2	Anchor rod	Property class 4.8, 5.8 or 8.8; EN ISO 898-1:2013 zinc plated ≥ 5 µm, ISO 4042:2018/Zn5/An(A2K) or hot dip galvanised ≥ 40 µm EN ISO 10684:2004 f_{uk} ≤ 1000 N/mm² A_5 > 12% fracture elongation	Property class 50, 70 or 80 EN ISO 3506-1:2009 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362; 1.4062, 1.4662, 1.4462; EN 10088-1:2014 f_{uk} ≤ 1000 N/mm² A_5 > 12% fracture elongation	Property class 50 or 80 EN ISO 3506-1:2009 or property class 70 with f_{yk}= 560 N/mm² 1.4565; 1.4529; EN 10088-1:2014 f_{uk} ≤ 1000 N/mm² A_5 > 12% fracture elongation
		Fracture elongation A_5 > 8 %, for applications without requirements for seismic performance category C2		
3	Washer ISO 7089:2000	zinc plated ≥ 5 µm, ISO 4042:2018/Zn5/An(A2K) or hot dip galvanised ≥ 40 µm EN ISO 10684:2004	1.4401; 1.4404; 1.4578;1.4571; 1.4439; 1.4362; EN 10088-1:2014	1.4565; 1.4529; EN 10088-1:2014
4	Hexagon nut	Property class 4, 5 or 8; EN ISO 898-2:2012 zinc plated ≥ 5 µm, ISO 4042:2018/Zn5/An(A2K) or hot dip galvanised ≥ 40 µm EN ISO 10684:2004	Property class 50, 70 or 80 EN ISO 3506-1:2009 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362; EN 10088-1:2014	Property class 50, 70 or 80 EN ISO 3506-1:2009 1.4565; 1.4529 EN 10088-1:2014
5	BERNER internal threaded anchor MCS Plus I	Property class 5.8 ISO 898-1:2013 zinc plated ≥ 5 µm, ISO 4042:2018/Zn5/An(A2K)	Property class 70 EN ISO 3506-1:2009 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362; EN 10088-1:2014	Property class 70 EN ISO 3506-1:2009 1.4565; 1.4529; EN 10088-1:2014
6	Commercial standard screw or threaded rod for BERNER internal threaded anchor MCS Plus I	Property class 5.8 or 8.8; EN ISO 898-1:2013 zinc plated ≥ 5 µm, ISO 4042:2018/Zn5/An(A2K) A_5 > 8 % fracture elongation	Property class 70 EN ISO 3506-1:2009 1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362; EN 10088-1:2014 A_5 > 8 % fracture elongation	Property class 70 EN ISO 3506-1:2009 1.4565; 1.4529; EN 10088-1:2014 A_5 > 8 % fracture elongation
7	BERNER filling disc similar to DIN 6319-G	zinc plated ≥ 5 µm, ISO 4042:2018/Zn5/An(A2K) or hot dip galvanised ≥ 40 µm EN ISO 10684:2004	1.4401; 1.4404; 1.4578; 1.4571; 1.4439; 1.4362; EN 10088-1:2014	1.4565;1.4529; EN 10088-1:2014
8	Reinforcing bar EN 1992-1-1:2004 and AC:2010, Annex C	Bars and de-coiled rods, class B or C with f_{yk} and k according to NDP or NCL according to EN 1992-1-1/NA $f_{uk} = f_{tk} = k \cdot f_{yk}$		
9	BERNER rebar anchor BRA	Rebar part: Bars and de-coiled rods class B or C with f_{yk} and k according to NDP or NCL of EN 1992-1-1:2004+AC:2010 $f_{uk} = f_{tk} = k \cdot f_{yk}$	Threaded part: Property class 70 or 80 EN ISO 3506-1:2009 1.4401, 1.4404, 1.4571, 1.4578, 1.4439, 1.4362, 1.4062 acc. to EN 10088-1:2014 Corrosion resistance class CRC III acc. to EN 1993-1-4:2015 1.4565; 1.4529 acc. to EN 10088-1:2014 Corrosion resistance class CRC V acc. to EN 1993-1-4:2015	

BERNER multicompound system MCS Uni Plus

Product description
Materials

Annex A 6

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Specifications of intended use (part 1)

Table B1.1: Overview use and performance categories

Anchorages subject to			**BERNER MCS Uni Plus with …**							
			Anchor rod		BERNER internal threaded anchor MCS Plus I 		Reinforcing bar 		BERNER rebar anchor BRA 	
Hammer drilling with standard drill bit			all sizes							
Hammer drilling with hollow drill bit (BERNER Cleandrill dustless, fischer “FHD”, Heller "Duster Expert"; Bosch „Speed Clean“; Hilti "TE-CD, TE-YD"), DreBo D-Plus, DreBo D-Max 			Nominal drill bit diameter (d_0) 12 mm to 35 mm							
Static and quasi static load, in	uncracked concrete		all sizes	Tables: C1.1 C4.1 C5.1 C9.1	all sizes	Tables: C2.1 C4.1 C6.1 C9.2	all sizes	Tables: C3.1 C4.1 C7.1 C10.1	all sizes	Tables: C3.2 C4.1 C8.1 C10.2
	cracked concrete		M8 to M30		-[2]		ϕ 10 to ϕ 28			
Seismic performance category (only hammer drilling with standard / hollow drill bits)	C1[1]		M10 to M30	Tables: C11.1 C12.1 C13.1	-[2]		-[2]		-[2]	
	C2[1]		M12 M16 M20 M24	Tables: C11.1 C12.1 C14.1						
Use category	I1	dry or wet concrete	all sizes							
	I2	water filled hole	M 12 to M 30		all sizes		-[2]		-[2]	
Installation direction			D3 (downward and horizontal and upwards (e.g. overhead) installation)							
Installation temperature			$T_{i,min}$ = -10 °C to $T_{i,max}$ = +40 °C							
In-service temperature	Temperature range I		-40 °C to +80 °C		(max. short term temperature +80 °C; max. long term temperature +50 °C)					
	Temperature range II		-40 °C to +120 °C		(max. short term temperature +120 °C; max. long term temperature +72 °C)					

[1] Not for MCS Uni Plus S or MCS Uni Plus WE
[2] No performance assessed

BERNER multicompound system MCS Uni Plus

Intended use
Specifications (part 1)

Annex B 1

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Specifications of intended use (part 2)

Base materials:

- Compacted reinforced or unreinforced normal weight concrete without fibres of strength classes C20/25 to C50/60 according to EN 206:2013+A1:2016

Use conditions (Environmental conditions):

- Structures subject to dry internal conditions
  (zinc coated steel, stainless steel or high corrosion resistant steel).
- For all other conditions according to EN1993-1-4:2015 corresponding to corrosion resistance classes to Annex A 6 table A6.1.

Design:

- Anchorages have to be designed by a responsible engineer with experience of concrete anchor design.
- Verifiable calculation notes and drawings are to be prepared taking account of the loads to be anchored. The position of the anchor is indicated on the design drawings (e. g. position of the anchor relative to reinforcement or to supports, etc.).
- Anchorages are designed in accordance with:
  EN 1992-4:2018 and EOTA Technical Report TR 055, Edition February 2018.

Installation:

- Anchor installation is to be carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site
- In case of aborted hole: The hole shall be filled with mortar
- Anchorage depth should be marked and adhered to on installation
- Overhead installation is allowed

BERNER multicompound system MCS Uni Plus	**Annex B 2**
Intended use Specifications (part 2)	

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table B3.1: Installation parameters for **anchor rods**

Anchor rods			**Thread**	**M6**	**M8**	**M10**	**M12**	**M16**	**M20**	**M24**	**M27**	**M30**
Width across flats		SW		10	13	17	19	24	30	36	41	46
Nominal drill hole diameter		d_0		8	10	12	14	18	24	28	30	35
Drill hole depth		h_0		$h_0 = h_{ef}$								
Effective embedment depth		$h_{ef,\,min}$		50	60	60	70	80	90	96	108	120
		$h_{ef,\,max}$		72	160	200	240	320	400	480	540	600
Minimum spacing and minimum edge distance		s_{min} = c_{min}	[mm]	40	40	45	55	65	85	105	125	140
Diameter of the clearance hole of the fixture	pre-positioned installation	d_f		7	9	12	14	18	22	26	30	33
	push through installation	d_f		9	12	14	16	20	26	30	33	40
Minimum thickness of concrete member		h_{min}		h_{ef} + 30 (≥100)				h_{ef} + 2d_0				
Maximum installation torque		max T_{inst}	[Nm]	5	10	20	40	60	120	150	200	300

BERNER anchor rod

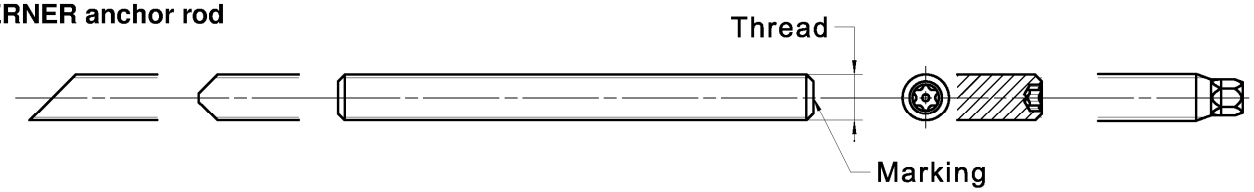

Marking (on random place) BERNER anchor rod:

Steel zinc plated PC[1] 8.8	• or +	Steel hot-dip PC[1] 8.8	•
High corrosion resistant steel HCR PC[1] 50	•	High corrosion resistant steel HCR PC[1] 70	–
High corrosion resistant steel HCR PC[1] 80	(	Stainless steel R property class 50	~
Stainless steel R property class 80	✳		

Alternatively: Colour coding according to DIN 976-1: 2016

[1] PC = property class

Installation conditions:

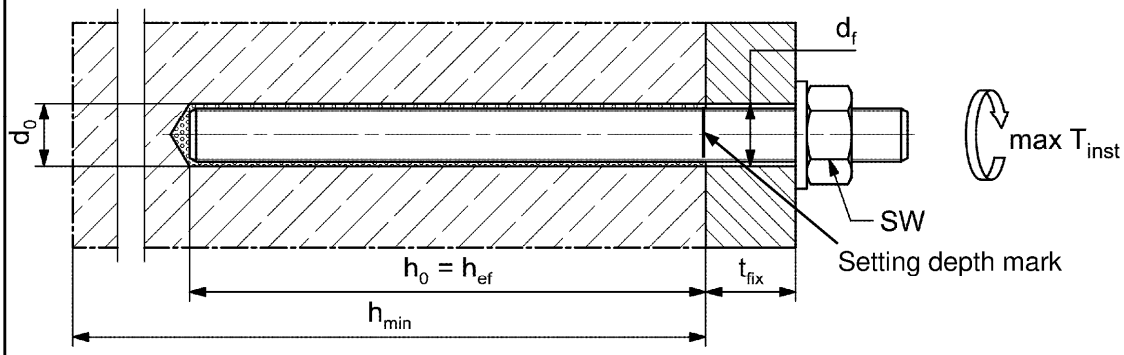

Commercial standard threaded rods, washers and hexagon nuts may also be used if the following requirements are fulfilled

- Materials, dimensions and mechanical properties according to Annex A 6, Table A6.1
- Inspection certificate 3.1 according to EN 10204:2004, the documents have to be stored
- Setting depth is marked

Figures not to scale

BERNER multicompound system MCS Uni Plus

Intended use
Installation parameters anchor rods

Annex B 3

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table B4.1: Installation parameters for **BERNER internal threaded anchors MCS Plus I**

Internal threaded anchors MCS Plus I		**Thread**	**M8**	**M10**	**M12**	**M16**	**M20**
Diameter of anchor	$d_{nom} = d_H$		12	16	18	22	28
Nominal drill hole diameter	d_0		14	18	20	24	32
Drill hole depth	h_0		$h_0 = h_{ef} = L_H$				
Effective embedment depth ($h_{ef} = L_H$)	h_{ef}		90	90	125	160	200
Minimum spacing and minimum edge distance	s_{min} = c_{min}	[mm]	55	65	75	95	125
Diameter of clearance hole in the fixture	d_f		9	12	14	18	22
Minimum thickness of concrete member	h_{min}		120	125	165	205	260
Maximum screw-in depth	$l_{E,max}$		18	23	26	35	45
Minimum screw-in depth	$l_{E,min}$		8	10	12	16	20
Maximum installation torque	max T_{inst}	[Nm]	10	20	40	80	120

BERNER internal threaded anchor MCS Plus I

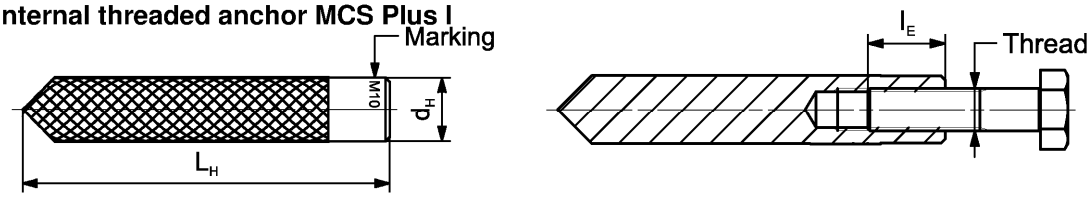

Marking: Anchor size e. g.: **M10**
Stainless steel → additional **R**; e.g.: **M10 R**
High corrosion resistant steel → additional **HCR**; e.g.: **M10 HCR**

Retaining bolt or threaded rods (including nut and washer) must comply with the appropriate material and strength class of Annex A 6, Table A6.1

Installation conditions:

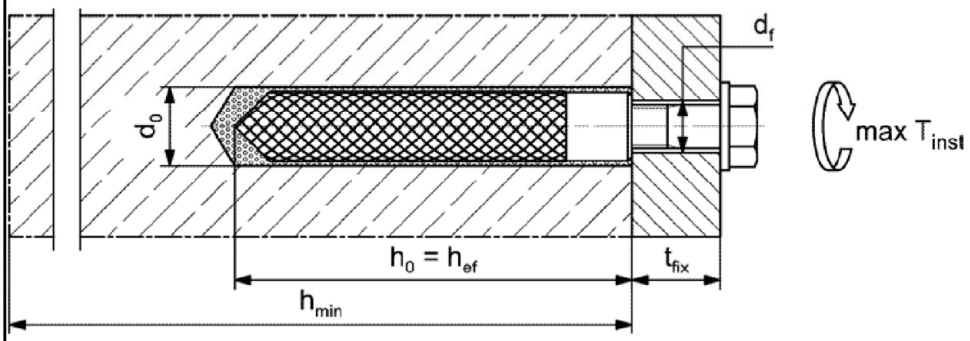

Figures not to scale

BERNER multicompound system MCS Uni Plus

Intended use
Installation parameters BERNER internal threaded anchors MCS Plus I

Annex B 4

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table B5.1: Installation parameters for **reinforcing bars**

Nominal diameter of the bar		**ϕ**	**8**[1]		**10**[1]		**12**[1]		**14**	**16**	**20**	**25**	**28**
Nominal drill hole diameter	d_0	[mm]	10	12	12	14	14	16	18	20	25	30	35
Drill hole depth	h_0		$h_0 = h_{ef}$										
Effective embedment depth	$h_{ef,min}$		60		60		70		75	80	90	100	112
	$h_{ef,max}$		160		200		240		280	320	400	500	560
Minimum spacing and minimum edge distance	s_{min} = c_{min}		40		45		55		60	65	85	110	130
Minimum thickness of concrete member	h_{min}		h_{ef} + 30 (≥ 100)						h_{ef} + $2d_0$				

[1] Both drill hole diameters can be used

Reinforcing bar

- The minimum value of related rib area $f_{R,min}$ must fulfil the requirements of EN 1992-1-1:2004+AC:2010
- The rib height must be within the range: $0{,}05 \cdot \phi \le h_{rib} \le 0{,}07 \cdot \phi$
  (ϕ = Nominal diameter of the bar, h_{rib} = rib height)

Installation conditions:

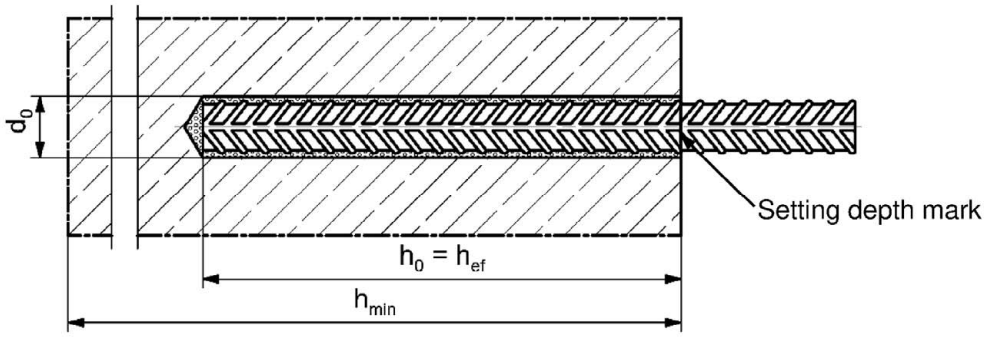

Figures not to scale

BERNER multicompound system MCS Uni Plus

Intended use
Installation parameters reinforcing bars

Annex B 5

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table B6.1: Installation parameters for **BERNER rebar anchor BRA**

Rebar anchor BRA			**Thread**	**M12**[1]		**M16**	**M20**	**M24**
Nominal diameter of the bar		ϕ	[mm]	12		16	20	25
Width across flats		SW		19		24	30	36
Nominal drill hole diameter		d_0		14	16	20	25	30
Drill hole depth		h_0		$h_{ef} + l_e$				
Effective embedment depth		$h_{ef,min}$		70		80	90	96
		$h_{ef,max}$		140		220	300	380
Distance concrete surface to welded joint		l_e		100				
Minimum spacing and minimum edge distance		s_{min} = c_{min}		55		65	85	105
Diameter of clearance hole in the fixture	pre-positioned anchorage	$\leq d_f$		14		18	22	26
	push through anchorage	$\leq d_f$		18		22	26	32
Minimum thickness of concrete member		h_{min}		$h_0 + 30$	$h_0 + 2d_0$			
Maximum installation torque		max T_{inst}	[Nm]	40		60	120	150

[1] Both drill hole diameters can be used

BERNER rebar anchor BRA

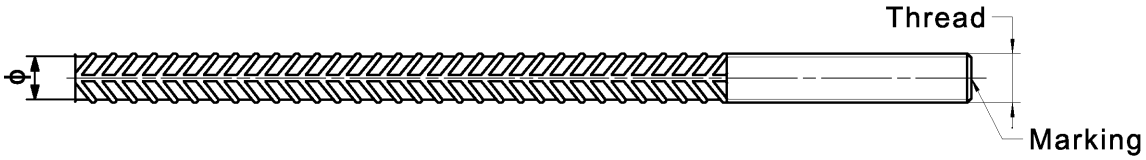

Marking frontal e. g: BRA (for stainless steel);
BRA HCR (for high corrosion resistant steel)

Installation conditions:

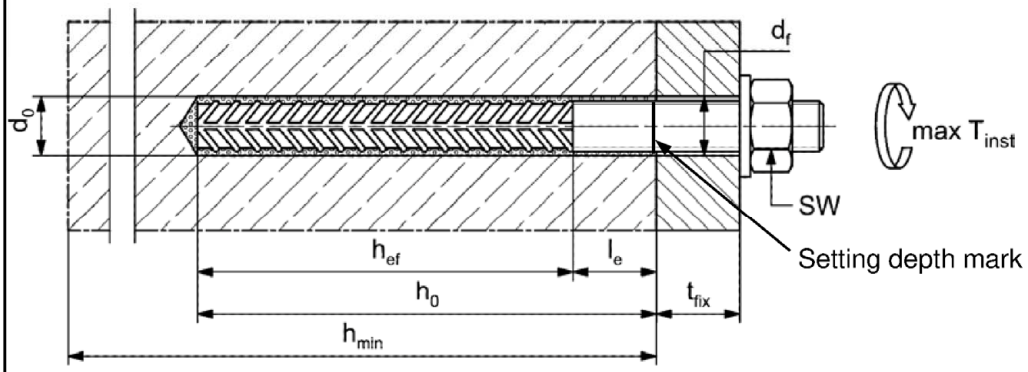

Figures not to scale

BERNER multicompound system MCS Uni Plus

Intended use
Installation parameters BERNER rebar anchor BRA

Annex B 6

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table B7.1: Parameters of the **cleaning brush** (steel brush with steel bristles)

The size of the cleaning brush refers to the drill hole diameter

Nominal drill hole diameter	d_0	[mm]	8	10	12	14	16	18	20	24	25	28	30	35
Steel brush diameter	d_b		9	11	14	16	20		25	26	27	30	40	

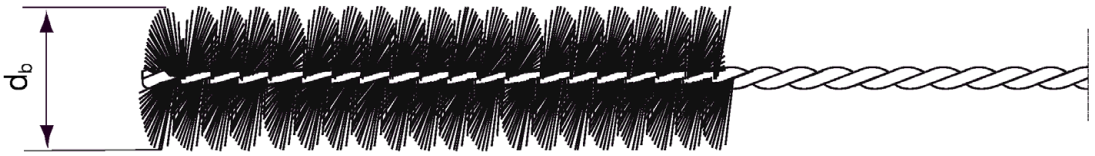

Table B7.2 **Maximum processing** time of the mortar and **minimum curing** time (During the curing time of the mortar the concrete temperature may not fall below the listed minimum temperature)

Temperature at anchoring base [°C]	Maximum processing time t_{work}			Minimum curing time [1] t_{cure}		
	MCS Uni Plus WE	MCS Uni Plus	MCS Uni Plus S	MCS Uni Plus WE	MCS Uni Plus	MCS Uni Plus S
-10 to -5 [2]	-	-	-	12 h	-	-
> -5 to 0 [2]	5 min	-	-	3 h	24 h	-
> 0 to 5 [2]	5 min	13 min	-	3 h	3 h	6 h
> 5 to 10	3 min	9 min	20 min	50 min	90 min	3 h
> 10 to 20	1 min	5 min	10 min	30 min	60 min	2 h
> 20 to 30	-	4 min	6 min	-	45 min	60 min
> 30 to 40	-	2 min	4 min	-	35 min	30 min

[1] In wet concrete or water filled holes the curing times must be doubled
[2] Minimal cartridge temperature +5°C

Electronic copy of the ETA by DIBt: ETA-11/0079

BERNER multicompound system MCS Uni Plus

Intended use
Cleaning brush (steel brush)
Processing time and curing time

Annex B 7

Deutsches Institut für Bautechnik DIBt

Installation instructions part 1

Drilling and cleaning the hole (hammer drilling with standard drill bit)

1	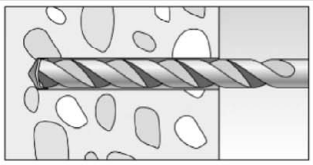	Drill the hole. Nominal drill hole diameter $\mathbf{d_0}$ and drill hole depth $\mathbf{h_0}$ see **tables B3.1, B4.1, B5.1, B6.1**		
2	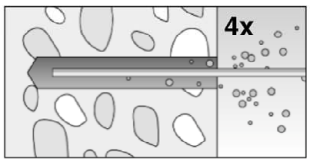	Clean the drill hole: For $h_{ef} \leq 12d$ and $d_0 < 18$ mm blow out the hole four times by hand	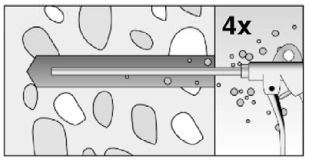	For $h_{ef} > 12d$ and / or $d_0 \geq 18$ mm blow out the hole four times with oil-free compressed air ($p \geq 6$ bar)
3	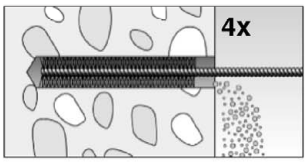	Brush the drill hole four times. For deep holes use an extension. Corresponding brushes see **table B7.1**		
4	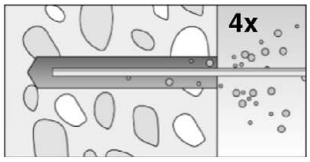	Clean the drill hole: For $h_{ef} \leq 12d$ and $d_0 < 18$ mm blow out the hole four times by hand	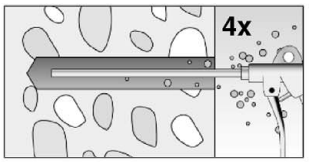	For $h_{ef} > 12d$ and / or $d_0 \geq 18$ mm blow out the hole four times with oil-free compressed air ($p \geq 6$ bar)

Go to step 5

Drilling and cleaning the hole (hammer drilling with hollow drill bit)

1		Check a suitable hollow drill (see **table B1.1**) for correct operation of the dust extraction
2	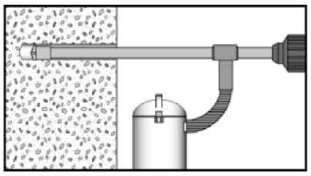	Use a suitable dust extraction system, e. g. BWDVC PERM M-1 or a comparable dust extraction system with equivalent performance data Drill the hole with hollow drill bit. The dust extraction system has to extract the drill dust nonstop during the drilling process and must be adjusted to maximum power. Nominal drill hole diameter $\mathbf{d_0}$ and drill hole depth $\mathbf{h_0}$ see **tables B3.1, B4.1, B5.1, B6.1**

Go to step 5

BERNER multicompound system MCS Uni Plus

Intended use
Installation instructions part 1

Annex B 8

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Installation instructions part 2

Preparing the cartridge

5	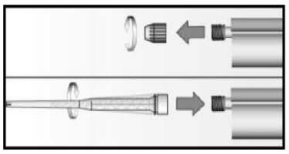	Remove the sealing cap Screw on the static mixer (the spiral in the static mixer must be clearly visible)
6	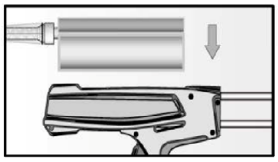 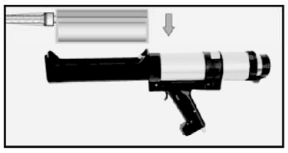	Place the cartridge into the dispenser
7	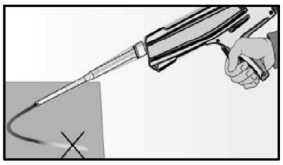 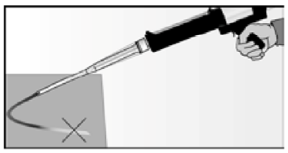	Extrude approximately 10 cm of material out until the resin is evenly grey in colour. Do not use mortar that is not uniformly grey

Go to step 8

Injection of the mortar

8	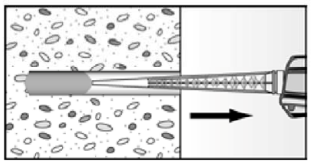 Fill approximately 2/3 of the drill hole with mortar. Always begin from the bottom of the hole and avoid bubbles	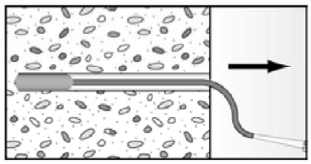 For drill hole depth ≥ 150 mm use an extension tube	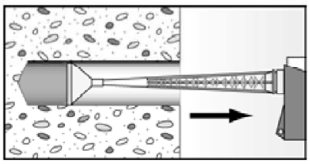 For overhead installation, deep holes (h_0 > 250 mm) or drill hole diameter (d_0 ≥ 40 mm) use an injection adapter

Go to step 9

BERNER multicompound system MCS Uni Plus

Intended use
Installation instructions part 2

Annex B 9

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Installation instructions part 3

Installation of anchor rods or BERNER internal threaded anchors MCS Plus I

9

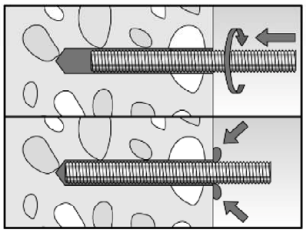

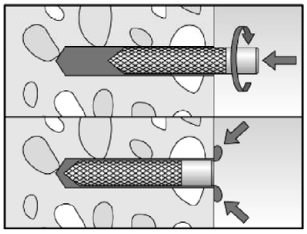

Only use clean and oil-free metal parts.
Mark the setting depth of the metal part. Push the anchor rod or BERNER internal threaded MCS Plus I anchor down to the bottom of the hole, turning it slightly while doing so.
After inserting the metal parts, excess mortar must be emerged around the anchor element.



For overhead installations support the metal part with wedges (e. g. centering wedges) or overhead clips.

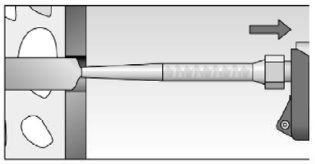

For push through installation fill the annular gap with mortar

10

Wait for the specified curing time t_{cure}
see **table B7.2**

11

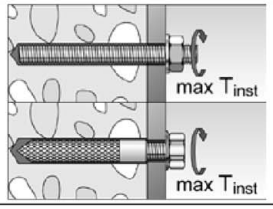

Mounting the fixture
max T_{inst} see **tables B3.1 and B4.1**

Option

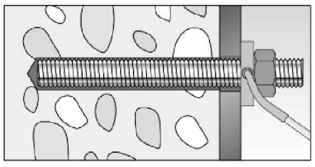

After the minimum curing time is reached, the gap between metal part and fixture (annular clearance) may be filled with mortar via the BERNER filling disc BFD. Compressive strength ≥ 50 N/mm² (e.g. injection mortars MCS Uni Plus or MCS Diamond). ATTENTION: Using BERNER filling disc BFD reduces t_{fix} (usable length of the anchor).

Installation reinforcing bars and BERNER rebar anchor BRA

9

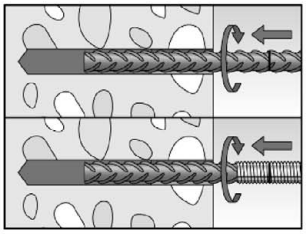

Only use clean and oil-free reinforcing bars or BERNER rebar anchor BRA.
Mark the setting depth. Turn while using force to push the reinforcement bar or the BERNER rebar anchor BRA into the filled hole up to the setting depth mark

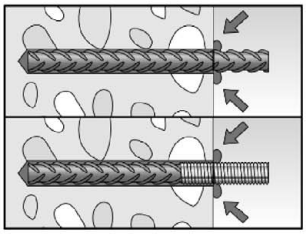

When the setting depth mark is reached, excess mortar must be emerged from the mouth of the drill hole.

10



Wait for the specified curing time t_{cure} see **table B7.2**

11

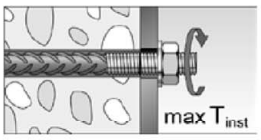

Mounting the fixture
max T_{inst}
see **table B6.1**

BERNER multicompound system MCS Uni Plus

Intended use
Installation instructions part 3

Annex B 10

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C1.1: Characteristic values for **steel failure** under tension / shear load of **BERNER anchor rods** and **standard threaded rods**

Anchor rod / standard threaded rod				**M6**	**M8**	**M10**	**M12**	**M16**	**M20**	**M24**	**M27**	**M30**
Bearing capacity under tension load, steel failure [3]												
Characteristic resistance $N_{Rk,s}$	Steel zinc plated	Property class	4.8	8	15(13)	23(21)	33	63	98	141	184	224
			5.8	10	19(17)	29(27)	43	79	123	177	230	281
			8.8	16	29(27)	47(43)	68	126	196	282	368	449
	Stainless steel R and high corrosion resistant steel HCR		50	10	19	29	43	79	123	177	230	281
			70	14	26	41	59	110	172	247	322	393
			80	16	30	47	68	126	196	282	368	449
		[kN]										
Partial factors [1]												
Partial factor $\gamma_{Ms,N}$	Steel zinc plated	Property class	4.8	1,50								
			5.8	1,50								
			8.8	1,50								
	Stainless steel R and high corrosion resistant steel HCR		50	2,86								
			70	1,50[2] / 1,87								
			80	1,60								
		[-]										
Bearing capacity under shear load, steel failure [3]												
without lever arm												
Characteristic resistance $V^0_{Rk,s}$	Steel zinc plated	Property class	4.8	4	9(8)	14(13)	20	38	59	85	110	135
			5.8	6	11(10)	17(16)	25	47	74	106	138	168
			8.8	8	15(13)	23(21)	34	63	98	141	184	225
	Stainless steel R and high corrosion resistant steel HCR		50	5	9	15	21	39	61	89	115	141
			70	7	13	20	30	55	86	124	161	197
			80	8	15	23	34	63	98	141	184	225
		[kN]										
Ductility factor		k_7	[-]	1,0								
with lever arm												
Charact. resistance $M^0_{Rk,s}$	Steel zinc plated	Property class	4.8	6	15(13)	30(27)	52	133	259	448	665	899
			5.8	7	19(16)	37(33)	65	166	324	560	833	1123
			8.8	12	30(26)	60(53)	105	266	519	896	1333	1797
	Stainless steel R and high corrosion resistant steel HCR		50	7	19	37	65	166	324	560	833	1123
			70	10	26	52	92	232	454	784	1167	1573
			80	12	30	60	105	266	519	896	1333	1797
		[Nm]										
Partial factors [1]												
Partial factor $\gamma_{Ms,V}$	Steel zinc plated	Property class	4.8	1.25								
			5.8	1.25								
			8.8	1.25								
	Stainless steel R and high corrosion resistant steel HCR		50	2.38								
			70	1.25[2] / 1.56								
			80	1.33								
		[-]										

[1] In absence of other national regulations
[2] Only admissible for high corrosion resist. steel HCR, with $f_{yk} / f_{uk} \geq 0,8$ and $A_5 > 12$ % (e.g. BERNER anchor rods)
[3] Values in brackets are valid for undersized threaded rods with smaller stress area A_s for hot dip galvanised standard threaded rods according to EN ISO 10684:2004+AC:2009

BERNER multicompound system MCS Uni Plus

Performances
Characteristic values for steel failure under tension / shear load of BERNER anchor rods and standard threaded rods

Annex C 1

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C2.1: Characteristic values for **steel failure** under tension / shear load of **BERNER internal threaded anchors MCS Plus I**

internal threaded anchors MCS Plus I					**M8**	**M10**	**M12**	**M16**	**M20**
Bearing capacity under tension load, steel failure									
Charact. resistance with screw	$N_{Rk,s}$	Property class	5.8	[kN]	19	29	43	79	123
			8.8		29	47	68	108	179
		Property class 70	R		26	41	59	110	172
			HCR		26	41	59	110	172
Partial factors[1)]									
Partial factors	$\gamma_{Ms,N}$	Property class	5.8	[-]	1,50				
			8.8		1,50				
		Property class 70	R		1,87				
			HCR		1,87				
Bearing capacity under shear load, steel failure									
Without lever arm									
Charact. resistance with screw	$V^0_{Rk,s}$	Property class	5.8	[kN]	9,2	14,5	21,1	39,2	62,0
			8.8		14,6	23,2	33,7	54,0	90,0
		Property class 70	R		12,8	20,3	29,5	54,8	86,0
			HCR		12,8	20,3	29,5	54,8	86,0
Ductility factor			k_7	[-]	1,0				
With lever arm									
Charact. resistance with screw	$M^0_{Rk,s}$	Property class	5.8	[Nm]	20	39	68	173	337
			8.8		30	60	105	266	519
		Property class 70	R		26	52	92	232	454
			HCR		26	52	92	232	454
Partial factors[1)]									
Partial factors	$\gamma_{Ms,V}$	Property class	5.8	[-]	1,25				
			8.8		1,25				
		Property class 70	R		1,56				
			HCR		1,56				

[1)] In absence of other national regulations

Electronic copy of the ETA by DIBt: ETA-11/0079

BERNER multicompound system MCS Uni Plus

Performances
Characteristic values for steel failure under tension / shear load of BERNER internal threaded anchor MCS Plus I

Annex C 2

Deutsches Institut für Bautechnik DIBt

Table C3.1: Characteristic values **for steel failure** under tension / shear load of **reinforcing bars**

Nominal diameter of the bar		**ϕ**	**8**	**10**	**12**	**14**	**16**	**20**	**25**	**28**
Bearing capacity under tension load, steel failure										
Characteristic resistance	$N_{Rk,s}$	[kN]	$A_s \cdot f_{uk}$ [1)]							
Bearing capacity under shear load, steel failure										
Without lever arm										
Characteristic resistance	$V^0_{Rk,s}$	[kN]	$0,5 \cdot A_s \cdot f_{uk}$ [1)]							
Ductility factor	k_7	[-]	1,0							
With lever arm										
Characteristic resistance	$M^0_{Rk,s}$	[Nm]	$1,2 \cdot W_{el} \cdot f_{uk}$ [1)]							

[1)] f_{uk} or f_{yk} respectively must be taken from the specifications of the reinforcing bar

Table C3.2: Characteristic values for **steel failure** under tension / shear load of **BERNER rebar anchors BRA**

BERNER rebar anchor BRA			**M12**	**M16**	**M20**	**M24**
Bearing capacity under tension load, steel failure						
Characteristic resistance	$N_{Rk,s}$	[kN]	63	111	173	270
Partial factor[1)]						
Partial factor	$\gamma_{Ms,N}$	[-]	1,4			
Bearing capacity under shear load, steel failure						
Without lever arm						
Characteristic resistance	$V^0_{Rk,s}$	[kN]	30	55	86	124
Ductility factor	k_7	[-]	1,0			
With lever arm						
Characteristic resistance	$M^0_{Rk,s}$	[Nm]	92	233	454	785
Partial factor[1)]						
Partial factor	$\gamma_{Ms,V}$	[-]	1,56			

[1)] In absence of other national regulations

BERNER multicompound system MCS Uni Plus

Performances
Characteristic values for steel failure under tension / shear load of reinforcing bars and BERNER rebar anchors BRA

Annex C 3

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C4.1: Characteristic values for **concrete failure** under tension / shear load

Size				**All sizes**								
Tension load												
Installation factor		γ_{inst}	[-]	See annex C 5 to C 8 and C 13 to C14								
Factors for the compressive strength of concrete > C20/25												
Increasing factor for τ_{Rk}	C25/30	Ψ_c	[-]	1,05								
	C30/37			1,10								
	C35/45			1,15								
	C40/50			1,19								
	C45/55			1,22								
	C50/60			1,26								
Splitting failure												
Edge distance	$h / h_{ef} \geq 2,0$	$c_{cr,sp}$	[mm]	$1,0\ h_{ef}$								
	$2,0 > h / h_{ef} > 1,3$			$4,6\ h_{ef} - 1,8\ h$								
	$h / h_{ef} \leq 1,3$			$2,26\ h_{ef}$								
Spacing		$s_{cr,sp}$		$2\ c_{cr,sp}$								
Concrete cone failure												
Uncracked concrete		$k_{ucr,N}$	[-]	11,0								
Cracked concrete		$k_{cr,N}$		7,7								
Edge distance		$c_{cr,N}$	[mm]	$1,5\ h_{ef}$								
Spacing		$s_{cr,N}$		$2\ c_{cr,N}$								
Factors for sustained tension load												
Temperature range			[-]	50 °C / 80 °C					72 °C / 120 °C			
Factor		Ψ^0_{sus}	[-]	0,74					0,87			
Shear load												
Installation factor		γ_{inst}	[-]	1,0								
Concrete pry-out failure												
Factor for pry-out failure		k_8	[-]	2,0								
Concrete edge failure												
Effective length of fastener in shear loading		l_f	[mm]	for $d_{nom} \leq 24$ mm: min (h_{ef}; 12 d_{nom}) for $d_{nom} > 24$ mm: min (h_{ef}; 8 d_{nom}; 300 mm)								
Calculation diameters												
Size				M6	M8	M10	M12	M16	M20	M24	M27	M30
BERNER anchor rods and standard threaded rods		d_{nom}	[mm]	6	8	10	12	16	20	24	27	30
internal threaded anchors MCS Plus I		d_{nom}		-[1)]	12	16	18	22	28	-[1)]	-[1)]	-[1)]
rebar anchor BRA		d_{nom}		-[1)]	-[1)]	-[1)]	12	16	20	25	-[1)]	-[1)]
Size (nominal diameter of the bar)			ϕ	8	10	12	14	16	20	25	28	
Reinforcing bar		d_{nom}	[mm]	8	10	12	14	16	20	25	28	

[1)] Anchortyp not part of the assessment

BERNER multicompound system MCS Uni Plus

Performances
Characteristic values for concrete failure under tension / shear load

Annex C 4

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C5.1: Characteristic values for **combined pull-out** and concrete failure for **BERNER anchor rods** and **standard threaded rods** in hammer drilled holes; **uncracked or cracked concrete**

Anchor rod / standard threaded rod				**M6**	**M8**	**M10**	**M12**	**M16**	**M20**	**M24**	**M27**	**M30**
Combined pullout and concrete cone failure												
Calculation diameter		d	[mm]	6	8	10	12	16	20	24	27	30
Uncracked concrete												
Characteristic bond resistance in uncracked concrete C20/25												
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)												
Temperature range	I: 50 °C / 80 °C	$\tau_{Rk,ucr}$	[N/mm²]	9,0	11,0	11,0	11,0	10,0	9,5	9,0	8,5	8,5
	II: 72 °C / 120 °C			6,5	9,5	9,5	9,0	8,5	8,0	7,5	7,0	7,0
Hammer-drilling with standard drill bit or hollow drill bit (water filled hole)[1]												
Temperature range	I: 50 °C / 80 °C	$\tau_{Rk,ucr}$	[N/mm²]	-[2]	-[2]	-[2]	9,5	8,5	8,0	7,5	7,0	7,0
	II: 72 °C / 120 °C			-[2]	-[2]	-[2]	7,5	7,0	6,5	6,0	6,0	6,0
Installation factors												
Dry or wet concrete		γ_{inst}	[-]	1,0								
Water filled hole				-[2]	-[2]	-[2]	1,2 [1]					
Cracked concrete												
Characteristic bond resistance in cracked concrete C20/25												
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)												
Temperature range	I: 50 °C / 80 °C	$\tau_{Rk,cr}$	[N/mm²]	-[2]	5,5	6,0	6,0	6,0	5,5	4,5	4,0	4,0
	II: 72 °C / 120 °C			-[2]	4,5	5,0	6,0	6,0	5,0	4,0	3,5	3,5
Hammer-drilling with standard drill bit or hollow drill bit (water filled hole)[1]												
Temperature range	I: 50 °C / 80 °C	$\tau_{Rk,cr}$	[N/mm²]	-[2]	-[2]	-[2]	5,0	5,0	4,5	4,0	3,5	3,5
	II: 72 °C / 120 °C			-[2]	-[2]	-[2]	4,0	4,0	4,0	3,5	3,0	3,0
Installation factors												
Dry or wet concrete		γ_{inst}	[-]	1,0								
Water filled hole				-[2]	-[2]	-[2]	1,2 [1]					

[1] Only with coaxial cartridges: 380ml, 400 ml, 410 ml
[2] No performance assessed

BERNER multicompound system MCS Uni Plus

Performances
Characteristic values for combined pull-out and concrete failure for BERNER anchor rod and standard threaded rods

Annex C 5

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C6.1: Characteristic values for **combined pull-out** and concrete failure for **BERNER internal threaded anchors MCS Plus I** in hammer drilled holes; **uncracked concrete**

BERNER Internal threaded anchor MCS Plus I			**M8**	**M10**	**M12**	**M16**	**M20**
Combined pullout and concrete cone failure							
Calculation diameter	d	[mm]	12	16	18	22	28
Uncracked concrete							
Characteristic bond resistance in uncracked concrete C20/25							
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)							
Temperature range I: 50 °C / 80 °C	$\tau_{Rk,ucr}$	[N/mm²]	10,5	10,0	9,5	9,0	8,5
Temperature range II: 72 °C / 120 °C	$\tau_{Rk,ucr}$	[N/mm²]	9,0	8,0	8,0	7,5	7,0
Hammer-drilling with standard drill bit or hollow drill bit (water filled hole)[1)]							
Temperature range I: 50 °C / 80 °C	$\tau_{Rk,ucr}$	[N/mm²]	10,0	9,0	9,0	8,5	8,0
Temperature range II: 72 °C / 120 °C	$\tau_{Rk,ucr}$	[N/mm²]	7,5	6,5	6,5	6,0	6,0
Installation factors							
Dry or wet concrete	γ_{inst}	[-]	1,0				
Water filled hole	γ_{inst}	[-]	1,2[1)]				

[1)] Only with coaxial cartridges: 380 ml, 400 ml, 410 ml

BERNER multicompound system MCS Uni Plus

Performances
Characteristic values for combined pull-out and concrete failure for BERNER internal threaded anchors MCS Plus I

Annex C 6

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C7.1: Characteristic values for **combined pull-out** and concrete failure for **reinforcing bars** in hammer drilled holes; **uncracked or cracked concrete**

Nominal diameter of the bar		**ϕ**	**8**	**10**	**12**	**14**	**16**	**20**	**25**	**28**
Combined pullout and concrete cone failure										
Calculation diameter	d	[mm]	8	10	12	14	16	20	25	28
Uncracked concrete										
Characteristic bond resistance in uncracked concrete C20/25										
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)										
Temperature range I: 50 °C / 80 °C	$\tau_{Rk,ucr}$	[N/mm²]	11,0	11,0	11,0	10,0	10,0	9,5	9,0	8,5
Temperature range II: 72 °C / 120 °C	$\tau_{Rk,ucr}$	[N/mm²]	9,5	9,5	9,0	8,5	8,5	8,0	7,5	7,0
Installation factor										
Dry or wet concrete	γ_{inst}	[-]	1,0							
Cracked concrete										
Characteristic bond resistance in cracked concrete C20/25										
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)										
Temperature range I: 50 °C / 80 °C	$\tau_{Rk,cr}$	[N/mm²]	-[1)]	3,0	5,0	5,0	5,0	4,5	4,0	4,0
Temperature range II: 72 °C / 120 °C	$\tau_{Rk,cr}$	[N/mm²]	-[1)]	3,0	4,5	4,5	4,5	4,0	3,5	3,5
Installation factor										
Dry or wet concrete	γ_{inst}	[-]	1,0							

1) No performance assessed

Electronic copy of the ETA by DIBt: ETA-11/0079

BERNER multicompound system MCS Uni Plus

Performances
Characteristic values for combined pull-out and concrete failure for reinforcing bars

Annex C 7

Deutsches Institut für Bautechnik DIBt

Table C8.1: Characteristic values for **combined pull-out** and concrete failure for **BERNER rebar anchors BRA** in hammer drilled holes; **uncracked or cracked concrete**

BERNER rebar anchor BRA				**M12**	**M16**	**M20**	**M24**
Combined pullout and concrete cone failure							
Calculation diameter		d	[mm]	12	16	20	25
Uncracked concrete							
Characteristic bond resistance in uncracked concrete C20/25							
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)							
Temperature range	I: 50 °C / 80 °C	$\tau_{Rk,ucr}$	[N/mm²]	11,0	10,0	9,5	9,5
	II: 72 °C / 120 °C			9,0	8,5	8,0	7,5
Installation factors							
Dry or wet concrete		γ_{inst}	[-]	1,0			
Cracked concrete							
Characteristic bond resistance in cracked concrete C20/25							
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)							
Temperature range	I: 50 °C / 80 °C	$\tau_{Rk,cr}$	[N/mm²]	5,0	5,0	4,5	4,0
	II: 72 °C / 120 °C			4,5	4,5	4,0	3,5
Installation factors							
Dry or wet concrete		γ_{inst}	[-]	1,0			

BERNER multicompound system MCS Uni Plus

Performances
Characteristic values for combined pull-out and concrete failure for BERNER rebar anchors BRA

Annex C 8

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C9.1: Displacements for anchor rods

Anchor rod		M6	M8	M10	M12	M16	M20	M24	M27	M30
Displacement-Factors for tension load[1)]										
Uncracked concrete; Temperature range I, II										
$\delta_{N0\text{-Factor}}$	[mm/(N/mm²)]	0,09	0,09	0,09	0,10	0,10	0,10	0,10	0,11	0,12
$\delta_{N\infty\text{-Factor}}$		0,10	0,10	0,10	0,12	0,12	0,12	0,13	0,13	0,14
Cracked concrete; Temperature range I, II										
$\delta_{N0\text{-Factor}}$	[mm/(N/mm²)]	-[3)]	0,12	0,12	0,12	0,13	0,13	0,13	0,14	0,15
$\delta_{N0\text{-Factor}}$		-[3)]	0,25	0,27	0,30	0,30	0,30	0,35	0,35	0,40
Displacement-Factors for shear load[2)]										
Uncracked or cracked concrete; Temperature range I, II										
$\delta_{V0\text{-Factor}}$	[mm/kN]	0,11	0,11	0,11	0,10	0,10	0,09	0,09	0,08	0,07
$\delta_{V\infty\text{-Factor}}$		0,12	0,12	0,12	0,11	0,11	0,10	0,10	0,09	0,09

[1)] Calculation of effective displacement:

$\delta_{N0} = \delta_{N0\text{-Factor}} \cdot \tau_{Ed}$

$\delta_{N\infty} = \delta_{N\infty\text{-Factor}} \cdot \tau_{Ed}$

(τ_{Ed}: Design value of the applied tensile stress)

[2)] Calculation of effective displacement:

$\delta_{V0} = \delta_{V0\text{-Factor}} \cdot V_{Ed}$

$\delta_{V\infty} = \delta_{V\infty\text{-Factor}} \cdot V_{Ed}$

(V_{Ed}: Design value of the applied shear force)

[3)] No performance assessed

Table C9.2: Displacements for BERNER internal threaded anchors MCS Plus I

Internal threaded anchor MCS Plus I		M8	M10	M12	M16	M20
Displacement-Factors for tension load[1)]						
Uncracked concrete; Temperature range I, II						
$\delta_{N0\text{-Factor}}$	[mm/(N/mm²)]	0,10	0,11	0,12	0,13	0,14
$\delta_{N\infty\text{-Factor}}$		0,13	0,14	0,15	0,16	0,18
Displacement-Factors for shear load[2)]						
Uncracked concrete; Temperature range I, II						
$\delta_{V0\text{-Factor}}$	[mm/kN]	0,12	0,12	0,12	0,12	0,12
$\delta_{V\infty\text{-Factor}}$		0,14	0,14	0,14	0,14	0,14

[1)] Calculation of effective displacement:

$\delta_{N0} = \delta_{N0\text{-Factor}} \cdot \tau_{Ed}$

$\delta_{N\infty} = \delta_{N\infty\text{-Factor}} \cdot \tau_{Ed}$

(τ_{Ed}: Design value of the applied tensile stress)

[2)] Calculation of effective displacement:

$\delta_{V0} = \delta_{V0\text{-Factor}} \cdot V_{Ed}$

$\delta_{V\infty} = \delta_{V\infty\text{-Factor}} \cdot V_{Ed}$

(V_{Ed}: Design value of the applied shear force)

BERNER multicompound system MCS Uni Plus

Performances
Displacements for anchor rods and BERNER internal threaded anchors MCS Plus I

Annex C 9

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C10.1: Displacements for reinforcing bars

Nominal diameter of the bar ϕ		8	10	12	14	16	20	25	28
Displacement-Factors for tension load[1)]									
Uncracked concrete; Temperature range I, II									
$\delta_{N0\text{-Factor}}$	[mm/(N/mm²)]	0,09	0,09	0,10	0,10	0,10	0,10	0,10	0,11
$\delta_{N\infty\text{-Factor}}$		0,10	0,10	0,12	0,12	0,12	0,12	0,13	0,13
Cracked concrete; Temperature range I, II									
$\delta_{N0\text{-Factor}}$	[mm/(N/mm²)]	-[3)]	0,12	0,13	0,13	0,13	0,13	0,13	0,14
$\delta_{N\infty\text{-Factor}}$		-[3)]	0,27	0,30	0,30	0,30	0,30	0,35	0,37
Displacement-Factors for shear load[2)]									
Uncracked or cracked concrete; Temperature range I, II									
$\delta_{V0\text{-Factor}}$	[mm/kN]	0,11	0,11	0,10	0,10	0,10	0,09	0,09	0,08
$\delta_{V\infty\text{-Factor}}$		0,12	0,12	0,11	0,11	0,11	0,10	0,10	0,09

[1)] Calculation of effective displacement:

$\delta_{N0} = \delta_{N0\text{-Factor}} \cdot \tau_{Ed}$

$\delta_{N\infty} = \delta_{N\infty\text{-Factor}} \cdot \tau_{Ed}$

(τ_{Ed}: Design value of the applied tensile stress)

[2)] Calculation of effective displacement:

$\delta_{V0} = \delta_{V0\text{-Factor}} \cdot V_{Ed}$

$\delta_{V\infty} = \delta_{V\infty\text{-Factor}} \cdot V_{Ed}$

(V_{Ed}: Design value of the applied shear force)

[3)] No performance assessed

Table C10.2: Displacements for BERNER rebar anchors BRA

rebar anchor BRA		M12	M16	M20	M24
Displacement-Factors for tension load[1)]					
Uncracked concrete; Temperature range I, II					
$\delta_{N0\text{-Factor}}$	[mm/(N/mm²)]	0,10	0,10	0,10	0,10
$\delta_{N\infty\text{-Factor}}$		0,12	0,12	0,12	0,13
Cracked concrete; Temperature range I, II					
$\delta_{N0\text{-Factor}}$	[mm/(N/mm²)]	0,12	0,13	0,13	0,13
$\delta_{N\infty\text{-Factor}}$		0,30	0,30	0,30	0,35
Displacement-Factors for shear load[2)]					
Uncracked or cracked concrete; Temperature range I, II					
$\delta_{V0\text{-Factor}}$	[mm/kN]	0,10	0,10	0,09	0,09
$\delta_{V\infty\text{-Factor}}$		0,11	0,11	0,10	0,10

[1)] Calculation of effective displacement:

$\delta_{N0} = \delta_{N0\text{-Factor}} \cdot \tau_{Ed}$

$\delta_{N\infty} = \delta_{N\infty\text{-Factor}} \cdot \tau_{Ed}$

(τ_{Ed}: Design value of the applied tensile stress)

[2)] Calculation of effective displacement:

$\delta_{V0} = \delta_{V0\text{-Factor}} \cdot V_{Ed}$

$\delta_{V\infty} = \delta_{V\infty\text{-Factor}} \cdot V_{Ed}$

(V_{Ed}: Design value of the applied shear force)

BERNER multicompound system MCS Uni Plus

Performances
Displacements for reinforcing bars and BERNER rebar anchors BRA

Annex C 10

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C11.1: Characteristic values for **steel failure** under tension / shear load of **BERNER anchor rods** and **standard threaded rods** under seismic action performance category **C1 or C2**

Anchor rod / standard threaded rod				**M10**	**M12**	**M16**	**M20**	**M24**	**M27**	**M30**
Bearing capacity under tension load, steel failure[1]										
BERNER anchor rods and standard threaded rods, performance category C1 [2]										
Characteristic resistance $N_{Rk,s,C1}$	Steel zinc plated	Property class	5.8	[kN]	29(27)	43	79	123	177	230	281
			8.8		47(43)	68	126	196	282	368	449
	Stainless steel R and high corrosion resistant steel HCR		50		29	43	79	123	177	230	281
			70		41	59	110	172	247	322	393
			80		47	68	126	196	282	368	449
BERNER anchor rods and standard threaded rods, performance category C2 [2]										
Characteristic reistance $N_{Rk,s,C2}$	Steel zinc plated	Property class	5.8	[kN]	-[4]	39	72	108	-[4]	-[4]	-[4]
			8.8		-[4]	61	116	173	-[4]	-[4]	-[4]
	Stainless steel R and high corrosion resistant steel HCR		50		-[4]	39	72	108	-[4]	-[4]	-[4]
			70		-[4]	53	101	152	-[4]	-[4]	-[4]
			80		-[4]	61	116	173	-[4]	-[4]	-[4]
Bearing capacity under shear load, steel failure without lever arm[1]										
BERNER anchor rods, performance category C1 [2]										
Characteristic resistance $V_{Rk,s,C1}$	Steel zinc plated	Property class	5.8	[kN]	17(16)	25	47	74	106	138	168
			8.8		23(21)	34	63	98	141	184	225
	Stainless steel R and high corrosion resistant steel HCR		50		15	21	39	61	89	115	141
			70		20	30	55	86	124	161	197
			80		23	34	63	98	141	184	225
Standard threaded rods, performance category C1 [2]										
Characteristic resistance $V_{Rk,s,C1}$	Steel zinc plated	Property class	5.8	[kN]	12(11)	17	33	52	74	97	118
			8.8		16(14)	24	44	69	99	129	158
	Stainless steel R and high corrosion resistant steel HCR		50		11	15	27	43	62	81	99
			70		14	21	39	60	87	113	138
			80		16	24	44	69	99	129	158
BERNER anchor rods and standard threaded rods, performance category C2										
Characteristic resistance $V_{Rk,s,C2}$	Steel zinc plated	Property class	5.8	[kN]	NPA [4]	14	27	43	-[4]	-[4]	-[4]
			8.8			22	44	69	-[4]	-[4]	-[4]
	Stainless steel R and high corrosion resistant steel HCR		50			14	27	43	-[4]	-[4]	-[4]
			70			20	39	60	-[4]	-[4]	-[4]
			80			22	44	69	-[4]	-[4]	-[4]
Factor for the annular gap		α_{gap}		[-]	0,5 (1,0)[3]						

[1] Partial factors for performance category C1 or C2 see table C12.1;
for BERNER anchor rods MCS Plus A / BCA M the factor for steel ductility is 1,0

[2] Values in brackets are valid for undersized threaded rods with smaller stress area A_s for hot dip galvanised standard threaded rods according to EN ISO 10684:2004+AC:2009.

[3] Values in brackets are valid for filled annular gaps between the anchor rod and the through-hole in the attachment. It is necessary to use the filling disc according to Annex A 1

[4] No performance assessed

BERNER multicompound system MCS Uni Plus

Performances
Characteristic values for steel failure under tension / shear load for BERNER anchor rods and standard threaded rods under seismic action (performance category C1 / C2)

Annex C 11

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C12.1: Partial factors for BERNER anchor rods, standard threaded rods under seismic action performance category C1 or C2

Anchor rod / standard threaded rod				M10	M12	M16	M20	M24	M27	M30
Tension load, steel failure[1)]										
Partial factor $\gamma_{Ms,N}$	Steel zinc plated	Property class	5.8	[-]	1,50					
			8.8		1,50					
	Stainless steel R and high corrosion resistant steel HCR		50		2,86					
			70		1,50[2)] / 1,87					
			80		1,60					
Shear load, steel failure[1)]										
Partial factor $\gamma_{Ms,V}$	Steel zinc plated	Property class	5.8	[-]	1,25					
			8.8		1,25					
	Stainless steel R and high corrosion resistant steel HCR		50		2,38					
			70		1,25[2)] / 1,56					
			80		1,33					

[1)] In absence of other national regulations
[2)] Only admissible for high corrosion resistant steel HCR, with $f_{yk} / f_{uk} \geq 0,8$ and $A_5 > 12$ % (e.g. BERNER anchor rods)

Electronic copy of the ETA by DIBt: ETA-11/0079

BERNER multicompound system MCS Uni Plus

Performances
Partial factors under seismic action (performance category C1 and C2) for BERNER anchor rods and standard threaded rods

Annex C 12

Deutsches Institut für Bautechnik DIBt

Table C13.1: Characteristic values for **combined pull-out** and concrete failure for **BERNER anchor rods** and **standard threaded rods** in hammer drilled holes under seismic action performance category **C1**

Anchor rod / standard threaded rod				**M10**	**M12**	**M16**	**M20**	**M24**	**M27**	**M30**
Characteristic bond resistance, combined pullout and concrete cone failure										
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)										
Temperature range	I: 50 °C / 80 °C	$\tau_{Rk,C1}$	[N/mm²]	4,5	5,5	5,5	5,5	4,5	4,0	4,0
	II: 72 °C / 120 °C			4,0	4,5	4,5	4,5	4,0	3,5	3,5
Hammer-drilling with standard drill bit or hollow drill bit (water filled hole [1])										
Temperature range	I: 50 °C / 80 °C	$\tau_{Rk,C1}$	[N/mm²]	-[2]	5,0	5,0	4,5	4,0	3,5	3,5
	II: 72 °C / 120 °C			-[2]	4,0	4,0	4,0	3,5	3,0	3,0
Installation factors										
Dry or wet concrete		γ_{inst}	[-]	1,0						
Water filled hole				-[2]	1,2 [1]					

[1] Only with coaxial cartridges: 380ml, 400 ml, 410 ml
[2] No performance assessed

Electronic copy of the ETA by DIBt: ETA-11/0079

Deutsches Institut für Bautechnik DIBt

Table C14.1: Characteristic values for **combined pull-out** and concrete failure for **BERNER anchor rods** and **standard threaded rods** in hammer drilled holes under seismic action performance category **C2**

Anchor rod / standard threaded rod				**M12**	**M16**	**M20**
Characteristic bond resistance, combined pullout and concrete cone failure						
Hammer-drilling with standard drill bit or hollow drill bit (dry or wet concrete)						
Temperature range	I: 50 °C / 80 °C	$\tau_{Rk,C2}$	[N/mm²]	1,5	1,3	2,1
	II: 72 °C / 120 °C			1,3	1,2	1,9
Hammer-drilling with standard drill bit or hollow drill bit (water filled hole [3])						
Temperature range	I: 50 °C / 80 °C	$\tau_{Rk,C2}$	[N/mm²]	1,3	1,1	1,8
	II: 72 °C / 120 °C			1,1	1,0	1,6
Installation factors						
Dry or wet concrete		γ_{inst}	[-]	1,0		
Water filled hole				-[4]	1,2 [3]	
Displacement-Factors for tension load[1]						
$\delta_{N,C2\ (DLS)}$-Factor		[mm/(N/mm²)]		0,20	0,13	0,21
$\delta_{N,C2\ (ULS)}$-Factor				0,38	0,18	0,24
Displacement-Factors for shear load[2]						
$\delta_{V,C2\ (DLS)}$-Factor		[mm/kN]		0,18	0,10	0,07
$\delta_{V,C2\ (ULS)}$-Factor				0,25	0,14	0,11

[1] Calculation of effective displacement:

$\delta_{N,C2\ (DLS)} = \delta_{N,C2\ (DLS)\text{-Factor}} \cdot \tau_{Ed}$

$\delta_{N,C2\ (ULS)} = \delta_{N,C2\ (ULS)\text{-Factor}} \cdot \tau_{Ed}$

(τ_{Ed}: Design value of the applied tensile stress)

[2] Calculation of effective displacement:

$\delta_{V,C2\ (DLS)} = \delta_{V,C2\ (DLS)\text{-Factor}} \cdot V_{Ed}$

$\delta_{V,C2\ (ULS)} = \delta_{V,C2\ (ULS)\text{-Factor}} \cdot V_{Ed}$

(V_{Ed}: Design value of the applied shear force)

[3] Only with coaxial cartridges: 380ml, 400 ml, 410 ml

[4] No performance assessed

Electronic copy of the ETA by DIBt: ETA-11/0079

BERNER multicompound system MCS Uni Plus

Performances
Characteristic values for combined pull-out and concrete failure under seismic action (performance category C2) for BERNER anchor rods and standard threaded rods

Annex C 14