

Approval body for construction products
and types of construction

Bautechnisches Prüfamt

An institution established by the Federal and
Laender Governments



European Technical Assessment

ETA-20/0697
of 30 November 2020

English translation prepared by DIBt - Original version in German language

General Part

Technical Assessment Body issuing the
European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

Connector HCC-U with Hilti injection mortar
HIT-HY 200-R V3 and HIT-RE 500 V3 and HIT-HY 170

Product family
to which the construction product belongs

Connector for Strengthening of existing concrete
structures by concrete overlay

Manufacturer

Hilti Aktiengesellschaft
Feldkircherstrasse 100
9494 SCHAAN
FÜRSTENTUM LIECHTENSTEIN

Manufacturing plant

Hilti Werke

This European Technical Assessment
contains

23 pages including 3 annexes which form an integral part
of this assessment

This European Technical Assessment is
issued in accordance with Regulation (EU)
No 305/2011, on the basis of

EAD 332347-00-0601, Edition 12/2019

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

Specific Part

1 Technical description of the product

The Connector Hilti HCC-U is a headed fastener (threaded rod with nut) made of steel anchored with the Injectionmortar Hilti HIT-HY 200-R V3 or Hilti HIT-RE 500 V3 or Hilti HIT-HY 170 into a predrilled cylindrical drill hole in existing concrete. The Hilti HCC-U is connecting two layers of concrete cast at different times (existing concrete and concrete overlay). The side with the anchor head of Hilti HCC-U is finally embedded in the concrete overlay.
 The product description is given in Annex A.

2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.
 The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment

3.1 Mechanical resistance and stability (BWR 1)

Essential characteristic	Performance
Existing concrete: - resistances - edge distance and spacing	See Annex C 1 to C 4 See Annex B 2
Concrete overlay: - resistances - edge distance and spacing	See Annex C 5 See Annex B 2
Shear interface parameter under static and quasi-static and fatigue cyclic loading - material and geometric parameters - factor for fatigue cyclic loading	See Annex C 5 No performance assessed

3.2 Safety in case of fire (BWR 2)

Essential characteristic	Performance
Reaction to fire	Class A1

4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with European Assessment Document EAD No. 332347-00-0601 the applicable European legal act is: [96/582/EC].
 The system to be applied is: 1

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited with Deutsches Institut für Bautechnik.


Issued in Berlin on 30 November 2020 by Deutsches Institut für Bautechnik

Dipl.-Ing. Beatrix Wittstock
Head of Section

beglaubigt:
Tempel

Installed condition

Figure A1:
Connector Hilti HCC-U

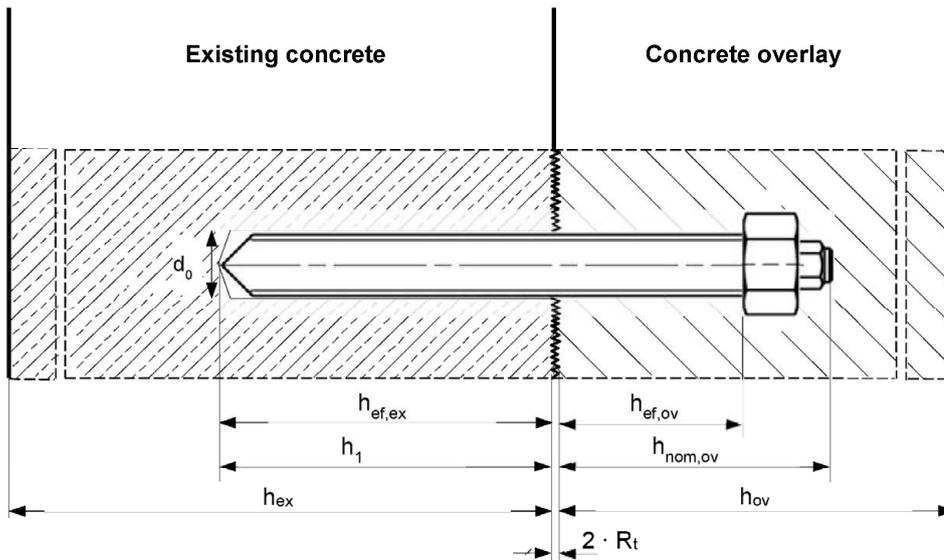

$h_{ef,ex}$ Effective embedment depth in existing concrete
 h_1 Drill hole depth
 h_{ex} Thickness of existing concrete
 R_t Roughness according to EOTA Technical Report TR 066:2018-11

$h_{ef,ov}$ Effective embedment depth in concrete overlay
 $h_{nom,ov}$ Overall embedment depth in the concrete overlay
 h_{ov} Thickness of concrete overlay


Connector Hilti HCC-U

Product description
Installed condition

Annex A1

Product description: Connector and injection mortar

steel element HAS-U-...: M8 to M30

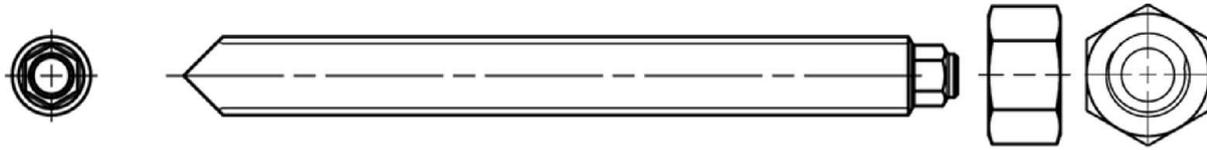

Injection mortar Hilti HIT-HY 200-R V3: hybrid system with aggregate

330 ml and 500 ml

Marking:
HILTI HIT
Product number
Production line
Expiry date mm/yyyy



Product name: "Hilti HIT-HY 200-R V3"

Injection mortar Hilti HIT-RE 500 V3: epoxy resin system with aggregate

330 ml, 500 ml and 1400 ml

Marking:
HILTI HIT
Product name
Production time and line
Expiry date mm/yyyy



Product name: "Hilti HIT-RE 500 V3"

Injection mortar Hilti HIT-HY 170: hybrid system with aggregate

330 ml and 500 ml

Marking:
HILTI HIT
Product number
Production line
Expiry date mm/yyyy



Product name: "Hilti HIT-HY 170"

Static mixer Hilti HIT-RE-M



Connector Hilti HCC-U

Product description

Steel element / Injection mortar / Static mixer


Annex A2

Table A1: Materials

Designation	Material
Metal parts made of zinc coated steel	
HAS-U-5.8 (HDG)	Strength class 5.8, $f_{uk} = 500 \text{ N/mm}^2$, $f_{yk} = 400 \text{ N/mm}^2$, Elongation at fracture ($l_0=5d$) > 8% ductile Electroplated zinc coated $\geq 5 \mu\text{m}$, (F) or (HDG) hot dip galvanized $\geq 45 \mu\text{m}$
HAS-U-8.8 (HDG)	Strength class 8.8, $f_{uk} = 800 \text{ N/mm}^2$, $f_{yk} = 640 \text{ N/mm}^2$, Elongation at fracture ($l_0=5d$) > 12% ductile Electroplated zinc coated $\geq 5 \mu\text{m}$, (F) or (HDG) hot dip galvanized $\geq 45 \mu\text{m}$
Nut	Strength class of nut adapted to strength class of threaded rod Electroplated zinc coated $\geq 5 \mu\text{m}$, (F) hot dip galvanized $\geq 45 \mu\text{m}$
Metal parts made of stainless steel corrosion resistance class III according EN 1993-1-4:2006	
HAS-U A4	For $\leq \text{M24}$: strength class 70, $f_{uk} = 700 \text{ N/mm}^2$, $f_{yk} = 450 \text{ N/mm}^2$; For $> \text{M24}$: strength class 50, $f_{uk} = 500 \text{ N/mm}^2$, $f_{yk} = 210 \text{ N/mm}^2$; Elongation at fracture ($l_0=5d$) > 8% ductile
Nut	For $\leq \text{M24}$: strength class 70, $f_{uk} = 700 \text{ N/mm}^2$, $f_{yk} = 450 \text{ N/mm}^2$; For $> \text{M24}$: strength class 50, $f_{uk} = 500 \text{ N/mm}^2$, $f_{yk} = 210 \text{ N/mm}^2$; Stainless steel 1.4401, 1.4404, 1.4578, 1.4571, 1.4439, 1.4362 EN 10088-1:2014
Metal parts made of high corrosion resistant steel corrosion resistance class V according EN 1993-1-4:2006+A1:2015-06	
HAS-U HCR	For $\leq \text{M20}$: $f_{uk} = 800 \text{ N/mm}^2$, $f_{yk} = 640 \text{ N/mm}^2$, For $> \text{M20}$: $f_{uk} = 700 \text{ N/mm}^2$, $f_{yk} = 400 \text{ N/mm}^2$, Elongation at fracture ($l_0=5d$) > 8% ductile
Nut	For $\leq \text{M20}$: $f_{uk} = 800 \text{ N/mm}^2$, $f_{yk} = 640 \text{ N/mm}^2$, For $> \text{M20}$: $f_{uk} = 700 \text{ N/mm}^2$, $f_{yk} = 400 \text{ N/mm}^2$, High corrosion resistant steel 1.4529, 1.4565 EN 10088-1:2014

Table A2: Specification

Connector Hilti HCC-U			M8	M10	M12	M16	M20	M24	M27	M30
Stressed section	A_s	[mm ²]	36,6	58,0	84,3	157	245	235	459	561
Overall length	L	[mm]	80 to 500							
Diameter of the head	d_h	[mm]	13	17	19	24	30	36	41	46
Height of the head	t_h	[mm]	6,5	8	10	13	16	19	22	24

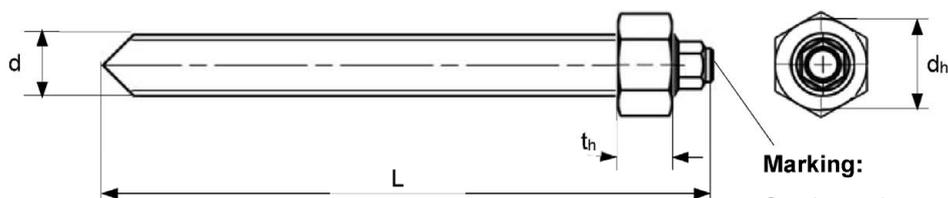

Marking:
Steel grade number and
length identification letter:
e.g. 8L

Connector Hilti HCC-U

Product description
Materials / Specification

Annex A3

Specifications of intended use

Anchorage subject to:

- static or quasi static actions
 - surface roughness “very smooth” to “very rough” of the shear interface according to EOTA Technical Report TR 066:2019-10

Base materials:

Connector for use to strengthen existing concrete by concrete overlay. Both concrete layers are made of compacted reinforced or unreinforced normal weight concrete without fibres with strength classes in the range C20/25 to C50/60 all in accordance with EN 206:2013+A1:2016; cracked and uncracked concrete; dry or wet concrete condition in existing concrete

Temperature in the base material (existing concrete):

For use with **HIT-HY 200-R V3**

- at installation: -10 °C to +40 °C for the standard variation of temperatures after installation (i.e. -10 °C to +24 °C in ≥ 12 hours)
- in-service:
 - Temperature range I: -40 °C to +40 °C
(max. long term temperature +24 °C and max. short term temperature +40 °C)
 - Temperature range II: -40 °C to +80 °C
(max. long term temperature +50 °C and max. short term temperature +80 °C)
 - Temperature range III: -40 °C to +120 °C
(max. long term temperature +72 °C and max. short term temperature +120 °C)

For use with **HIT-RE 500 V3**

- at installation: -5 °C to +40 °C for the standard variation of temperatures after installation (i.e. -10 °C to +24 °C in ≥ 12 hours)
- in-service:
 - Temperature range I: -40 °C to +40 °C
(max. long term temperature +24 °C and max. short term temperature +40 °C)
 - Temperature range II: -40 °C to +70 °C
(max. long term temperature +43 °C and max. short term temperature +70 °C)

For use with **HIT-HY 170**

- at installation:
 - 0 °C to +40 °C
- in-service:
 - Temperature range I: -40 °C to +40 °C
(max. long term temperature +24 °C and max. short term temperature +40 °C)
 - Temperature range II: -40 °C to +80 °C
(max. long term temperature +50 °C and max. short term temperature +80 °C)

Design:

- The design of an anchorage and the specification of the fastener is under the control of an engineer experienced in anchorages and concrete work
- Post-installed shear connections are designed in accordance with EOTA Technical Report TR 066:2018-11
- For the concrete overlay following requirements on the mixture apply:
 - Concrete compressive strength of the new concrete shall be higher than the concrete compressive strength of the existing concrete
 - Use of concrete with low shrinkage is recommended
 - Slump of fresh concrete $f \geq 380$ mm, a slump value $f \geq 450$ mm is recommended, if applicable

Connector Hilti HCC-U

**Intended Use
Specifications**

Annex B1

Installation:

- The fastener installation is executed by trained personnel, ensuring that the Installation instruction and the specifications by the engineer are observed
- Installation direction in existing concrete is downward and horizontal and upwards (e.g. overhead) installation (D3)
- The requirements for construction works given in EOTA Technical Report TR 066:2018-11 have to be considered.

Table B1: Installation parameters of connector Hilti HCC-U in existing concrete

Connector Hilti HCC-U			M8	M10	M12	M16	M20	M24	M27	M30
Effective embedment depth and drill hole depth	$h_{ef,ex} = h_1$	[mm]	60 to 160	60 to 200	70 to 240	80 to 320	90 to 400	96 to 480	108 to 540	120 to 600
Nominal diameter of drill bit	d_0	[mm]	10	12	14	18	22	28	30	35
Minimum thickness of existing concrete	$h_{min,ex}$	[mm]	max (100; $h_{ef} + 30$, $h_{ef} + 2 \cdot d_0$)							
Minimum spacing	$s_{min,ex}$	[mm]	40	50	60	75	90	115	120	140
Minimum edge distance	$c_{min,ex}$	[mm]	40	45	45	50	55	60	75	80


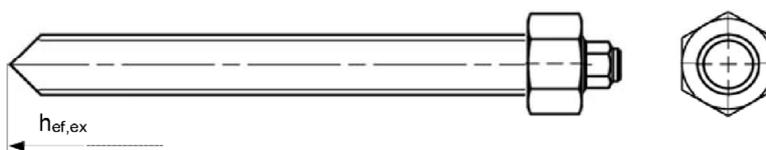


Table B2: Installation parameters of connector Hilti HCC-U in concrete overlay

Connector Hilti HCC-U			M8	M10	M12	M16	M20	M24	M27	M30
Effective embedment depth	$h_{ef,ov}$	[mm]	≥ 40							
Overall embedment depth	$h_{nom,ov}$	[mm]	$L - h_{ef,ex} - 2 \cdot R_t^{1)}$							
Minimum thickness of concrete overlay	$h_{min,ov}$	[mm]	$h_{nom,ov} + c_{nom}^{2)}$							
Minimum spacing	$s_{min,ov}$	[mm]	35	40	45	55	70	80	95	105
Minimum edge distance	$c_{min,ov}$	[mm]	$10 + c_{nom}^{2)}$	$10 + c_{nom}^{2)}$	$15 + c_{nom}^{2)}$	$15 + c_{nom}^{2)}$	$20 + c_{nom}^{2)}$	$20 + c_{nom}^{2)}$	$25 + c_{nom}^{2)}$	$30 + c_{nom}^{2)}$

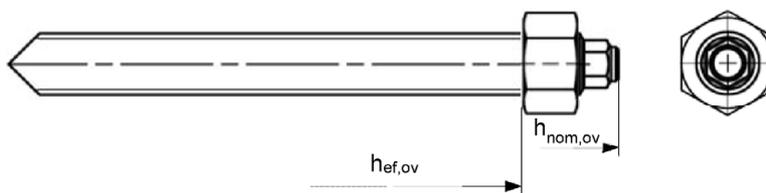

¹⁾ "R_t" Roughness according to EOTA Technical Report TR 066:2018-11

²⁾ "c_{nom}" Minimum concrete cover according to EN 1992-1-1:2004 + AC:2010.

Connector Hilti HCC-U

Intended Use
Specifications
Installation parameters

Annex B2

**Table B3: Maximum working time and minimum curing time
for Hilti HIT-HY 200-R V3**

Temperature in the base material T	Maximum working time t_{work}	Minimum curing time t_{cure}
-10 °C to -5 °C	3 hours	20 hours
> -5 °C to 0 °C	1,5 hours	8 hours
> 0 °C to 5 °C	45 min	4 hours
> 5 °C to 10 °C	30 min	2,5 hours
> 10 °C to 20 °C	15 min	1,5 hours
> 20 °C to 30 °C	9 min	1 hour
> 30 °C to 40 °C	6 min	1 hour

**Table B4: Maximum working time and minimum curing time
for Hilti HIT-RE 500 V3 ¹⁾**

Temperature in the base material T	Maximum working time t_{work}	Minimum curing time t_{cure}
-5 °C to -1 °C	2 hours	168 hours
0 °C to 4 °C	2 hours	48 hours
5 °C to 9 °C	2 hours	24 hours
10 °C to 14 °C	1,5 hours	16 hours
15 °C to 19 °C	1 hours	16 hours
20 °C to 24 °C	30 min	7 hours
25 °C to 29 °C	20 min	6 hours
30 °C to 34 °C	15 min	5 hours
35 °C to 39 °C	12 min	4,5 hours
40 °C	10 min	4 hours

¹⁾ The curing time data are valid for dry base material only. In wet base material the curing times must be doubled.

Table B5: Maximum working time and minimum curing time for Hilti HIT-HY 170 ¹⁾

Temperature in the base material T	Maximum working time t_{work}	Minimum curing time t_{cure}
0°C to 5°C	10 min	5 hours
> 5°C to 10°C	8 min	2,5 hours
> 10°C to 20°C	5 min	1,5 hours
> 20°C to 30°C	3 min	45 min
> 30°C to 40°C	2 min	30 min

¹⁾ The curing time data are valid for dry base material only. In wet base material the curing times must be doubled.

Connector Hilti HCC-U

Intended Use
Maximum working time and minimum curing time

Annex B3

Table B6: Overview of installation options

Concrete condition	Drilling	Cleaning	HCC-U with ...		
			HIT-HY 200-R V3	HIT-RE 500 V3	HIT-HY 170
Dry / wet	Hammer drilling with hollow drill bit TE-CD or TE-YD 	none	✓	✓	✓
	Hammer drilling 	Manual cleaning	✓	⊘	✓
		Compressed air cleaning	✓	✓	✓
	Diamond drilling with roughening tool TE-YRT  	Cleaning of diamond cored holes with roughening	✓	✓	⊘
Diamond drilling 	Cleaning of diamond drilled holes	⊘	✓	⊘	
Waterfilled drill-hole	Hammer drilling 	Cleaning for Hammer drilled water filled	⊘	✓	⊘

Table B7: Parameters of cleaning and setting tools

Elements	Drill and clean				Installation	
	Hammer drilling		Diamond coring		Brush	Piston plug
		Hollow drill bit		Roughening tool		
						
size	d ₀ [mm]	d ₀ [mm]	d ₀ [mm]	d ₀ [mm]	HIT-RB	HIT-SZ
M8	10	-	10	-	10	-
M10	12	12 ¹⁾	12	-	12	12
M12	14	14 ¹⁾	14	-	14	14
M16	18	18	18	18	18	18
M20	22	22	22	22	22	22
M24	28	28	28	28	28	28
M27	30	-	30	30	30	30
M30	35	35	35	35	35	35

¹⁾ To be used in combination with Hilti vacuum cleaner with suction volume ≥ 61 l/s (VC 20/40 –Y in corded mode only).

Connector Hilti HCC-U

Intended Use

Overview of installation options / Parameters of cleaning and setting tools

Annex B4

Cleaning alternatives

Manual Cleaning (MC)

Hilti hand pump for blowing out drill holes with diameters $d_0 \leq 20$ mm and drill hole depths $h_0 \leq 10 \cdot d$.



Compressed air cleaning (CAC):

Air nozzle with an orifice opening of minimum 3,5 mm in diameter.



Automatic Cleaning (AC):

Cleaning is performed during drilling with Hilti TE-CD and TE-YD drilling system including vacuum cleaner.



Table B8: Parameters for use of the Hilti Roughening tool TE-YRT

Associated components			
Diamond coring		Roughening tool TE-YRT	Wear gauge RTG...
			
d_0 [mm]		d_0 [mm]	size
nominal	measured		
18	17,9 to 18,2	18	18
22	21,9 to 22,2	22	22
28	27,9 to 28,2	28	28
30	29,9 to 30,2	30	30
35	34,9 to 35,2	35	35

Connector Hilti HCC-U

Intended Use

Cleaning alternatives / Parameters for use of roughening tool

Annex B5

Table B9: Installation parameters for use of the Hilti Roughening tool TE-YRT

	Roughening time t_{roughen}	Minimum blowing time t_{blowing}
h_{ef} [mm]	$t_{\text{roughen}} [\text{sec}] = h_{\text{ef}} [\text{mm}] / 10$	$t_{\text{blowing}} [\text{sec}] = t_{\text{roughen}} [\text{sec}] + 20$
0 to 100	10	30
101 to 200	20	40
201 to 300	30	50
301 to 400	40	60
401 to 500	50	70
501 to 600	60	80

Hilti roughening tool TE-YRT and wear gauge RTG



Connector Hilti HCC-U


Intended Use
Parameters for use of roughening tool

Annex B6

Installation instruction


Hole drilling

a) Hammer drilling

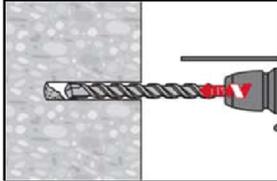


Drill hole to the required embedment depth with a hammer drill set in rotation-hammer mode using an appropriately sized carbide drill bit.

b) Hammer drilling with Hilti hollow drill bit

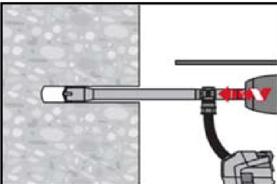


Drill hole to the required embedment depth with an appropriately sized Hilti TE-CD or TE-YD hollow drill bit attached to Hilti vacuum cleaner VC 20/40 (-Y) (suction volume ≥ 57 l/s) with automatic cleaning of the filter activated. This drilling system removes the dust and cleans the drill hole during drilling when used in accordance with the user's manual. When using TE-CD size 12 and 14 refer to Table B7. After drilling is completed, proceed to the "injection preparation" step in the installation instruction.

c) Diamond coring with roughening with Hilti roughening tool TE-YRT:

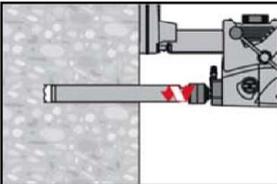


Diamond coring is permissible when suitable diamond core drilling machines and the corresponding core bits are used.
For the use in combination with Hilti roughening tool TE-YRT see parameters in Table B7, Table B8 and Table B9.

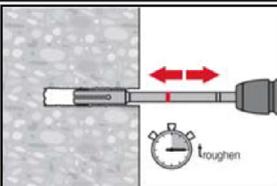

Before roughening water needs to be removed from the drill hole.
Check usability of the roughening tool with the wear gauge RTG.
Roughen the drill hole over the whole length to the required h_{ef} .

d) Diamond coring:

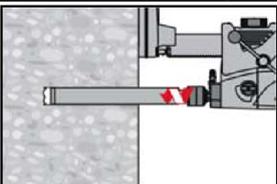


Diamond coring is permissible when suitable diamond core drilling machines and the corresponding core bits are used.

Drill hole cleaning

Just before setting an anchor, the drill hole must be free of dust and debris.
Inadequate hole cleaning = poor load values.

Manual Cleaning (MC)

Uncracked concrete only. For drill hole diameters $d_0 \leq 20$ mm and drill hole depths $h_0 \leq 10 \cdot d$.

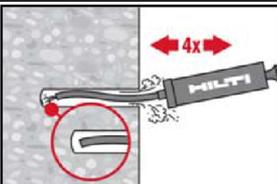


The Hilti hand pump may be used for blowing out drill holes up to diameters $d_0 \leq 20$ mm and drill hole depths $h_0 \leq 10 \cdot d$.
Blow out at least 4 times from the back of the drill hole until return air stream is free of noticeable dust.

Connector Hilti HCC-U

Intended Use
Installation instructions

Annex B7


	<p>Brush 4 times with the specified brush (see Table B7) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the drill hole (brush $\varnothing \geq$ drill hole \varnothing) - if not the brush is too small and must be replaced with the proper brush diameter.</p>
	<p>Blow out again with the Hilti hand pump at least 4 times until return air stream is free of noticeable dust.</p>
<p>Compressed air cleaning (CAC) for all drill hole diameters d_0 and all drill hole depths h_0</p>	
	<p>Blow 2 times from the back of the hole (if needed with nozzle extension) over the hole length with oil-free compressed air (min. 6 bar at 6 m³/h) until return air stream is free of noticeable dust. For drill hole diameters \geq 32 mm the compressor has to supply a minimum air flow of 140 m³/h.</p>
	<p>Brush 2 times with the specified brush (see Table B7) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the drill hole (brush $\varnothing \geq$ drill hole \varnothing) - if not the brush is too small and must be replaced with the proper brush diameter.</p>
	<p>Blow again with compressed air 2 times until return air stream is free of noticeable dust.</p>
<p>Cleaning of diamond cored holes with roughening with Hilti roughening tool TE-YRT.</p>	
	<p>Flush 2 times by inserting a water hose (water-line pressure) to the back of the hole until water runs clear.</p>
	<p>Brush 2 times with the specified brush (see Table B7) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the drill hole (brush $\varnothing \geq$ drill hole \varnothing) - if not the brush is too small and must be replaced with the proper brush diameter.</p>
<p>Connector Hilti HCC-U</p>	
<p>Intended Use Installation instructions</p>	<p>Annex B8</p>

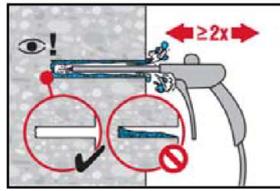


Blow 2 times from the back of the hole (if needed with nozzle extension) over the whole length with oil-free compressed air (min. 6 bar at 6 m³/h) until return air stream is free of noticeable dust and water. Remove all water from the drill hole until drill hole is completely dried before mortar injection. For drill hole diameters ≥ 32 mm the compressor has to supply a minimum air flow of 140 m³/h.

Cleaning of hammer drilled water-filled drill holes and diamond cored holes:


For all drill hole diameters d_0 and all drill hole depths h_0 .

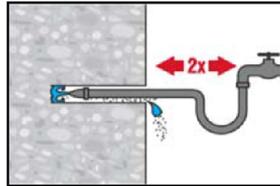


Flush 2 times by inserting a water hose (water-line pressure) to the back of the hole until water runs clear.

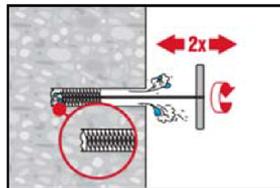


Brush 2 times with the specified brush (see Table B7) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the drill hole (brush $\varnothing \geq$ drill hole \varnothing) - if not the brush is too small and must be replaced with the proper brush diameter.

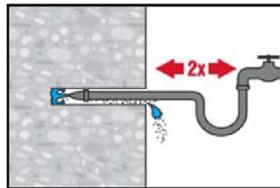


Flush 2 times by inserting a water hose (water-line pressure) to the back of the hole until water runs clear.

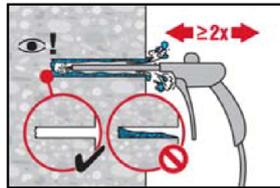

Blow 2 times from the back of the hole (if needed with nozzle extension) over the whole length with oil-free compressed air (min. 6 bar at 6 m³/h) until return air stream is free of noticeable dust and water. For drill hole diameters ≥ 32 mm the compressor has to supply a minimum air flow of 140 m³/h.

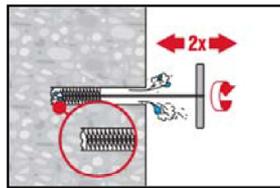

Brush 2 times with the specified brush size (brush $\varnothing \geq$ drill hole \varnothing , see Table B7) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the drill hole – if not the brush is too small and must be replaced with the proper brush diameter.

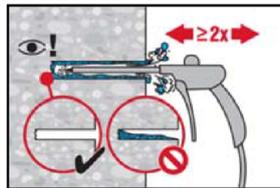


Blow again with compressed air 2 times until return air stream is free of noticeable dust and water.

Connector Hilti HCC-U

Intended Use
Installation instructions

Annex B9


Injection preparation

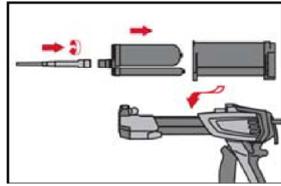


Tightly attach Hilti mixing nozzle HIT-RE-M to foil pack manifold. Do not modify the mixing nozzle.
Observe the instruction for use of the dispenser.
Check foil pack holder for proper function. Insert foil pack into foil pack holder and put holder into dispenser.

The foil pack opens automatically as dispensing is initiated. Depending on the size of the foil pack, an initial amount of adhesive has to be discarded. Discarded quantities are


- for use with HIT-HY 200-R V3:
 - 2 strokes for 330 ml foil pack,
 - 3 strokes for 500 ml foil pack,
 - 4 strokes for 500 ml foil pack $\leq 5^\circ\text{C}$.
 - for use with HIT-RE 500 V3:
 - 3 strokes for 330 ml foil pack,
 - 4 strokes for 500 ml foil pack,
 - 65 ml for 1400 ml foil pack
 - for use with HIT-HY 170:
 - 2 strokes for 330 ml foil pack,
 - 3 strokes for 500 ml foil pack,
- The minimum foil pack temperature is 0°C .
The minimum foil pack temperature is $+5^\circ\text{C}$.
The minimum foil pack temperature is 0°C .

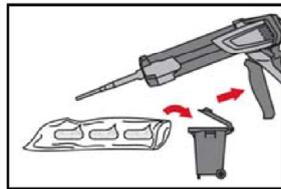


Inject adhesive from the back of the drill hole without forming air voids.

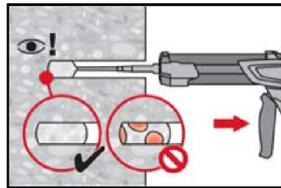

Inject the adhesive starting at the back of the hole, slowly withdrawing the mixer with each trigger pull.
Fill approximately 2/3 of the drill hole to ensure that the annular gap between the anchor and the concrete is completely filled with adhesive along the embedment length.
In water saturated concrete it is required to set the fastener immediately after cleaning the drill hole.

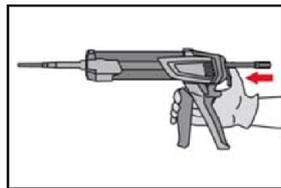


After injection is completed, depressurize the dispenser by pressing the release trigger. This will prevent further adhesive discharge from the mixer.

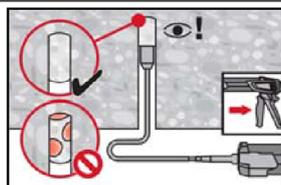

Overhead installation and/or installation with embedment depth $h_{ef} > 250\text{mm}$.
For overhead installation the injection is only possible with the aid of extensions and piston plugs. Assemble HIT-RE-M mixer, extension(s) and appropriately sized piston plug (see Table B7). Insert piston plug to back of the hole and inject adhesive. During injection the piston plug will be naturally extruded out of the drill hole by the adhesive pressure.

Setting the element

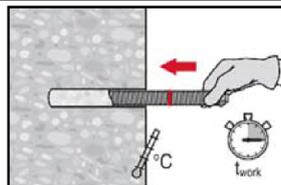


Before use, verify that the element is dry and free of oil and other contaminants.
Mark and set element to the required embedment depth before working time t_{work} has elapsed. The working time t_{work} is given in Table B4, Table B5 and Table B6.


Connector Hilti HCC-U

Intended Use
Installation instructions


Annex B10

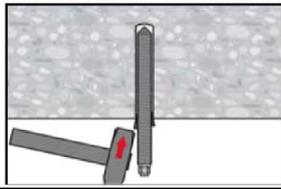

For overhead installation use piston plugs and fix embedded parts with e.g. wedges (Hilti HIT-OHW).

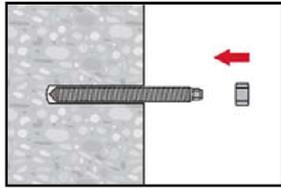


Assembly of the nut.

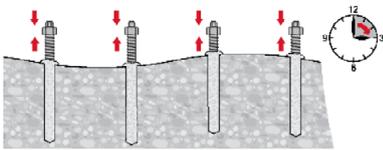

Levelling of the nut to ensure the required embedment depth.

Observe the curing time t_{cure} , which varies according to temperature of base material (see Table B4, Table B5 and Table B6). After t_{cure} has elapsed the concrete overlay can be concreted.

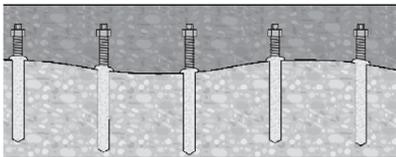

Observe the required condition of the surface before concreting and the use of the correct concrete composition.

For requirements on concrete composition see EOTA TR 066:2018-11.


Connector Hilti HCC-U

Intended Use
Installation instructions

Annex B11

Table C1: Essential characteristics of connector Hilti HCC-U in existing concrete under static or quasi-static tension load

Connector Hilti HCC-U			M8	M10	M12	M16	M20	M24	M27	M30		
Steel failure												
Characteristic resistance	$N_{Rk,s,ex}$	[kN]	$A_s f_{uk}$									
Partial factor HAS-U-5.8 (HDG)	$\gamma_{Ms,N,ex}$	[-]	1,5									
Partial factor HAS-U-8.8 (HDG)	$\gamma_{Ms,N,ex}$	[-]	1,5									
Partial factor HAS-U A4	$\gamma_{Ms,N,ex}$	[-]	1,86						2,86			
Partial factor HAS-U HCR	$\gamma_{Ms,N,ex}$	[-]	1,5					2,1				
Concrete cone failure												
Factor for cracked concrete	$k_{Cr,N,ex}$	[-]	7,7									
Factor for uncracked concrete	$k_{ucr,N,ex}$	[-]	11,0									
Edge distance	$c_{Cr,N,ex}$	[mm]	$1,5 \cdot h_{ef,ex}$									
Spacing	$s_{Cr,N,ex}$	[mm]	$3,0 \cdot h_{ef,ex}$									
Splitting failure												
Edge distance $c_{Cr,sp,ex}$ [mm] for	$h / h_{ef,ex} \geq 2,0$		$1,0 \cdot h_{ef,ex}$									
	$2,0 > h / h_{ef,ex} > 1,3$		$4,6 \cdot h_{ef,ex} - 1,8 \cdot h$									
	$h / h_{ef,ex} \leq 1,3$		$2,26 \cdot h_{ef,ex}$									
Spacing	$s_{Cr,sp,ex}$	[mm]	$2,0 \cdot c_{Cr,sp,ex}$									

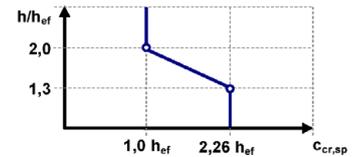

Connector Hilti HCC-U

Performances
Essential characteristics under tension load in existing concrete

Annex C1

Table C1: continued

Connector Hilti HCC-U				M8	M10	M12	M16	M20	M24	M27	M30
Installation factor for HCC-U with HIT-HY 200-R V3											
Hammer drilling	γ_{inst}	[-]		1,0							
Hammer drilling with hollow drill bit TE-CD or TE-YD	γ_{inst}	[-]	1)	1,0							
Diamond coring with roughening with Hilti roughening tool TE-YRT	γ_{inst}	[-]	1)	1,0							
Combined pullout and concrete cone failure for HCC-U with HIT-HY 200-R V3											
Characteristic bond resistance in cracked concrete C20/25 in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD											
Temperature range I:	40 °C / 24 °C	$\tau_{Rk,cr}$	[N/mm ²]	7,5			8,5			9,0	
Temperature range II:	80 °C / 50 °C	$\tau_{Rk,cr}$	[N/mm ²]	6,0			7,0			7,5	
Temperature range III:	120 °C / 72 °C	$\tau_{Rk,cr}$	[N/mm ²]	5,5			6,0			6,5	
Characteristic bond resistance in uncracked concrete C20/25 in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD											
Temperature range I:	40 °C / 24 °C	$\tau_{Rk,ucr}$	[N/mm ²]	18							
Temperature range II:	80 °C / 50 °C	$\tau_{Rk,ucr}$	[N/mm ²]	15							
Temperature range III:	120 °C / 72 °C	$\tau_{Rk,ucr}$	[N/mm ²]	13							
Influence factors ψ on bond resistance τ_{Rk}											
Cracked and uncracked concrete: Factor for concrete strength	$\psi_{c,ex}$	C30/37		1,04							
		C40/50		1,07							
		C50/60		1,10							
Cracked and uncracked concrete: Sustained load factor	ψ_{sus}^0	40 °C / 24 °C		0,74							
		80 °C / 50 °C		0,89							
		120 °C / 72 °C		0,72							

1) no performance assessed

Connector Hilti HCC-U

Performances
Essential characteristics under tension load in existing concrete

Annex C2

Table C1: continued

Connector Hilti HCC-U				M8	M10	M12	M16	M20	M24	M27	M30
Installation factor for HCC-U with HIT-RE 500 V3											
Hammer drilling	γ_{inst}	[-]		1,0							
Hammer drilling with hollow drill bit TE-CD or TE-YD	γ_{inst}	[-]	1)	1,0							
Diamond coring with roughening with Hilti roughening tool TE-YRT	γ_{inst}	[-]	1)	1,0							
Diamond coring	γ_{inst}	[-]		1,2						1,4	
Hammer drilling in water-filled drill holes	γ_{inst}	[-]		1,4							
Combined pullout and concrete cone failure HCC-U with HIT-RE 500 V3											
Characteristic bond resistance in cracked concrete C20/25 in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and diamond cored holes with roughening with Hilti roughening tool TE-YRT											
Temperature range I:	40 °C / 24 °C	$\tau_{RK,cr}$	[N/mm ²]	7,5	8,0	9,5	9,5	9,5	8,5	9,0	8,5
Temperature range II:	70 °C / 43 °C	$\tau_{RK,cr}$	[N/mm ²]	6,0	7,0	7,5	7,5	7,5	7,0	7,0	6,5
Characteristic bond resistance in uncracked concrete C20/25 in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and diamond cored holes with roughening with Hilti roughening tool TE-YRT											
Temperature range I:	40 °C / 24 °C	$\tau_{RK,ucr}$	[N/mm ²]	19	18	18	17	16	15	15	14
Temperature range II:	70 °C / 43 °C	$\tau_{RK,ucr}$	[N/mm ²]	14	14	14	13	12	12	11	11
Characteristic bond resistance in uncracked concrete C20/25 in diamond cored holes											
Temperature range I:	40 °C / 24 °C	$\tau_{RK,ucr}$	[N/mm ²]	13	13	13	13	12	12	12	12
Temperature range II:	70 °C / 43 °C	$\tau_{RK,ucr}$	[N/mm ²]	10	9,5	9,5	9,5	9,0	9,0	9,0	9,0
Characteristic bond resistance in uncracked concrete C20/25 in hammer drilled holes and installation in water-filled drill holes											
Temperature range I:	40 °C / 24 °C	$\tau_{RK,ucr}$	[N/mm ²]	16	16	15	15	14	13	12	12
Temperature range II:	70 °C / 43 °C	$\tau_{RK,ucr}$	[N/mm ²]	12	12	12	11	10	10	9,5	9,5
Influence factors ψ on bond resistance τ_{RK}											
Cracked and uncracked concrete: Factor for concrete strength	in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and diamond cored holes	$\psi_{c,ex}$	C30/37	1,04							
	C40/50		1,07								
	C50/60		1,10								
Factor for concrete strength	in diamond cored holes with roughening with Hilti roughening tool TE-YRT	$\psi_{c,ex}$	C30/37	1)				1,0			
	C40/50		1)				1,0				
	C50/60		1)				1,0				
Cracked and uncracked concrete:	ψ_{sus}^0	40 °C / 24 °C	0,88								
Sustained load factor		70 °C / 43 °C	0,70								

1) no performance assessed

Connector Hilti HCC-U

Performances

Essential characteristics under tension load in existing concrete

Annex C3

Table C1: continued

Connector Hilti HCC-U				M8	M10	M12	M16	M20	M24	M27	M30
Installation factor for HCC-U with HIT-HY 170											
Hammer drilling and Hammer drilling with hollow drill bit TE-CD or TE-YD				γ_{inst}	[-]		1,0			1)	
Combined pullout and concrete cone failure HCC-U with HIT-HY 170											
Characteristic bond resistance in cracked concrete C20/25 in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD											
Temperature range I:		40 °C / 24 °C	$\tau_{RK,cr}$	[N/mm ²]	1)	5,5			1)		
Temperature range II:		80 °C / 50 °C	$\tau_{RK,cr}$	[N/mm ²]	1)	4,0			1)		
Characteristic bond resistance in uncracked concrete C20/25 in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD											
Temperature range I:		40 °C / 24 °C	$\tau_{RK,ucr}$	[N/mm ²]	10			1)			
Temperature range II:		80 °C / 50 °C	$\tau_{RK,ucr}$	[N/mm ²]	7,5			1)			
Influence factors ψ on bond resistance τ_{RK}											
Cracked and uncracked concrete: Factor for concrete strength		$\psi_{c,ex}$	C30/37	1,04			1)				
			C40/50	1,07			1)				
			C50/60	1,09			1)				
Cracked and uncracked concrete: Sustained load factor		ψ_{sus}^0	40 °C / 24 °C	0,95			1)				
			80 °C / 50 °C	0,79			1)				

1) no performance assessed

Connector Hilti HCC-U

Performances
Essential characteristics under tension load in existing concrete

Annex C4

Table C2: Essential characteristics of connector Hilti HCC-U in concrete overlay under static or quasi-static tension load

Connector Hilti HCC-U				M8	M10	M12	M16	M20	M24	M27	M30
Steel failure											
Characteristic resistance	$N_{Rk,s,ov}$	[kN]	$A_s \cdot f_{uk}$								
Partial factor HAS-U-5.8 (HDG)	$\gamma_{Ms,N,ov}$	[-]	1,5								
Partial factor HAS-U-8.8 (HDG)	$\gamma_{Ms,N,ov}$	[-]	1,5								
Partial factor HAS-U A4	$\gamma_{Ms,N,ov}$	[-]	1,86						2,86		
Partial factor HAS-U HCR	$\gamma_{Ms,N,ov}$	[-]	1,5					2,1			
Pullout failure for anchor heads											
Projected area of the head	A_h	[mm ²]	82	148	170	251	393	565	748	955	
Height of the head	t_h	[mm]	6,5	8	10	13	16	19	22	24	
Concrete cone failure											
Effective embedment depth	$h_{ef,ov}$	[mm]	≥ 40								
Factor for cracked concrete	$k_{cr,N,ov}$	[-]	8,9								
Factor for uncracked concrete	$k_{ucr,N,ov}$	[-]	12,7								
Edge distance	$c_{cr,N,ov}$	[mm]	$1,5 \cdot h_{ef,ov}$								
Spacing	$s_{cr,N,ov}$	[mm]	$3,0 \cdot h_{ef,ov}$								
Splitting failure											
Edge distance	$c_{cr,sp,ov}$	[mm]	$3,0 \cdot h_{ef,ov}$								
Spacing	$s_{cr,sp,ov}$	[mm]	$6,0 \cdot h_{ef,ov}$								
Blow-out failure											
Projected area of the head	A_h	[mm ²]	82	148	170	251	393	565	748	955	
Factor for cracked concrete	k_5	[-]	8,7								
Factor for uncracked concrete	k_5	[-]	12,2								

1) "R_t" Roughness according to EOTA Technical Report TR 066:2018-11

Table C3: Essential characteristics for connector Hilti HCC-U for the shear interface under static, quasi-static loading

Connector Hilti HCC-U				M8	M10	M12	M16	M20	M24	M27	M30
Characteristic yield strength	HAS-U-5.8 (HDG)	f_{yk}	[N/mm ²]	400							
	HAS-U-8.8 (HDG)	f_{yk}	[N/mm ²]	640							
	HAS-U A4	f_{yk}	[N/mm ²]	450						210	
	HAS-U HCR	f_{yk}	[N/mm ²]	450					210		
Product specific factor for ductility	α_{k1}	[-]	1,0								
Stressed cross section	A_s	[mm ²]	36,6	58,0	84,3	157	245	235	459	561	
Product specific factor for geometry	α_{k2}	[-]	1,0								

Connector Hilti HCC-U

Performances

Essential characteristics under tension load in concrete overlay
Essential characteristics for the shear interface

Annex C5