

Approval body for construction products  
and types of construction

Bautechnisches Prüfamt

An institution established by the Federal and  
Laender Governments



## European Technical Assessment

**ETA-07/0256**  
**of 6 December 2021**

English translation prepared by DIBt - Original version in German language

### General Part

Technical Assessment Body issuing the  
European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

Halfen Injection System HB-VMZ

Product family  
to which the construction product belongs

Bonded fastener for use in concrete

Manufacturer

Leviat GmbH  
Liebigstraße 14  
40764 Langenfeld  
DEUTSCHLAND

Manufacturing plant

Leviat Herstellwerk HB1

This European Technical Assessment  
contains

32 pages including 3 annexes which form an integral part  
of this assessment

This European Technical Assessment is  
issued in accordance with Regulation (EU)  
No 305/2011, on the basis of

EAD 330499-01-0601, Edition 04/2020

This version replaces

ETA-07/0256 issued on 1 September 2016

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

## Specific Part

### 1 Technical description of the product

The Halfen Injection System HB-VMZ is a torque controlled bonded fastener consisting of a cartridge with injection mortar HB-VMZ or HB-VMZ Express and an anchor rod with expansion cones and external connection thread (type HB-VMZ-A) or with internal connection thread (type HB-VMZ-IG).

The load transfer is realised by mechanical interlock of several cones in the bonding mortar and then via a combination of bonding and friction forces in the anchorage ground (concrete).

The product description is given in Annex A.

### 2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the fastener is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

### 3 Performance of the product and references to the methods used for its assessment

#### 3.1 Mechanical resistance and stability (BWR 1)

| Essential characteristic   | Performance                     |
|--|---------------------------------|
| Characteristic resistance to tension load (static and quasi-static loading)              | See Annex C1 – C3, C10, B5 – B6 |
| Characteristic resistance to shear load (static and quasi-static loading)                | See Annex C4 – C5, C11          |
| Displacements under short-term and long-term loading                                     | See Annex C8 – C9, C11          |
| Characteristic resistance and displacements for seismic performance categories C1 and C2 | See Annex C6 – C9               |

#### 3.2 Hygiene, health and the environment (BWR 3)

| Essential characteristic                                 | Performance             |
|--|-------------------------|
| Content, emission and/or release of dangerous substances | No performance assessed |

English translation prepared by DIBt

**4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base**

In accordance with EAD 330499-01-0601 the applicable European legal act is: [96/582/EC]

The system to be applied is: 1

**5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document**

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Deutsches Institut für Bautechnik.

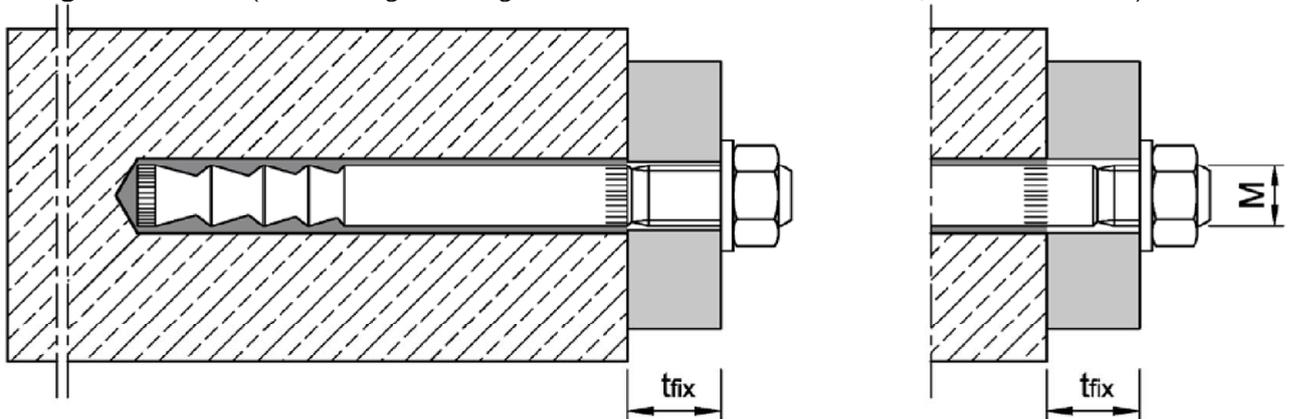
Issued in Berlin on 6 December 2021 by Deutsches Institut für Bautechnik

Dipl.-Ing. Beatrix Wittstock  
Head of Section


*beglaubigt:*  
Baderschneider

### Anchor rod HB-VMZ-A


**Pre-setting installation** (and through-setting installation HB-VMZ-A 75 M12, see Annex B11)



### Through-setting installation

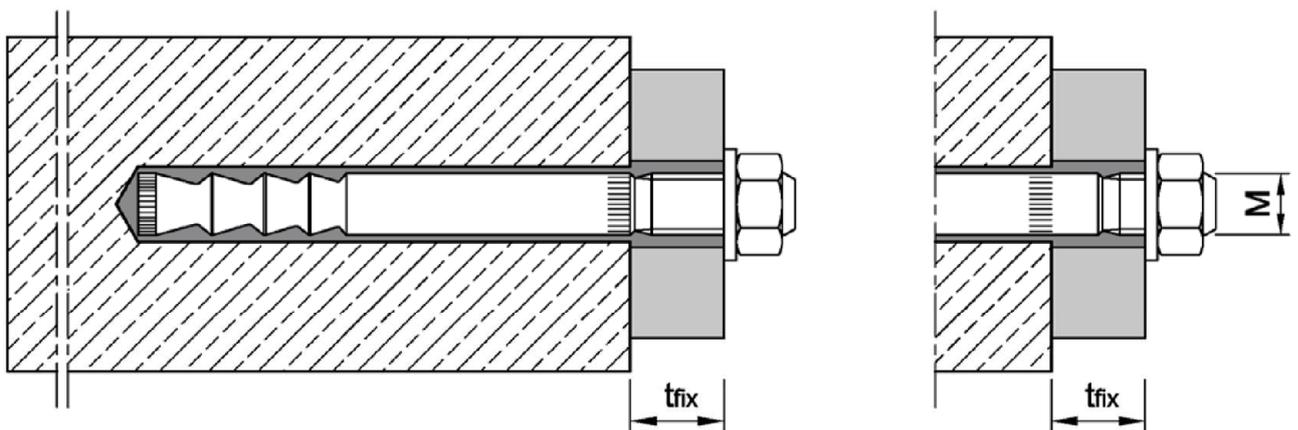

### Anchor rod HB-VMZ-IG with internal thread<sup>1)</sup>

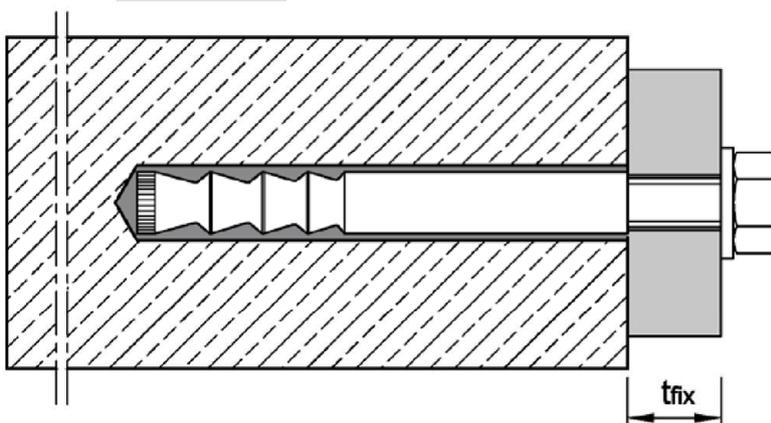

<sup>1)</sup> Illustration with hexagon head screw exemplified; other screws or threaded rods also permitted (see Annex A5, requirements of the fastening screw or threaded rod).

### Injection System HB-VMZ

**Product description**  
Installation situation

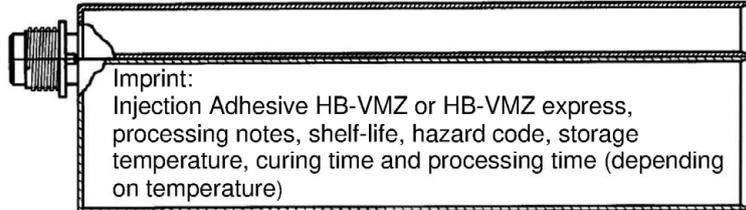

**Annex A1**

### Injection System HB-VMZ


Mortar cartridge



Imprint:  
Injection Adhesive HB-VMZ or HB-VMZ  
express, processing notes, shelf-life, hazard  
code, storage temperature, curing time and  
processing time (depending on temperature)




Imprint:  
Injection Adhesive HB-VMZ or HB-VMZ express,  
processing notes, shelf-life, hazard code, storage  
temperature, curing time and processing time (depending  
on temperature)



Sealing  
cap



Reducing  
adapter



Static mixer HB-VM-X



Blow-out pump HB-VM-AP



Air Blower HB-VM-ABP

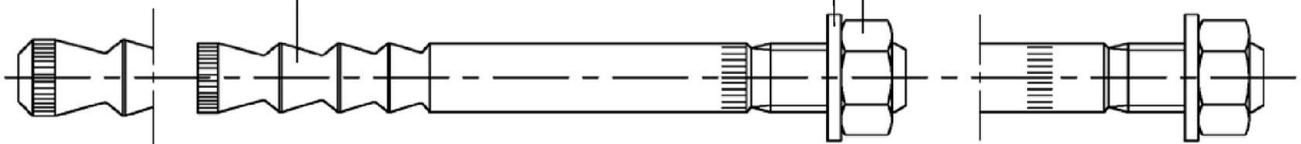
Cleaning Brush HB-RB




Anchor rod HB-VMZ-A

Washer  
(optional: washer with bore)

Hexagon nut



Anchor rod HB-VMZ-IG

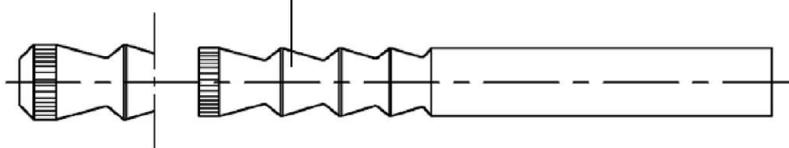


### Injection System HB-VMZ

**Product description**  
Cartridges, Cleaning tools, Anchor types

**Annex A2**

**Table A1: Materials HB-VMZ-A**
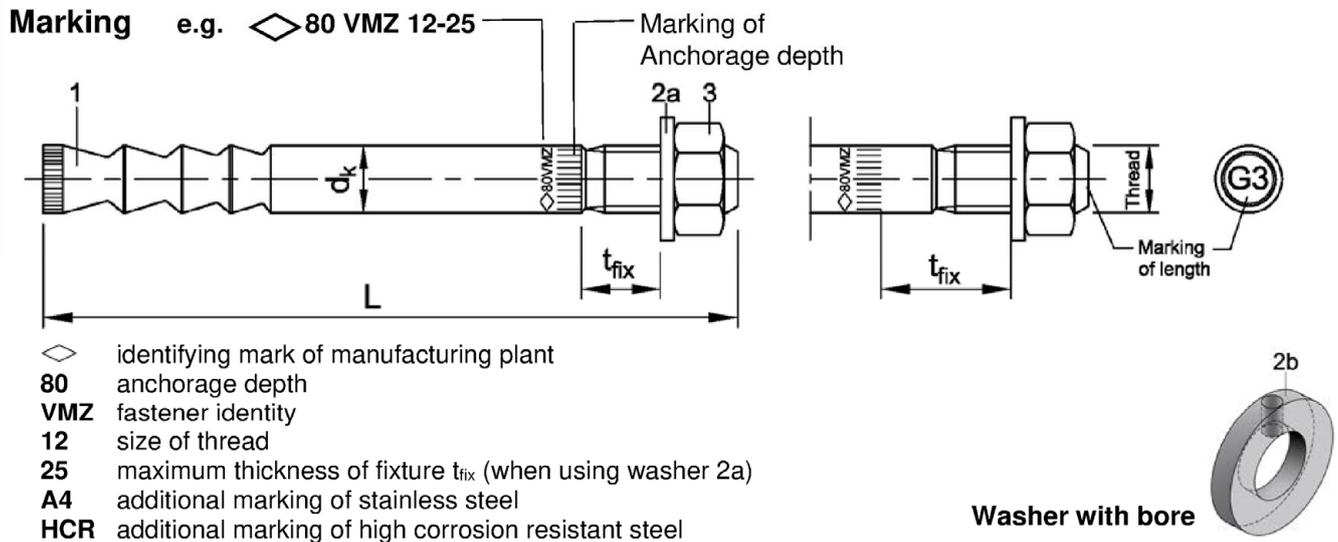
| Part | Designation      | Steel, zinc plated                                |   |                                   | Stainless steel A4 (CRC III)                                   | High corrosion resistant steel HCR (CRC V)   |
|------|------------------|---|---|-----------------------------------|--|--|
|      |                  | galvanised $\geq 5\mu\text{m}$                    | hot-dip galvanised $\geq 40\mu\text{m}$ (50 $\mu\text{m}$ in average) | sherardized $\geq 45\mu\text{m}$  |  |  |
| 1    | Anchor rod       | Steel acc. to EN ISO 683-1:2018                   |   |                                   | Stainless steel, 1.4401, 1.4404, 1.4571, EN 10088:2014, coated | High corrosion resistant steel 1.4529, 1.4565 EN 10088:2014, coated                                |
|      |                  | galvanised and coated                             | hot-dip galvanised and coated   | sherardized and coated            |  |  |
| 2a   | Washer           | Steel, zinc plated                                |   |                                   | Stainless steel, EN 10088:2014                                 | High corrosion resistant steel 1.4529, 1.4565 EN 10088:2014  |
| 2b   | Washer with bore |   |   |                                   |  |  |
| 3    | Hexagon nut      | Property class 8 acc. to EN ISO 898-2:2012        |   |                                   | EN ISO 3506-2:2020, A4-70, A4-80 1.4401, 1.4571 EN 10088:2014  | EN ISO 3506-2:2020, Property class 70, high corrosion resistant steel 1.4529, 1.4565 EN 10088:2014 |
|      |                  | galvanised  | hot-dip galvanised  | sherardized or hot-dip galvanised |  |  |
| 4    | Mortar cartridge | Vinylester resin, styrene free, mixing ratio 1:10 |   |                                   |  |  |



| Marking of length  |            | B     | C     | D     | E     | F     | G     | H     | I     | J     | K     | L     | M     | N     |
|--------------------|------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| Length of fastener | min $\geq$ | 50,8  | 63,5  | 76,2  | 88,9  | 101,6 | 114,3 | 127,0 | 139,7 | 152,4 | 165,1 | 177,8 | 190,5 | 203,2 |
|                    | max $<$    | 63,5  | 76,2  | 88,9  | 101,6 | 114,3 | 127,0 | 139,7 | 152,4 | 165,1 | 177,8 | 190,5 | 203,2 | 215,9 |
| Marking of length  |            | O     | P     | Q     | R     | S     | T     | U     | V     | W     | X     | Y     | Z     | >Z    |
| Length of fastener | min $\geq$ | 215,9 | 228,6 | 241,3 | 254,0 | 279,4 | 304,8 | 330,2 | 355,6 | 381,0 | 406,4 | 431,8 | 457,2 | 482,6 |
|                    | max $<$    | 228,6 | 241,3 | 254,0 | 279,4 | 304,8 | 330,2 | 355,6 | 381,0 | 406,4 | 431,8 | 457,2 | 482,6 |       |

**Injection System HB-VMZ**

**Product description**  
**HB-VMZ-A:** Materials, Marking, Marking of length

**Annex A3**

**Table A2: Dimensions of anchor rod, HB-VMZ-A M8 – M12**

| Fastener size      | HB-VMZ-A    | 40<br>M8   | 50<br>M8            | 60<br>M10           | 75<br>M10           | 75<br>M12           | 70<br>M12           | 80<br>M12           | 95<br>M12                | 100<br>M12               | 110<br>M12               | 125<br>M12               |                          |
|--------------------|-------------|--|---------------------|---------------------|---------------------|---------------------|---------------------|---------------------|--------------------------|--------------------------|--------------------------|--------------------------|--------------------------|
| Additional marking |             | 1  | 2                   | 1                   | 2                   | 1                   | 2                   | 3                   | 4                        | 5                        | 6                        | 7                        |                          |
| 1                  | Anchor rod  | Thread   | M8                  |                     | M10                 |                     | M12                 |                     |                          |                          |                          |                          |                          |
|                    |             | Number of cones  | 2                   | 3                   | 3                   | 3                   | 3                   | 3                   | 4                        | 4                        | 6                        | 6                        | 6                        |
|                    |             | $d_k =$  | 8,0                 | 8,0                 | 9,7                 | 9,7                 | 10,7                | 12,5                | 12,5                     | 12,5                     | 12,5                     | 12,5                     | 12,5                     |
|                    |             | Length L<br>(with washer 2a)   | 52+t <sub>fix</sub> | 63+t <sub>fix</sub> | 75+t <sub>fix</sub> | 90+t <sub>fix</sub> | 95+t <sub>fix</sub> | 90+t <sub>fix</sub> | 100<br>+t <sub>fix</sub> | 115<br>+t <sub>fix</sub> | 120<br>+t <sub>fix</sub> | 130<br>+t <sub>fix</sub> | 145<br>+t <sub>fix</sub> |
|                    |             | Reduction t <sub>fix</sub> <sup>1)</sup><br>(with washer with bore 2b) | 3,4                 | 3,4                 | 3                   | 3                   | 2,5                 | 2,5                 | 2,5                      | 2,5                      | 2,5                      | 2,5                      | 2,5                      |
| 3                  | Hexagon nut | SW   | 13                  | 13                  | 17                  | 17                  | 19                  | 19                  | 19                       | 19                       | 19                       | 19                       |                          |

<sup>1)</sup> When using washer with bore (2b) the thickness of fixture is reduced by the specified value.

Dimensions in mm

**Table A3: Dimensions of anchor rod, HB-VMZ-A M16 – M24**

| Fastener size      | HB-VMZ-A    | 90<br>M16  | 105<br>M16               | 125<br>M16               | 145<br>M16               | 160<br>M16               | 115<br>M20               | 170<br>M20<br>(LG)       | 190<br>M20<br>(LG)       | 170<br>M24<br>(LG)       | 200<br>M24<br>(LG)       | 225<br>M24<br>(LG)       |                          |
|--------------------|-------------|--|--------------------------|--------------------------|--------------------------|--------------------------|--------------------------|--------------------------|--------------------------|--------------------------|--------------------------|--------------------------|--------------------------|
| Additional marking |             | 1  | 2                        | 3                        | 4                        | 5                        | 1                        | 2                        | 3                        | 1                        | 2                        | 3                        |                          |
| 1                  | Anchor rod  | Thread   | M16                      |                          |                          |                          | M20                      |                          |                          | M24                      |                          |                          |                          |
|                    |             | Number of cones  | 3                        | 4                        | 6                        | 6                        | 6                        | 3                        | 6                        | 6                        | 6                        | 6                        | 6                        |
|                    |             | $d_k =$  | 16,5                     | 16,5                     | 16,5                     | 16,5                     | 16,5                     | 19,7                     | 22,0                     | 22,0                     | 24,0                     | 24,0                     | 24,0                     |
|                    |             | Length L<br>(with washer 2a)   | 114<br>+t <sub>fix</sub> | 129<br>+t <sub>fix</sub> | 150<br>+t <sub>fix</sub> | 170<br>+t <sub>fix</sub> | 185<br>+t <sub>fix</sub> | 143<br>+t <sub>fix</sub> | 203<br>+t <sub>fix</sub> | 223<br>+t <sub>fix</sub> | 210<br>+t <sub>fix</sub> | 240<br>+t <sub>fix</sub> | 265<br>+t <sub>fix</sub> |
|                    |             | Reduction t <sub>fix</sub> <sup>1)</sup><br>(with washer with bore 2b) | 2                        | 2                        | 2                        | 2                        | 2                        | 2                        | 2                        | 2                        | 2                        | 2                        | 2                        |
| 3                  | Hexagon nut | SW   | 24                       | 24                       | 24                       | 24                       | 24                       | 30                       | 30                       | 30                       | 36                       | 36                       | 36                       |

<sup>1)</sup> When using washer with bore (2b) the thickness of fixture is reduced by the specified value.

Dimensions in mm

**Injection System HB-VMZ**


**Product description**  
HB-VMZ-A: Fastener dimensions

**Annex A4**

**Table A4: Materials HB-VMZ-IG**

| Part | Designation      | Steel, zinc plated $\geq 5\mu\text{m}$                 | Stainless steel A4 (CRC III)  | High corrosion resistant steel HCR (CRC V)                                  |
|------|------------------|--|---|---|
| 1    | Anchor rod       | Steel acc. to EN ISO 683-4:2018, galvanized and coated | Stainless steel, 1.4401, 1.4404, 1.4571 acc. to EN 10088:2014, coated | High corrosion resistant steel 1.4529, 1.4565 acc. to EN 10088:2014, coated |
| 4    | Mortar cartridge | Vinylester resin, styrene free, mixing ratio 1:10      |   |   |

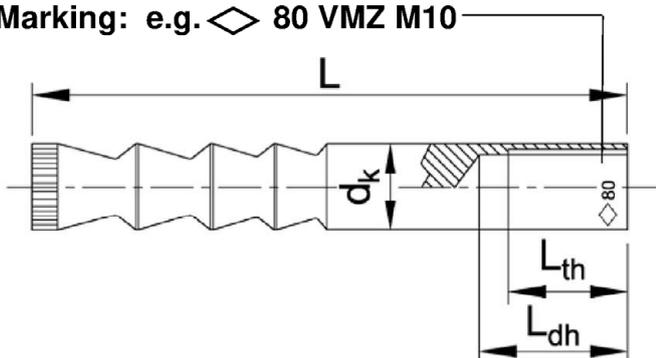Marking: e.g.  $\diamond$  80 VMZ M10



- $\diamond$  identifying mark of manufacturing plant
- 80 anchorage depth
- VMZ fastener identity
- M10 size of internal thread
- A4 additional marking of stainless steel
- HCR additional marking of high corrosion resistant steel

**Table A5: Dimensions of anchor rod HB-VMZ-IG**

| Fastener size     | HB-VMZ-IG     | 40 M6         | 50 M6         | 60 M8           | 75 M8           | 70 M10        | 80 M10        | 90 M12          | 105 M12                | 125 M12         | 115 M16    | 170 M16    | 170 M20 |
|-------------------|---------------|---------------|---------------|-----------------|-----------------|---------------|---------------|-----------------|------------------------|-----------------|------------|------------|---------|
| Internal thread   | -             | M6            |               | M8              |                 | M10           |               | M12             |                        |                 | M16        |            | M20     |
| Number of cones   | -             | 2             | 3             | 3               | 3               | 3             | 4             | 3               | 4                      | 6               | 3          | 6          | 6       |
| Outer diameter    | $d_k$ [mm]    | 8,0           | 8,0           | 9,7             | 10,7            | 12,5          | 12,5          | 16,5            | 16,5                   | 16,5            | 19,7       | 22,0       | 24,0    |
| Thread length     | $L_{th}$ [mm] | 12            | 15            | 16              | 19              | 20            | 23            | 24              | 27                     | 30              | 32         | 32         | 40      |
| Total length      | $L$ [mm]      | 41            | 52            | 63              | 78              | 74            | 84            | 94              | 109                    | 130             | 120        | 180        | 182     |
| Length identifier | [mm]          | $L_{dh}$ < 18 | $L_{dh}$ > 19 | $L_{dh}$ < 22,5 | $L_{dh}$ > 23,5 | $L_{dh}$ < 27 | $L_{dh}$ > 28 | $L_{dh}$ < 31,5 | 32,5 < $L_{dh}$ < 34,5 | $L_{dh}$ > 35,5 | $d_k$ < 21 | $d_k$ > 21 | -       |

**Requirements of the fastening screw or the threaded rod and nut**

- Minimum screw-in depth  $L_{sdmin}$  see Table B7
- The length of screw or the threaded rod must depending on the thickness of fixture  $t_{fix}$ , available thread length  $L_{th}$  (=maximum available thread length, see Table B7) and the minimum screw-in depth  $L_{sdmin}$  be established
- $A_5 > 8\%$  ductility
- Material
  - **Steel, zinc plated:** Minimum property class 8.8 according to EN ISO 898-1:2013 or EN ISO 898-2:2012
  - **Stainless steel A4:** Minimum property class 70 according to EN ISO 3506:2020
  - **High corrosion resistant steel (HCR):** Minimum property class 70 according to EN ISO 3506:2020

**Injection System HB-VMZ**

**Product description**  
HB-VMZ-IG: Materials, Marking, Fastener dimensions

**Annex A5**

| Specifications of intended use  |   |          |  |     |                 |     |     |     |  |
|---|---|----------|--|-----|-----------------|-----|-----|-----|--|
| Injection System HB-VMZ with anchor rod   |   | HB-VMZ-A | M8   | M10 | M12             | M16 | M20 | M24 |  |
| Static and quasi-static action  |   |          |  |     |                 | ✓   |     |     |  |
| Seismic action (Category C1 + C2)   |   |          | -  | ✓   | ✓               | ✓   | ✓   | ✓   |  |
| Cracked or uncracked concrete   |   |          |  |     |                 | ✓   |     |     |  |
| Strength classes acc. to EN 206:2013+A1:2016  |   |          | C20/25 to C50/60   |     |                 |     |     |     |  |
| Compacted reinforced or unreinforced normal weight concrete without fibres acc. to EN 206: 2013+A1:2016 |   |          |  |     |                 | ✓   |     |     |  |
| Temperature Range I   | -40 °C to +80 °C                            |          | max. short term temperature +80 °C<br>max. long term temperature +50 °C  |     |                 |     |     |     |  |
| Temperature Range II  | -40 °C to +120 °C                           |          | max. short term temperature +120 °C<br>max. long term temperature +72 °C |     |                 |     |     |     |  |
| Making of drill hole  | Hammer drill bit                            |          |  |     |                 | ✓   |     |     |  |
|   | Vacuum drill bit <sup>1)</sup>              |          | -  | ✓   | ✓               | ✓   | ✓   | ✓   |  |
|   | Diamond drill bit (seismic action excluded) |          | -  | ✓   | ✓               | ✓   | ✓   | ✓   |  |
| Installation allowable in   | dry concrete                                |          |  |     |                 | ✓   |     |     |  |
|   | wet concrete                                |          |  |     |                 | ✓   |     |     |  |
|   | water-filled hole                           |          | -  | -   | ✓ <sup>2)</sup> | ✓   | ✓   | ✓   |  |
| Overhead installation   |   |          |  |     |                 | ✓   |     |     |  |
| Pre-setting installation  |   |          |  |     |                 | ✓   |     |     |  |
| Trough-setting installation   |   |          | -  | ✓   | ✓               | ✓   | ✓   | ✓   |  |

<sup>1)</sup> e.g. MKT vacuum drill bit, Würth hammer drill bit with suction or Heller Duster Expert  
<sup>2)</sup> Exception: VMZ-A 75 M12 (Installation in water-filled drill hole is not allowed)

| Injection System HB-VMZ with anchor rod   |                                | HB-VMZ-IG | M6   | M8 | M10 | M12 | M16 | M20 |  |
|---|--------------------------------|-----------|--|----|-----|-----|-----|-----|--|
| Static and quasi-static action  |                                |           |  |    |     | ✓   |     |     |  |
| Seismic action (Category C1 + C2)   |                                |           |  |    |     | -   |     |     |  |
| Cracked and uncracked concrete  |                                |           |  |    |     | ✓   |     |     |  |
| Strength classes acc. to EN 206:2013+A1:2016  |                                |           | C20/25 to C50/60   |    |     |     |     |     |  |
| Compacted reinforced or unreinforced normal weight concrete without fibres acc. to EN 206: 2013+A1:2016 |                                |           |  |    |     | ✓   |     |     |  |
| Temperature Range I   | -40 °C to +80 °C               |           | max. short term temperature +80 °C<br>max. long term temperature +50 °C  |    |     |     |     |     |  |
| Temperature Range II  | -40 °C to +120 °C              |           | max. short term temperature +120 °C<br>max. long term temperature +72 °C |    |     |     |     |     |  |
| Making of drill hole  | Hammer drill bit               |           |  |    |     | ✓   |     |     |  |
|   | Vacuum drill bit <sup>1)</sup> |           | -  | ✓  | ✓   | ✓   | ✓   | ✓   |  |
|   | Diamond drill bit              |           | -  | ✓  | ✓   | ✓   | ✓   | ✓   |  |
| Installation allowable in   | dry concrete                   |           |  |    |     | ✓   |     |     |  |
|   | wet concrete                   |           |  |    |     | ✓   |     |     |  |
|   | water-filled hole              |           | -  | -  | ✓   | ✓   | ✓   | ✓   |  |
| Overhead installation   |                                |           |  |    |     | ✓   |     |     |  |
| Pre-setting installation  |                                |           |  |    |     | ✓   |     |     |  |

<sup>1)</sup> e.g. MKT vacuum drill bit, Würth hammer drill bit with suction or Heller Duster Expert

|   |  |                 |
|---|--|-----------------|
| <b>Injection System HB-VMZ</b>                                    |  | <b>Annex B1</b> |
| <b>Intended use</b><br>Specifications and installation conditions |  |                 |

## Specifications of intended use

### Use conditions (Environmental conditions):

- Structures subject to dry internal conditions: all versions HB-VMZ-A and HB-VMZ-IG
- For all other conditions:  
Intended use of materials according to Annex A3, Table A1 and Annex A5, Table A4 corresponding to the corrosion resistance class CRC to EN 1993-1-4:2015

### Design:

- Fasteners are designed under the responsibility of an engineer experienced in anchorages and concrete work.
- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the fastener is indicated on the design drawings (e.g. position of the fastener relative to reinforcement or to supports, etc.).
- Fasteners are designed in accordance with EN 1992-4:2018 and Technical Report TR 055, Edition February 2018.

### Installation:

- Drill hole must be cleaned directly prior to installation of the fastener or the drill hole has to be protected against re-contamination in an appropriate way until dispensing the mortar in the drill hole.
- Water filled drill holes must not be polluted – otherwise the cleaning of the drill hole must be repeated.
- The fastener component installation temperature shall be at least +5 °C; during curing of the injection mortar the temperature of the concrete must not fall below -15 °C.
- It must be ensured that icing does not occur in the drill hole.
- Optionally, the annular gap between anchor rod and fixture may be filled with injection adhesive HB-VMZ using the washer with bore (Part 2b, Annex A3) instead of the washer (Part 2a, Annex A3).

**Injection System HB-VMZ**

**Intended use  
Specifications**

**Annex B2**

**Table B1: Working and curing time HB-VMZ**

| Temperature in the drill hole | Maximum working time | Minimum curing time dry concrete <sup>1)</sup> |
|-------------------------------|----------------------|--|
| - 15 °C to - 10 °C            | 45 min               | 7 d  |
| - 9 °C to - 5 °C              | 45 min               | 10:30 h  |
| - 4 °C to - 1 °C              | 45 min               | 6:00 h   |
| 0 °C to + 4 °C                | 20 min               | 3:00 h   |
| +5 °C to + 9 °C               | 12 min               | 2:00 h   |
| +10 °C to +19 °C              | 6 min                | 1:20 h   |
| +20 °C to +29 °C              | 4 min                | 45 min   |
| +30 °C to +34 °C              | 2 min                | 25 min   |
| +35 °C to +39 °C              | 1,4 min              | 20 min   |
| + 40 °C                       | 1,4 min              | 15 min   |
| <b>Cartridge temperature</b>  | <b>≥ 5°C</b>         |  |

<sup>1)</sup> Curing time in wet concrete shall be doubled.

**Table B2: Working and curing time HB-VMZ express**

| Temperature in the drill hole | Maximum working time | Minimum curing time dry concrete <sup>1)</sup> |
|-------------------------------|----------------------|--|
| - 5 °C to - 1 °C              | 20 min               | 4:00 h   |
| 0 °C to + 4 °C                | 10 min               | 2:00 h   |
| + 5 °C to + 9 °C              | 6 min                | 1:00 h   |
| +10 °C to +19 °C              | 3 min                | 40 min   |
| +20 °C to +29 °C              | 1 min                | 20 min   |
| + 30 °C                       | 1 min                | 10 min   |
| <b>Cartridge temperature</b>  | <b>≥ 5°C</b>         |  |

<sup>1)</sup> Curing time in wet concrete shall be doubled.

**Injection System HB-VMZ**

**Intended use**  
Working and curing time

**Annex B3**

**Table B3: Installation parameters, HB-VMZ-A M8 – M12**

| Fastener size                             | HB-VMZ-A             | 40 M8 | 50 M8 | 60 M10 | 75 M10 | 75 M12                   | 70 M12 | 80 M12 | 95 M12 | 100 M12 | 110 M12 | 125 M12 |
|---|----------------------|-------|-------|--------|--------|--------------------------|--------|--------|--------|---------|---------|---------|
| Effective anchorage depth                 | $h_{ef} \geq$ [mm]   | 40    | 50    | 60     | 75     | 75                       | 70     | 80     | 95     | 100     | 110     | 125     |
| Nominal diameter of drill hole            | $d_0 =$ [mm]         | 10    | 10    | 12     | 12     | 12                       | 14     | 14     | 14     | 14      | 14      | 14      |
| Depth of drill hole                       | $h_0 \geq$ [mm]      | 42    | 55    | 65     | 80     | 80                       | 75     | 85     | 100    | 105     | 115     | 130     |
| Diameter of cleaning brush                | $D \geq$ [mm]        | 10,8  | 10,8  | 13,0   | 13,0   | 13,0                     | 15,0   | 15,0   | 15,0   | 15,0    | 15,0    | 15,0    |
| Installation torque                       | $T_{inst} \leq$ [Nm] | 10    | 10    | 15     | 15     | 25                       | 25     | 25     | 25     | 30      | 30      | 30      |
| Diameter of clearance hole in the fixture |                      |       |       |        |        |                          |        |        |        |         |         |         |
| Pre-setting installation                  | $d_f \leq$ [mm]      | 9     | 9     | 12     | 12     | 14                       | 14     | 14     | 14     | 14      | 14      | 14      |
| Through-setting installation              | $d_f \leq$ [mm]      | -     | -     | 14     | 14     | 14 <sup>1)</sup> /<br>16 | 16     | 16     | 16     | 16      | 16      | 16      |

<sup>1)</sup> see Annex B11

**Table B4: Installation parameters, HB-VMZ-A M16 – M24**

| Fastener size                             | HB-VMZ-A             | 90 M16 | 105 M16 | 125 M16 | 145 M16 | 160 M16 | 115 M20 | 170 M20 (LG) | 190 M20 (LG) | 170 M24 (LG) | 200 M24 (LG) | 225 M24 (LG) |
|---|----------------------|--------|---------|---------|---------|---------|---------|--------------|--------------|--------------|--------------|--------------|
| Effective anchorage depth                 | $h_{ef} \geq$ [mm]   | 90     | 105     | 125     | 145     | 160     | 115     | 170          | 190          | 170          | 200          | 225          |
| Nominal diameter of drill hole            | $d_0 =$ [mm]         | 18     | 18      | 18      | 18      | 18      | 22      | 24           | 24           | 26           | 26           | 26           |
| Depth of drill hole                       | $h_0 \geq$ [mm]      | 98     | 113     | 133     | 153     | 168     | 120     | 180          | 200          | 185          | 215          | 240          |
| Diameter of cleaning brush                | $D \geq$ [mm]        | 19,0   | 19,0    | 19,0    | 19,0    | 19,0    | 23,0    | 25,0         | 25,0         | 27,0         | 27,0         | 27,0         |
| Installation torque                       | $T_{inst} \leq$ [Nm] | 50     | 50      | 50      | 50      | 50      | 80      | 80           | 80           | 100          | 120          | 120          |
| Diameter of clearance hole in the fixture |                      |        |         |         |         |         |         |              |              |              |              |              |
| Pre-setting installation                  | $d_f \leq$ [mm]      | 18     | 18      | 18      | 18      | 18      | 22      | 24 (22)      | 24 (22)      | 26           | 26           | 26           |
| Through-setting installation              | $d_f \leq$ [mm]      | 20     | 20      | 20      | 20      | 20      | 24      | 26           | 26           | 28           | 28           | 28           |

**Pre-setting installation**

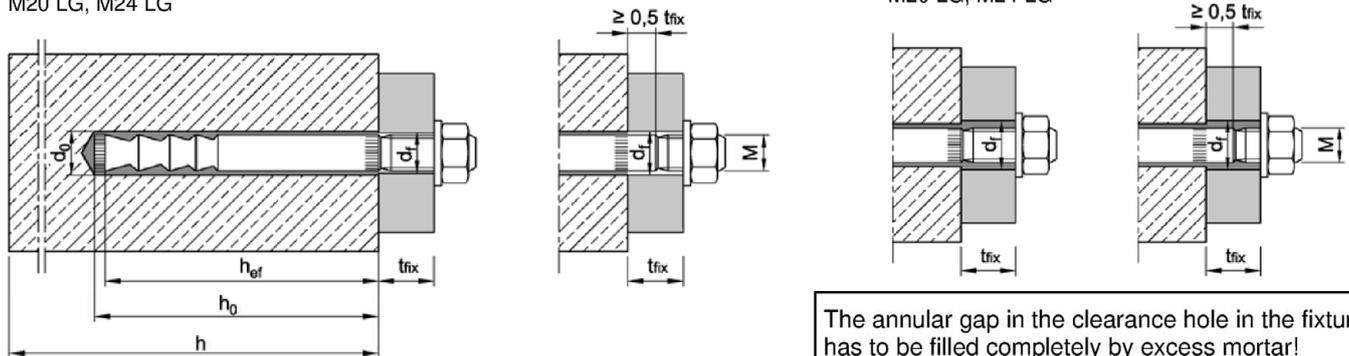
**Through-setting installation**

size  
M8 to M16,  
M20 LG, M24 LG

size  
M20 + M24

size  
M10 to M16,  
M20 LG, M24 LG

size  
M20 + M24



The annular gap in the clearance hole in the fixture has to be filled completely by excess mortar!

**Injection System HB-VMZ**

**Intended use**  
Installation parameters **HB-VMZ-A**

**Annex B4**

**Table B5: Minimum spacing and edge distance, HB-VMZ-A M8 – M12**

| Fastener size                 |           | HB-VMZ-A | 40<br>M8 | 50<br>M8 | 60<br>M10 | 75<br>M10                | 75<br>M12 | 70<br>M12 | 80<br>M12 | 95<br>M12                | 100<br>M12       | 110<br>M12       | 125<br>M12       |
|-------------------------------|-----------|----------|----------|----------|-----------|--------------------------|-----------|-----------|-----------|--------------------------|------------------|------------------|------------------|
| Minimum thickness of concrete | $h_{min}$ | [mm]     | 80       | 80       | 100       | 110<br>100 <sup>1)</sup> | 110       | 110       | 110       | 130<br>125 <sup>1)</sup> | 130              | 140              | 160              |
| <b>Cracked concrete</b>       |           |          |          |          |           |                          |           |           |           |                          |                  |                  |                  |
| Minimum spacing               | $s_{min}$ | [mm]     | 40       | 40       | 40        | 40                       | 50        | 55        | 40        | 40                       | 50               | 50               | 50               |
| Minimum edge distance         | $c_{min}$ | [mm]     | 40       | 40       | 40        | 40                       | 50        | 55        | 50        | 50                       | 50               | 50               | 50               |
| <b>Uncracked concrete</b>     |           |          |          |          |           |                          |           |           |           |                          |                  |                  |                  |
| Minimum spacing               | $s_{min}$ | [mm]     | 40       | 40       | 50        | 50                       | 50        | 55        | 55        | 55                       | 80 <sup>2)</sup> | 80 <sup>2)</sup> | 80 <sup>2)</sup> |
| Minimum edge distance         | $c_{min}$ | [mm]     | 40       | 40       | 50        | 50                       | 50        | 55        | 55        | 55                       | 55 <sup>2)</sup> | 55 <sup>2)</sup> | 55 <sup>2)</sup> |

**Table B6: Minimum spacing and edge distance, HB-VMZ-A M16 – M24**

| Fastener size                 |           | HB-VMZ-A | 90<br>M16 | 105<br>M16 | 125<br>M16               | 145<br>M16               | 160<br>M16               | 115<br>M20 | 170<br>M20<br>(LG)       | 190<br>M20<br>(LG)       | 170<br>M24<br>(LG)       | 200<br>M24<br>(LG)       | 225<br>M24<br>(LG)       |
|-------------------------------|-----------|----------|-----------|------------|--------------------------|--------------------------|--------------------------|------------|--------------------------|--------------------------|--------------------------|--------------------------|--------------------------|
| Minimum thickness of concrete | $h_{min}$ | [mm]     | 130       | 150        | 170<br>160 <sup>1)</sup> | 190<br>180 <sup>1)</sup> | 205<br>200 <sup>1)</sup> | 160        | 230<br>220 <sup>1)</sup> | 250<br>240 <sup>1)</sup> | 230<br>220 <sup>1)</sup> | 270<br>260 <sup>1)</sup> | 300<br>290 <sup>1)</sup> |
| <b>Cracked concrete</b>       |           |          |           |            |                          |                          |                          |            |                          |                          |                          |                          |                          |
| Minimum spacing               | $s_{min}$ | [mm]     | 50        | 50         | 60                       | 60                       | 60                       | 80         | 80                       | 80                       | 80                       | 80                       | 80                       |
| Minimum edge distance         | $c_{min}$ | [mm]     | 50        | 50         | 60                       | 60                       | 60                       | 80         | 80                       | 80                       | 80                       | 80                       | 80                       |
| <b>Uncracked concrete</b>     |           |          |           |            |                          |                          |                          |            |                          |                          |                          |                          |                          |
| Minimum spacing               | $s_{min}$ | [mm]     | 50        | 60         | 60                       | 60                       | 60                       | 80         | 80                       | 80                       | 80                       | 105                      | 105                      |
| Minimum edge distance         | $c_{min}$ | [mm]     | 50        | 60         | 60                       | 60                       | 60                       | 80         | 80                       | 80                       | 80                       | 105                      | 105                      |

<sup>1)</sup> The reverse of the concrete member must not be damaged after drilling and must be filled with high-strength mortar if drilled through.

<sup>2)</sup> For an edge distance  $c \geq 80$  mm a minimum spacing  $s_{min} = 55$  mm is applicable.

**Injection System HB-VMZ**


**Intended use**  
Minimum spacing and edge distance, **HB-VMZ-A**

**Annex B5**

**Table B7: Installation parameters HB-VMZ-IG**

| Fastener size                             | HB-VMZ-IG       |      | 40   | 50   | 60   | 75   | 70   | 80   | 90   | 105  | 125                      | 115  | 170                      | 170                      |
|---|-----------------|------|------|------|------|------|------|------|------|------|--------------------------|------|--------------------------|--------------------------|
|   |                 |      | M6   | M6   | M8   | M8   | M10  | M10  | M12  | M12  | M12                      | M16  | M16                      | M20                      |
| Effective anchorage depth                 | $h_{ef}$        | [mm] | 40   | 50   | 60   | 75   | 70   | 80   | 90   | 105  | 125                      | 115  | 170                      | 170                      |
| Nominal diameter of drill hole            | $d_0$           | [mm] | 10   | 10   | 12   | 12   | 14   | 14   | 18   | 18   | 18                       | 22   | 24                       | 26                       |
| Depth of drill hole                       | $h_0 \geq$      | [mm] | 42   | 55   | 65   | 80   | 80   | 85   | 98   | 113  | 133                      | 120  | 180                      | 185                      |
| Diameter of cleaning brush                | $D \geq$        | [mm] | 10,8 | 10,8 | 13,0 | 13,0 | 15,0 | 15,0 | 19,0 | 19,0 | 19,0                     | 23,0 | 25,0                     | 27,0                     |
| Installation torque                       | $T_{inst} \leq$ | [Nm] | 8    | 8    | 10   | 10   | 15   | 15   | 25   | 25   | 25                       | 50   | 50                       | 80                       |
| Diameter of clearance hole in the fixture | $d_f \leq$      | [mm] | 7    | 7    | 9    | 9    | 12   | 12   | 14   | 14   | 14                       | 18   | 18                       | 22                       |
| Available thread length                   | $L_{th}$        | [mm] | 12   | 15   | 16   | 19   | 20   | 23   | 24   | 27   | 30                       | 32   | 32                       | 40                       |
| Minimum screw-in depth                    | $L_{sdmin}$     | [mm] | 7    | 7    | 9    | 9    | 12   | 12   | 14   | 14   | 14                       | 18   | 18                       | 22                       |
| Minimum thickness of concrete             | $h_{min}$       | [mm] | 80   | 80   | 100  | 110  | 110  | 110  | 130  | 150  | 170<br>160 <sup>1)</sup> | 160  | 230<br>220 <sup>1)</sup> | 230<br>220 <sup>1)</sup> |
| <b>Cracked concrete</b>                   |                 |      |      |      |      |      |      |      |      |      |                          |      |                          |                          |
| Minimum spacing                           | $s_{min}$       | [mm] | 40   | 40   | 40   | 40   | 55   | 40   | 50   | 50   | 60                       | 80   | 80                       | 80                       |
| Minimum edge distance                     | $c_{min}$       | [mm] | 40   | 40   | 40   | 40   | 55   | 50   | 50   | 50   | 60                       | 80   | 80                       | 80                       |
| <b>Uncracked concrete</b>                 |                 |      |      |      |      |      |      |      |      |      |                          |      |                          |                          |
| Minimum spacing                           | $s_{min}$       | [mm] | 40   | 40   | 50   | 50   | 55   | 55   | 50   | 60   | 60                       | 80   | 80                       | 80                       |
| Minimum edge distance                     | $c_{min}$       | [mm] | 40   | 40   | 50   | 50   | 55   | 55   | 50   | 60   | 60                       | 80   | 80                       | 80                       |
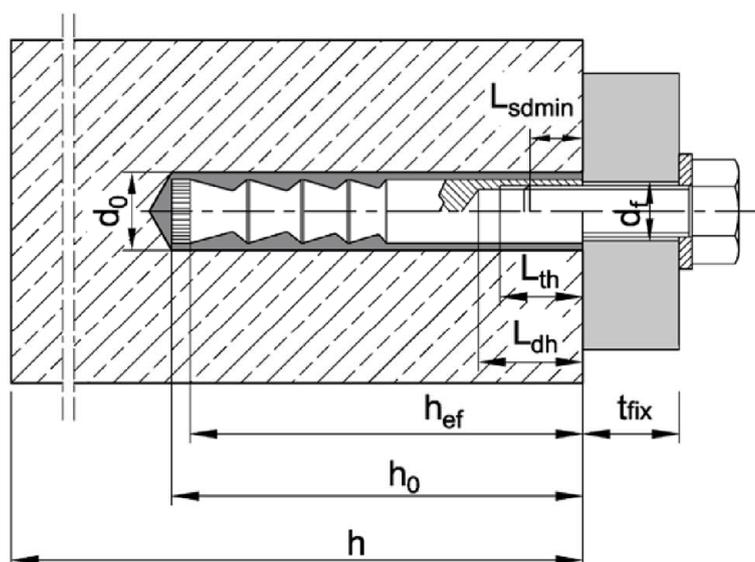
<sup>1)</sup> The reverse of the concrete member must not be damaged after drilling and must be filled with high-strength mortar if drilled through.



**Injection System HB-VMZ**

**Intended use**  
Installation parameters **HB-VMZ-IG**

**Annex B6**

## Installation instructions - Hammer drill bit

### Hammer drill bit

#### Hole drilling

|   |  |   |
|---|--|---|
| 1 |  | Use hammer drill or compressed air drill with drill bit and depth gauge. Drill perpendicular to concrete surface. |
|---|--|---|

#### Cleaning

##### Cleaning with compressed air (all sizes)

|    |  |  |
|----|--|--|
| 2a |  | Connect Air Blower to compressed air (min. 6 bar, oil-free). Open air valve and blow out drill hole along the entire depth with back and forth motion at least two times.  |
| 3a |  | Check diameter of cleaning brush. If the brush can be pushed into the drill hole without any resistance, it must be replaced. Chuck brush into drill machine. Turn on drill machine and brush drill hole back and forth along the entire drill hole depth at least two times while rotated by drill machine. |
| 4a |  | Connect Air Blower to compressed air (min. 6 bar, oil-free). Open air valve and blow out drill hole along the entire depth with back and forth motion at least two times.  |

##### Manual cleaning (alternatively, up to drill hole diameter 18mm)

|    |  |  |
|----|--|--|
| 2b |  | Blow out drill hole from the bottom with Blow-out pump at least two times.   |
| 3b |  | Check diameter of cleaning brush. If the brush can be pushed into the drill hole without any resistance, it must be replaced. Chuck brush into drill machine. Turn on drill machine and brush drill hole back and forth along the entire drill hole depth at least two times while rotated by drill machine. |
| 4b |  | Blow out drill hole from the bottom with Blow-out pump at least two times.   |

### Injection System HB-VMZ

#### Intended use

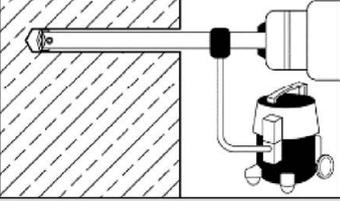
Installation instructions  
Hole drilling and cleaning (hammer drill bit)

**Annex B7**

## Installation instructions - Vacuum drill bit

### Vacuum drill bit


#### Hole drilling and cleaning

|  |   |  |
|--|---|--|
| 1  |  | <p>Drill hole perpendicular to concrete surface by using a vacuum drill bit (see Annex B1). The nominal underpressure of the vacuum cleaner must be at least 230 mbar / 23kPa.</p> <p><b>Pay attention to the function of the dust extraction system!</b><br/>Make sure the dust extraction is working properly throughout the whole drilling process.</p> |
| <p><b>Additional cleaning is not necessary - continue with step 5!</b></p> |   |  |




## Installation instructions - Diamond drilling
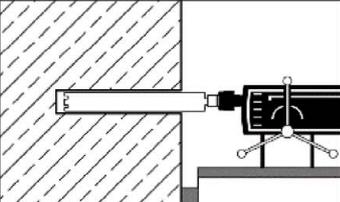
### Diamond drilling

#### Hole drilling

|   |   |   |
|---|---|---|
| 1 |  | <p>Use diamond drill with diamond drill bit and depth gauge. Drill perpendicular to concrete surface.</p> |
|---|---|---|

#### Cleaning

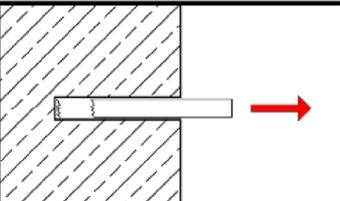
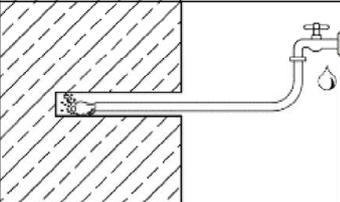
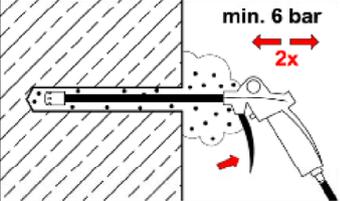
|   |   |  |
|---|---|--|
| 2 |  | <p>Remove drill core at least up to the nominal hole depth and check drill hole depth.</p>   |
| 3 |  | <p>Flushing of drill hole:<br/>Flush drill hole with water, starting from the bottom, until clear water gets out of the drill hole.</p>  |
| 4 |  | <p>Connect Air Blower to compressed air (min. 6 bar, oil-free).<br/>Open air valve and blow out drill hole along the entire depth with back and forth motion at least two times.</p> |

### Injection System HB-VMZ

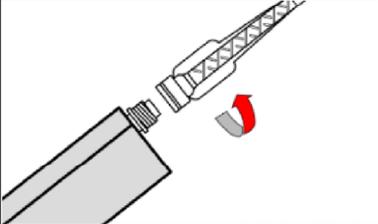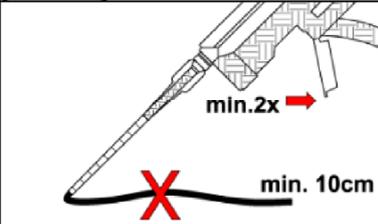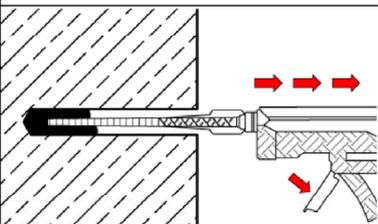**Intended use**  
Installation instructions  
Hole drilling and cleaning (vacuum drill bit and diamond drill bit)

**Annex B8**

## Installation instructions - Continuation

| Injection |  |
|-----------|--|
| 5         |  <p>Check expiration date on cartridge. Never use when expired. Remove cap from cartridge. Attach the supplied static mixer to the cartridge. For every working interruption longer than the recommended working time (Table B1 or Table B2) as well as for a new cartridge always use a new static mixer. Never use static mixer without helix inside.</p> |
| 6         |  <p>Insert cartridge in Dispenser. Before injecting discard mortar (at least 2 full strokes or a line of 10 cm) until it shows a consistent grey colour. Never use this mortar.</p>   |
| 7         |  <p>Prior to injection, check if static mixer reaches the bottom of the drill hole. If it does not reach the bottom, plug Mixer Extension onto static mixer in order to fill the drill hole properly. Fill hole with a sufficient quantity of injection mortar. Start from the bottom of the drill hole and work out to avoid trapping air pockets.</p>    |

### Injection System HB-VMZ

**Intended use**  
Installation instructions  
Injection

**Annex B9**

## Installation instructions - Continuation

### Anchor rod HB-VMZ-A

#### Inserting the anchor rod

|    |  |   |
|----|--|---|
| 8  |  | Insert the anchor rod HB-VMZ-A by hand, rotating slightly up to the full embedment depth as marked on the anchor rod. The anchor rod is properly set when excess mortar seeps from the hole (Pre-setting installation) or the annular gap in the clearance hole in the fixture is completely filled by excess mortar (Through-setting installation). If the hole is not completely filled, pull out anchor rod, let mortar cure, drill out hole and repeat entire cleaning process. |
| 9  |  | Follow minimum curing time shown in Table B1 or Table B2. During curing time, anchor rod must not be moved or loaded.   |
| 10 |  | Remove excess mortar.   |
| 11 |  | The fixture can be mounted after curing time. Apply installation torque $T_{inst}$ according to Table B3 or Table B4 by using torque wrench.  |

#### Filling annular gap

|          |  |   |
|----------|--|---|
| Optional |  | Annular gap between anchor rod and attachment may optionally be filled with mortar. Therefore, replace regular washer by washer with bore and plug on reducing adapter on static mixer. Annular gap is completely filled, when excess mortar seeps out. |
|----------|--|---|

### Injection System HB-VMZ

**Intended use**  
Installation instructions  
Installation Anchor rod **HB-VMZ-A**

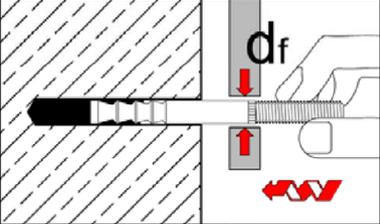
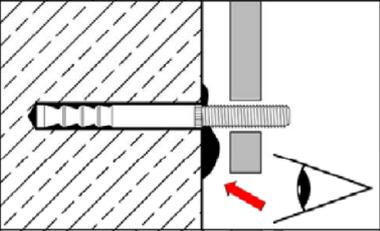
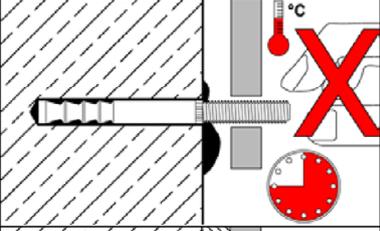
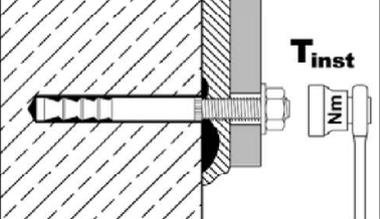
**Annex B10**

## Installation instructions – Stand-off Installation

### Stand-off installation with Anchor rod HB-VMZ-A 75 M12

Requirement: Diameter of clearance hole in the fixture  $d_f \leq 14 \text{ mm}$

Work step 1-7 as illustrated in Annexes B7 – B9

|    |   |  |
|----|---|--|
| 8  |    | <p>Insert the anchor rod HB-VMZ-A by hand, rotating slightly up to the full embedment depth.</p>   |
| 9  |    | <p>Check if excess mortar seeps from the hole. If the hole is not completely filled, pull out anchor rod, let mortar cure, drill out hole and repeat the entire cleaning process.</p> <p><b>The annular gap in the fixture does not have to be filled.</b></p> |
| 10 |   | <p>During curing time according to Table B1 or Table B2 anchor rod must not be moved or loaded.</p>  |
| 11 |  | <p>Washer and nut can be mounted after curing time and backfilling of anchor plate. Apply installation torque <math>T_{inst}</math> according to Table B3 by using torque wrench.</p>  |

### Injection System HB-VMZ

#### Intended use

Installation instructions **HB-VMZ-A 75 M12**

Through-setting installation with clearance between concrete and anchor plate

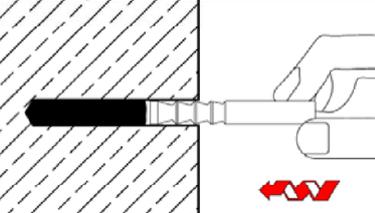
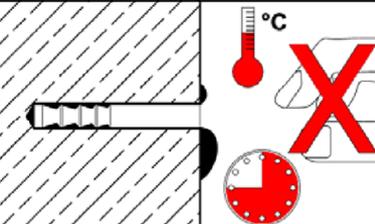
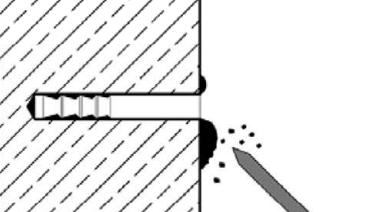
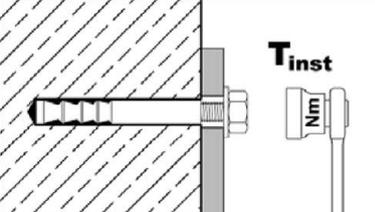
**Annex B11**

## Installation instructions - Continuation

### Anchor rod HB-VMZ-IG

#### Setting of fastener

Work step 1-7 as illustrated in Annexes B7 – B9

|    |   |   |
|----|---|---|
| 8  |    | Insert the anchor rod HB-VMZ-IG by hand, rotating slightly up to about 1 mm below the concrete surface in the drill hole. The anchor rod is properly set when excess mortar seeps from the hole. If the hole is not completely filled, pull out anchor rod, let mortar cure, drill out hole and repeat the entire cleaning process. |
| 9  |    | Follow minimum curing time shown in Table B1 and Table B2. During curing time anchor rod must not be moved or loaded.   |
| 10 |  | Remove excess mortar.   |
| 11 |  | The fixture can be mounted after curing time. Apply installation torque $T_{inst}$ according to Table B7 by using torque wrench.  |

### Injection System HB-VMZ

#### Intended use

Installation instructions  
Fastener installation HB-VMZ-IG

Annex B12

**Table C1: Characteristic values for concrete failure and splitting**

| Fastener size   |                    | HB-VMZ-A<br>HB-VMZ-IG |      | all sizes                      |
|---|--------------------|-----------------------|------|--------------------------------|
| Concrete cone failure   |                    |                       |      |                                |
| Factor for  | uncracked concrete | $k_{ucr,N}$           | [-]  | 11,0                           |
|   | cracked concrete   | $k_{cr,N}$            | [-]  | 7,7                            |
| Characteristic edge distance  |                    | $c_{cr,N}$            | [mm] | $1,5 \cdot h_{ef}$             |
| Characteristic spacing  |                    | $s_{cr,N}$            | [mm] | $2 \cdot c_{cr,N}$             |
| <b>Splitting</b>  |                    |                       |      |                                |
| For each proof of splitting failure, $N_{Rk,sp}$ shall be calculated according to EN 1992-4:2018, equation (7.23). The higher value for $N_{Rk,sp}$ of case 1 and case 2 may be applied for the design. |                    |                       |      |                                |
| Case 1  |                    |                       |      |                                |
| Characteristic resistance   |                    | $N^0_{Rk,sp}$         | [kN] | see following tables           |
| Characteristic edge distance  |                    | $c_{cr,sp}$           | [mm] | $1,5 \cdot h_{ef}$             |
| Characteristic spacing  |                    | $s_{cr,sp}$           | [mm] | $2 \cdot c_{cr,sp}$            |
| Case 2  |                    |                       |      |                                |
| Characteristic resistance   |                    | $N^0_{Rk,sp}$         | [kN] | $\min [N_{Rk,p} ; N^0_{Rk,c}]$ |
| Characteristic edge distance  |                    | $c_{cr,sp}$           | [mm] | see following tables           |
| Characteristic spacing  |                    | $s_{cr,sp}$           | [mm] | $2 \cdot c_{cr,sp}$            |

**Injection System HB-VMZ**

**Performance**

Characteristic values for **concrete failure and splitting, HB-VMZ-A and HB-VMZ-IG**

**Annex C1**

**Table C2: Characteristic values for tension loads, HB-VMZ-A M8 – M12, static and quasi-static action**

| Fastener size  |                            | HB-VMZ-A   | 40<br>M8                               | 50<br>M8     | 60<br>M10    | 75<br>M10    | 75<br>M12    | 70<br>M12    | 80<br>M12    | 95<br>M12  | 100<br>M12 | 110<br>M12   | 125<br>M12 |      |
|--|----------------------------|------------|--|--------------|--------------|--------------|--------------|--------------|--------------|------------|------------|--------------|------------|------|
| Installation factor  | $\gamma_{inst}$            | [-]        | 1,0                                    |              |              |              |              |              |              |            |            |              |            |      |
| <b>Steel failure</b>   |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| Characteristic resistance  | $N_{Rk,s}$                 | [kN]       | 15                                     | 18           | 25           | 35           | 49           | 54           | 57           |            |            |              |            |      |
| Partial factor   | $\gamma_{Ms}$              | [-]        | 1,5                                    |              |              |              |              |              |              |            |            |              |            |      |
| <b>Pull-out</b>  |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| Characteristic resistance (concrete C20/25)  |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| uncracked<br>concrete  | 50°C / 80°C <sup>1)</sup>  | $N_{Rk,p}$ | [kN]                                   | 9            | 17,4         | 22,9         | 32           | 32           | 28,8         | 35,2       | 40         | 49,2         | 50         | 50   |
|  | 72°C / 120°C <sup>1)</sup> |            | [kN]                                   | 6            | 9            | 16           | 16           | 16           | 16           | 25         | 25         | 30           | 30         | 30   |
| cracked<br>concrete  | 50°C / 80°C <sup>1)</sup>  | $N_{Rk,p}$ | [kN]                                   | 8,7          | 12,2         | 16           | 22,4         | 22,4         | 20,2         | 24,6       | 31,9       | 34,4         | 39,7       | 48,1 |
|  | 72°C / 120°C <sup>1)</sup> |            | [kN]                                   | 5            | 7,5          | 12           | 12           | 12           | 16           | 20         | 20         | 30           | 30         | 30   |
| <b>Splitting</b>   |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| Splitting for <b>standard thickness of concrete member</b>   |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| Standard thickness of<br>concrete  | $h_{min,1} \geq$           | [mm]       | 100                                    | 120          | 150          | 150          | 140          | 160          | 190          | 200        | 220        | 250          |            |      |
| <b>Case 1</b>  |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| Characteristic resistance<br>(concrete C20/25)   | $N^0_{Rk,sp}$              | [kN]       | 7,5                                    | 9            | 16           | 20           | 20           | 35,2         | 30           | 40         |            |              |            |      |
| <b>Case 2</b>  |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| Characteristic edge distance   | $c_{cr,sp}$                | [mm]       | 3 $h_{ef}$                             | 2,5 $h_{ef}$ | 3,5 $h_{ef}$ | 3,5 $h_{ef}$ | 2,5 $h_{ef}$ | 1,5 $h_{ef}$ | 2,5 $h_{ef}$ | 2 $h_{ef}$ | 3 $h_{ef}$ | 2,5 $h_{ef}$ |            |      |
| Splitting for <b>minimum thickness of concrete member</b>  |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| Minimum thickness of<br>concrete   | $h_{min,2} \geq$           | [mm]       | 80                                     | 100          | 110          |              |              | 125          | 130          | 140        | 160        |              |            |      |
| <b>Case 1</b>  |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| Characteristic resistance<br>(concrete C20/25)   | $N^0_{Rk,sp}$              | [kN]       | 7,5                                    | 2)           | 16           | 16           | 20           | 25           | 25           | 30         |            |              |            |      |
| <b>Case 2</b>  |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| Characteristic edge distance   | $c_{cr,sp}$                | [mm]       | 3 $h_{ef}$                             | 3,5 $h_{ef}$ | 3 $h_{ef}$   | 3,5 $h_{ef}$ | 3,5 $h_{ef}$ | 3 $h_{ef}$   | 3,5 $h_{ef}$ | 3 $h_{ef}$ |            |              |            |      |
| Increasing factor for (Case 1)<br>$N_{Rk,p} = \psi_c \cdot N_{Rk,p}$ (C20/25) and<br>$N^0_{Rk,sp} = \psi_c \cdot N^0_{Rk,sp}$ (C20/25) | $\psi_c$                   | [-]        | $\left(\frac{f_{ck}}{20}\right)^{0,5}$ |              |              |              |              |              |              |            |            |              |            |      |
| <b>Concrete cone failure</b>   |                            |            |  |              |              |              |              |              |              |            |            |              |            |      |
| Effective anchorage depth  | $h_{ef}$                   | [mm]       | 40                                     | 50           | 60           | 75           | 75           | 70           | 80           | 95         | 100        | 110          | 125        |      |

<sup>1)</sup> Maximum long-term temperature / Maximum short-term temperature

<sup>2)</sup> No performance assessed

**Injection System HB-VMZ**

**Performance**

Characteristic values for **tension loads, HB-VMZ-A M8 – M12, static and quasi-static action**

**Annex C2**

**Table C3:** Characteristic values for **tension loads, HB-VMZ-A M16 – M24,**  
static and quasi-static action

| Fastener size   |                          | HB-VMZ-A   | 90<br>M16                              | 105<br>M16 | 125<br>M16   | 145<br>M16   | 160<br>M16   | 115<br>M20    | 170<br>M20<br>(LG) | 190<br>M20<br>(LG) | 170<br>M24<br>(LG) | 200<br>M24<br>(LG) | 225<br>M24<br>(LG) |       |
|---|--------------------------|------------|--|------------|--------------|--------------|--------------|---------------|--------------------|--------------------|--------------------|--------------------|--------------------|-------|
| Installation factor   | $\gamma_{inst}$          | [-]        | 1,0                                    |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| <b>Steel failure</b>  |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| Characteristic tension resistance $N_{Rk,s}$  | Steel, zinc plated       | [kN]       | 88                                     | 95         | 111          | 97           | 96           | 188           | 222                |                    |                    |                    |                    |       |
|   | A4, HCR                  | [kN]       | 88                                     | 95         | 111          | 97           | 114          | 165           | 194                |                    |                    |                    |                    |       |
| Partial factor  | $\gamma_{Ms}$            | [-]        | 1,5                                    |            |              |              |              | 1,68          | 1,5                | 1,5                |                    |                    |                    |       |
| <b>Pull-out</b>   |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| Characteristic resistance (concrete C20/25)   |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| uncracked concrete  | 50°C/80°C <sup>1)</sup>  | $N_{Rk,p}$ | [kN]                                   | 42         | 52,9         | 68,8         | 75           | 90            | 60,7               | 109                | 128,8              | 109                | 139,1              | 166   |
|   | 72°C/120°C <sup>1)</sup> |            | [kN]                                   | 25         | 35           | 50           | 53           | 40            | 75                 | 95                 |                    |                    |                    |       |
| cracked concrete  | 50°C/80°C <sup>1)</sup>  | $N_{Rk,p}$ | [kN]                                   | 29,4       | 37,1         | 48,1         | 60,1         | 69,7          | 42,5               | 76,3               | 90,2               | 76,3               | 97,4               | 116,2 |
|   | 72°C/120°C <sup>1)</sup> |            | [kN]                                   | 25         | 30           | 50           | 51           | 30            | 60                 | 75                 |                    |                    |                    |       |
| <b>Splitting</b>  |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| Splitting for <b>standard thickness of concrete</b>   |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| Standard thickness of concrete  | $h_{min,1} \geq$         | [mm]       | 180                                    | 200        | 250          | 290          | 320          | 230           | 340                | 380                | 340                | 400                | 450                |       |
| <b>Case 1</b>   |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| Characteristic resistance (concrete C20/25)   | $N^0_{Rk,sp}$            | [kN]       | 40                                     | 50         | 60           | 80           | 60,7         | 109           | 115                | 109                | 139,1              | 140                |                    |       |
| <b>Case 2</b>   |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| Characteristic edge distance  | $c_{cr,sp}$              | [mm]       | 2 $h_{ef}$                             |            |              |              |              | 1,5 $h_{ef}$  | 2 $h_{ef}$         | 1,5 $h_{ef}$       | 1,8 $h_{ef}$       |                    |                    |       |
| Splitting for <b>minimum thickness of concrete</b>  |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| Minimum thickness of concrete   | $h_{min,2} \geq$         | [mm]       | 130                                    | 150        | 160          | 180          | 200          | 160           | 220                | 240                | 220                | 260                | 290                |       |
| <b>Case 1</b>   |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| Characteristic resistance (concrete C20/25)   | $N^0_{Rk,sp}$            | [kN]       | 35                                     | 50         | 40           | 50           | 71           | <sup>2)</sup> | 75                 | 109                | 115                |                    |                    |       |
| <b>Case 2</b>   |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| Characteristic edge distance  | $c_{cr,sp}$              | [mm]       | 2,5 $h_{ef}$                           | 3 $h_{ef}$ | 2,5 $h_{ef}$ | 2,5 $h_{ef}$ | 2,6 $h_{ef}$ | 2,2 $h_{ef}$  | 2,6 $h_{ef}$       | 2,2 $h_{ef}$       |                    |                    |                    |       |
| Increasing factor for (Case 1)<br>$N_{Rk,p} = \psi_c \cdot N_{Rk,p} (C20/25)$ and $\psi_c$<br>$N^0_{Rk,sp} = \psi_c \cdot N^0_{Rk,sp} (C20/25)$ |                          | [-]        | $\left(\frac{f_{ck}}{20}\right)^{0,5}$ |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| <b>Concrete cone failure</b>  |                          |            |  |            |              |              |              |               |                    |                    |                    |                    |                    |       |
| Effective anchorage depth   | $h_{ef}$                 | [mm]       | 90                                     | 105        | 125          | 145          | 160          | 115           | 170                | 190                | 170                | 200                | 225                |       |

<sup>1)</sup> Maximum long-term temperature / Maximum short-term temperature

<sup>2)</sup> No performance assessed

**Injection System HB-VMZ**

**Performance**  
Characteristic values for **tension loads, HB-VMZ-A M16 – M24,**  
static and quasi-static action

**Annex C3**

**Table C4:** Characteristic values for **shear load, HB-VMZ-A M8 – M12,**  
static and quasi-static action

| Fastener size                                  |                    | HB-VMZ-A | 40<br>M8 | 50<br>M8 | 60<br>M10 | 75<br>M10 | 75<br>M12 | 70<br>M12 | 80<br>M12 | 95<br>M12 | 100<br>M12 | 110<br>M12 | 125<br>M12 |
|--|--------------------|----------|----------|----------|-----------|-----------|-----------|-----------|-----------|-----------|------------|------------|------------|
| Installation factor                            | $\gamma_{inst}$    | [-]      | 1,0      |          |           |           |           |           |           |           |            |            |            |
| <b>Steel failure without lever arm</b>         |                    |          |          |          |           |           |           |           |           |           |            |            |            |
| Characteristic resistance $V_{Rk,s}^0$         | Steel, zinc plated | [kN]     | 14       | 21       |           |           | 34        |           |           |           |            |            |            |
|  | A4, HCR            | [kN]     | 15       | 23       |           |           | 34        |           |           |           |            |            |            |
| Partial factor                                 | $\gamma_{Ms}$      | [-]      | 1,25     |          |           |           |           |           |           |           |            |            |            |
| Ductility factor                               | $k_7$              | [-]      | 1,0      |          |           |           |           |           |           |           |            |            |            |
| <b>Steel failure with lever arm</b>            |                    |          |          |          |           |           |           |           |           |           |            |            |            |
| Characteristic bending resistance $M_{Rk,s}^0$ | Steel, zinc plated | [Nm]     | 30       | 60       |           |           | 105       |           |           |           |            |            |            |
|  | A4, HCR            | [Nm]     | 30       | 60       |           |           | 105       |           |           |           |            |            |            |
| Partial factor                                 | $\gamma_{Ms}$      | [-]      | 1,25     |          |           |           |           |           |           |           |            |            |            |
| <b>Concrete pry-out failure</b>                |                    |          |          |          |           |           |           |           |           |           |            |            |            |
| Pry-out factor                                 | $k_8$              | [-]      | 2        |          |           |           |           |           |           |           |            |            |            |
| <b>Concrete edge failure</b>                   |                    |          |          |          |           |           |           |           |           |           |            |            |            |
| Effective length of fastener in shear load     | $l_f$              | [mm]     | 40       | 50       | 60        | 75        | 75        | 70        | 80        | 95        | 100        | 110        | 125        |
| Outside diameter of fastener                   | $d_{nom}$          | [mm]     | 10       |          | 12        |           | 12        | 14        |           |           |            |            |            |

**Injection System HB-VMZ**

**Performance**


Characteristic values for **shear load, HB-VMZ-A M8 – M12,**  
static and quasi-static action

**Annex C4**

**Table C5:** Characteristic values for **shear load, HB-VMZ-A M16 – M24,**  
static or quasi-static action

| Fastener size                                     |                    | HB-VMZ-A | 90<br>M16 | 105<br>M16 | 125<br>M16 | 145<br>M16 | 160<br>M16 | 115<br>M20                | 170<br>M20<br>(LG) | 190<br>M20<br>(LG)         | 170<br>M24<br>(LG) | 200<br>M24<br>(LG) | 225<br>M24<br>(LG) |
|---|--------------------|----------|-----------|------------|------------|------------|------------|---------------------------|--------------------|----------------------------|--------------------|--------------------|--------------------|
| Installation factor                               | $\gamma_{inst}$    | [-]      | 1,0       |            |            |            |            |                           |                    |                            |                    |                    |                    |
| <b>Steel failure without lever arm</b>            |                    |          |           |            |            |            |            |                           |                    |                            |                    |                    |                    |
| Characteristic resistance<br>$V_{Rk,s}^0$         | Steel, zinc plated | [kN]     | 63        |            |            |            | 70         | 149 <sup>1)</sup><br>(98) |                    | 178 <sup>1)</sup><br>(141) |                    |                    |                    |
|   | A4, HCR            | [kN]     | 63        |            |            |            | 86         | 131 <sup>1)</sup><br>(86) |                    | 156 <sup>1)</sup><br>(123) |                    |                    |                    |
| Partial factor                                    | $\gamma_{Ms}$      | [-]      | 1,25      |            |            |            | 1,4        | 1,25                      |                    | 1,25                       |                    |                    |                    |
| Ductility factor                                  | $k_7$              | [-]      | 1,0       |            |            |            |            |                           |                    |                            |                    |                    |                    |
| <b>Steel failure with lever arm</b>               |                    |          |           |            |            |            |            |                           |                    |                            |                    |                    |                    |
| Characteristic bending resistance<br>$M_{Rk,s}^0$ | Steel, zinc plated | [Nm]     | 266       |            |            |            | 392        | 519                       |                    | 896                        |                    |                    |                    |
|   | A4, HCR            | [Nm]     | 266       |            |            |            | 454        |                           | 784                |                            |                    |                    |                    |
| Partial factor                                    | $\gamma_{Ms}$      | [-]      | 1,25      |            |            |            | 1,4        | 1,25                      |                    | 1,25                       |                    |                    |                    |
| <b>Concrete pry-out failure</b>                   |                    |          |           |            |            |            |            |                           |                    |                            |                    |                    |                    |
| Pry-out factor                                    | $k_8$              | [-]      | 2,0       |            |            |            |            |                           |                    |                            |                    |                    |                    |
| <b>Concrete edge failure</b>                      |                    |          |           |            |            |            |            |                           |                    |                            |                    |                    |                    |
| Effective length of fastener in shear load        | $l_f$              | [mm]     | 90        | 105        | 125        | 145        | 160        | 115                       | 170                | 190                        | 170                | 200                | 225                |
| Outside diameter of fastener                      | $d_{nom}$          | [mm]     | 18        |            |            |            | 22         | 24                        |                    | 26                         |                    |                    |                    |
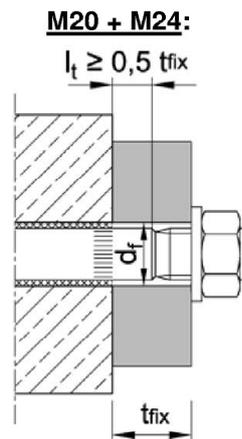
<sup>1)</sup> This value may only be applied if  $l_t \geq 0,5 t_{fix}$



**Injection System HB-VMZ**

**Performance**

Characteristic values for **shear load, HB-VMZ-A M16 – M24,**  
static and quasi-static action

**Annex C5**

**Table C6: Characteristic values for seismic action,  
HB-VMZ-A M10 – M12 performance category C1 and C2**

| Fastener size  |                                | HB-VMZ-A                   | 60<br>M10 | 75<br>M10 | 75<br>M12 | 70<br>M12 | 80<br>M12 | 95<br>M12 | 100<br>M12 | 110<br>M12 | 125<br>M12 |
|--|--------------------------------|----------------------------|-----------|-----------|-----------|-----------|-----------|-----------|------------|------------|------------|
| <b>Tension loads</b>   |                                |                            |           |           |           |           |           |           |            |            |            |
| Installation factor  | $\gamma_{inst}$                | [-]                        | 1,0       |           |           |           |           |           |            |            |            |
| <b>Steel failure, steel zinc plated, stainless steel A4, HCR</b> |                                |                            |           |           |           |           |           |           |            |            |            |
| Characteristic resistance  | $N_{Rk,s,C1}$<br>$N_{Rk,s,C2}$ | [kN]                       | 25        | 35        | 49        | 54        | 57        |           |            |            |            |
| Partial factor   | $\gamma_{Ms}$                  | [-]                        | 1,5       |           |           |           |           |           |            |            |            |
| <b>Pull-out (concrete C20/25 to C50/60)</b>                      |                                |                            |           |           |           |           |           |           |            |            |            |
| Characteristic resistance  | $N_{Rk,p,C1}$                  | 50°C / 80°C <sup>1)</sup>  | [kN]      | 14,5      | 14,5      | 30,6      | 36,0      | 41,5      | 42,8       |            |            |
|  |                                | 72°C / 120°C <sup>1)</sup> | [kN]      | 10,9      | 10,9      | 20,0      | 30,0      |           |            |            |            |
|  | $N_{Rk,p,C2}$                  | 50°C / 80°C <sup>1)</sup>  | [kN]      | 7,4       | 7,4       | 8,7       | 17,6      |           |            |            |            |
|  |                                | 72°C / 120°C <sup>1)</sup> | [kN]      | 5,1       | 5,1       | 6,5       | 12,3      |           |            |            |            |

|   |                      |                |      |      |  |  |  |  |  |  |  |
|---|----------------------|----------------|------|------|--|--|--|--|--|--|--|
| <b>Shear loads</b>  |                      |                |      |      |  |  |  |  |  |  |  |
| <b>Steel failure without lever arm, steel zinc plated</b>       |                      |                |      |      |  |  |  |  |  |  |  |
| Characteristic resistance                                       | $V_{Rk,s,C1}$        | [kN]           | 11,8 | 27,2 |  |  |  |  |  |  |  |
|   | $V_{Rk,s,C2}$        | [kN]           | 12,6 | 27,2 |  |  |  |  |  |  |  |
| Partial factor  | $\gamma_{Ms}$        | [-]            | 1,25 |      |  |  |  |  |  |  |  |
| <b>Steel failure without lever arm, stainless steel A4, HCR</b> |                      |                |      |      |  |  |  |  |  |  |  |
| Characteristic resistance                                       | $V_{Rk,s,C1}$        | [kN]           | 12,9 | 27,2 |  |  |  |  |  |  |  |
|   | $V_{Rk,s,C2}$        | [kN]           | 13,8 | 27,2 |  |  |  |  |  |  |  |
| Partial factor  | $\gamma_{Ms}$        | [-]            | 1,25 |      |  |  |  |  |  |  |  |
| Factor for fasteners with                                       | filled annular gap   | $\alpha_{gap}$ | [-]  | 1,0  |  |  |  |  |  |  |  |
|   | unfilled annular gap | $\alpha_{gap}$ | [-]  | 0,5  |  |  |  |  |  |  |  |

<sup>1)</sup> Maximum long-term temperature / Maximum short-term temperature

**Injection System HB-VMZ**

**Performance**  
Characteristic values for **seismic action, HB-VMZ-A M10 – M12,**  
performance category **C1** and **C2**

**Annex C6**

**Table C7: Characteristic values for seismic action,  
HB-VMZ-A M16 – M24, performance category C1 and C2**

| Fastener size                                 | HB-VMZ-A                       | 90<br>M16                  | 105<br>M16 | 125<br>M16 | 145<br>M16 | 160<br>M16 | 115<br>M20 | 170<br>M20<br>(LG) | 190<br>M20<br>(LG) | 170<br>M24<br>(LG) | 200<br>M24<br>(LG) | 225<br>M24<br>(LG) |
|---|--------------------------------|----------------------------|------------|------------|------------|------------|------------|--------------------|--------------------|--------------------|--------------------|--------------------|
| <b>Tension loads</b>                          |                                |                            |            |            |            |            |            |                    |                    |                    |                    |                    |
| Installation factor                           | $\gamma_{inst}$                | [-]                        |            | 1,0        |            |            |            |                    |                    |                    |                    |                    |
| <b>Steel failure, steel zinc plated</b>       |                                |                            |            |            |            |            |            |                    |                    |                    |                    |                    |
| Characteristic resistance                     | $N_{Rk,s,C1}$<br>$N_{Rk,s,C2}$ | [kN]                       | 88         | 95         | 111        | 97         | 96         | 188                | 222                |                    |                    |                    |
| <b>Steel failure, stainless steel A4, HCR</b> |                                |                            |            |            |            |            |            |                    |                    |                    |                    |                    |
| Characteristic resistance                     | $N_{Rk,s,C1}$<br>$N_{Rk,s,C2}$ | [kN]                       | 88         | 95         | 111        | 97         | 114        | 165                | 194                |                    |                    |                    |
| Partial factor                                | $\gamma_{Ms}$                  | [-]                        |            | 1,5        |            |            | 1,68       | 1,5                | 1,5                |                    |                    |                    |
| <b>Pull-out (concrete C20/25 to C50/60)</b>   |                                |                            |            |            |            |            |            |                    |                    |                    |                    |                    |
| Characteristic resistance                     | $N_{Rk,p,C1}$                  | 50°C / 80°C <sup>1)</sup>  | [kN]       | 30,7       | 38,7       | 43,7       |            | 44,4               | 88,2               | 90,7               |                    |                    |
|   |                                | 72°C / 120°C <sup>1)</sup> | [kN]       | 25,0       | 30,0       | 38,5       |            | 29,4               | 55,8               | 59,3               |                    |                    |
|   | $N_{Rk,p,C2}$                  | 50°C / 80°C <sup>1)</sup>  | [kN]       | 16,3       | 22,1       | 26,1       |            | 30,9               | 59,7               | 59,7               |                    |                    |
|   |                                | 72°C / 120°C <sup>1)</sup> | [kN]       | 10,5       | 14,4       | 19,5       |            | 16,2               | 44,4               | 44,4               |                    |                    |

|   |                      |                |      |      |     |  |      |                               |                                |  |  |  |
|---|----------------------|----------------|------|------|-----|--|------|-------------------------------|--------------------------------|--|--|--|
| <b>Shear loads</b>  |                      |                |      |      |     |  |      |                               |                                |  |  |  |
| <b>Steel failure without lever arm, steel zinc plated</b>       |                      |                |      |      |     |  |      |                               |                                |  |  |  |
| Characteristic resistance                                       | $V_{Rk,s,C1}$        | [kN]           | 39,1 |      |     |  | 39,1 | 82,3                          | 107                            |  |  |  |
|   | $V_{Rk,s,C2}$        | [kN]           | 50,4 |      |     |  | 51   | 108,8 <sup>1)</sup><br>(71,5) | 154,9 <sup>1)</sup><br>(122,7) |  |  |  |
| Partial factor  | $\gamma_{Ms}$        | [-]            |      | 1,25 |     |  | 1,4  | 1,25                          | 1,25                           |  |  |  |
| <b>Steel failure without lever arm, stainless steel A4, HCR</b> |                      |                |      |      |     |  |      |                               |                                |  |  |  |
| Characteristic resistance                                       | $V_{Rk,s,C1}$        | [kN]           | 39,1 |      |     |  | 39,1 | 72,2                          | 93                             |  |  |  |
|   | $V_{Rk,s,C2}$        | [kN]           | 50,4 |      |     |  | 62,6 | 95,6 <sup>1)</sup><br>(62,8)  | 135,7 <sup>1)</sup><br>(107)   |  |  |  |
| Partial factor  | $\gamma_{Ms}$        | [-]            |      | 1,25 |     |  | 1,4  | 1,25                          | 1,25                           |  |  |  |
| Factor for fasteners with                                       | filled annular gap   | $\alpha_{gap}$ | [-]  |      | 1,0 |  |      |                               |                                |  |  |  |
|   | unfilled annular gap | $\alpha_{gap}$ | [-]  |      | 0,5 |  |      |                               |                                |  |  |  |

<sup>1)</sup> This value may only be applied if  $l_t \geq 0,5 t_{fix}$ , (see Annex C4)

**Injection System HB-VMZ**

**Performance**

Characteristic values for seismic action, HB-VMZ-A M16 – M24, performance category C1 and C2

**Annex C7**

**Table C8: Displacements under tension loads, HB-VMZ-A M8 – M12**

| Fastener size                                       |                      | HB-VMZ-A | 40<br>M8                        | 50<br>M8 | 60<br>M10 | 75<br>M10 | 75<br>M12 | 70<br>M12 | 80<br>M12 | 95<br>M12 | 100<br>M12 | 110<br>M12 | 125<br>M12 |
|---|----------------------|----------|---------------------------------|----------|-----------|-----------|-----------|-----------|-----------|-----------|------------|------------|------------|
| Tension load in <b>cracked</b> concrete             | N                    | [kN]     | 4,3                             | 6,1      | 8,0       | 11,1      | 11,1      | 10,0      | 12,3      | 15,9      | 17,1       | 19,8       | 24,0       |
| Displacement  | $\delta_{N0}$        | [mm]     | 0,5                             |          | 0,5       | 0,6       | 0,6       |           |           |           | 0,7        |            |            |
|   | $\delta_{N\infty}$   | [mm]     | 1,3                             |          |           |           |           |           |           |           |            |            |            |
| Tension load in <b>uncracked</b> concrete           | N                    | [kN]     | 4,3                             | 8,5      | 11,1      | 15,6      | 15,6      | 14,1      | 17,2      | 19,0      | 24,0       | 23,8       | 23,8       |
| Displacement  | $\delta_{N0}$        | [mm]     | 0,2                             | 0,4      | 0,4       |           | 0,4       |           |           |           | 0,6        |            |            |
|   | $\delta_{N\infty}$   | [mm]     | 1,3                             |          |           |           |           |           |           |           |            |            |            |
| <b>Displacements under seismic tension loads C2</b> |                      |          |                                 |          |           |           |           |           |           |           |            |            |            |
| Displacements for DLS                               | $\delta_{N,C2(DLS)}$ | [mm]     | no perfor-<br>mance<br>assessed |          | 1,0       |           | 1,0       |           | 1,3       |           | 1,1        |            |            |
| Displacements for ULS                               | $\delta_{N,C2(ULS)}$ | [mm]     | no perfor-<br>mance<br>assessed |          | 3,0       |           | 3,0       |           | 3,9       |           | 3,0        |            |            |

**Table C9: Displacements under tension loads, HB-VMZ-A M16 – M24**

| Fastener size                                       |                      | HB-VMZ-A | 90<br>M16 | 105<br>M16 | 125<br>M16 | 145<br>M16 | 160<br>M16 | 115<br>M20 | 170<br>M20<br>(LG) | 190<br>M20<br>(LG) | 170<br>M24<br>(LG) | 200<br>M24<br>(LG) | 225<br>M24<br>(LG) |
|---|----------------------|----------|-----------|------------|------------|------------|------------|------------|--------------------|--------------------|--------------------|--------------------|--------------------|
| Tension load in <b>cracked</b> concrete             | N                    | [kN]     | 14,6      | 18,4       | 24,0       | 30,0       | 34,7       | 21,1       | 38,0               | 44,9               | 38,0               | 48,5               | 57,9               |
| Displacement  | $\delta_{N0}$        | [mm]     | 0,7       |            |            | 0,8        | 1,2        | 0,7        | 0,8                |                    | 0,8                | 0,9                |                    |
|   | $\delta_{N\infty}$   | [mm]     | 1,3       |            |            |            | 1,6        | 1,1        | 1,3                |                    | 1,3                |                    |                    |
| Tension load in <b>uncracked</b> concrete           | N                    | [kN]     | 20,5      | 25,9       | 33,0       | 35,7       | 48,1       | 29,6       | 53,3               | 63,0               | 53,3               | 67,9               | 81,1               |
| Displacement  | $\delta_{N0}$        | [mm]     | 0,6       |            |            |            | 0,8        | 0,5        | 0,6                |                    | 0,6                |                    |                    |
|   | $\delta_{N\infty}$   | [mm]     | 1,3       |            |            |            | 1,6        | 1,1        | 1,3                |                    | 1,3                |                    |                    |
| <b>Displacements under seismic tension loads C2</b> |                      |          |           |            |            |            |            |            |                    |                    |                    |                    |                    |
| Displacements for DLS                               | $\delta_{N,C2(DLS)}$ | [mm]     | 1,6       |            | 1,5        |            | 1,7        |            | 1,9                |                    | 1,9                |                    |                    |
| Displacements for ULS                               | $\delta_{N,C2(ULS)}$ | [mm]     | 3,7       |            | 4,4        |            | 4,0        |            | 4,5                |                    | 4,5                |                    |                    |

**Injection System HB-VMZ**

**Performance**  
Displacements under tension loads, **HB-VMZ-A**

**Annex C8**

**Table C10: Displacements under shear loads HB-VMZ-A M8 – M12**

| Fastener size                                     |                      | HB-VMZ-A | 40<br>M8                        | 50<br>M8 | 60<br>M10 | 75<br>M10 | 75<br>M12 | 70<br>M12 | 80<br>M12 | 95<br>M12 | 100<br>M12 | 110<br>M12 | 125<br>M12 |
|---|----------------------|----------|---------------------------------|----------|-----------|-----------|-----------|-----------|-----------|-----------|------------|------------|------------|
| Shear load  | V                    | [kN]     | 8,3                             |          | 13,3      |           | 19,3      |           |           |           |            |            |            |
| Displacements                                     | $\delta_{V0}$        | [mm]     | 2,4                             | 2,5      | 2,9       |           | 3,3       |           |           |           |            |            |            |
|   | $\delta_{V\infty}$   | [mm]     | 3,6                             | 3,8      | 4,4       |           | 5,0       |           |           |           |            |            |            |
| <b>Displacements under seismic shear loads C2</b> |                      |          |                                 |          |           |           |           |           |           |           |            |            |            |
| Displacements for DLS                             | $\delta_{V,C2(DLS)}$ | [mm]     | no perfor-<br>mance<br>assessed |          | 2,1       |           | 2,5       |           |           |           |            |            |            |
| Displacements for ULS                             | $\delta_{V,C2(ULS)}$ | [mm]     | no perfor-<br>mance<br>assessed |          | 3,7       |           | 5,1       |           |           |           |            |            |            |

**Table C11: Displacements under shear loads HB-VMZ-A M16 – M24**

| Fastener size                                     |                      | HB-VMZ-A | 90<br>M16 | 105<br>M16 | 125<br>M16 | 145<br>M16 | 160<br>M16 | 115<br>M20 | 170<br>M20<br>(LG) | 190<br>M20<br>(LG) | 170<br>M24<br>(LG) | 200<br>M24<br>(LG) | 225<br>M24<br>(LG) |
|---|----------------------|----------|-----------|------------|------------|------------|------------|------------|--------------------|--------------------|--------------------|--------------------|--------------------|
| Shear load  | V                    | [kN]     | 36        |            |            |            | 44         |            | 75<br>(49)         |                    | 89<br>(71)         |                    |                    |
| Displacements                                     | $\delta_{V0}$        | [mm]     | 3,8       |            |            |            | 3,0        |            | 4,3<br>(3,0)       |                    | 4,6<br>(3,5)       |                    |                    |
|   | $\delta_{V\infty}$   | [mm]     | 5,7       |            |            |            | 4,5        |            | 6,5<br>(4,5)       |                    | 6,9<br>(5,3)       |                    |                    |
| <b>Displacements under seismic shear loads C2</b> |                      |          |           |            |            |            |            |            |                    |                    |                    |                    |                    |
| Displacements for DLS                             | $\delta_{V,C2(DLS)}$ | [mm]     | 2,9       |            |            |            | 3,5        |            | 3,7                |                    |                    |                    |                    |
| Displacements for ULS                             | $\delta_{V,C2(ULS)}$ | [mm]     | 6,8       |            |            |            | 9,3        |            | 9,3                |                    |                    |                    |                    |

**Injection System HB-VMZ**

**Performance**  
Displacements under shear loads, **HB-VMZ-A**

**Annex C9**

**Table C12: Characteristic values for tension load, HB-VMZ-IG**

| Fastener size  |                            | HB-VMZ-IG           | 40<br>M6                               | 50<br>M6      | 60<br>M8     | 75<br>M8     | 70<br>M10    | 80<br>M10  | 90<br>M12    | 105<br>M12   | 125<br>M12    | 115<br>M16   | 170<br>M16   | 170<br>M20   |      |
|--|----------------------------|---------------------|--|---------------|--------------|--------------|--------------|------------|--------------|--------------|---------------|--------------|--------------|--------------|------|
| Installation factor  |                            | $\gamma_{inst}$ [-] | 1,0                                    |               |              |              |              |            |              |              |               |              |              |              |      |
| <b>Steel failure</b>   |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| Characteristic resistance $N_{Rk,s}$   | Steel, zinc plated         | [kN]                | 15                                     | 16            | 19           | 29           | 35           |            |              | 67           |               | 52           | 125          | 108          |      |
|  | A4, HCR                    | [kN]                | 11                                     |               | 19           | 21           | 33           |            |              | 47           |               | 65           | 88           | 94           |      |
| Partial factor   |                            | $\gamma_{Ms}$ [-]   | 1,5                                    |               |              |              |              |            |              |              |               |              |              |              |      |
| <b>Pull-out</b>  |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| Characteristic resistance (concrete C20/25)  |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| uncracked<br>concrete  | 50°C / 80°C <sup>1)</sup>  | $N_{Rk,p}$          | [kN]                                   | 9             | 17,4         | 22,9         | 32           | 28,8       | 35,2         | 42           | 52,9          | 68,8         | 60,7         | 109          | 109  |
|  | 72°C / 120°C <sup>1)</sup> |                     | [kN]                                   | 6             | 9            | 16           | 16           | 16         | 25           | 25           | 35            | 50           | 40           | 75           | 95   |
| cracked<br>concrete  | 50°C / 80°C <sup>1)</sup>  | $N_{Rk,p}$          | [kN]                                   | 8,7           | 12,2         | 16           | 22,4         | 20,2       | 24,6         | 29,4         | 37,1          | 48,1         | 42,5         | 76,3         | 76,3 |
|  | 72°C / 120°C <sup>1)</sup> |                     | [kN]                                   | 5             | 7,5          | 12           | 12           | 16         | 20           | 20           | 30            | 50           | 30           | 60           | 75   |
| <b>Splitting</b>   |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| <b>Splitting for standard thickness of concrete</b>  |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| Standard thickness of concrete $h_{min,1} \geq$  |                            | [mm]                | 100                                    | 120           | 150          | 140          | 160          | 180        | 200          | 250          | 230           | 340          | 340          |              |      |
| <b>Case 1</b>  |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| Characteristic resistance (concrete C20/25)  |                            | $N^0_{Rk,sp}$ [kN]  | 7,5                                    | 9             | 16           | 20           | 20           | 35,2       | 40           | 50           | 50            | 60,7         | 109          | 109          |      |
| <b>Case 2</b>  |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| Characteristic edge distance   |                            | $c_{cr,sp}$ [mm]    | 3 $h_{ef}$                             | 2,5 $h_{ef}$  | 3,5 $h_{ef}$ | 2,5 $h_{ef}$ | 1,5 $h_{ef}$ | 2 $h_{ef}$ |              |              |               | 1,5 $h_{ef}$ | 1,5 $h_{ef}$ |              |      |
| <b>Splitting for minimum thickness of concrete</b>   |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| Minimum thickness of concrete $h_{min,2} \geq$   |                            | [mm]                | 80                                     | 100           | 110          | 110          | 130          | 150        | 160          | 160          | 220           | 220          |              |              |      |
| <b>Case 1</b>  |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| Characteristic resistance (concrete C20/25)  |                            | $N^0_{Rk,sp}$ [kN]  | 7,5                                    | <sup>2)</sup> | 16           | 20           | 25           | 35         | 50           | 40           | <sup>2)</sup> | 75           | 109          |              |      |
| <b>Case 2</b>  |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| Characteristic edge distance   |                            | $c_{cr,sp}$ [mm]    | 3 $h_{ef}$                             | 3,5 $h_{ef}$  | 3 $h_{ef}$   | 3,5 $h_{ef}$ | 3,5 $h_{ef}$ | 3 $h_{ef}$ | 2,5 $h_{ef}$ | 2,5 $h_{ef}$ | 3 $h_{ef}$    | 2,5 $h_{ef}$ | 2,6 $h_{ef}$ | 2,6 $h_{ef}$ |      |
| Increasing factor for (Case 1)<br>$N_{Rk,p} = \psi_c \cdot N_{Rk,p}$ (C20/25) and<br>$N^0_{Rk,sp} = \psi_c \cdot N^0_{Rk,sp}$ (C20/25) |                            | $\psi_c$ [-]        | $\left(\frac{f_{ck}}{20}\right)^{0,5}$ |               |              |              |              |            |              |              |               |              |              |              |      |
| <b>Concrete cone failure</b>   |                            |                     |  |               |              |              |              |            |              |              |               |              |              |              |      |
| Effective anchorage depth  |                            | $h_{ef}$ [mm]       | 40                                     | 50            | 60           | 75           | 70           | 80         | 90           | 105          | 125           | 115          | 170          | 170          |      |

<sup>1)</sup> Maximum long-term temperature / Maximum short-term temperature

<sup>2)</sup> No performance assessed

**Injection System HB-VMZ**

**Performance**  
Characteristic values for tension loads, **HB-VMZ-IG**

**Annex C10**

**Table C13: Characteristic values for shear load, HB-VMZ-IG**

| Fastener size                                  |                    | HB-VMZ-IG | 40<br>M6 | 50<br>M6 | 60<br>M8 | 75<br>M8 | 70<br>M10 | 80<br>M10 | 90<br>M12 | 105<br>M12 | 125<br>M12 | 115<br>M16 | 170<br>M16 | 170<br>M20 |
|--|--------------------|-----------|----------|----------|----------|----------|-----------|-----------|-----------|------------|------------|------------|------------|------------|
| Installation factor                            | $\gamma_{inst}$    | [-]       | 1,0      |          |          |          |           |           |           |            |            |            |            |            |
| <b>Steel failure without lever arm</b>         |                    |           |          |          |          |          |           |           |           |            |            |            |            |            |
| Characteristic resistance $V_{Rk,s}^0$         | Steel, zinc plated | [kN]      | 8,0      | 9,5      | 15       | 18       | 34        |           |           | 26         | 63         | 54         |            |            |
|  | A4, HCR            | [kN]      | 5,5      | 9,5      | 10       | 16       | 24        |           |           | 32         | 44         | 47         |            |            |
| Partial factor                                 | $\gamma_{Ms}$      | [-]       | 1,25     |          |          |          |           |           |           |            |            |            |            |            |
| Ductility factor                               | $k_7$              | [-]       | 1,0      |          |          |          |           |           |           |            |            |            |            |            |
| <b>Steel failure with lever arm</b>            |                    |           |          |          |          |          |           |           |           |            |            |            |            |            |
| Characteristic bending resistance $M_{Rk,s}^0$ | Steel, zinc plated | [kN]      | 12       | 30       | 60       | 105      |           |           | 212       | 266        | 519        |            |            |            |
|  | A4, HCR            | [kN]      | 8,5      | 21       | 42       | 74       |           |           | 187       | 187        | 365        |            |            |            |
| Partial factor                                 | $\gamma_{Ms}$      | [-]       | 1,25     |          |          |          |           |           |           |            |            |            |            |            |
| <b>Concrete pry-out failure</b>                |                    |           |          |          |          |          |           |           |           |            |            |            |            |            |
| Pry-out factor                                 | $k_8$              | [-]       | 2,0      |          |          |          |           |           |           |            |            |            |            |            |
| <b>Concrete edge failure</b>                   |                    |           |          |          |          |          |           |           |           |            |            |            |            |            |
| Effective length of fastener in shear load     | $l_f$              | [mm]      | 40       | 50       | 60       | 75       | 70        | 80        | 90        | 105        | 125        | 115        | 170        | 170        |
| Outside diameter of fastener                   | $d_{nom}$          | [mm]      | 10       |          | 12       |          | 14        |           | 18        |            |            | 22         | 24         | 26         |

**Table C14: Displacements under tension loads, HB-VMZ-IG**

| Fastener size                             |                    | HB-VMZ-IG | 40<br>M6 | 50<br>M6 | 60<br>M8 | 75<br>M8 | 70<br>M10 | 80<br>M10 | 90<br>M12 | 105<br>M12 | 125<br>M12 | 115<br>M16 | 170<br>M16 | 170<br>M20 |     |
|---|--------------------|-----------|----------|----------|----------|----------|-----------|-----------|-----------|------------|------------|------------|------------|------------|-----|
| Tension load in <b>cracked</b> concrete   | N                  | [kN]      | 4,3      | 6,1      | 8,0      | 11,1     | 10,0      | 12,3      | 14,6      | 18,4       | 24,0       | 21,1       | 38,0       | 38,0       |     |
| Displacement                              | $\delta_{N0}$      | [mm]      | 0,5      |          | 0,5      | 0,6      | 0,6       |           |           | 0,7        |            |            | 0,7        | 0,8        | 0,8 |
|   | $\delta_{N\infty}$ | [mm]      | 1,3      |          |          |          |           |           |           |            |            |            |            |            |     |
| Tension load in <b>uncracked</b> concrete | N                  | [kN]      | 4,3      | 8,5      | 11,1     | 15,6     | 14,1      | 17,2      | 20,5      | 25,9       | 33,0       | 29,6       | 53,3       | 53,3       |     |
| Displacement                              | $\delta_{N0}$      | [mm]      | 0,2      | 0,4      | 0,4      |          | 0,4       |           |           | 0,6        |            |            | 0,5        | 0,6        | 0,6 |
|   | $\delta_{N\infty}$ | [mm]      | 1,3      |          |          |          |           |           |           |            |            |            |            |            |     |

**Table C15: Displacements under shear loads, HB-VMZ-IG**

| Fastener size                              |                    | HB-VMZ-IG | 40<br>M6 | 50<br>M6 | 60<br>M8 | 75<br>M8 | 70<br>M10 | 80<br>M10 | 90<br>M12 | 105<br>M12 | 125<br>M12 | 115<br>M16 | 170<br>M16 | 170<br>M20 |      |
|--|--------------------|-----------|----------|----------|----------|----------|-----------|-----------|-----------|------------|------------|------------|------------|------------|------|
| Shear load <b>Steel, zinc plated</b>       | V                  | [kN]      | 4,6      |          | 5,4      | 8,4      | 10,1      |           |           | 19,3       |            |            | 14,8       | 35,8       | 30,7 |
| Displacement                               | $\delta_{V0}$      | [mm]      | 0,4      |          | 0,5      | 0,4      | 0,5       |           |           | 1,2        |            |            | 0,8        | 1,9        | 1,2  |
|  | $\delta_{V\infty}$ | [mm]      | 0,7      |          | 0,8      | 0,7      | 0,8       |           |           | 1,9        |            |            | 1,2        | 2,8        | 1,9  |
| Shear load <b>Stainless steel A4 / HCR</b> | V                  | [kN]      | 3,2      |          | 5,4      | 5,9      | 9,3       |           |           | 13,5       |            |            | 18,5       | 25,2       | 26,9 |
| Displacement                               | $\delta_{V0}$      | [mm]      | 0,3      |          | 0,5      | 0,3      | 0,5       |           |           | 0,9        |            |            | 1,0        | 1,4        | 1,1  |
|  | $\delta_{V\infty}$ | [mm]      | 0,4      |          | 0,7      | 0,5      | 0,7       |           |           | 1,4        |            |            | 1,5        | 2,1        | 1,6  |

**Injection System HB-VMZ**

**Performance**  
Characteristic values for **shear load HB-VMZ-IG, Displacements HB-VMZ-IG**

**Annex C11**