

Approval body for construction products  
and types of construction

Bautechnisches Prüfamt

An institution established by the Federal and  
Laender Governments



## European Technical Assessment

**ETA-09/0338**  
**of 20 September 2022**

English translation prepared by DIBt - Original version in German language

### General Part

Technical Assessment Body issuing the  
European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

JORDAHL anchor channel JTA, JZA and JXA

Product family  
to which the construction product belongs

Anchor channels

Manufacturer

PohlCon GmbH  
Nobelstraße 51  
12057 Berlin  
DEUTSCHLAND

Manufacturing plant

14959 Trebbin, Industriestr. 5

This European Technical Assessment  
contains

53 pages including 3 annexes which form an integral part  
of this assessment

This European Technical Assessment is  
issued in accordance with Regulation (EU)  
No 305/2011, on the basis of

EAD 330008-03-0601-V01, Edition 06/2022

This version replaces

ETA-09/0338 issued on 28 June 2021

**European Technical Assessment**

**ETA-09/0338**

English translation prepared by DIBt

**Page 2 of 53 | 20 September 2022**

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

## Specific Part

### 1 Technical description of the product

The JORDAHL anchor channel JTA, JZA and JXA is system consisting of C-shaped channel profile steel and stainless steel and at least two metal anchors non-detachably fixed on the channel back and channel bolts.

The anchor channel is embedded surface-flush in the concrete. Channel bolts JORDAHL T-bolts with appropriate hexagon nuts and washers are fixed to the channel.

The product description is given in Annex A.

### 2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor channel is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor channel of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

### 3 Performance of the product and references to the methods used for its assessment

#### 3.1 Mechanical resistance and stability (BWR 1)

Essential characteristic	Performance
Characteristic resistance under tension load (static and quasi-static loading)	
- Resistance to steel failure of anchors	$N_{Rk,s,a}$ see Annex C1 to C3
- Resistance to steel failure of the connection between anchors and channel	$N_{Rk,s,c}$ see Annex C1 to C3
- Resistance to steel failure of channel lips and subsequently pull-out of channel bolt	$N_{Rk,s,l}^0$ ; $s_{l,N}$ see Annex C1 to C3
- Resistance to steel failure of channel bolt	$N_{Rk,s}$ see Annex C6
- Resistance to steel failure by exceeding the bending strength of the channel	$s_{max}$ see Annex A10 and A11 $M_{Rk,s,flex}$ see Annex C4 and C5
- Maximum installation torque to avoid damage during installation	$T_{inst,g}$ ; $T_{inst,s}$ see Annex B5 and B6
- Resistance to pull-out failure of the anchor	$N_{Rk,p}$ see Annex C7 to C9
- Resistance to concrete cone failure	$h_{ef}$ see Annex B3 and B4 $k_{cr,N}$ ; $k_{ucr,N}$ see Annex C7 to C9
- Minimum edge distances, spacing and member thickness to avoid concrete splitting during installation	$s_{min}$ see Annex A10 and A11 $c_{min}$ ; $h_{min}$ see Annex B3 and B4
- Characteristic edge distance and spacing to avoid splitting of concrete under load	$s_{cr,sp}$ ; $c_{cr,sp}$ see Annex C7 to C9
- Resistance to blowout failure - bearing area of anchor head	$A_h$ see Annex A7 and A8

Essential characteristic	Performance
<p>Characteristic resistance under shear load (static and quasi-static loading)</p> <ul style="list-style-type: none"> <li>- Resistance to steel failure of channel bolt under shear loading without lever arm</li> <li>- Resistance to steel failure by bending of the channel bolt under shear load with lever arm</li> <li>- Resistance to steel failure of channel lips, steel failure of connection between anchor and channel and steel failure of anchor (shear load in transverse direction)</li> <li>- Resistance to steel failure of connection between channel lips and channel bolt (shear load in longitudinal channel axis)</li> <li>- Factor for sensitivity to installation (longitudinal shear)</li> <li>- Resistance to steel failure of the anchor (longitudinal shear)</li> <li>- Resistance to steel failure of connection between anchor and channel (longitudinal shear)</li> <li>- Resistance to concrete pry-out failure</li> <li>- Resistance to concrete edge failure</li> </ul>	<p><math>V_{Rk,s}</math> see Annex C16 and C17</p> <p><math>M_{Rk,s}^0</math> see Annex C16 and C17</p> <p><math>V_{Rk,s,l,y}^0 ; S_{l,V} ; V_{Rk,s,c,y} ; V_{Rk,s,a,y}</math> see Annex C11 to C13</p> <p><math>V_{Rk,s,l,x}</math> see Annex C11 and C13</p> <p><math>\gamma_{inst}</math> see Annex C11 and C13</p> <p><math>V_{Rk,s,a,x}</math> see Annex C11 and C13</p> <p><math>V_{Rk,s,c,x}</math> see Annex C11 and C13</p> <p><math>k_8</math> see Annex C14 and C15</p> <p><math>k_{cr,V} ; k_{ucr,V}</math> see Annex C14 and C15</p>
<p>Characteristic resistance under combined tension and shear load (static and quasi-static load)</p> <ul style="list-style-type: none"> <li>- Resistance to steel failure of the anchor channel</li> </ul>	<p><math>k_{13} ; k_{14}</math> see Annex C19</p>
<p>Characteristic resistance under fatigue tension loading</p> <ul style="list-style-type: none"> <li>- Fatigue resistance to steel failure of the whole system (continuous or tri-linear function, test method A1, A2)</li> <li>- Fatigue limit resistance to steel failure of the whole system (test method B)</li> <li>- Fatigue resistance to steel failure of the whole system (linearized function, test method C)</li> <li>- Fatigue resistance to concrete related failure (exponential function, test method A1, A2)</li> <li>- Fatigue limit resistance to concrete related failure (test method B)</li> <li>- Fatigue resistance to concrete related failure (linearized function, test method C)</li> </ul>	<p><math>\Delta N_{Rk,s,0,n}</math> (<math>n = 1</math> to <math>n = \infty</math>) see Annex C23</p> <p><math>\Delta N_{Rk,s,0,\infty}</math> see Annex C23</p> <p><math>\Delta N_{Rk,s,lo,n} ; N_{lok,s,n}</math> (<math>n = 10^4</math> to <math>n = \infty</math>) see Annex C24</p> <p><math>\Delta N_{Rk,c,0,n} ; \Delta N_{Rk,p,0,n}</math> (<math>n = 1</math> to <math>n = \infty</math>) see Annex C23</p> <p><math>\Delta N_{Rk,c,0,\infty} ; \Delta N_{Rk,p,0,\infty}</math> see Annex C23</p> <p><math>\Delta N_{Rk,c,E,n} ; \Delta N_{Rk,p,E,n}</math> (<math>n = 10^4</math> to <math>n = \infty</math>) see Annex C25</p>

Essential characteristic	Performance
Displacements (static and quasi-static load)	$\delta_{N0}$ ; $\delta_{N\infty}$ see Annex C10 $\delta_{V,y,0}$ ; $\delta_{V,y,\infty}$ ; $\delta_{V,x,0}$ ; $\delta_{V,x,\infty}$ see Annex C18

### 3.2 Safety in case of fire (BWR 2)

Essential characteristic	Performance
Reaction to fire	Class A1
Resistance to fire	See Annex C20 to C22

### 3.3 Other essential characteristics

Essential characteristic	Performance
Durability	See Annex B1

## 4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with EAD No. 330008-03-0601-V01, the applicable European legal act is: [2000/273/EC].

The system to be applied is: 1


## 5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable EAD

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited with Deutsches Institut für Bautechnik.

Issued in Berlin on 20 September 2022 by Deutsches Institut für Bautechnik

Dipl.-Ing. Beatrix Wittstock  
Head of Section

*beglaubigt:*  
Müller

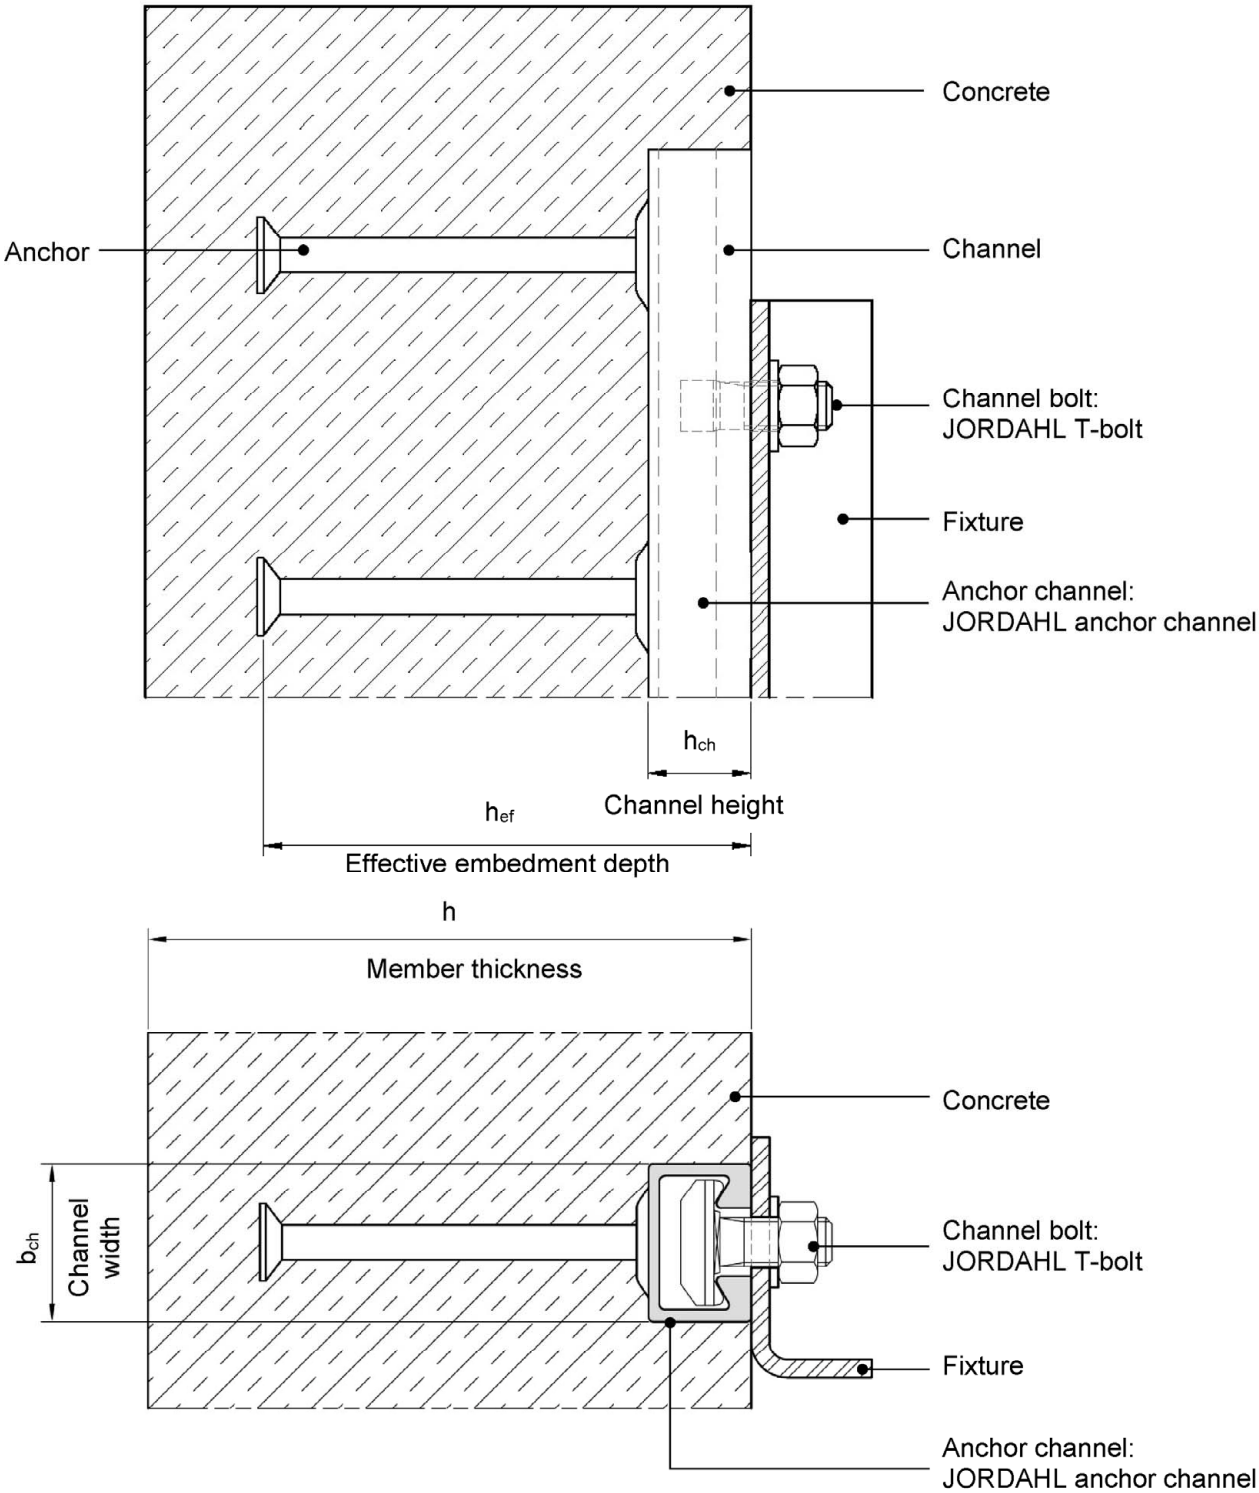

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Installed condition

**Annex A1**

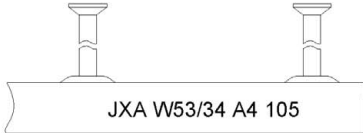
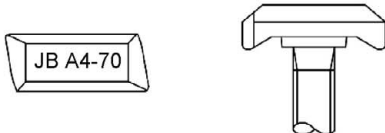
Anchor channels JTA with W profile		Anchor channels JXA with K profile		Anchor channels JXA with serrated W profile		Anchor channel JZA with serrated K profile	
<p><b>Anchor</b> also possible as welded anchor (I-anchor, T-anchor and round anchor)</p> <p>e.g. JTA W 53/34</p> <p><b>Channel</b></p> <p><b>Channel bolt</b> e.g. JB M16x60</p> <p><b>Washer</b></p> <p><b>Hex nut</b></p>							
<div><div><p><b>Example of marking of the JORDAHL anchor channels JTA and JXA: e.g. JXA W53/34 A4</b></p><p></p><p>J or JORDAHL = Identifying mark of the manufacturer JXA W = Anchor channel type 53/34 = Size A4 = Material 105 = Embedment depth if <math>h_{ef} &gt; h_{ef,min}</math></p><p><b>Material channels:</b> <u>Carbon steel</u> No marking = Hot-dip galvanized</p><p><u>Stainless steel</u> A2 = CRC II <sup>1)</sup> A4, L4 = CRC III <sup>1)</sup> F4, FA = CRC III <sup>1)</sup> HCR = CRC IV, V <sup>1)</sup></p><p><sup>1)</sup> Corrosion resistance class</p><p>Close to the anchors a nail hole is positioned</p></div><div><p><b>Example of marking of the JORDAHL T-bolt: e.g. JB A4-70</b></p><p></p><p>J or JORDAHL = Identifying mark of the manufacturer JB = Channel bolt type A4 = Material 70 = Strength grade</p><p><b>Material bolts:</b> <u>Carbon steel</u> No marking = Hot-dip galvanized G = Electroplated</p><p><u>Stainless steel</u> A2 = CRCII <sup>1)</sup> A4, L4 = CRCIII <sup>1)</sup> F4, FA = CRC III <sup>1)</sup> HCR = CRC IV, V <sup>1)</sup></p><p><b>Strength grade bolts:</b> <u>Carbon steel</u> 4.6, 8.8 = Strength grade 4.6, 8.8 <u>Stainless steel</u> 50, 70 = Strength grade 50, 70</p></div></div>							
JORDAHL anchor channel JTA, JZA and JXA						Annex A2	
Product description Marking and materials							

Table A1: Materials and intended use

Item no.	Specification	Intended use	
		1	2
		Anchor channels may only be used in structures subject to dry internal conditions	Anchor channels may also be used in structures subject to internal conditions with usual humidity
		Materials	
1	Channel profile	Carbon steel hot-dip galvanized $\geq 55 \mu\text{m}$ <sup>4)</sup>	Carbon steel hot-dip galvanized $\geq 55 \mu\text{m}$ <sup>4)</sup>
			Stainless steel <sup>5)</sup> CRC II
2	Anchor	Carbon steel hot-dip galvanized $\geq 55 \mu\text{m}$ <sup>4)</sup>	Carbon steel hot-dip galvanized $\geq 55 \mu\text{m}$ <sup>4)</sup>
			Stainless steel <sup>5)</sup> CRC II
3	Channel bolt	Carbon steel strength grade 4.6, 8.8 <sup>6)</sup> electroplated $\geq 5 \mu\text{m}$ <sup>2)</sup>	Carbon steel strength grade 4.6, 8.8 <sup>6)</sup> hot-dip galvanized $\geq 50 \mu\text{m}$ <sup>3)</sup>
			Stainless steel <sup>5)</sup> CRC II strength grade 50, 70 <sup>9)</sup>
4	Washer	Carbon steel product class A <sup>7)</sup> hardness class 200 HV <sup>7)</sup> electroplated $\geq 5 \mu\text{m}$ <sup>2)</sup>	Carbon steel hot-dip galvanized $\geq 50 \mu\text{m}$ <sup>3)</sup>
			Stainless steel <sup>5)</sup> steel type A2, A3, A4 <sup>9)</sup>
5	Hexagonal nut	Carbon steel strength grade 5, 8 <sup>8)</sup> electroplated $\geq 5 \mu\text{m}$ <sup>2)</sup>	Carbon steel strength grade 5, 8 <sup>8)</sup> hot-dip galvanized $\geq 50 \mu\text{m}$ <sup>3)</sup>
			Stainless steel <sup>5)</sup> steel type A2, A3, A4 <sup>9)</sup> strength grade 70, 80 <sup>9)</sup>

<sup>1)</sup> Carbon steel only for welded anchors, with sufficient concrete cover according to EN 1992-1-1:2004 + AC:2010

<sup>2)</sup> Electroplated according to EN ISO 4042:2018

<sup>3)</sup> Hot-dip galvanized according to EN ISO 10684:2004 + AC:2009

<sup>4)</sup> Hot-dip galvanized on the basis of EN ISO 1461:2009, but coating thickness  $\geq 55 \mu\text{m}$

<sup>5)</sup> Stainless steel anchors only in combination with stainless steel channels, bolts, washers and nuts

<sup>6)</sup> According to EN ISO 898-1:2013

<sup>7)</sup> According to EN ISO 7089:2000 and EN ISO 7093-1:2000, not included in delivery

<sup>8)</sup> According to EN ISO 4032:2012

<sup>9)</sup> According to EN ISO 3506-1:2020

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Materials and intended use

**Annex A3**



Table A1 (continuation): Materials and intended use

Item no.	Specification	Intended use		
		3	4	5
		For CRC III according to EN 1993-1-4:2006	Für CRC IV gemäß EN 1993-1-4:2006	Für CRC V gemäß EN 1993-1-4:2006
		Materials		
1	Channel profile	Stainless steel CRC III	Stainless steel CRC IV	Stainless steel CRC V
2	Anchor	Stainless steel CRC III	Stainless steel CRC IV	Stainless steel CRC V
		Carbon steel <sup>1)</sup>	Carbon steel <sup>1)</sup>	
3	Channel bolt	Stainless steel CRC III strength grade 50, 70 <sup>9)</sup>	Stainless steel CRC IV strength grade 50, 70 <sup>9)</sup>	Stainless steel CRC V strength grade 50, 70 <sup>9)</sup>
4	Washer	Stainless steel CRC III steel type A4 <sup>9)</sup>	Stainless steel CRC IV steel type A5 <sup>9)</sup>	Stainless steel CRC V steel type A8 <sup>9)</sup>
5	Hexagonal nut	Stainless steel CRC III steel type A4 <sup>9)</sup> strength grade 70, 80 <sup>6)</sup>	Stainless steel CRC IV steel type A5 <sup>9)</sup> strength grade 70, 80 <sup>6)</sup>	Stainless steel CRC V steel type A8 <sup>9)</sup> strength grade 70, 80 <sup>6)</sup>

<sup>1)</sup> Carbon steel only for welded anchors, with sufficient concrete cover according to EN 1992-1-1:2004 + AC:2010

<sup>2)</sup> Electroplated according to EN ISO 4042:2018

<sup>3)</sup> Hot-dip galvanized according to EN ISO 10684:2004 + AC:2009

<sup>4)</sup> Hot-dip galvanized on the basis of EN ISO 1461:2009, but coating thickness  $\geq 55 \mu\text{m}$

<sup>5)</sup> Stainless steel anchors only in combination with stainless steel channels, bolts, washers and nuts

<sup>6)</sup> According to EN ISO 898-1:2013

<sup>7)</sup> According to EN ISO 7089:2000 and EN ISO 7093-1:2000, not included in delivery

<sup>8)</sup> According to EN ISO 4032:2012

<sup>9)</sup> According to EN ISO 3506-1:2020

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Materials and intended use

**Annex A4**

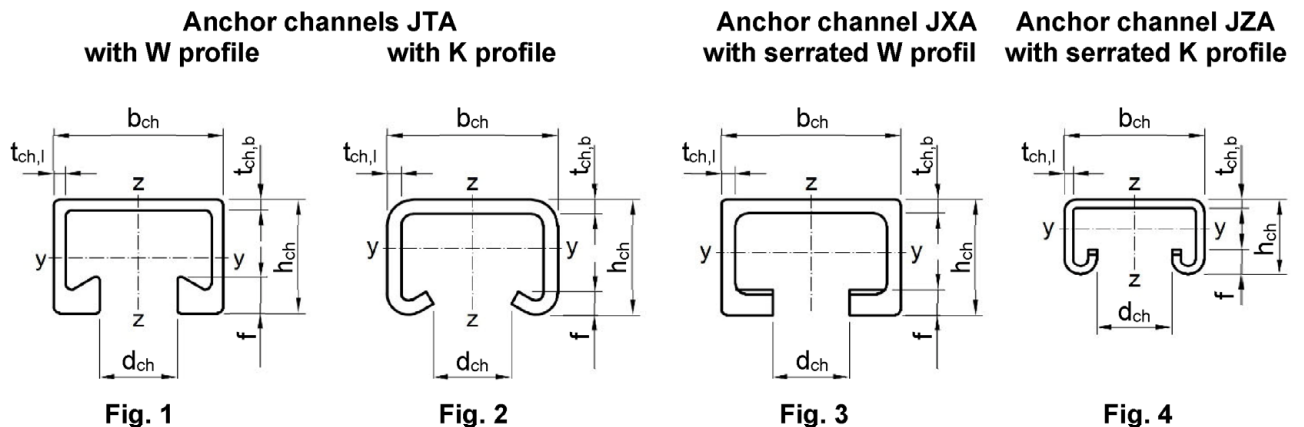


Table A2: Dimensions of profile – carbon steel

Anchor channel		Fig.	Material	Dimension [mm]						[mm <sup>4</sup> ]
				b <sub>ch</sub>	h <sub>ch</sub>	t <sub>ch,b</sub>	t <sub>ch,l</sub>	d <sub>ch</sub>	f	
JTA	W40/22	1	Carbon steel	39,50	23,00	2,60	2,40	18,00	6,00	20.029
	W40+	1		49,00	30,00	3,20	2,75	22,50	7,85	52.896
	W50/30	1		52,50	33,50	4,10	4,00	22,50	10,50	93.262
	W50+	1		54,50	42,00	5,00	5,00	26,00	12,90	187.464
	W53/34	1		72,00	48,50	4,50	5,00	33,00	15,50	349.721
	W55/42	1		28,00	15,25	2,25	2,25	12,00	2,25	4.060
	K28/15	2		38,00	17,50	3,00	3,00	18,00	3,00	8.547
	K38/17	2		40,00	25,00	2,75	2,75	18,00	5,60	20.570
	K40/25	2		50,00	30,00	3,00	3,00	22,00	7,39	41.827
	K50/30	2		53,50	33,00	4,50	4,50	22,00	7,90	72.079
JXA	K53/34	2		72,00	49,00	6,00	6,00	33,00	9,90	293.579
	K72/48	2		41,00	22,50	2,50	2,50	22,0	8,00	15.000
	JZA K41/22	4		29,00	20,00	2,50	3,50	14,00	5,00	10.200
	W29/20	3		38,00	23,00	3,50	3,00	18,00	5,50	20.953
JZA	W38/23	3		52,50	34,00	4,00	4,00	22,50	7,50	92.910
	W53/34	3		64,00	44,00	4,50	5,00	26,00	10,00	241.800
JXA	W64/44	3								

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Types of channels – carbon steel

**Annex A5**

Table A3: Dimensions of profile – stainless steel

Anchor channel		Fig. <sup>1)</sup>	Material	Dimension [mm]						[mm <sup>4</sup> ]
				b <sub>ch</sub>	h <sub>ch</sub>	t <sub>ch,b</sub>	t <sub>ch,l</sub>	d <sub>ch</sub>	f	
JTA	W40/22 W40+	1	Stainless steel	39,50	23,00	2,60	2,40	18,00	6,00	20.029
	W50/30 W50+	1		49,00	30,00	3,20	2,75	22,50	7,85	52.896
	W53/34	1		52,50	33,50	4,10	4,00	22,50	10,50	93.262
	W55/42 <sup>2)</sup>	1		–	–	–	–	–	–	–
	W72/48	1		72,00	48,50	4,50	5,00	33,00	15,50	349.721
	K28/15	2		28,00	15,25	2,25	2,25	12,00	2,25	4.060
	K38/17	2		38,00	17,50	3,00	3,00	18,00	3,00	8.547
	K40/25	2		39,50	25,00	2,50	2,50	18,00	5,40	19.097
	K50/30	2		50,00	30,00	3,00	3,00	22,00	7,39	41.827
	K53/34	2		53,50	33,00	4,50	4,50	22,00	7,90	72.079
	K72/48	2		72,00	49,00	6,00	6,00	33,00	9,90	293.579
JZA	K41/22	4		41,00	22,50	2,5	2,50	22,00	6,50	15.000
JXA	W29/20 <sup>2)</sup>	3		–	–	–	–	–	–	–
	W38/23	3		38,00	23,00	3,50	3,00	18,00	5,50	20.953
	W53/34	3		52,50	34,00	4,00	4,00	22,50	7,50	92.910
	W64/44 <sup>2)</sup>	3		–	–	–	–	–	–	–

<sup>1)</sup> Fig. according to Annex A5


<sup>2)</sup> Product not available

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Types of channels – stainless steel

**Annex A6**

Round anchor

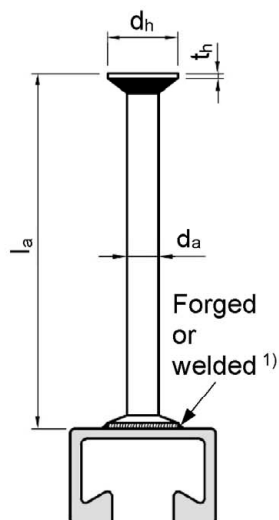

<sup>1)</sup> Only anchor channel JTA: welded anchors


Table A4: Dimensions of round anchors

Anchor channel		Type	d <sub>a</sub> [mm]	d <sub>h</sub> [mm]	t <sub>h</sub> [mm]	A <sub>h</sub> [mm <sup>2</sup> ]	l <sub>a,min</sub> [mm]	Material	
								Carbon steel	Stainless steel
JTA	K28/15	R	7,0	12,0	2,0	75	31,8	✓	✓
	W40/22, K40/25		8,5	15,0	2,0	120	56,0	✓	✓
	W40+						70,0	–	✓
	K38/17		9,0	17,0	3,0	163	61,5	✓	✓
	W40/22, K40/25						57,0	✓	✓
	W50/30, K50/30		9,0	17,5	3,0	176	67,0	✓	✓
	W50+		10,0	19,5	3,0	220	79,0	✓	✓
	W40+		10,8	19,0	3,0	191	71,0	✓	–
	W50/30, K50/30						67,0	✓	–
	W53/34, K53/34		11,5	23,5	3,0	330	124,5	✓	✓
	W55/42		15,5	28,0	3,5	427	136,5	✓	–
	W72/48, K72/48		15,5	31,0	3,5	566	133,5	✓	✓
JZA	K41/22	R	9,0	17,0	3,0	163	55,5	✓	✓
JXA	W29/20		9,0	17,0	3,0	163	61,0	✓	–
	W38/23		10,0	19,5	3,0	220	75,0	✓	✓
	W53/34		11,5	23,5	3,0	330	124,5	✓	✓

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Types of anchors – round anchors

**Annex A7**

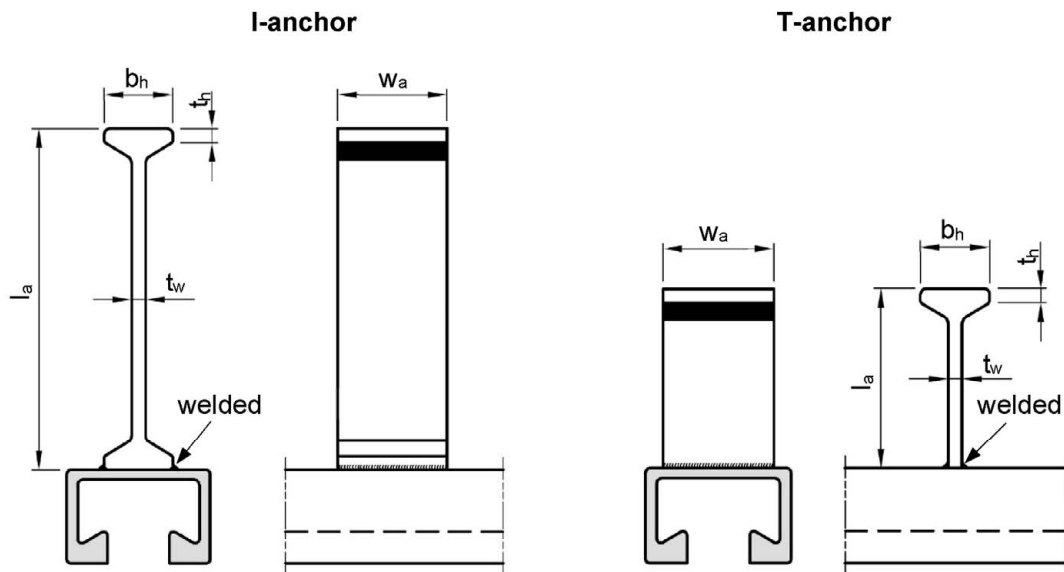

Available configurations (anchor type, orientation of anchor and welding): refer to Annex A9, A10 and A11

Table A5: Dimensions of I-anchors and T-anchors

Anchor channel		Type	w <sub>a</sub> [mm]	b <sub>h</sub> [mm]	t <sub>w</sub> [mm]	t <sub>h</sub> [mm]	A <sub>h</sub> [mm <sup>2</sup> ]	l <sub>a,min</sub> [mm]	Material	
									Carbon steel	Stainless steel
JTA	K28/15, K38/17	I 60	10	18,0	5,0	3,3	130	62	✓	✓
	K40/25		12				234	62	✓	✓
	W40/22		20				260	62	✓	✓
	W40/22	T 60	20				260	38	✓	✓
	K50/30	I 69	18	18,0	5,0	3,5	234	69	✓	✓
	W50/30		25				325	69	✓	✓
	W50/30	T 69	25				325	45	✓	✓
	W40+	I 128	25	17,0	6,0	5,0	275	128	✓	–
	W50+		30				330	128	✓	–
	K53/34		26				286	128	✓	–
	W53/34		40				440	128	✓	–
	W53/34	T 128	40				440	48	✓	–
	W55/42	I 140	45	20,0	7,1	6,0	581	140	✓	–
	W72/48, K72/48		40				516	140	✓	–
	W55/42	T 140	45				581	48	✓	–
JXA	W38/23	I 128	20	17,0	6,0	5,0	220	128	✓	–
	W53/34		40				440	128	✓	–
	W38/23	T 128	20				220	36	✓	–
	W53/34		40				440	47	✓	–
	W64/44	I 140	45	20,0	7,1	5,0	581	140	✓	–

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Types of anchors – I-anchors and T-anchors

**Annex A8**

Table A6: Overview – anchor and channel bolt types

Anchor channel		Anchor type					Channel bolt type		
		Round anchor	I-anchor		T-anchor		Smooth channel bolt	Double notching bolt	Serrated bolt
			Anchor position	Weld seam position	Anchor position	Weld seam position			
JTA	W40/22	✓	transversal/ longitudinal	transversal/ longitudinal	transversal	transversal	✓	✓	–
	W40+	✓	transversal/ longitudinal	transversal/ longitudinal	–	–	✓	✓	–
	W50/30	✓	transversal/ longitudinal	transversal/ longitudinal	transversal	transversal	✓	✓	–
	W50+	✓	transversal/ longitudinal	transversal/ longitudinal	–	–	✓	✓	–
	W53/34	✓	transversal/ longitudinal	transversal/ longitudinal	transversal	transversal	✓	✓	–
	W55/42	✓	transversal/ longitudinal	transversal/ longitudinal	transversal	transversal	✓	–	–
	W72/48	✓	transversal/ longitudinal	transversal/ longitudinal	–	–	✓	–	–
	K28/15	✓	transversal/ longitudinal	transversal/ longitudinal	–	–	✓	–	–
	K38/17	✓	transversal/ longitudinal	transversal/ longitudinal	–	–	✓	–	–
	K40/25	✓	transversal/ longitudinal	transversal/ longitudinal	–	–	✓	–	–
	K50/30	✓	transversal/ longitudinal	transversal/ longitudinal	–	–	✓	–	–
	K53/34	✓	transversal/ longitudinal	transversal/ longitudinal	–	–	✓	–	–
	K72/48	✓	transversal/ longitudinal	transversal/ longitudinal	–	–	✓	–	–
JZA	K41/22	✓	–	–	–	–	–	–	✓
JXA	W29/20	✓	–	–	–	–	–	–	✓
	W38/23	✓	transversal	transversal	transversal	transversal	–	–	✓
	W53/34	✓	transversal	transversal	transversal	transversal	–	–	✓
	W64/44	–	transversal	longitudinal	–	–	–	–	✓

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Overview – anchor and channel bolt types

**Annex A9**

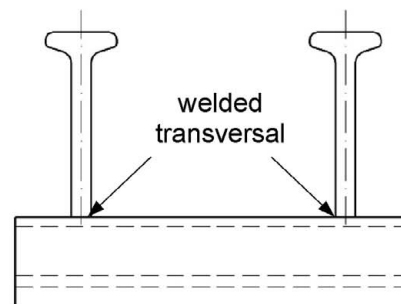
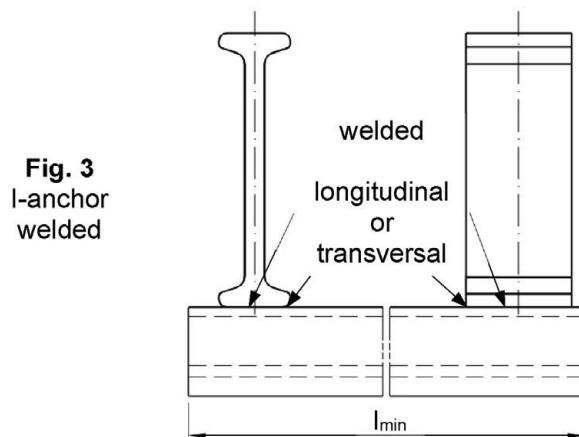
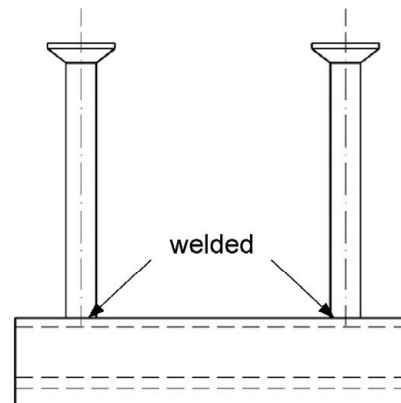
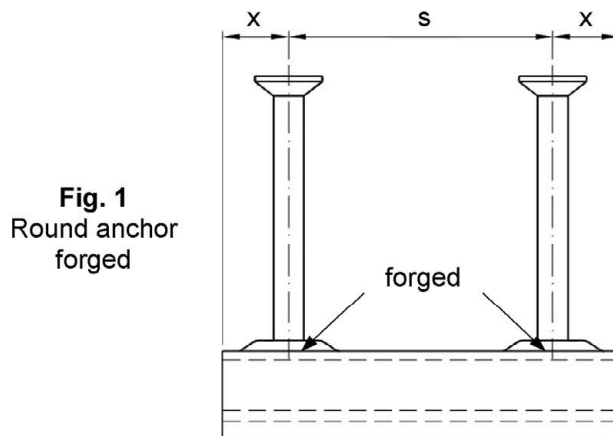


Table A7: Anchor positioning (JTA W and JTA K)

Anchor channel		Anchor spacing		End spacing	Min. channel length	Configuration according to Fig.
		$s_{min}$	$s_{max}$	$x$	$l_{min}$	
		[mm]		[mm]	[mm]	
JTA	K28/15 K38/17	50	200	25	100	1, 2, 3
	K40/25 K50/30 W40+ W50+	50	250	25 <sup>1)</sup>	100	1, 2, 3
	W40/22 W50/30	50	250	25 <sup>1)</sup>	100	1, 2, 3, 4
	K53/34	80	250	35	150	1, 2, 3 <sup>2)</sup>
	W53/34	80	250	35	150	1, 2, 3 <sup>2)</sup> , 4 <sup>2)</sup>
	W55/42	80	300	35	150	1, 2, 3 <sup>2)</sup> , 4 <sup>2)</sup>
	K72/48 W72/48	80	400	35	150	1, 2, 3 <sup>2)</sup>

<sup>1)</sup> End spacing may be increased to 35 mm


<sup>2)</sup> Only carbon steel anchor available

JORDAHL anchor channel JTA, JZA and JXA


**Product description**  
Anchor positioning and channel length (JTA)

**Annex A10**


**Fig. 1**  
Round anchor  
forged

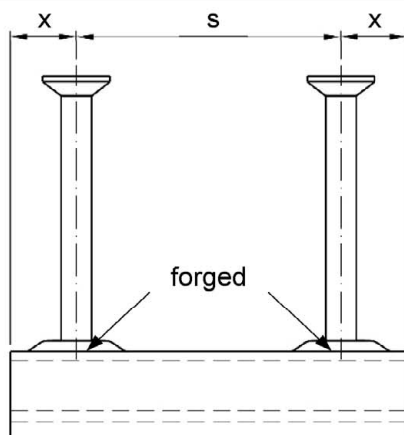

**Fig. 2**  
I-anchor  
welded

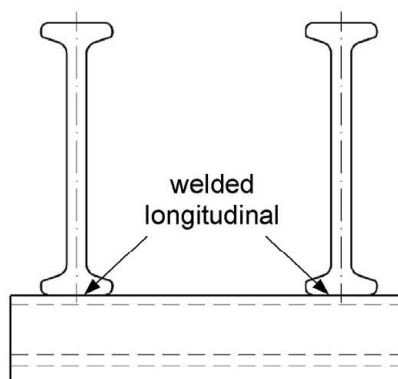

**Fig. 3**  
I-anchor  
welded

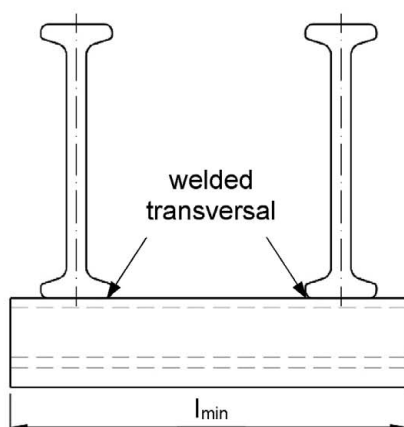

**Fig. 4**  
T-anchor  
welded

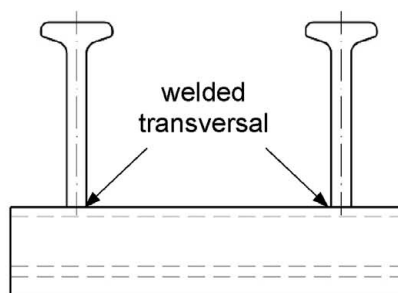


Table A8: Anchor positioning (JZA and JXA)

Anchor channel		Anchor spacing		End spacing	Min. channel length	Configuration according to Fig.
		$s_{min}$	$s_{max}$	$x$	$l_{min}$	
		[mm]		[mm]	[mm]	
JZA	K41/22	50	250	25	100	1
JXA	W29/22	50	200	25	100	1
	W38/23	50	250	25	100	1, 3 <sup>1)</sup> , 4 <sup>1)</sup>
	W53/34	80	250	35	150	1, 3 <sup>1)</sup> , 4 <sup>1)</sup>
	W64/44	80	250	35	150	2

<sup>1)</sup> Only carbon steel anchor available

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Anchor positioning and channel length (JZA, JXA)

**Annex A11**



Table A9: Dimensions of channel bolts for JTA anchor channels

Anchor channel	Fig.	Channel bolt	Dimension [mm]			
			b <sub>cbo,1</sub>	b <sub>cbo,2</sub>	t <sub>cbo</sub>	d
JTA	1	JD	11,2	22,4	4,5	6
					4,5	8
					5,0	10
					6,5	12
	1	JH	16,5	30,5	6,0	10
					7,0	12
					8,0	16
	2	JC	14,0	32,0	8,0	10
					8,0	12
			17,0		11,0	16
	3	JKC	16,8	32,7	8,0	12
					8,0	16
	2	JB	17,0	41,5	9,0	10
			17,5		10,0	12
			20,5		13,0	16
	3	JKB	17,0	41,5	12,0	16
			20,5		13,5	20
	2	JB	24,5	41,5	18,5	24
K72/48 W72/48	2	JA	25,0	58,0	14,0	20
			25,0		20,0	24
			28,0		20,0	27
			31,0		20,0	30

Channel bolts  
JD, JH


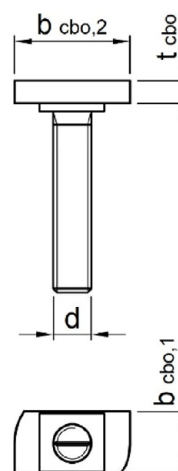


Fig. 1

Channel bolts  
JA, JB, JC

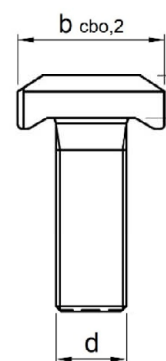

Double notching  
channel bolts  
JKB, JKC

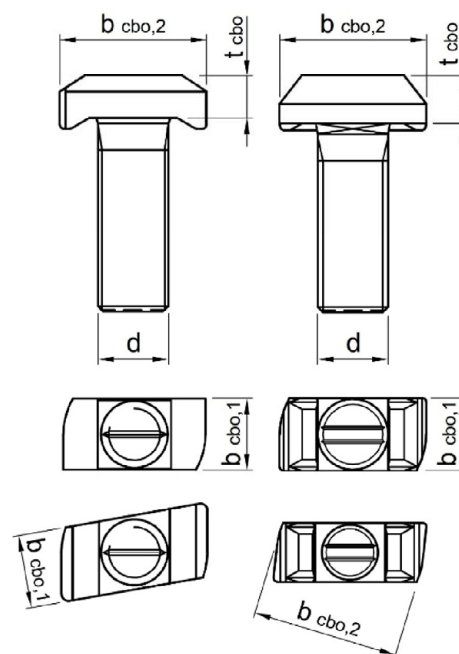


Fig. 2

Fig. 3

Grooves for marking the position

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Types of channel bolts – geometry

**Annex A12**

Table A10: Dimensions of channel bolts for JZA and JXA anchor channels

Anchor channel		Fig.	Channel bolt	Dimension [mm]			
				b <sub>cbo,1</sub>	b <sub>cbo,2</sub>	t <sub>cbo</sub>	d
JZA	K41/22	2	JZS	19,5	34,5	9,0	12
						9,0 <sup>1)</sup>	16
JXA	W29/20	1	JXD	13,5	22,0	6,5	10
						6,5	12
	W38/23	1	JXH	17,2	28,9	8,0	12
						8,0	16
	W53/34	1	JXB	21,0	41,6	11,5	16
						13,0	20
	W64/44	1	JXE	24,7	51,0	14,0	20
						16,0	24

<sup>1)</sup> Value for carbon steel; stainless steel 7,0

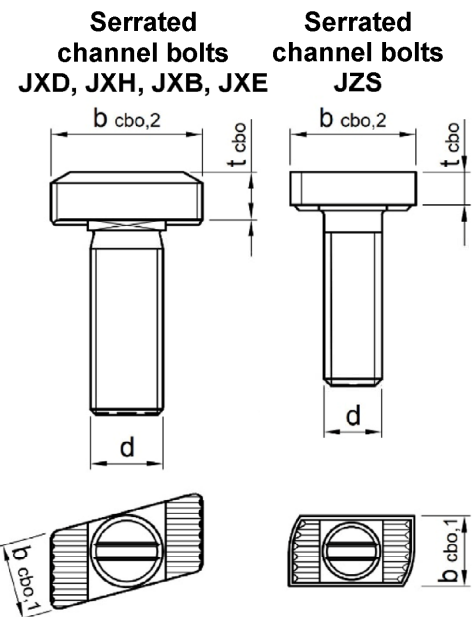


Fig. 1

Fig. 2

Grooves for marking the position

Table A11: Strength grades of channel bolts

Channel bolt		Carbon steel <sup>1)</sup>		Stainless steel <sup>1)</sup>	
Strength grade <sup>2)</sup>		4.6	8.8	50	70
f <sub>uk</sub>	[N/mm <sup>2</sup> ]	400	800	500	700
f <sub>yk</sub>		240	640	210	450
Surface		electroplated, hot-dip galvanized		—	

<sup>1)</sup> Materials according to Annex A3 to A4, Table A1

<sup>2)</sup> Material properties according to EN ISO 898-1:2013

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Types of channel bolts – geometry and material

**Annex A13**

Table A12: Overview – strength grades of channel bolts for JTA, JZA and JXA anchor channels

Channel bolt	Strength grade <sup>1)</sup>			
	4.6	8.8	50	70
JD	✓	– <sup>2)</sup>	✓	✓
JH	✓	✓	✓	– <sup>2)</sup>
JC	✓	✓	✓	✓
JKC	– <sup>2)</sup>	✓	– <sup>2)</sup>	✓
JB	✓	✓	✓	✓
JKB	– <sup>2)</sup>	✓	– <sup>2)</sup>	✓
JA	✓	✓	✓	– <sup>2)</sup>
JZS	– <sup>2)</sup>	✓	✓	– <sup>2)</sup>
JXD	– <sup>2)</sup>	✓	– <sup>2)</sup>	– <sup>2)</sup>
JXH	– <sup>2)</sup>	✓	– <sup>2)</sup>	✓
JXB	– <sup>2)</sup>	✓	– <sup>2)</sup>	✓
JXE	– <sup>2)</sup>	✓	– <sup>2)</sup>	– <sup>2)</sup>

<sup>1)</sup> Material properties according to EN ISO 898-1:2013

<sup>2)</sup> Product not available

JORDAHL anchor channel JTA, JZA and JXA

**Product description**  
Types of channel bolts – strength grade

**Annex A14**

## Specifications of intended use

### Anchor channels and channel bolts subject to:

- Static and quasi-static tension, shear perpendicular to the longitudinal axis of the channel and shear in the direction of the longitudinal axis of the channel.
- Fatigue cyclic tension loading.
- Fire exposure for strength class C20/25 to C50/60.

### Base materials:

- Reinforced or unreinforced normal weight concrete according to EN 206-1:2000.
- Strength classes C12/15 to C90/105 according to EN 206-1:2000.
- Cracked or uncracked concrete.

### Service conditions (environmental conditions):

- Structures subject to dry internal conditions (anchor channels and channel bolts according to Annex A3 and A4, Table A1, column 1 – 5).
- Structures subject to internal conditions with usual humidity (e.g. kitchen, bath and laundry in residential buildings, exceptional or permanent damp conditions and applications under water) (anchor channels and channel bolts according to Annex A3 and A4, Table A1, column 2 – 5).
- According to EN 1993-1-4:2006 + A2:2015 relating to corrosion resistance class CRC III (anchor channels and channel bolts according to A4, Table A1, column 3 – 5).
- According to EN 1993-1-4:2006 + A2:2015 relating to corrosion resistance class CRC IV (anchor channels and channel bolts according to A4, Table A1, column 4 – 5).
- According to EN 1993-1-4:2006 + A2:2015 relating to corrosion resistance class CRC V (anchor channels and channel bolts according to A4, Table A1, column 5).

### Design:

- Anchor channels are designed under the responsibility on an engineer experienced in anchorages and concrete work.
- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the anchor channel and channel bolts are indicated on the design drawings (e.g. position of the anchor channel relative to the reinforcement or to supports).
- For static and quasi-static loading as well as fire exposure the anchor channels are designed in accordance with EOTA TR 047 "Design of Anchor Channels", March 2018 or EN 1992-4:2018.
- For fatigue loading the anchor channels are designed in accordance with EOTA TR 050 "Calculation Method for the Performance of Anchor Channels under Fatigue Cyclic Loading", June 2022.
- The characteristic resistances are calculated with the minimum effective embedment depth.

JORDAHL anchor channel JTA, JZA and JXA

Intended use  
Specifications

Annex B1

### Installation:

- The installation of anchor channels is carried out by appropriately qualified personnel under the supervision of the person responsible for the technical matters on site.
- Use of the anchor channels only as supplied by the manufacturer – without any manipulations, repositioning or exchanging of channel components.
- Cutting of anchor channels is allowed only if pieces according to Annex A10, Table A7 and Annex A11, Table A8 are generated including end spacing and minimum channel length and only to be used in dry internal conditions (Annex A3 and A4, Table A1, column 1). For anchor channels made of stainless steel there are no restrictions regarding corrosion resistance when using cut channel pieces, if cutting is done professionally and contamination of cutting edges with corroding material is avoided.
- Installation in accordance with the installation instructions given in Annexes B8 and B9.
- The anchor channels are fixed on the formwork, reinforcement or auxiliary construction such that no movement of the channels will occur during the time of laying the reinforcement and of placing and compacting the concrete.
- The concrete under the head of the anchors is properly compacted. The channels are protected from penetration of concrete into the internal space of the channel.
- Washer may be chosen according to Annex A3 and Annex A4 and provided separately by the user.
- Orientating the channel bolt (groove according to Annex A12 and Annex A13) perpendicular to the channel axis.
- The required installation torques given in Annex B5 and B6 must be applied and must not be exceeded.

JORDAHL anchor channel JTA, JZA and JXA

**Intended use**  
**Specifications**

**Annex B2**

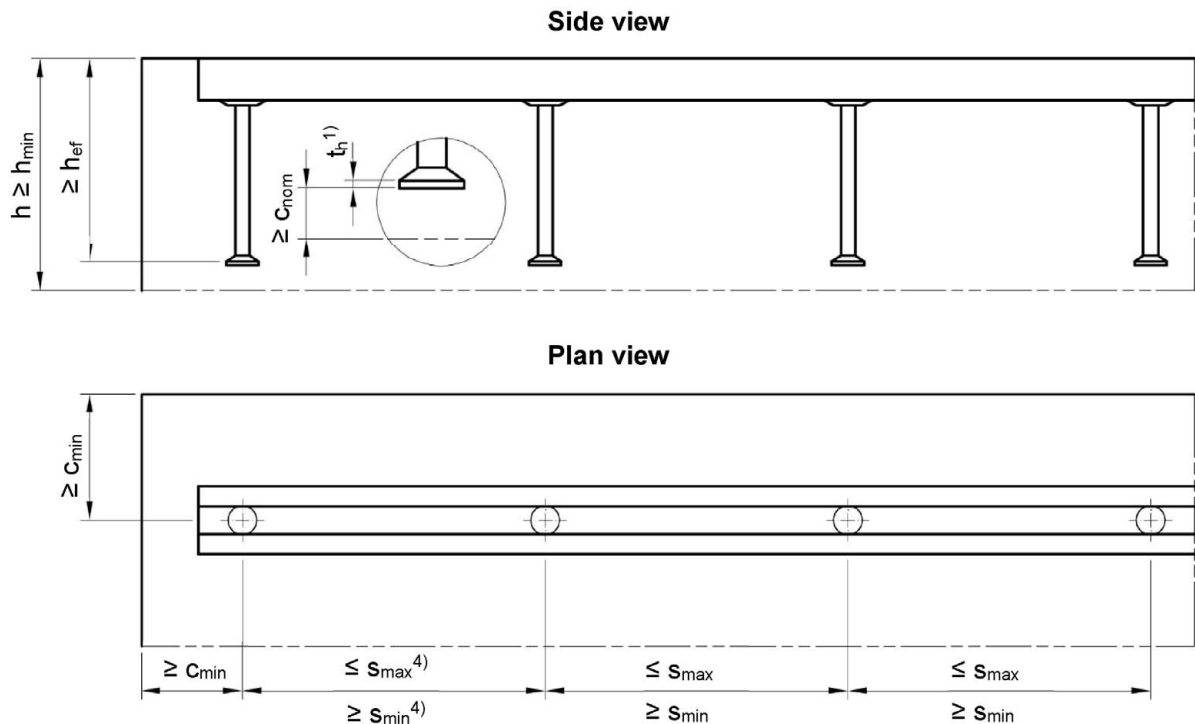


Table B1: Minimum effective embedment depth, edge distance and member thickness (JTA W)

Anchor channel		JTA						
		W40/22	W40+	W50/30	W50+	W53/34	W55/42	W72/48
Min. effective embedment depth round anchors and I-anchors	$h_{ef,min}$	79	91	94	106	155	175	179
Min. effective embedment depth, T-anchors	$h_{ef,min}$	57	— <sup>3)</sup>	71	— <sup>3)</sup>	76	84	— <sup>3)</sup>
Min. edge distance round anchors and I-anchors	$c_{min}$	50	50	75	75	100	100	150
Min. edge distance T-anchors	$c_{min}$	50	— <sup>3)</sup>	50	— <sup>3)</sup>	75	75	— <sup>3)</sup>
Min. member thickness round anchors and I-anchors	$h_{min}$	90	102	105	118	170	191	195
Min. member thickness T-anchors	$h_{min}$	95	— <sup>3)</sup>	100	— <sup>3)</sup>	110	130	— <sup>3)</sup>
Min. member thickness in general	$h_{min}$	$h_{ef} + t_h^{1)} + c_{nom}^{2)}$						

<sup>1)</sup>  $t_h$  according to Annex A7, Table A4 and Annex A8, Table A5

<sup>2)</sup>  $c_{nom}$  according to EN 1992-1-1:2004 + AC:2010

<sup>3)</sup> Product not available

<sup>4)</sup>  $s_{min}$ ,  $s_{max}$  according to Annex A10, Table A7 and Annex A11, Table A8

JORDAHL anchor channel JTA, JZA and JXA

**Intended use**  
Installation parameters for anchor channels (JTA W)

**Annex B3**

Table B2: Minimum effective embedment depth, edge distance and member thickness (JTA K)

Anchor channel			JTA					
			K28/15	K38/17	K40/25	K50/30	K53/34	K72/48
Min. effective embedment depth round anchors and I-anchors	$h_{ef,min}$	[mm]	45	76	79	94	155	179
Min. edge distance round anchors and I-anchors	$c_{min}$		40	50	50	75	100	150
Min. member thickness round anchors and I-anchors	$h_{min}$		55	87	90	105	170	195
Min. member thickness in general	$h_{min}$		$h_{ef} + t_h^{1)} + c_{nom}^{2)}$					

<sup>1)</sup>  $t_h$  according to Annex A7, Table A4 and Annex A8, Table A5

<sup>2)</sup>  $c_{nom}$  according to EN 1992-1-1:2004 + AC:2010

Table B3: Minimum effective embedment depth, edge distance and member thickness (JZA and JXA)

Anchor channel			JZA	JXA			
			K41/22	W29/20	W38/23	W53/34	W64/44
Min. effective embedment depth round anchors and I-anchors	$h_{ef,min}$	[mm]	75	78	95	155	179
Min. effective embedment depth T-anchors	$h_{ef,min}$		— <sup>3)</sup>	— <sup>3)</sup>	54	76	— <sup>3)</sup>
Min. edge distance round anchors and I-anchors	$c_{min}$		50	50	75	100	100
Min. edge distance T-anchors	$c_{min}$		— <sup>3)</sup>	— <sup>3)</sup>	50	100	— <sup>3)</sup>
Min. member thickness round anchors and I-anchors	$h_{min}$		120	120	120	190	210
Min. member thickness T-anchors	$h_{min}$		— <sup>3)</sup>	— <sup>3)</sup>	100	110	— <sup>3)</sup>
Min. member thickness in general	$h_{min}$		$h_{ef} + t_h^{1)} + c_{nom}^{2)}$				

<sup>1)</sup>  $t_h$  according to Annex A7, Table A4 and Annex A8, Table A5

<sup>2)</sup>  $c_{nom}$  according to EN 1992-1-1:2004 + AC:2010

<sup>3)</sup> Product not available

JORDAHL anchor channel JTA, JZA and JXA

**Intended use**  
Installation parameters for anchor channels (JTA K, JZA and JXA)

**Annex B4**

Table B4: Minimum spacing and installation torque of channel bolts (for JTA)

Anchor channel		Channel bolt		Min. spacing of the channel bolt $s_{min,cbo}$	Installation torque $T_{inst}^{4)}$		
					General <sup>2)</sup> $T_{inst,g}$	Steel-steel <sup>3)</sup> $T_{inst,s}$	
		Type	d		Steel 4.6; 8.8 <sup>1)</sup> Stainless steel 50; 70 <sup>1)</sup>	Steel 4.6 <sup>1)</sup> Stainless steel 50 <sup>1)</sup>	Steel 8.8 <sup>1)</sup> Stainless steel 70 <sup>1)</sup>
			[mm]		[Nm]		
JTA	K28/15	JD	6	30	3	3	8
			8	40	8	8	20
			10	50	13	15	40
			12	60	15	25	70
	K38/17	JH	10	50	15	15	40
			12	60	25	25	70
			16	80	40	65	180
	K40/25 W40/22 W40+	JC	10	50	15	15	40
			12	60	25	25	70
			16	80	45	65	180
	W40/22 W40+	JKC	12	-	-	-	70
			16	-	-	-	180
	K50/30 W50/30 W50+	JB	10	50	15	15	40
			12	60	25	25	70
			16	80	60	65	180
			20	100	75	130	360
	K53/34 W53/34	JB	10	50	15	15	40
			12	60	25	25	70
			16	80	60	65	180
			20	100	120	130	360
	W50/30 W50+ W53/34	JKB	16	-	-	-	180
			20	-	-	-	360
	W55/42	JB	10	50	15	15	40
			12	60	25	25	70
			16	80	60	65	180
			20	100	120	130	360
			24	120	200	230	620
	K72/48 W72/48	JA	20	100	120	130	360
			24	120	200	230	620
			27	135	300	340	900
			30	150	380	460	1200

<sup>1)</sup> Materials according to Annex A13 and A14

<sup>2)</sup> According to Annex B7, Fig. 1

<sup>3)</sup> According to Annex B7, Fig. 2

<sup>4)</sup>  $T_{inst}$  must not be exceeded

JORDAHL anchor channel JTA, JZA and JXA

**Intended use**  
Installation parameters of channel bolts (JTA)

**Annex B5**



Table B5: Minimum spacing and installation torque of channel bolts (for JZA and JXA)

Anchor channel		Channel bolt		Min. spacing of the channel bolt $s_{min,cbo}$	Installation torque $T_{inst}^{4)}$		
					General <sup>2)</sup> $T_{inst,g}$	Steel-steel <sup>3)</sup> $T_{inst,s}$	
		Type	d		Steel 4.6; 8.8 <sup>1)</sup> Stainless steel 50; 70 <sup>1)</sup>	Steel 4.6 <sup>1)</sup> Stainless steel 50 <sup>1)</sup>	Steel 8.8 <sup>1)</sup> Stainless steel 70 <sup>1)</sup>
					[mm]	[mm]	[Nm]
JZA	K41/22	JZS	12	60	70	70	70
			16	80	130	130	130
JXA	W29/20	JXD	10	50	30	— <sup>5)</sup>	40
			12	60	70	— <sup>5)</sup>	70
	W38/23	JXH	12	60	70	— <sup>5)</sup>	70
			16	80	120	— <sup>5)</sup>	180
	W53/34	JXB	16	80	180	— <sup>5)</sup>	180
			20	100	300	— <sup>5)</sup>	360
	W64/44	JXE	20	100	300	— <sup>5)</sup>	360
			24	120	350	— <sup>5)</sup>	450

<sup>1)</sup> Materials according to Annex A13 and A14

<sup>2)</sup> According to Annex B7, Fig. 1

<sup>3)</sup> According to Annex B7, Fig. 2

<sup>4)</sup>  $T_{inst}$  must not be exceeded

<sup>5)</sup> Product not available

JORDAHL anchor channel JTA, JZA and JXA

**Intended use**  
Installation parameters of channel bolts (JZA and JXA)

**Annex B6**

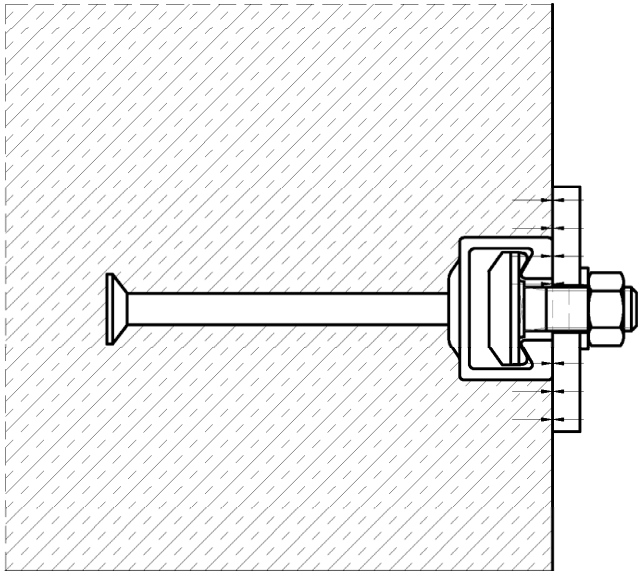


Fig. 1

**General:**

The fixture is in contact with the channel profile and the concrete surface. The installation torques according to Annex B5, Table B4 and Annex B6, Table B5 shall be applied and must not be exceeded.

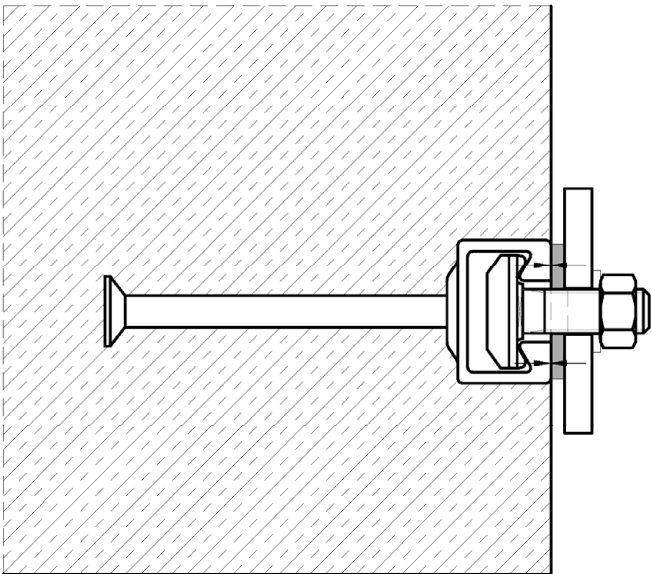


Fig. 2

**Steel-steel contact:**

The fixture is not in contact with the concrete surface. The fixture is fastened to the anchor channel by suitable steel part (e.g. washer). The installation torques according to Annex B5, Table B4 and Annex B6, Table B5 shall be applied and must not be exceeded.


JORDAHL anchor channel JTA, JZA and JXA

**Intended use**  
Position of the fixture

**Annex B7**

### 1. Fixing anchor channel


Install the channel surface flush and fix the channel undisplaceable to the formwork or to the reinforcement.



#### a) Fixing to steel formwork

With JORDAHL T-bolts and nuts, with rivets, cramps or with magnet fixings.


or



#### b) Fixing to timber formwork

With nails through the pre punched holes in the back of the channels and with staples.

or

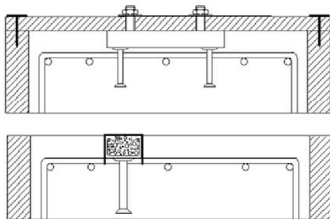


#### c) Fixing of anchor channels at the top

- To timber batten on the side formwork (e.g. with JORDAHL T-bolts).
- Fixing from above directly to the reinforcement or to a mounting reinforcing bar, attach the channel by wire binding.


### 2. Pouring concrete and regular compacting of concrete

Compact the concrete properly around the channel and the anchors.




a) at side of member

or

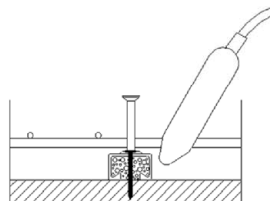

b) at bottom of member


or

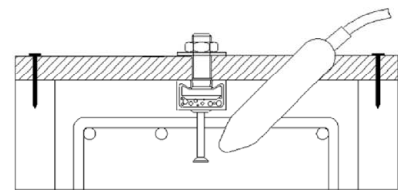

c) at top of member

### 3. Removing of the infill


Clean the channel on the outside after removing the formwork.



#### a) PS foam infill

With a hammer or a hook.

or

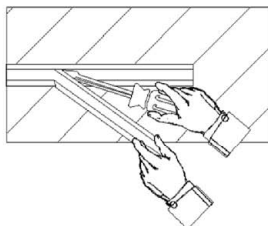

#### b) PE foam infill

By hand or with help of a screw driver in one piece.

JORDAHL anchor channel JTA, JZA and JXA


**Intended use**

Installation instruction anchor channels

**Annex B8**

#### 4. Fastening the JORDAHL T-bolt to the JORDAHL anchor channel

Fig. 1

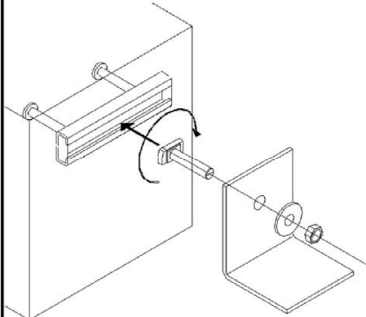

##### a) Installation torques (general)

1. Insert the JORDAHL T-bolt into the channel slot at any point along the channel length (Fig. 1)
2. Turn the channel bolt 90° clockwise and the head of the channel bolt locks into position (Fig. 1).
3. Do not mount the channel bolt at the end of the channel within the end spacing  $x$  according to Annex A10 and A11.
4. Use the washer under the nut (Fig. 1).
5. Check the correct fit of the channel bolt.  
The groove on the shank end of the channel bolt must be perpendicular to the channel longitudinal axis.
6. Tighten the nuts to the installation torque according to Table 1 (Fig. 2). The installation torque must not be exceeded.

Fig. 2

Table 1

**Table 1**

Anchor channel		Strength grade	T <sub>inst,g</sub> [Nm]								
			M6	M8	M10	M12	M16	M20	M24	M27	M30
JTA	K28/15	4.6, 8.8; 50, 70	3	8	13	15	-	-	-	-	-
	K38/17		-	-	15	25	40	-	-	-	-
	K40/25 W40/22 W40+		-	-	15	25	45	-	-	-	-
	K50/30 W50/30 W50+		-	-	15	25	60	75	-	-	-
	K53/34 W53/34		-	-	15	25	60	120	-	-	-
	W55/42		-	-	15	25	60	120	200	-	-
	K72/48 W72/48		-	-	-	-	-	120	200	300	380
JZA	K41/22		-	-	-	70	130	-	-	-	-
JXA	W29/20	4.6, 8.8; 50, 70	-	-	30	70	-	-	-	-	-
	W38/23		-	-	-	70	120	-	-	-	-
	W53/34		-	-	-	-	180	300	-	-	-
	W64/44		-	-	-	-	-	300	350	-	-

OR

Fig. 3

##### b) Installation torques (steel-steel contact)

1. Use washers between the channel and the fixture to create a defined contact
2. Tighten the nuts to the installation torque according to Table 2. The installation torque must not be exceeded.

Table 2

Table 2

Anchor channel		Strength grade	T <sub>inst.s</sub> [Nm]	M6	M8	M10	M12	M16	M20	M24	M27	M30
JTA	K28/15, K38/17, W40/22, W40+, W50/30, W50+, W53/34, W55/42, W72/48	4.6	3	8	15	25	65	130	230	340	460	
		50	-	-	13	24	60	115	-	-	-	
		8.8	-	20	40	70	180	360	620	-	-	
		70	-	15	30	50	130	250	-	-	-	
JZA	K41/22	8.8; 50	-	-	-	70	130	-	-	-	-	
JXA	W29/20	8.8	-	-	40	70	-	-	-	-	-	
	W38/23	8.8; 70	-	-	-	70	180	-	-	-	-	
	W53/34	8.8; 70	-	-	-	-	180	360	-	-	-	
	W64/44	8.8	-	-	-	-	-	360	450	-	-	

JORDAHL anchor channel JTA, JZA and JXA

Intended use  
Installation instruction channel bolts

Annex B9

Table C1: Characteristic resistances under tension load – Steel failure of anchor channel (JTA W)

Anchor channel			JTA						
			W40/22	W40+	W50/30	W50+	W53/34	W55/42	W72/48
Steel failure: Anchor									
Characteristic resistance	N <sub>Rk,s,a</sub>	[kN]	20,0	30,0	32,0	39,0	56,0	103,0	102,0
Partial factor	γ <sub>Ms</sub> <sup>1)</sup>		1,8						
Steel failure: Connection between anchor and channel									
Characteristic resistance	N <sub>Rk,s,c</sub>	[kN]	20,0	29,0	31,0	39,0	55,0	103,0	100,0
Partial factor	γ <sub>Ms,ca</sub> <sup>1)</sup>		1,8						
Steel failure: Local flexure of channel lips									
Spacing of channel bolts for N <sub>Rk,s,l</sub>	s <sub>l,N</sub>	[mm]	79	79	98	98	105	109	144
Characteristic resistance	N <sup>0</sup> <sub>Rk,s,l</sub>	[kN]	38,0	38,0	38,0	38,0	72,0	119,0	120,0
Partial factor	γ <sub>Ms,l</sub> <sup>1)</sup>		1,8						

<sup>1)</sup> In absence of other national regulations

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under tension load – steel failure anchor channels (JTA W)

**Annex C1**

Table C2: Characteristic resistances under tension load – Steel failure of anchor channel (JTA K)

Anchor channel			JTA					
			K28/15	K38/17	K40/25	K50/30	K53/34	K72/48
Steel failure: Anchor								
Characteristic resistance	N <sub>Rk,s,a</sub>	[kN]	13,0	18,0	20,0	32,0	56,0	102,0
Partial factor	γ <sub>Ms</sub> <sup>1)</sup>		1,8					
Steel failure: Connection between anchor and channel								
Characteristic resistance	N <sub>Rk,s,c</sub>	[kN]	9,0	18,0	20,0	31,0	55,0	100,0
Partial factor	γ <sub>Ms,ca</sub> <sup>1)</sup>		1,8					
Steel failure: Local flexure of channel lips								
Spacing of channel bolts for N <sub>Rk,s,l</sub>	s <sub>l,N</sub>	[mm]	56	76	80	100	107	144
Characteristic resistance	N <sup>0</sup> <sub>Rk,s,l</sub>	[kN]	9,0	18,0	20,0	31,0	55,0	100,0
Partial factor	γ <sub>Ms,l</sub> <sup>1)</sup>		1,8					

<sup>1)</sup> In absence of other national regulations

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under tension load – steel failure anchor channels (JTA K)

**Annex C2**

Table C3: Characteristic resistances under tension load – Steel failure of anchor channel (JZA and JXA)

Anchor channel			JZA	JXA			
			K41/22	W29/20	W38/23	W53/34	W64/44
Steel failure: Anchor							
Characteristic resistance	N <sub>Rk,s,a</sub>	[kN]	25,4 <sup>2)</sup>	25,4 <sup>2)</sup>	31,4 <sup>2)</sup>	57,1 <sup>2)</sup>	115,0 <sup>2)</sup>
			25,4 <sup>3)</sup>	— <sup>4)</sup>	31,4 <sup>3)</sup>	57,1 <sup>3)</sup>	— <sup>4)</sup>
Partial factor	γ <sub>Ms</sub> <sup>1)</sup>		1,8				
Steel failure: Connection between anchor and channel							
Characteristic resistance	N <sub>Rk,s,c</sub>	[kN]	14,5 <sup>2)</sup>	19,3 <sup>2)</sup>	35,3 <sup>2)</sup>	72,6 <sup>2)</sup>	106,3 <sup>2)</sup>
			18,0 <sup>3)</sup>	— <sup>4)</sup>	39,0 <sup>3)</sup>	49,0 <sup>3)</sup>	— <sup>4)</sup>
Partial factor	γ <sub>Ms,ca</sub> <sup>1)</sup>		1,8				
Steel failure: Local flexure of channel lips							
Spacing of channel bolts for N <sub>Rk,s,l</sub>	s <sub>l,N</sub>	[mm]	82	58	76	105	128
Characteristic resistance	N <sup>0</sup> <sub>Rk,s,l</sub>	[kN]	14,5 <sup>2)</sup>	19,3 <sup>2)</sup>	35,3 <sup>2)</sup>	72,6 <sup>2)</sup>	106,3 <sup>2)</sup>
			18,0 <sup>3)</sup>	— <sup>4)</sup>	42,8 <sup>3)</sup>	64,6 <sup>3)</sup>	— <sup>4)</sup>
Partial factor	γ <sub>Ms,l</sub> <sup>1)</sup>		1,8				

<sup>1)</sup> In absence of other national regulations

<sup>2)</sup> Carbon steel

<sup>3)</sup> Stainless steel

<sup>4)</sup> Product not available

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under tension load – steel failure anchor channels (JZA and JXA)

**Annex C3**

Table C4: Characteristic flexural resistance of anchor channel (JTA W)

Anchor channel				JTA						
				W40/22	W40+	W50/30	W50+	W53/34	W55/42	W72/48
Steel failure: Flexure of channel										
Characteristic flexural resistance of channel	Round anchor, I-anchor	M <sub>Rk,s,flex</sub>	[Nm]	1406	1406	2830	2830	3373	6447	8593
	T-anchor			703	— <sup>2)</sup>	1416	— <sup>2)</sup>	2297	4454	— <sup>2)</sup>
Characteristic flexural resistance of channel, notching bolt	Round anchor, I-anchor	M <sub>Rk,s,flex</sub>	[Nm]	1138	1138	1756	1756	3373	— <sup>2)</sup>	— <sup>2)</sup>
	T-anchor			703	— <sup>2)</sup>	1416	— <sup>2)</sup>	2297	— <sup>2)</sup>	— <sup>2)</sup>
Partial factor		γ <sub>Ms,flex</sub> <sup>1)</sup>		1,15						

<sup>1)</sup> In absence of other national regulations

<sup>2)</sup> Product not available

Table C5: Characteristic flexural resistance of anchor channel (JTA K)

Anchor channel				JTA					
				K28/15	K38/17	K40/25	K50/30	K53/34	K72/48
<b>Steel failure: Flexure of channel</b>									
Characteristic flexural resistance of channel	Round anchor, I-anchor	$M_{Rk,s,flex}$	[Nm]	317	580	1071	1673	2984	8617
Partial factor		$\gamma_{Ms,flex}^{1)}$		1,15					

<sup>1)</sup> In absence of other national regulations

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under tension load – steel failure anchor channels (JTA)

**Annex C4**



Table C6: Characteristic flexural resistance of anchor channel (JZA and JXA)

Anchor channel				JZA	JXA				
				K41/22	W29/20	W38/23	W53/34	W64/44	
Steel failure: Flexure of channel									
Characteristic flexural resistance of channel	Round anchor	M <sub>Rk,s,flex</sub>	[Nm]	629 <sup>2)</sup>	608	1052 <sup>3)</sup>	3247 <sup>4)</sup>	— <sup>5)</sup>	
	I-anchor			— <sup>5)</sup>	— <sup>5)</sup>	1581	4147	7078	
	T-anchor			— <sup>5)</sup>	— <sup>5)</sup>	832	2476	— <sup>5)</sup>	
Partial factor		γ <sub>Ms,flex</sub> <sup>1)</sup>		1,15					

<sup>1)</sup> In absence of other national regulations

<sup>2)</sup> Value for carbon steel; stainless steel – 765 Nm

<sup>3)</sup> Value for stainless steel; carbon steel –1581 Nm

<sup>4)</sup> Value for stainless steel; carbon steel –4147 Nm

<sup>5)</sup> Product not available

JORDAHL anchor channel JTA, JZA and JXA

#### Performance

Characteristic resistances under tension load – steel failure anchor channels (JZA and JXA)

**Annex C5**

Table C7: Characteristic resistances under tension load – Steel failure of channel bolts (JTA)

Channel bolt			JD, JH, JC, JKC, JB, JKB, JA									
Thread diameter			M6	M8	M10	M12	M16	M20	M24	M27	M30	
Steel failure: Channel bolt												
Characteristic resistance <sup>2)</sup>	N <sub>Rk,s</sub>	[kN]	4.6 <sup>1)</sup>	8,0	14,6	23,2	33,7	62,8	98,0	141,2	183,6	224,4
			8.8 <sup>1)</sup>	16,1	29,3	46,4	67,4	125,6	196,0	282,4	367,2	448,8
			50 <sup>1)</sup>	10,1	18,3	29,0	42,2	78,5	122,5	176,5	229,5	280,5
			70 <sup>1)</sup>	14,1	25,6	40,6	59,0	109,9	171,5	247,1	321,3	392,7
Partial factor	$\gamma_{Ms}$ <sup>3)</sup>		4.6 <sup>1)</sup>	2,00								
			8.8 <sup>1)</sup>	1,50								
			50 <sup>1)</sup>	2,86								
			70 <sup>1)</sup>	1,87								

<sup>1)</sup> Materials according to Annex A2 to A4

<sup>2)</sup> In conformity to EN ISO 898-1:2013

<sup>3)</sup> In absence of other national regulations

Table C8: Characteristic resistances under tension load – Steel failure of channel bolts (JZA and JXA)

Channel bolt				JZS		JXD, JXH, JXB, JXE				
Thread diameter				M12	M16	M10	M12	M16	M20	M24
Steel failure: Channel bolt										
Characteristic resistance <sup>2)</sup>	N <sub>Rk,s</sub>	[kN]	8.8 <sup>1)</sup>	48,9	98,9	46,4	67,4	125,6	196,0	282,4
			50 <sup>1)</sup>	42,2	78,5	— <sup>5)</sup>	— <sup>5)</sup>	— <sup>5)</sup>	— <sup>5)</sup>	— <sup>5)</sup>
			70 <sup>1)</sup>	— <sup>5)</sup>	— <sup>5)</sup>	— <sup>5)</sup>	59,0 <sup>4)</sup>	109,9 <sup>4)</sup>	171,5 <sup>4)</sup>	— <sup>5)</sup>
Partial factor	$\gamma_{Ms}$ <sup>3)</sup>		8.8 <sup>1)</sup>	1,50						
			50 <sup>1)</sup>	2,86						
			70 <sup>1)</sup>	1,87						

<sup>1)</sup> Materials according to Annex A2 to A4

<sup>2)</sup> In conformity to EN ISO 898-1:2013

<sup>3)</sup> In absence of other national regulations

<sup>4)</sup> Available only as JXH and JXB

<sup>5)</sup> Product not available

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under tension load – steel failure channel bolts

**Annex C6**

Table C9: Characteristic resistances under tension load – Concrete failure of anchor channel (JTA W)

Anchor channel				JTA						
				W40/22	W40+	W50/30	W50+	W53/34	W55/42	W72/48
Concrete failure: Pullout										
Characteristic resistance in cracked concrete C12/15	Round anchor	N <sub>Rk,p</sub>	[kN]	10,8	17,3 (10,8) <sup>1)</sup>	15,9	19,8	29,7	38,4	50,9
	I-anchor			23,4	24,8	29,2	29,7	39,6	52,2	46,4
	T-anchor				— <sup>3)</sup>		— <sup>3)</sup>			— <sup>3)</sup>
Characteristic resistance in uncracked concrete C12/15	Round anchor	N <sub>Rk,p</sub>	[kN]	15,1	24,2 (15,1) <sup>1)</sup>	22,3	27,7	41,6	53,8	71,3
	I-anchor			32,8	34,7	40,9	41,6	55,4	73,1	65,0
	T-anchor				— <sup>3)</sup>		— <sup>3)</sup>			— <sup>3)</sup>
Factor of N <sub>Rk,p</sub> = N <sub>Rk,p</sub> (C12/15) · ψ <sub>c</sub>	C20/25	ψ <sub>c</sub>	[-]	1,67						
	C25/30			2,08						
	C30/37			2,50						
	C35/45			2,92						
	C40/50			3,33						
	C45/55			3,75						
	C50/60			4,17						
	C55/67			4,58						
	≥C60/75			5,00						
Partial factor		γ <sub>Mp</sub> <sup>2)</sup>		1,5						
Concrete failure: Concrete cone										
Product factor k <sub>1</sub>	Round, I-anchor	k <sub>cr,N</sub>	[-]	7,9	8,0	8,1	8,2	8,7	8,9	8,9
	T-anchor			7,5	— <sup>3)</sup>	7,7	— <sup>3)</sup>	7,8	7,9	— <sup>3)</sup>
	Round, I-anchor	k <sub>ucr,N</sub>	[-]	11,2	11,5	11,5	11,7	12,4	12,6	12,7
	T-anchor			10,7	— <sup>3)</sup>	11,0	— <sup>3)</sup>	11,2	11,3	— <sup>3)</sup>
Partial factor		γ <sub>Mc</sub> <sup>2)</sup>		1,5						
Concrete failure: Splitting										
Charact. edge dist.	Round, I-anchor	C <sub>cr,sp</sub>	[mm]	237	273	282	318	465	525	537
	T-anchor			171	— <sup>3)</sup>	213	— <sup>3)</sup>	228	252	— <sup>3)</sup>
Charact. spacing	Round, I-anchor	S <sub>cr,sp</sub>	[mm]	474	546	564	636	930	1050	1074
	T-anchor			342	— <sup>3)</sup>	426	— <sup>3)</sup>	456	504	— <sup>3)</sup>
Partial factor		γ <sub>Msp</sub> <sup>2)</sup>		1,5						

<sup>1)</sup> Values in brackets for stainless steel anchors

<sup>2)</sup> In absence of other national regulations

<sup>3)</sup> Product not available

JORDAHL anchor channel JTA, JZA and JXA

## Performance

Characteristic resistances under tension load – concrete failure anchor channels (JTA W)

Annex C7

Table C10: Characteristic resistances under tension load – Concrete failure of anchor channel (JTA K)

Anchor channel				JTA					
				K28/15	K38/17	K40/25	K50/30	K53/34	K72/48
Concrete failure: Pullout									
Characteristic resistance in cracked concrete C12/15	Round anchor	N <sub>Rk,p</sub>	[kN]	6,7	14,7	10,8	15,9	29,7	50,9
	I-anchor			11,7	11,7	14,0	21,1	25,7	46,4
Characteristic resistance in uncracked concrete C12/15	Round anchor	N <sub>Rk,p</sub>	[kN]	9,4	20,6	15,1	22,3	41,6	71,3
	I-anchor			16,4	16,4	19,7	29,5	36,0	65,0
Factor of N <sub>Rk,p</sub> = N <sub>Rk,p</sub> (C12/15) · ψ <sub>c</sub>	C20/25	ψ <sub>c</sub>	[-]	1,67					
	C25/30			2,08					
	C30/37			2,50					
	C35/45			2,92					
	C40/50			3,33					
	C45/55			3,75					
	C50/60			4,17					
	C55/67			4,58					
	≥C60/75			5,00					
Partial factor		γ <sub>Mp</sub> <sup>1)</sup>		1,5					
Concrete failure: Concrete cone									
Product factor k <sub>1</sub>	Round, I-anchor	k <sub>cr,N</sub>	[-]	7,2	7,8	7,9	8,1	8,7	8,9
	Round, I-anchor	k <sub>ucr,N</sub>	[-]	10,3	11,2	11,2	11,5	12,4	12,7
Partial factor		γ <sub>Mc</sub> <sup>1)</sup>		1,5					
Concrete failure: Splitting									
Charact. edge dist.	Round, I-anchor	C <sub>cr,sp</sub>	[mm]	135	228	237	282	465	537
Charact. spacing	Round, I-anchor	S <sub>cr,sp</sub>	[mm]	270	456	474	564	930	1074
Partial factor		γ <sub>Msp</sub> <sup>1)</sup>		1,5					

<sup>1)</sup> In absence of other national regulations

JORDAHL anchor channel JTA, JZA and JXA

### Performance

Characteristic resistances under tension load – concrete failure anchor channels (JTA K)

**Annex C8**

Table C11: Characteristic resistances under tension load – Concrete failure of anchor channel (JZA and JXA)

Anchor channel				JZA	JXA			
				K41/22	W29/20	W38/23	W53/34	W64/44
Concrete failure: Pullout								
Characteristic resistance in cracked concrete C12/15	Round anchor	N <sub>Rk,p</sub>	[kN]	14,7	14,7	19,8	29,7	— <sup>2)</sup>
	I-anchor			— <sup>2)</sup>	— <sup>2)</sup>	19,8	39,6	52,2
	T-anchor			— <sup>2)</sup>	— <sup>2)</sup>	19,8	39,6	— <sup>2)</sup>
Characteristic resistance in uncracked concrete C12/15	Round anchor	N <sub>Rk,p</sub>	[kN]	20,5	20,5	27,7	41,6	— <sup>2)</sup>
	I-anchor			— <sup>2)</sup>	— <sup>2)</sup>	27,7	55,4	73,1
	T-anchor			— <sup>2)</sup>	— <sup>2)</sup>	27,7	55,4	— <sup>2)</sup>
Factor of N <sub>Rk,p</sub> = N <sub>Rk,p</sub> (C12/15) · ψ <sub>c</sub>	C20/25	ψ <sub>c</sub>	[-]	1,67				
	C25/30			2,08				
	C30/37			2,50				
	C35/45			2,92				
	C40/50			3,33				
	C45/55			3,75				
	C50/60			4,17				
	C55/67			4,58				
	≥C60/75			5,00				
Partial factor		γ <sub>Mp</sub> <sup>1)</sup>		1,5				
Concrete failure: Concrete cone								
Product factor k <sub>1</sub>	Round, I-anchor	k <sub>cr,N</sub>	[-]	7,8	7,9	8,1	8,7	8,9
	T-anchor			— <sup>2)</sup>	— <sup>2)</sup>	7,4	7,8	— <sup>2)</sup>
	Round, I-anchor	k <sub>ucr,N</sub>	[-]	11,1	11,2	11,5	12,4	12,7
	T-anchor			— <sup>2)</sup>	— <sup>2)</sup>	10,6	11,2	— <sup>2)</sup>
Partial factor		γ <sub>Mc</sub> <sup>1)</sup>		1,5				
Concrete failure: Splitting								
Charact. edge dist.	Round, I-anchor	c <sub>cr,sp</sub>	[mm]	225	234	285	465	537
	T-anchor			— <sup>2)</sup>	— <sup>2)</sup>	162	228	— <sup>2)</sup>
Charact. spacing	Round, I-anchor	s <sub>cr,sp</sub>	[mm]	450	468	570	930	1074
	T-anchor			— <sup>2)</sup>	— <sup>2)</sup>	324	456	— <sup>2)</sup>
Partial factor		γ <sub>Msp</sub> <sup>1)</sup>		1,5				

<sup>1)</sup> In absence of other national regulations

<sup>2)</sup> Product not available

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under tension load – concrete failure anchor channels (JZA and JXA)

**Annex C9**

Table C12: Displacements under tension load (JTA W)

Anchor channel			JTA						
			W40/22	W40+	W50/30	W50+	W53/34	W55/42	W72/48
Tension load	N	[kN]	15,1	15,1	14,9	14,9	28,6	47,2	39,7
Short-term displacement	$\delta_{N0}$	[mm]	1,9	1,9	1,7	1,7	1,6	2,4	0,5
Long-term displacement	$\delta_{N\infty}$	[mm]	3,8	3,8	3,4	3,4	3,1	4,8	1,0

Table C13: Displacements under tension load (JTA K)

Anchor channel			JTA					
			K28/15	K38/17	K40/25	K50/30	K53/34	K72/48
Tension load	N	[kN]	3,6	7,1	7,9	12,3	21,8	39,7
Short-term displacement	$\delta_{N0}$	[mm]	0,3	0,3	0,4	0,4	0,5	0,5
Long-term displacement	$\delta_{N\infty}$	[mm]	0,6	0,6	0,8	0,8	1,0	1,0

Table C14: Displacements under tension load (JZA and JXA)

Anchor channel			JZA	JXA			
			K41/22	W29/20	W38/23	W53/34	W64/44
Tension load	N	[kN]	7,4	8,0	14,8	27,4	42,9
Short-term displacement	$\delta_{N0}$	[mm]	0,6	0,4	1,3	1,4	1,5
Long-term displacement	$\delta_{N\infty}$	[mm]	1,2	0,8	2,6	2,8	3,0

JORDAHL anchor channel JTA, JZA and JXA

**Performance**  
Displacements under tension load

**Annex C10**

Table C15: Characteristic resistances under shear load – Steel failure of anchor channel (JTA W)

Anchor channel			JTA						
			W40/22	W40+	W50/30	W50+	W53/34	W55/42	W72/48
Steel failure: Anchor									
Characteristic resistance	V <sub>Rk,s,a,y</sub>	[kN]	35,0	35,0	52,0	59,0	78,0	110,0	146,0
Characteristic resistance <sup>5)</sup>	V <sub>Rk,s,a,x</sub>	[kN]	12,2	18,0	19,0	23,5	34,2	— <sup>4)</sup>	— <sup>4)</sup>
Partial factor	γ <sub>Ms</sub> <sup>1)</sup>		1,5						
Steel failure: Connection between anchor and channel									
Characteristic resistance	V <sub>Rk,s,c,y</sub>	[kN]	35,0	35,0	52,0	59,0	78,0	110,0	146,0
Characteristic resistance <sup>5)</sup>	V <sub>Rk,s,c,x</sub>	[kN]	10,0	14,5	15,5	19,5	27,5	— <sup>4)</sup>	— <sup>4)</sup>
Partial factor	γ <sub>Ms,ca</sub> <sup>1)</sup>		1,8						
Steel failure: Local flexure of channel lips									
Spacing of channel bolts for V <sub>Rk,s,l</sub>	s <sub>l,v</sub>	[mm]	79	79	98	98	105	109	144
Characteristic resistance	V <sup>0</sup> <sub>Rk,s,l,y</sub>	[kN]	35,0	35,0	52,0	59,0	78,0	110,0	146,0
Partial factor	γ <sub>Ms,l</sub> <sup>1)</sup>		1,8						
Characteristic resistance <sup>5)</sup>	V <sub>Rk,s,l,x</sub>	[kN]	6,1 <sup>2)</sup>		13,2 <sup>2)</sup>		— <sup>4)</sup>	— <sup>4)</sup>	
			2,9 <sup>3)</sup>		4,7 <sup>3)</sup>				
Installation factor	γ <sub>inst</sub>		1,4 <sup>2)</sup>		1,2 <sup>2)</sup>		—		
			1,4 <sup>3)</sup>		1,4 <sup>3)</sup>				
Partial factor	γ <sub>Ms,l,x</sub> <sup>1)</sup>		1,8						

<sup>1)</sup> In absence of other national regulations

<sup>2)</sup> Carbon steel

<sup>3)</sup> Stainless steel

<sup>4)</sup> No performance assessed

<sup>5)</sup> If notching channel bolts are used

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under shear load – steel failure anchor channels (JTA W)

**Annex C11**

Table C16: Characteristic resistances under shear load – Steel failure of anchor channel (JTA K)

Anchor channel			JTA					
			K28/15	K38/17	K40/25	K50/30	K53/34	K72/48
Steel failure: Anchor								
Characteristic resistance	$V_{Rk,s,a,y}$	[kN]	13,0	18,0	20,0	32,0	56,0	102,0
Partial factor	$\gamma_{Ms}^{1)}$		1,5					
Steel failure: Connection between anchor and channel								
Characteristic resistance	$V_{Rk,s,c,y}$	[kN]	9,0	18,0	20,0	31,0	55,0	100,0
Partial factor	$\gamma_{Ms,ca}^{1)}$		1,8					
Steel failure: Local flexure of channel lips								
Spacing of channel bolts for $V_{Rk,s,l}$	$s_{l,v}$	[mm]	56	76	80	100	107	144
Characteristic resistance	$V^0_{Rk,s,l,y}$	[kN]	9,0	18,0	20,0	31,0	55,0	100,0
Partial factor	$\gamma_{Ms,l}^{1)}$		1,8					

<sup>1)</sup> In absence of other national regulations

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under shear load – steel failure anchor channels (JTA K)

**Annex C12**



Table C17: Characteristic resistances under shear load – Steel failure of anchor channel (JZA and JXA)

Anchor channel			JZA	JXA			
			K41/22	W29/20	W38/23	W53/34	W64/44
Steel failure: Anchor							
Characteristic resistance	$V_{Rk,s,a,y}$	[kN]	24,2 <sup>2)</sup>	18,0 <sup>2)</sup>	48,3 <sup>2)</sup>	101,1 <sup>2)</sup>	121,0 <sup>2)</sup>
			28,0 <sup>3)</sup>	—	42,6 <sup>3)</sup>	91,7 <sup>3)</sup>	—
Characteristic resistance	$V_{Rk,s,a,x}$	[kN]	15,3 <sup>2)</sup>	15,3 <sup>2)</sup>	18,8 <sup>2)</sup>	34,3 <sup>2)</sup>	69,0 <sup>2)</sup>
			15,3 <sup>3)</sup>	—	18,8 <sup>3)</sup>	34,3 <sup>3)</sup>	—
Partial factor	$\gamma_{Ms}^{1)}$		1,5				
Steel failure: Connection between anchor and channel							
Characteristic resistance	$V_{Rk,s,c,y}$	[kN]	24,2 <sup>2)</sup>	18,0 <sup>2)</sup>	48,3 <sup>2)</sup>	101,1 <sup>2)</sup>	121,0 <sup>2)</sup>
			28,0 <sup>3)</sup>	—	42,6 <sup>3)</sup>	91,7 <sup>3)</sup>	—
Characteristic resistance	$V_{Rk,s,c,x}$	[kN]	8,7 <sup>2)</sup>	11,6 <sup>2)</sup>	21,2 <sup>2)</sup>	43,6 <sup>2)</sup>	63,8 <sup>2)</sup>
			10,8 <sup>3)</sup>	—	23,5 <sup>3)</sup>	29,4 <sup>3)</sup>	—
Partial factor	$\gamma_{Ms,ca}^{1)}$		1,8				
Steel failure: Local flexure of channel lips							
Spacing of channel bolts for $V_{Rk,s,l}$	$s_{l,v}$	[mm]	82	58	76	105	128
Characteristic resistance	$V^0_{Rk,s,l,y}$	[kN]	24,2 <sup>2)</sup>	18,0 <sup>2)</sup>	48,3 <sup>2)</sup>	101,1 <sup>2)</sup>	121,0 <sup>2)</sup>
			28,0 <sup>3)</sup>	—	42,6 <sup>3)</sup>	91,7 <sup>3)</sup>	—
Partial factor	$\gamma_{Ms,l}^{1)}$		1,8				
Characteristic resistance	$V_{Rk,s,l,x}$	[kN]	10,0 <sup>2)</sup>	12,0 <sup>2)</sup>	19,4 <sup>2)</sup>	33,8 <sup>2)</sup>	64,5 <sup>2)</sup>
			10,7 <sup>3)</sup>	—	11,9 <sup>3)</sup>	22,8 <sup>3)</sup>	—
Installation factor	$\gamma_{inst}$		1,0				
Partial factor	$\gamma_{Ms,l,x}^{1)}$		1,8				

<sup>1)</sup> In absence of other national regulations

<sup>2)</sup> Carbon steel

<sup>3)</sup> Stainless steel

<sup>4)</sup> No performance assessed

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under shear load – steel failure anchor channels (JZA and JXA)

**Annex C13**

Table C18: Characteristic resistances under shear load – Concrete failure of anchor channel (JTA W)

Anchor channel			JTA					
			W40/22	W40+	W50/30	W50+	W53/34	W55/42
Concrete failure: Pry-out								
Product factor		k <sub>8</sub>	2,0 (1,0) <sup>2)</sup>	2,0	2,0	2,0	2,0	2,0
Partial factor		γ <sub>Mc</sub> <sup>1)</sup>	1,5					
Concrete failure: Concrete edge								
Product factor k <sub>12</sub>	cracked concrete	k <sub>cr,V</sub>	7,5 (7,0) <sup>2)</sup>	7,5	7,5	7,5	7,5	7,5 (6,9) <sup>2)</sup>
	uncracked concrete	k <sub>ucr,V</sub>	10,5 (9,8) <sup>2)</sup>	10,5	10,5	10,5	10,5	10,5 (9,7) <sup>2)</sup>
Partial factor		γ <sub>Mc</sub> <sup>1)</sup>	1,5					

<sup>1)</sup> In absence of other national regulations

<sup>2)</sup> Values in brackets for T-anchors

Table C19: Characteristic resistances under shear load – Concrete failure of anchor channel (JTA K)

Anchor channel			JTA				
			K28/15	K38/17	K40/25	K50/30	K53/34
Concrete failure: Pry-out							
Product factor		k <sub>8</sub>	1,0	2,0			
Partial factor		γ <sub>Mc</sub> <sup>1)</sup>	1,5				
Concrete failure: Concrete edge							
Product factor k <sub>12</sub>	cracked concrete	k <sub>cr,V</sub>	4,5	7,5			
	uncracked concrete	k <sub>ucr,V</sub>	6,3	10,5			
Partial factor		γ <sub>Mc</sub> <sup>1)</sup>	1,5				

<sup>1)</sup> In absence of other national regulations

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under shear load – concrete failure anchor channels (JTA)

**Annex C14**

Table C20: Characteristic resistances under shear load – Concrete failure of anchor channel (JZA and JXA)

Anchor channel			JZA	JXA			
			K41/22	W29/20	W38/23	W53/34	W64/44
Concrete failure: Pry-out							
Product factor	k <sub>8</sub>	2,0	2,0	2,0 (1,0) <sup>2)</sup>	2,0	2,0	
Partial factor	γ <sub>Mc</sub> <sup>2)</sup>	1,5					
Concrete failure: Concrete edge							
Product factor k <sub>12</sub>	cracked concrete	k <sub>cr,V</sub>	7,5	6,1	7,5 (5,6) <sup>2)</sup>	7,5 (6,4) <sup>2)</sup>	7,5
	uncracked concrete	k <sub>ucr,V</sub>	10,5	8,6	10,5 (7,9) <sup>2)</sup>	10,5 (8,9) <sup>2)</sup>	10,5
Partial factor	γ <sub>Mc</sub> <sup>1)</sup>	1,5					

<sup>1)</sup> In absence of other national regulations

<sup>2)</sup> Values in brackets for T-anchors

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under shear load – concrete failure anchor channels (JZA and JXA)

**Annex C15**

Table C21: Characteristic resistances under shear loads – Steel failure of channel bolts (JTA)

Channel bolt				JD, JH, JC, JKC, JB, JKB, JA								
Thread diameter				M6	M8	M10	M12	M16	M20	M24	M27	M30
Steel failure: Channel bolt												
Characteristic resistance <sup>2)</sup>	V <sub>Rk,s</sub>	[kN]	4.6 <sup>1)</sup>	4,8	8,8	13,9	20,2	37,7	58,8	84,7	110,2	134,6
			8.8 <sup>1)</sup>	8,0	14,6	23,2	33,7	62,8	98,0	141,2	183,6	224,4
			50 <sup>1)</sup>	6,0	11,0	17,4	25,3	47,1	73,5	105,9	137,7	168,3
			70 <sup>1)</sup>	8,4	15,4	24,4	35,4	65,9	102,9	148,3	192,8	235,6
Characteristic flexural resistance	M <sup>0</sup> <sub>Rk,s</sub>	[Nm]	4.6 <sup>1)</sup>	6,3	15,0	29,9	52,4	133,2	259,6	449,0	665,8	889,6
			8.8 <sup>1)</sup>	12,2	30,0	59,8	104,8 <sup>3)</sup>	266,4 <sup>4)</sup>	519,3	898,0	1331,5	1799,2
			50 <sup>1)</sup>	7,6	18,7	37,4	65,5	166,5	324,5	561,3	832,2	1124,5
			70 <sup>1)</sup>	10,7	26,2	52,3	91,7 <sup>3)</sup>	233,1	454,4	785,8	1165,1	1574,3
Partial factor	γ <sub>Ms</sub> <sup>5)</sup>	4.6 <sup>1)</sup>	1,67									
		8.8 <sup>1)</sup>	1,25									
		50 <sup>1)</sup>	2,38									
		70 <sup>1)</sup>	1,56									

<sup>1)</sup> Materials according to Annex A2 bis A4

<sup>2)</sup> In conformity to EN ISO 898-1:2013

<sup>3)</sup> In combination with anchor channel JTA K 28/15 limited to 85,5 Nm

<sup>4)</sup> In combination with anchor channel JTA K 38/17 limited to 234,0 Nm

<sup>5)</sup> In absence of other national regulations

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under shear load – steel failure channel bolts

**Annex C16**

Table C22: Characteristic resistances under shear loads – Steel failure of channel bolts (JZA and JXA)

Channel bolt			JZS		JXD, JXH, JXB, JXE					
Thread diameter			M12	M16	M10	M12	M16	M20	M24	
<b>Steel failure: Channel bolt</b>										
Characteristic resistance <sup>2)</sup>	$V_{Rk,s}$	[kN]	8.8 <sup>1)</sup>	33,7	62,8	23,2	33,7	62,8	98,0	141,2
			50 <sup>1)</sup>	25,3	47,1	– <sup>5)</sup>	– <sup>5)</sup>	– <sup>5)</sup>	– <sup>5)</sup>	– <sup>5)</sup>
			70 <sup>1)</sup>	– <sup>5)</sup>	– <sup>5)</sup>	– <sup>5)</sup>	35,4 <sup>4)</sup>	65,9 <sup>4)</sup>	102,9 <sup>4)</sup>	– <sup>5)</sup>
Characteristic flexural resistance	$M^0_{Rk,s}$	[Nm]	8.8 <sup>1)</sup>	104,8	266,4	59,8	104,8	266,4	519,3	898,0
			50 <sup>1)</sup>	65,5	166,5	– <sup>5)</sup>	– <sup>5)</sup>	– <sup>5)</sup>	– <sup>5)</sup>	– <sup>5)</sup>
			70 <sup>1)</sup>	– <sup>5)</sup>	– <sup>5)</sup>	– <sup>5)</sup>	91,7 <sup>4)</sup>	233,1 <sup>4)</sup>	454,4 <sup>4)</sup>	– <sup>5)</sup>
Partial factor	$\gamma_{Ms}$ <sup>3)</sup>	8.8 <sup>1)</sup>	1,25							
		50 <sup>1)</sup>	2,38							
		70 <sup>1)</sup>	1,56							

<sup>1)</sup> Materials according to Annex A2 bis A4

<sup>2)</sup> In conformity to EN ISO 898-1:2013

<sup>3)</sup> In absence of other national regulations

<sup>4)</sup> Available only as JXH and JXB

<sup>5)</sup> Product not available

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under shear load – steel failure channel bolts

**Annex C17**

Table C23: Displacements under shear load (JTA W)

Anchor channel			JTA						
			W40/22	W40+	W50/30	W50+	W53/34	W55/42	W72/48
Shear load	$V_y$	[kN]	13,9	13,9	20,6	23,4	31,0	43,7	57,9
Short-term displacement	$\delta_{V,y,0}$	[mm]	0,6	0,6	0,6	0,6	1,2	1,2	1,2
Long-term displacement	$\delta_{V,y,\infty}$	[mm]	0,9	0,9	0,9	0,9	1,8	1,8	1,8
Shear load	$V_x$	[kN]	2,4	2,4	5,2	5,2	5,2	— <sup>1)</sup>	— <sup>1)</sup>
Short-term displacement	$\delta_{V,x,0}$	[mm]	0,4	0,4	0,8	0,8	0,8	— <sup>1)</sup>	— <sup>1)</sup>
Long-term displacement	$\delta_{V,x,\infty}$	[mm]	0,5	0,5	1,2	1,2	1,2	— <sup>1)</sup>	— <sup>1)</sup>

<sup>1)</sup> No performance assessed

Table C24: Displacements under shear load (JTA K)

Anchor channel			JTA					
			K28/15	K38/17	K40/25	K50/30	K53/34	K72/48
Shear load	$V_y$	[kN]	3,6	7,1	7,9	12,3	21,8	39,7
Short-term displacement	$\delta_{V,y,0}$	[mm]	0,6	0,6	0,6	0,6	1,2	1,2
Long-term displacement	$\delta_{V,y,\infty}$	[mm]	0,9	0,9	0,9	0,9	1,8	1,8

Table C25: Displacements under shear load (JZA and JXA)

Anchor channel			JZA	JXA			
			K41/22	W29/20	W38/23	W53/34	W64/44
Shear load	$V_y$	[kN]	10,4	7,7	18,1	38,3	48,3
Short-term displacement	$\delta_{V,y,0}$	[mm]	1,4	0,8	1,9	1,5	3,1
Long-term displacement	$\delta_{V,y,\infty}$	[mm]	2,1	1,1	2,9	2,3	4,7
Shear load	$V_x$	[kN]	4,1	4,8	6,2	11,2	25,6
Short-term displacement	$\delta_{V,x,0}$	[mm]	0,7	1,3	0,6	1,0	2,0
Long-term displacement	$\delta_{V,x,\infty}$	[mm]	1,0	1,9	0,9	1,5	3,0

JORDAHL anchor channel JTA, JZA and JXA

**Performance**  
Displacements under shear load

**Annex C18**

Table C26: Characteristic resistances under combined tension and shear load (JTA W)

Anchor channel		JTA						
		W40/22	W40+	W50/30	W50+	W53/34	W55/42	W72/48
Steel failure								
Product factors	k <sub>13</sub> , k <sub>14</sub>	Values are taken from EN 1992-4:2018						

Table C27: Characteristic resistances under combined tension and shear load (JTA K)

Anchor channel		JTA					
		K28/15	K38/17	K40/25	K50/30	K53/34	K72/48
Steel failure							
Product factors	k <sub>13</sub> , k <sub>14</sub>	Values are taken from EN 1992-4:2018					

Table C28: Characteristic resistances under combined tension and shear load (JZA and JXA)

Anchor channel		JZA	JXA			
		K41/22	W29/20	W38/23	W53/34	W64/44
Steel failure						
Product factors	k <sub>13</sub> , k <sub>14</sub>	Values are taken from EN 1992-4:2018				

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under combined tension and shear load

**Annex C19**

Table C29: Characteristic resistances under fire exposure

Anchor channel					JTA									
					K28/15	K38/17	K40/25 W40/22	W40+	K50/30 W50/30	W50+	K53/34 W53/34	W55/42	K72/48 W72/48	
Steel failure: Anchor, connection between anchor and channel, local flexure of channel lip, channel bolt														
Characteristic resistance	R30	M8	$N_{Rk,s,fi}$ = $V_{Rk,s,y,fi}$	[kN]	1,0	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	
		M10			1,0	1,7	1,9	1,9	1,9	1,9	1,9	— <sup>1)</sup>	— <sup>1)</sup>	
		M12			1,9	1,7	<div>1,9 3,0</div>	3,0	2,5	2,5	2,5	— <sup>1)</sup>	— <sup>1)</sup>	
		M16			— <sup>1)</sup>	3,2	<div>3,6 7,8</div>	7,8	<div>4,0 6,0</div>	6,0	6,0	6,3	— <sup>1)</sup>	
		M20			— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	<div>4,0 9,5</div>	9,5	<div>8,9 10,1</div>	10,3	10,3	
		M24			— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	14,8	14,8	
	R60	M8			0,8	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>
		M10			0,8	1,5	1,5	1,5	1,5	1,5	1,5	1,5	— <sup>1)</sup>	— <sup>1)</sup>
		M12			1,3	1,5	<div>1,5 2,6</div>	2,6	2,5	2,5	2,5	2,5	— <sup>1)</sup>	— <sup>1)</sup>
		M16			— <sup>1)</sup>	2,4	<div>3,6 5,3</div>	5,3	<div>3,5 4,5</div>	4,5	4,5	4,8	— <sup>1)</sup>	
		M20			— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	<div>3,5 7,1</div>	7,1	<div>6,5 7,5</div>	7,6	7,6	
		M24			— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	11,1	11,1	
	R90	M8			0,6	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>
		M10			0,6	1,0	1,1	1,1	1,1	1,1	1,1	1,1	— <sup>1)</sup>	— <sup>1)</sup>
		M12			0,7	1,0	<div>1,1 1,6</div>	1,6	1,6	1,6	1,6	1,6	— <sup>1)</sup>	— <sup>1)</sup>
		M16			— <sup>1)</sup>	1,4	<div>2,0 2,9</div>	2,9	<div>2,5 3,0</div>	3,0	3,0	3,3	— <sup>1)</sup>	
		M20			— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	<div>2,5 4,8</div>	4,8	<div>4,2 4,8</div>	4,9	4,9	
		M24			— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	7,3	7,3	
Partial factor			$\gamma_{Ms,fi}^{2)}$	1,0										

<sup>1)</sup> No performance assessed

<sup>2)</sup> In absence of other national regulations

JORDAHL anchor channel JTA, JZA and JXA

**Performance**  
Characteristic resistances under fire exposure

**Annex C20**



Table C29 (continuation): Characteristic resistances under fire exposure

Anchor channel					JTA								
					K28/15	K38/17	K40/25 W40/22	W40+	K50/30 W50/30	W50+	K53/34 W53/34	W55/42	K72/48 W72/48
<b>Steel failure: Anchor, connection between anchor and channel, local flexure of channel lip, channel bolt</b>													
Characteristic resistance	R120	M8	$N_{Rk,s,fi}$ = $V_{Rk,s,y,fi}$	[kN]	0,5	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>
		M10			0,5	0,8	0,8	0,8	0,8	0,8	0,8	— <sup>1)</sup>	— <sup>1)</sup>
		M12			0,5	0,8	0,8 1,1	1,1	1,2	1,2	1,2	— <sup>1)</sup>	— <sup>1)</sup>
		M16			— <sup>1)</sup>	1,0	1,2 1,6	1,6	2,1 2,3	2,2 2,3	2,2 2,3	2,6	— <sup>1)</sup>
		M20			— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	2,1 3,6	3,6	3,0 3,5	3,6	3,6
		M24			— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	— <sup>1)</sup>	5,4	5,4
		Partial factor			$\gamma_{Ms,fi}$ <sup>2)</sup>								

<sup>1)</sup> No performance assessed

<sup>2)</sup> In absence of other national regulations

JORDAHL anchor channel JTA, JZA and JXA

**Performance**  
Characteristic resistances under fire exposure

**Annex C21**

Fig. 1

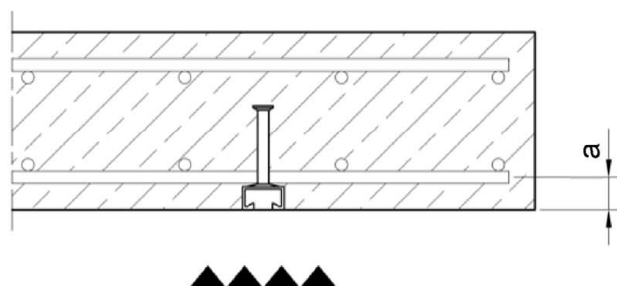


Fig. 2

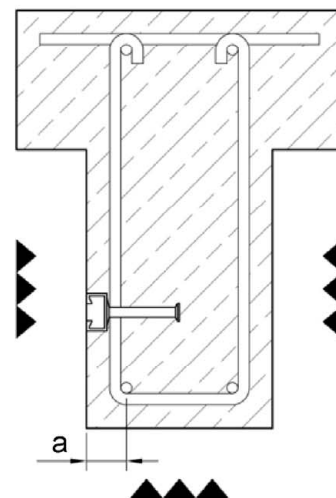


Table C30: Minimum axis distance under fire exposure

Anchor channel				JTA						
				K28/15	K38/17	K40/25 W40/22 W40+	K50/30 W50/30 W50+	K53/34 W53/34	W55/42	K72/48 W72/48
Minimum axis distance	R30	a	[mm]	35	35	35	35	50	50	50
	R60			35	35	35	35	50	50	50
	R90			45	45	45	45	50	50	50
	R120			60	60	60	60	65	70	70

JORDAHL anchor channel JTA, JZA and JXA

**Performance**  
Minimum axis distance under fire exposure

**Annex C22**

**For Design method I or II for test method A1 and A2 according to EOTA TR050, June 2022**

Table C31: Combinations of anchor channels JTA and channel bolts for fatigue tension loading

Anchor channel		Anchor		Channel bolt			
		Type	d <sub>a</sub> [mm]	Type	Thread diameter	Strength grade	Surface
JTA	W40/22	R	9,0	JC	M12	8.8	electroplated, hot-dip galvanized
					M16	4.6, 8.8	
	W40+		10,8	JC	M12	8.8	
					M16	4.6, 8.8	
	W50/30		9,0	JB	M16, M20	4.6, 8.8	
	W50+		10,0	JB	M16, M20	4.6, 8.8	
W53/34	11,5	JB	M16, M20	8.8			

Table C32: Characteristic resistances of anchor channels JTA and channel bolts under fatigue tension load with  $n$  load cycles without static preload ( $N_{Ed} = 0$  kN) – steel failure

Anchor channel		JTA				
		W40/22	W40+	W50/30	W50+	W53/34
Characteristic resistances under fatigue load in tension without static preload	Load cycles $n$	$\Delta N_{Rk,s,0,n}$ [kN]				
	$\leq 10^4$	11,7	12,8	16,5	16,5	22,2
	$\leq 10^5$	6,7	7,7	9,8	9,8	13,2
	$\leq 10^6$	3,8	4,7	5,8	5,8	7,9
	$\leq 2 \cdot 10^6$	3,2	4,0	4,9	4,9	6,7
	$\leq 5 \cdot 10^6$	2,6	3,3	4,0	4,0	5,5
	$\leq 10^8$	1,2				
	$\geq 10^8$	– <sup>1)</sup>				

<sup>1)</sup> No performance assessed

Table C33: Characteristic resistances of anchor channels JTA under fatigue tension load with  $n$  load cycles without static preload ( $N_{Ed} = 0$  kN) – concrete cone and pullout failure

Anchor channel		JTA
Reduction factor for $\Delta N_{Rk,c,0,n} = \eta_{c,fat} \cdot N_{Rk,c}$ $\Delta N_{Rk,p,0,n} = \eta_{p,fat} \cdot N_{Rk,p}$ Static resistances $N_{Rk,c}$ and $N_{Rk,p}$ according to Annex C7	Load cycles $n$	$\eta_{k,c,fat} = \eta_{k,p,fat}$ [-]
	$\leq 10^4$	0,736
	$\leq 10^5$	0,665
	$\leq 10^6$	0,600
	$\leq 2 \cdot 10^6$	0,582
	$\leq 5 \cdot 10^6$	0,559
	$\leq 6 \cdot 10^7$	0,500
	$\leq 10^8$	0,500
	$\geq 10^8$	0,500

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under fatigue tension load according test method A1 and A2 (JTA W)

**Annex C23**

For Design method I or II for test method C according to EOTA TR050, June 2022

Table C34: Combinations of anchor channels JXA and channel bolts for fatigue tension loading

Anchor channel		Anchor		Channel bolt			
		Type	$d_a; t_w$ [mm]	Type	Thread diameter	Strength grade	Surface
JXA	W38/23	R	10,0	JXH	M16	8.8	Electroplated, hot-dip galvanized
	W53/34	R, I	11,5; 6,0	JXB	M20	8.8	
	W64/44	I	7,1	JXE	M24	8.8	

Table C35: Characteristic resistances ( $\Delta N_{Rk,s,lo,n}$ ) of anchor channels JXA and channel bolts under fatigue tension load with n load cycles with characteristic lower load ( $N_{lok,s,n}$ ) – steel failure

Anchor channel		JXA					
		W38/23		W53/34		W64/44	
	Load cycles n	$\Delta N_{Rk,s,lo,n}$ [kN]	$N_{lok,s,n}$ [kN]	$\Delta N_{Rk,s,lo,n}$ [kN]	$N_{lok,s,n}$ [kN]	$\Delta N_{Rk,s,lo,n}$ [kN]	$N_{lok,s,n}$ [kN]
Characteristic resistances under fatigue tension load with static preload	$\leq 10^4$	16,0	0,0	30,0	0,0	55,0	0,0
	$2 \cdot 10^4$	16,0	0,0	29,0	0,0	45,2	0,0
	$5 \cdot 10^4$	13,3	2,5	22,5	3,0	34,6	9,4
	$1 \cdot 10^5$	10,9	4,9	18,5	6,7	28,3	16,9
	$2 \cdot 10^5$	8,9	6,9	15,2	9,7	23,1	23,0
	$5 \cdot 10^5$	6,9	9,0	11,8	12,9	17,7	29,4
	$1 \cdot 10^6$	5,6	10,2	9,7	14,9	14,5	33,2
	$2 \cdot 10^6$	4,6	11,2	8,0	16,5	11,8	36,4
	$5 \cdot 10^6$	3,5	12,3	6,2	18,1	9,1	39,6
	$1 \cdot 10^7$	3,5	12,3	6,2	18,1	7,4	41,6
	$5 \cdot 10^7$	3,5	12,3	6,2	18,1	4,6	44,9
	$\geq 10^8$	3,5	12,3	6,2	18,1	3,8	45,9

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under fatigue tension load  
according test method C (JXA)

**Annex C24**

**For Design method II for test method C according to EOTA TR050, June 2022**

Table C36: Characteristic resistances of anchor channels JXA under fatigue tension load with n load cycles with lower load share ( $S_{lok} = 2,25N_{Elok}/N_{Rk,c(p)} \leq 0,8$ ) – concrete cone and pullout failure<sup>1)</sup>

Anchor channel		JXA									
	Load cycles n	$\eta_{k,c,fat} = \eta_{k,p,fat}$ [-]									
		$S_{lok} = 0,0$	$S_{lok} = 0,1$	$S_{lok} = 0,2$	$S_{lok} = 0,3$	$S_{lok} = 0,4$	$S_{lok} = 0,5$	$S_{lok} = 0,6$	$S_{lok} = 0,7$	$S_{lok} = 0,8$	
Reduction factor for $\Delta N_{Rk,c,E,n} = \eta_{c,fat} \cdot N_{Rk,c}$ $\Delta N_{Rk,p,E,n} = \eta_{p,fat} \cdot N_{Rk,p}$	$\leq 10^4$	0,725	0,668	0,600	0,527	0,450	0,370	0,288	0,205	0,120	
	$2 \cdot 10^4$	0,704	0,650	0,585	0,514	0,439	0,360	0,279	0,197	0,114	
	$5 \cdot 10^4$	0,677	0,627	0,566	0,497	0,424	0,347	0,268	0,188	0,106	
	$1 \cdot 10^5$	0,656	0,610	0,551	0,484	0,412	0,337	0,260	0,181	0,100	
	$2 \cdot 10^5$	0,636	0,592	0,536	0,471	0,401	0,328	0,251	0,174	0,094	
Static resistances $N_{Rk,c}$ and $N_{Rk,p}$ according to Annex C9	$5 \cdot 10^5$	0,608	0,569	0,516	0,454	0,386	0,315	0,240	0,164	0,087	
	$1 \cdot 10^6$	0,588	0,551	0,501	0,441	0,375	0,305	0,232	0,157	0,081	
	$2 \cdot 10^6$	0,567	0,534	0,486	0,428	0,364	0,295	0,223	0,150	0,075	
	$5 \cdot 10^6$	0,539	0,511	0,466	0,411	0,349	0,282	0,212	0,140	0,067	
	$1 \cdot 10^7$	0,519	0,493	0,451	0,398	0,337	0,272	0,204	0,133	0,061	
	$2 \cdot 10^7$	0,498	0,476	0,436	0,385	0,326	0,262	0,195	0,126	0,055	
	$5 \cdot 10^7$	0,471	0,453	0,416	0,367	0,311	0,250	0,184	0,116	0,047	
	$\geq 10^8$	0,450	0,435	0,401	0,354	0,300	0,240	0,176	0,109	0,041	

<sup>1)</sup>  $N_{Elok}$  is the characteristic lower cyclic load on the anchor

In absence of other national regulations the following partial factors are recommended for design method I and II for all failure modes:

$\gamma_{Ms,fat} = 1,35$  (steel)

$\gamma_{Mc,fat} = \gamma_{Mp,fat} = 1,50$  (concrete)

JORDAHL anchor channel JTA, JZA and JXA

**Performance**

Characteristic resistances under fatigue tension load  
according test method C (JXA)

**Annex C25**