

Approval body for construction products
and types of construction

Bautechnisches Prüfamt

An institution established by the Federal and
Laender Governments



European Technical Assessment

ETA-19/0465
of 6 September 2023

English translation prepared by DIBt - Original version in German language

General Part

Technical Assessment Body issuing the
European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

Hilti HIT-HY 170 with HAS-U

Product family
to which the construction product belongs

Bonded fastener for use in concrete

Manufacturer

Hilti AG
Feldkircherstraße 100
9494 Schaan
FÜRSTENTUM LIECHTENSTEIN

Manufacturing plant

Hilti Corporation

This European Technical Assessment
contains

20 pages including 3 annexes which form an integral part
of this assessment

This European Technical Assessment is
issued in accordance with Regulation (EU)
No 305/2011, on the basis of

330499-01-0601, Edition 04/2020

This version replaces

ETA-19/0465 issued on 28 August 2019

European Technical Assessment

ETA-19/0465

English translation prepared by DIBt

Page 2 of 20 | 6 September 2023

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

Specific Part

1 Technical description of the product

The Injection system Hilti HIT-HY 170 is a bonded anchor consisting of a foil pack with injection mortar Hilti HIT-HY 170 and a steel element according to Annex A.

The steel element is placed into a drilled hole filled with injection mortar and is anchored via the bond between metal part, injection mortar and concrete.

The product description is given in Annex A.

2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment

3.1 Mechanical resistance and stability (BWR 1)

Characteristic resistance for static and quasi-static tension load	See Annex C1, C2, B3
Characteristic resistance for static and quasi-static shear load	See Annex C2
Displacements for static and quasi-static loads	See Annex C3
Characteristic resistance for seismic performance category C1	No performance assessed
Characteristic resistance and displacements for seismic performance category C2	See Annex C4

3.2 Hygiene, health and the environment (BWR 3)

Essential characteristic	Performance
Content, emission and/or release of dangerous substances	No performance assessed

4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with the European Assessment Document EAD 330499-01-0601 the applicable European legal act is: [96/582/EC].

The system to be applied is: 1

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Deutsches Institut für Bautechnik.

The following standards and documents are referred to in this European Technical Assessment:

- EN 1992-4:2018 Eurocode 2: Design of concrete structures - Part 4: Design of fastenings for use in concrete
- EN 1993-1-4:2006 + A1:2015 Eurocode 3: Design of steel structures - Part 1-4: General rules - Supplementary rules for stainless steels
- EN 10088-1:2014 Stainless steels - Part 1: List of stainless steels
- EN 206:2013 + A1:2016 Concrete - Specification, performance, production and conformity
- EOTA TR 055 Design of fastenings based on EAD 330232-00-0601, EAD 330499-00-0601 and EAD 330747-00-0601, February 2018

Issued in Berlin on 6 September 2023 by Deutsches Institut für Bautechnik

Dipl.-Ing. Beatrix Wittstock
Head of Section

beglaubigt:
Stiller

Installed condition

Figure A1:
Threaded rod, HAS..., HAS-U... and AM 8.8


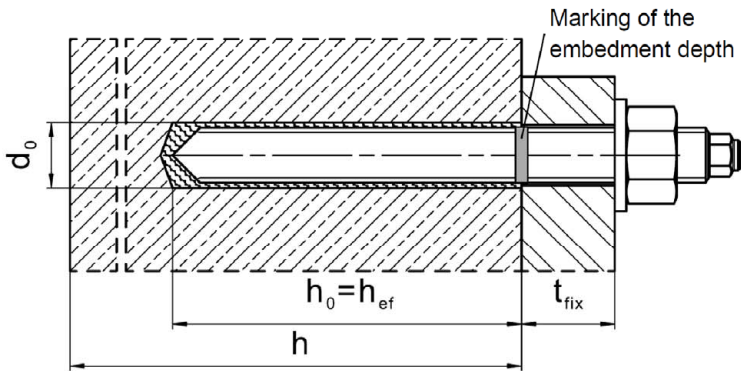


Figure A2:
Threaded rod, HAS..., HAS-U... and AM 8.8 with Hilti Filling Set

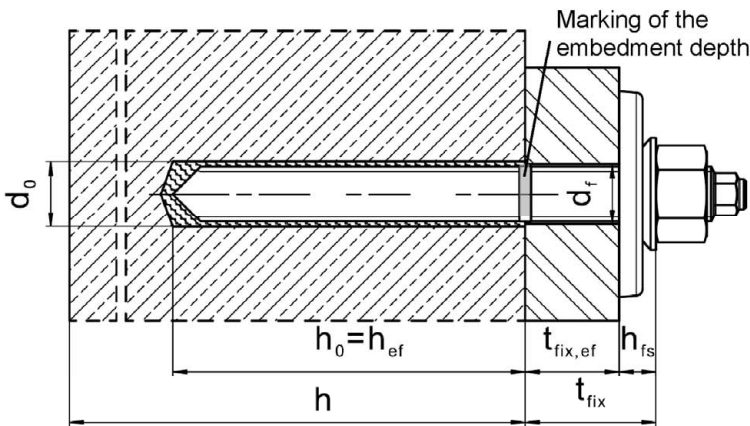


Injection system Hilti HIT-HY 170 with HAS-U

Product description
Installed condition

Annex A1

Product description: Injection mortar and steel elements



Injection mortar Hilti HIT-HY 170: hybrid system with aggregate
330 ml and 500 ml

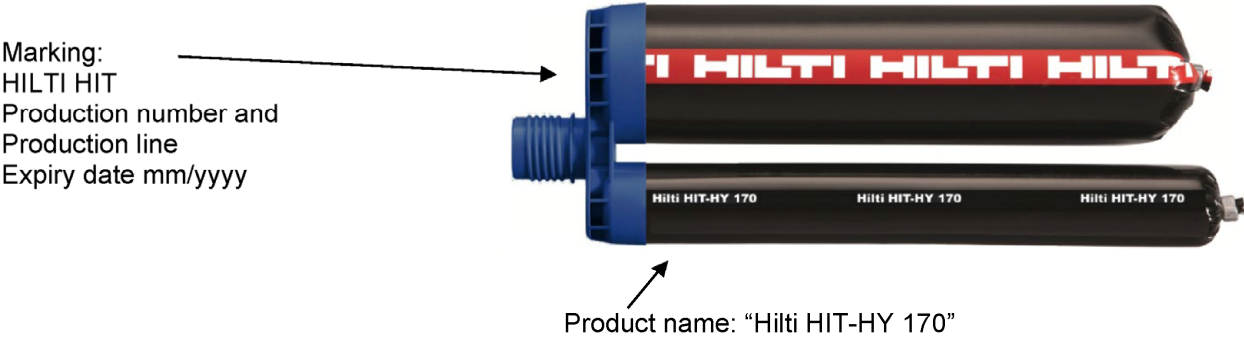

Static mixer Hilti HIT-RE-M



Steel elements

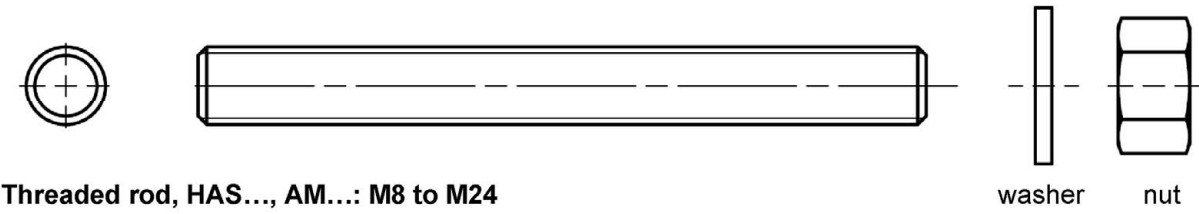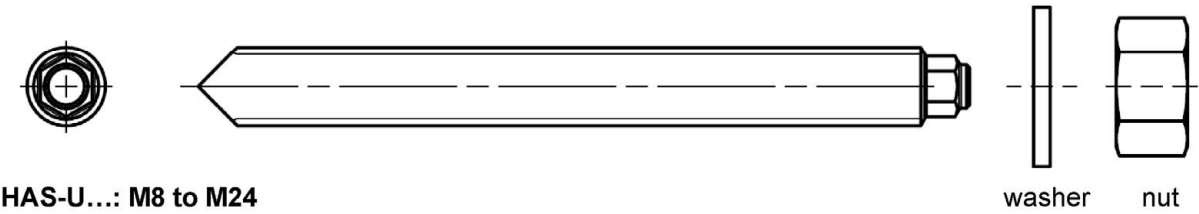


Injection system Hilti HIT-HY 170 with HAS-U

Product description
Injection mortar / Static mixer / Steel elements

Annex A2

Hilti Filling Set to fill the annular gap between anchor and fixture

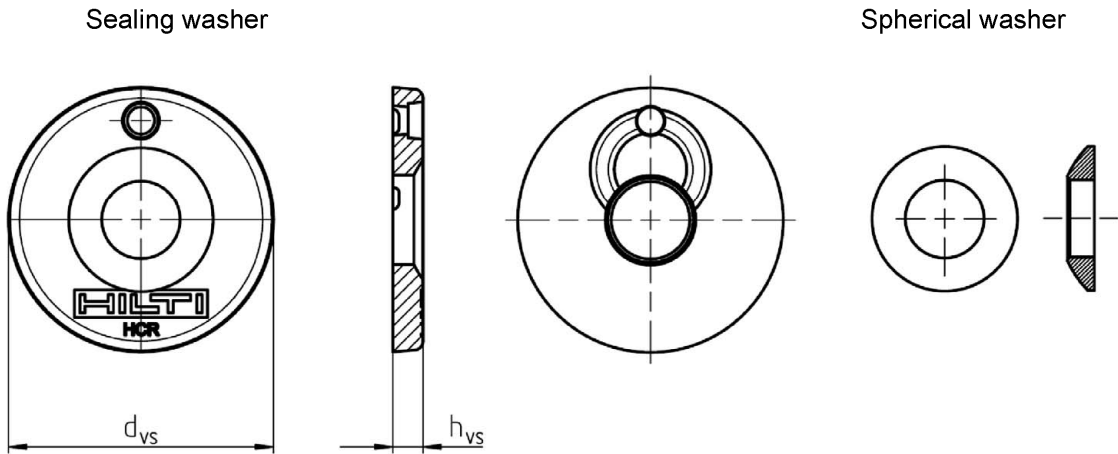

Hilti Filling Set		M12	M16
Diameter of sealing washer	d _{vs} [mm]	44	56
Thickness of sealing washer	h _{vs} [mm]	5	6
Thickness of Hilti Filling Set	h _{fs} [mm]	10	11

Injection system Hilti HIT-HY 170 with HAS-U

Product description
Steel elements

Annex A3

Table A1: Materials

Designation	Material
Steel elements made of zinc coated steel	
HAS 5.8 (HDG) HAS-U 5.8 (HDG), Threaded rod 5.8	Strength class 5.8, $f_{uk} = 500 \text{ N/mm}^2$; $f_{yk} = 400 \text{ N/mm}^2$ Elongation at fracture ($l_0=5d$) > 8% ductile Electroplated zinc coated $\geq 5 \mu\text{m}$, (HDG) Hot dip galvanized $\geq 50 \mu\text{m}$
Threaded rod 6.8	Strength class 6.8, $f_{uk} = 600 \text{ N/mm}^2$; $f_{yk} = 480 \text{ N/mm}^2$ Elongation at fracture ($l_0=5d$) > 8% ductile Electroplated zinc coated $\geq 5 \mu\text{m}$, Hot dip galvanized $\geq 50 \mu\text{m}$
HAS 8.8 (HDG) HAS-U-8.8 (HDG), AM 8.8 (HDG) Threaded rod 8.8	Strength class 8.8, $f_{uk} = 800 \text{ N/mm}^2$, $f_{yk} = 640 \text{ N/mm}^2$, Elongation at fracture ($l_0 = 5d$) > 12% ductile. Electroplated zinc coated $\geq 5 \mu\text{m}$, (F) or (HDG) Hot dip galvanized $\geq 50 \mu\text{m}$.
Washer	Electroplated zinc coated $\geq 5 \mu\text{m}$ Hot dip galvanized $\geq 50 \mu\text{m}$
Nut	Strength class of nut adapted to strength class of threaded rod. Electroplated zinc coated $\geq 5 \mu\text{m}$ Hot dip galvanized $\geq 50 \mu\text{m}$
Hilti Filling Set (F)	Filling washer: Electroplated zinc coated $\geq 5 \mu\text{m}$, (F) hot dip galvanized $\geq 50 \mu\text{m}$ Spherical washer: Electroplated zinc coated $\geq 5 \mu\text{m}$, (F) Hot dip galvanized $\geq 50 \mu\text{m}$ Lock nut: Electroplated zinc coated $\geq 5 \mu\text{m}$, (F) Electroplated zinc - nickel coated $\geq 6 \mu\text{m}$
Metal parts made of stainless steel corrosion resistance classes II according EN 1993-1-4	
Threaded rod	Strength class 70, $f_{uk} = 700 \text{ N/mm}^2$, $f_{yk} = 450 \text{ N/mm}^2$. Elongation at fracture ($l_0 = 5d$) > 12% ductile. Stainless steel 1.4301, 1.4307, 1.4311, 1.4541, 1.4306, 1.4567 EN 10088-1.
Washer	Stainless steel EN 10088-1
Nut	Strength class of nut adapted to strength class of threaded rod. Stainless steel EN 10088-1.
Metal parts made of stainless steel corrosion resistance classes III according EN 1993-1-4	
HAS A4 HAS-U A4	Strength class 70, $f_{uk} = 700 \text{ N/mm}^2$, $f_{yk} = 450 \text{ N/mm}^2$ Elongation at fracture ($l_0=5d$) > 12% ductile
Threaded rod	Strength class 70, $f_{uk} = 700 \text{ N/mm}^2$, $f_{yk} = 450 \text{ N/mm}^2$. Elongation at fracture ($l_0 = 5d$) > 12% ductile. Stainless steel 1.4401, 1.4404, 1.4578, 1.4571, 1.4439, 1.4362 EN 10088-1.
Washer	Stainless steel EN 10088-1
Nut	Strength class of nut adapted to strength class of threaded rod. Stainless steel EN 10088-1.

Injection system Hilti HIT-HY 170 with HAS-U

Product description
Materials

Annex A4

Table A2 continued

Designation	Material
Metal parts made of stainless steel corrosion resistance classes V according EN 1993-1-4	
HAS-U HCR	For $\leq M20$: $f_{uk} = 800 \text{ N/mm}^2$, $f_{yk} = 640 \text{ N/mm}^2$, For $> M20$: $f_{uk} = 700 \text{ N/mm}^2$, $f_{yk} = 400 \text{ N/mm}^2$, Elongation at fracture ($l_0=5d$) $> 12\%$ ductile
Theaded rod	For $\leq M20$: $f_{uk} = 800 \text{ N/mm}^2$, $f_{yk} = 640 \text{ N/mm}^2$, For $> M20$: $f_{uk} = 700 \text{ N/mm}^2$, $f_{yk} = 400 \text{ N/mm}^2$. Elongation at fracture ($l_0 = 5d$) $> 12\%$ ductile. High corrosion resistant steel 1.4529, 1.4565 EN 10088-1.
Washer	High corrosion resistant steel EN 10088-1.
Nut	Strength class of nut adapted to strength class of threaded rod. Stainless steel EN 10088-1.

Injection system Hilti HIT-HY 170 with HAS-U

Product description
Materials

Annex A5

Specifications of intended use

Anchorage subject to:

- Static and quasi-static loading: M8 to M24.
- Seismic performance category C2: M12 and M16.




Base material:

- Compacted reinforced or unreinforced normal weight concrete without fibres according to EN 206 + A1.
- Strength classes C20/25 to C50/60 according to EN 206 + A1.
- Cracked and uncracked concrete.

Temperature in the base material:

- **At installation**
0 °C to +40 °C for the standard variation of temperature after installation
- **In-service**
Temperature range I: -40 °C to +40 °C
(max. long term temperature +24 °C and max. short term temperature +40 °C)
Temperature range II: -40 °C to +80 °C
(max. long term temperature +50 °C and max. short term temperature +80 °C)

Table B1: Specifications of intended use

	HIT-HY 170 with ...
Elements	Threaded rod (Annex A) 
Hammer drilling with hollow drill bit TE-CD or TE-YD 	✓
Hammer drilling mode 	✓
Static and quasi-static loading in uncracked concrete	M8 to M24
Static and quasi-static loading in cracked concrete	M10 to M16
Seismic performance category C2	M12 and M16

Injection system Hilti HIT-HY 170 with HAS-U

Intended use
Specifications

Annex B1

Use conditions (Environmental conditions):

- Structures subject to dry internal conditions (all materials).
- For all other conditions according EN 1993-1-4 corresponding to corrosion resistance classes Annex A (stainless steels).

Design:

- Anchorages are designed under the responsibility of an engineer experienced in anchorages and concrete work.
- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the anchor is indicated on the design drawings (e. g. position of the anchor relative to reinforcement or to supports, etc.).
- The anchorages are designed in accordance with:
EN 1992-4 and EOTA Technical Report TR 055.

Installation:

- Use category: dry or wet concrete (not in flooded holes) for all drilling techniques.
- Drilling technique:
 - Hammer drilling,
 - Hammer drilling with Hilti hollow drill bit TE-CD, TE-YD
- Installation direction D3: downward, horizontal and upward (e.g. overhead) installation admissible for all elements.
- Anchor installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site.

Injection system Hilti HIT-HY 170 with HAS-U

Intended use
Specifications

Annex B2

Table B2: Installation parameters of threaded rod according to Annex A

Threaded rod according to Annex A			M8	M10	M12	M16	M20	M24
Diameter of element	d	[mm]	8	10	12	16	20	24
Nominal diameter of drill bit	d ₀	[mm]	10	12	14	18	22	28
Range of effective embedment depth and depth of drilled hole	h _{ef} = h ₀	[mm]	60 to 96	60 to 120	70 to 144	80 to 192	90 to 240	96 to 288
Maximum diameter of clearance hole in the fixture	d _f	[mm]	9	12	14	18	22	26
Thickness of Hilti Filling Set	h _{fs}	[mm]	-	-	10	11	-	-
Effective fixture thickness with Hilti Filling Set	t _{fix,ef}	[mm]	t _{fix,ef} = t _{fix} - h _{fs}					
Minimum thickness of concrete member	h _{min}	[mm]	h _{ef} + 30 mm ≥ 100 mm			h _{ef} + 2 · d ₀		
Maximum torque moment	T _{max}	[Nm]	10	20	40	80	150	200
Minimum spacing	s _{min}	[mm]	40	50	60	75	90	115
Minimum edge distance	c _{min}	[mm]	40	45	45	50	55	60

HAS-U...



Marking:

Steel grade number and length identification letter: e.g. 8L

Threaded rod, HAS..., and AM...



HAS Colour code marking:

5.8 = RAL 5010 (blue)
8.8 = RAL 1023 (yellow)
A4 = RAL 3000 (red)

Table B3: Maximum working time and minimum curing time¹⁾

Temperature in the base material T ²⁾	Maximum working time t _{work}	Minimum curing time t _{cure}
0°C to 5°C	10 min	5 h
> 5°C to 10°C	8 min	2,5 h
> 10°C to 20°C	5 min	1,5 h
> 20°C to 30°C	3 min	45 min
> 30°C to 40°C	2 min	30 min

¹⁾ The curing time data are valid for dry base material only. In wet base material the curing times must be doubled.

²⁾ The minimum temperature of the injection mortar Hilti HIT-HY 170 during installation is + 5°C






Injection system Hilti HIT-HY 170 with HAS-U

Intended use

Installation parameters of threaded rod, HAS..., HAS-U... and AM 8.8
Maximum working time and minimum curing time

Annex B3

Table B4: Parameters of cleaning and setting tools

Elements	Drill and clean			Installation
Threaded rod (Annex A)	Hammer drilling	Hollow drill bit ¹⁾	Brush	Piston plug
				
size	d ₀ [mm]	d ₀ [mm]	HIT-RB	HIT-SZ
M8	10	-	10	-
M10	12	12	12	12
M12	14	14	14	14
M16	18	18	18	18
M20	22	22	22	22
M24	28	28	28	28

¹⁾ With vacuum cleaner Hilti VC 10/20/40 (automatic filter cleaning activated, eco mode off) or a vacuum cleaner providing equivalent cleaning performance in combination with the specified Hilti hollow drill bit TE-CD or TE-YD.

Cleaning alternatives

Manual Cleaning (MC):

Hilti hand pump for blowing out drill holes with diameters $d_0 \leq 18$ mm and drill hole depths $h_0 \leq 10 \cdot d$



Compressed air cleaning (CAC):

Air nozzle with an orifice opening of minimum 3,5 mm in diameter.



Automatic Cleaning (AC):

Cleaning is performed during drilling with Hilti TE-CD and TE-YD drilling system including vacuum cleaner.



Injection system Hilti HIT-HY 170 with HAS-U


Intended use
Cleaning and setting tools
Cleaning alternatives

Annex B4

Installation


Hole drilling

a) Hammer drilling

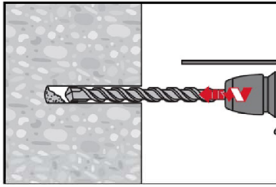

Drill hole to the required embedment depth with a hammer drill set in rotation-hammer mode using an appropriately sized carbide drill bit.

b) Hammer drilling with Hilti hollow drill bit

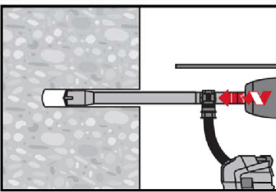


Drill hole to the required embedment depth with an appropriately sized Hilti TE-CD or TE-YD hollow drill bit with vacuum attachment following the requirements given in Table B4. This drilling system removes the dust and cleans the bore hole during drilling when used in accordance with the user's manual. After drilling is completed, proceed to the "injection preparation" step in the installation instruction.

Drill hole cleaning


Just before setting an anchor, the drill hole must be free of dust and debris.

Manual Cleaning (MC)


Non-cracked concrete.
For drill hole diameters $d_0 \leq 18$ mm and drill hole depths $h_0 \leq 10 \cdot d$

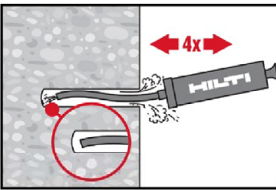

The Hilti manual pump may be used for blowing out drill holes up to diameters $d_0 \leq 18$ mm and embedment depths up to $h_{ef} \leq 10 \cdot d$. Blow out at least 4 times from the back of the drill hole until return air stream is free of noticeable dust

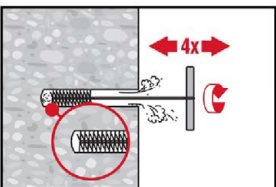

Brush 4 times with the specified brush (see Table B4) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the drill hole (brush $\varnothing \geq$ drill hole \varnothing) - if not the brush is too small and must be replaced with the proper brush diameter.

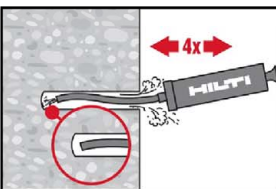


Blow out again with manual pump at least 4 times until return air stream is free of noticeable dust.

Injection system Hilti HIT-HY 170 with HAS-U


Intended use
Installation instructions

Annex B5


Compressed air cleaning (CAC) for all drill hole diameters d_0 and all drill hole depths h_0

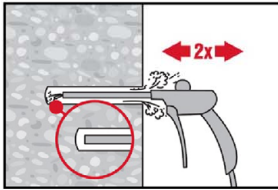

Blow 2 times from the back of the hole (if needed with nozzle extension) over the hole length with oil-free compressed air (min. 6 bar at 6 m³/h) until return air stream is free of noticeable dust.

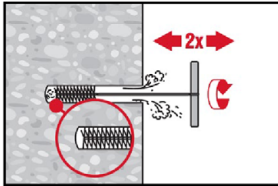


Brush 2 times with the specified brush (see Table B4) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it.
The brush must produce natural resistance as it enters the drill hole (brush $\varnothing \geq$ drill hole \varnothing) - if not the brush is too small and must be replaced with the proper brush diameter.

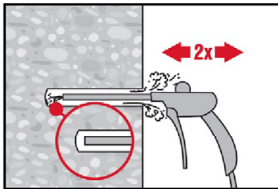


Blow again with compressed air 2 times until return air stream is free of noticeable dust.

Injection preparation

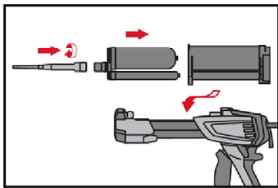


Tightly attach new Hilti mixing nozzle HIT-RE-M to foil pack manifold (snug fit). Do not modify the mixing nozzle.
Observe the instruction for use of the dispenser.
Check foil pack holder for proper function. Do not use damaged foil packs / holders.
Insert foil pack into foil pack holder and put holder into HIT-dispenser.

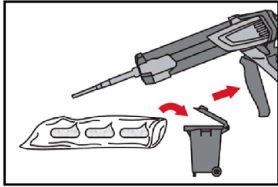


Discard initial adhesive. The foil pack opens automatically as dispensing is initiated. Depending on the size of the foil pack an initial amount of adhesive has to be discarded. Discarded quantities are

2 strokes	for 330 ml foil pack,
3 strokes	for 500 ml foil pack

Inject adhesive from the back of the drill hole without forming air voids.

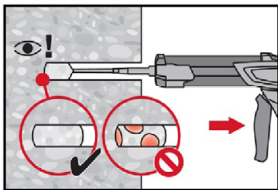

Inject the adhesive starting at the back of the hole, slowly withdrawing the mixer with each trigger pull.
Fill approximately 2/3 of the drill hole to ensure that the annular gap between the anchor and the concrete is completely filled with adhesive along the embedment length.
In water saturated concrete it is required to set the fastener immediately after cleaning the drillhole.

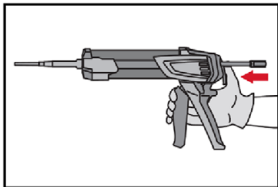


After injection is completed, depressurize the dispenser by pressing the release trigger. This will prevent further adhesive discharge from the mixer.

Injection system Hilti HIT-HY 170 with HAS-U


Intended use
Installation instructions

Annex B6

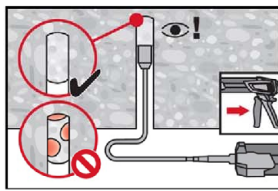


Overhead installation and/or installation with embedment depth $h_{ef} > 250\text{mm}$. For overhead installation the injection is only possible with the aid of extensions and piston plugs. Assemble HIT-RE-M mixer, extension(s) and appropriately sized piston plug HIT-SZ (see Table B4). Insert piston plug to back of the hole and inject adhesive. During injection the piston plug will be naturally extruded out of the drill hole by the adhesive pressure


Setting the element

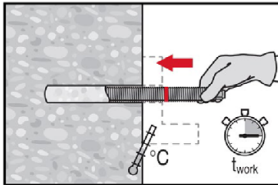

Before use, verify that the element is dry and free of oil and other contaminants. Mark and set element to the required embedment depth until working time t_{work} (see Table B3) has elapsed.

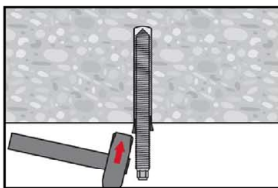


For overhead installation use piston plugs and fix embedded parts with e.g. wedges (HIT-OHW).

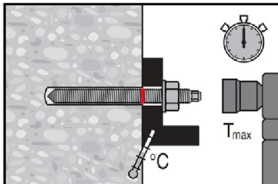


Loading the anchor: After required curing time t_{cure} (see Table B3) the anchor can be loaded. The applied installation torque shall not exceed the values T_{max} given in Table B2.


Installation of Hilti Filling Set

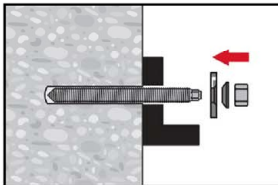


Use Hilti Filling Set with standard nut. Observe the correct orientation of filling washer and spherical washer.

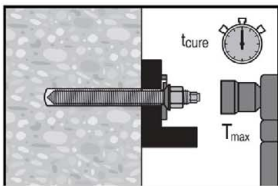

The applied installation torque shall not exceed the values T_{max} given in Table B2.

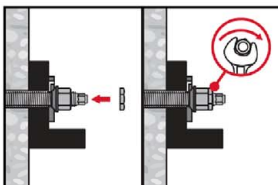

Optional:
Installation of lock nut. Tighten with a $\frac{1}{4}$ to $\frac{1}{2}$ turn.

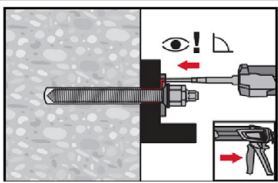

Fill the annular gap between the anchor rod and fixture with 1-3 strokes of Hilti injection mortar HIT-HY 170. Follow the installation instructions supplied with the foil pack. After required curing time t_{cure} the anchor can be loaded.

Injection system Hilti HIT-HY 170 with HAS-U

Intended use
Installation instructions

Annex B7

Table C1: Essential characteristics for threaded rod according to Annex A under tension load in concrete

Threaded rod according to Annex A			M8	M10	M12	M16	M20	M24
Installation factor		γ_{inst}	[-]		1,0			
Steel failure								
Characteristic resistance		$N_{Rk,s}$	[kN]		$A_s \cdot f_{uk}$			
Partial factor grade 5.8, 6.8 and 8.8		$\gamma_{Ms,N}^{1)}$	[-]		1,5			
Partial factor HAS A4, HAS-U A4, Threaded rod: CRC II and III (Table A1)		$\gamma_{Ms,N}^{1)}$	[-]		1,87			
Partial factor HAS-U HCR, Threaded rod: CRC V (Table A1)		$\gamma_{Ms,N}^{1)}$	[-]		1,5			2,1
Combined pullout and concrete cone failure								
Characteristic bond resistance in uncracked concrete C20/25								
Temperature range I: 24 °C / 40 °C		$\tau_{Rk,ucr}$	[N/mm ²]		10,0			
Temperature range II: 50 °C / 80 °C		$\tau_{Rk,ucr}$	[N/mm ²]		7,5			
Characteristic bond resistance in cracked concrete C20/25								
Temperature range I: 24 °C / 40 °C		$\tau_{Rk,cr}$	[N/mm ²]		2)	5,5		2)
Temperature range II: 50 °C / 80 °C		$\tau_{Rk,cr}$	[N/mm ²]		2)	4,0		2)
Influence factors ψ on bond resistance τ_{Rk} in cracked and uncracked concrete								
Influence of concrete strength class: $\tau_{Rk} = \tau_{Rk,(C20/25)} \cdot \psi_c$		ψ_c	C30/37		1,04			
			C40/50		1,07			
			C50/60		1,09			
Sustained load factor		ψ_{sus}^0	24 °C / 40 °C		0,95			
			50 °C / 80 °C		0,79			
Concrete cone failure								
Factor for uncracked concrete		$k_{ucr,N}$	[-]		11,0			
Factor for cracked concrete		$k_{cr,N}$	[-]		7,7			
Edge distance		$c_{cr,N}$	[mm]		$1,5 \cdot h_{ef}$			
Spacing		$s_{cr,N}$	[mm]		$3,0 \cdot h_{ef}$			

Injection system Hilti HIT-HY 170 with HAS-U

Performances
Essential characteristics under tension load in concrete

Annex C1

Table C2 continued

Splitting failure			
Edge distance $c_{cr,sp}$ [mm] for	$h / h_{ef} \geq 2,0$	$1,0 \cdot h_{ef}$	
	$2,0 > h / h_{ef} > 1,3$	$4,6 h_{ef} - 1,8 h$	
	$h / h_{ef} \leq 1,3$	$2,26 h_{ef}$	
Spacing	$s_{cr,sp}$	[mm]	$2 \cdot c_{cr,sp}$

1) In absence of national regulations.

2) No performance assessed

Table C3: Essential characteristics for threaded rod according to Annex A under shear load in concrete

Threaded rod according to Annex A			M8	M10	M12	M16	M20	M24
Steel failure without lever arm								
Characteristic resistance	$V_{Rk,s}$	[kN]	$0,5 \cdot A_s \cdot f_{uk}$					
Partial factor grade 5.8, 6.8 and 8.8	$\gamma_{Ms,V^{(1)}}$	[-]	1,25					
Partial factor HAS A4, HAS-U A4, Threaded rod: CRC II and III (Table A1)	$\gamma_{Ms,V^{(1)}}$	[-]	1,56					
Partial factor HAS-U HCR, Threaded rod: CRC V (Table A1)	$\gamma_{Ms,V^{(1)}}$	[-]	1,25					1,75
Ductility factor	k_7	[-]	1,0					
Steel failure with lever arm								
Bending moment	$M^0_{Rk,s}$	[Nm]	$1,2 \cdot W_{el} \cdot f_{uk}$					
Ductility factor	k_7	[-]	1,0					
Concrete pry-out failure								
Pry-out factor	k_8	[-]	2,0					
Concrete edge failure								
Effective length of fastener	l_f	[mm]	$\min(h_{ef}; 12 \cdot d_{nom})$					
Outside diameter of fastener	d_{nom}	[mm]	8	10	12	16	20	24

1) In absence of national regulations

Injection system Hilti HIT-HY 170 with HAS-U

Performances

Essential characteristics under tension and shear load in concrete

Annex C2

Table C4: Displacement under tension load

Threaded rod according to Annex A			M8	M10	M12	M16	M20	M24
Non-cracked concrete								
Displacement	δ_{N0}	[mm/(N/mm ²)]	0,07	0,07	0,07	0,08	0,08	0,09
Displacement	$\delta_{N\infty}$	[mm/(N/mm ²)]	0,07	0,07	0,07	0,08	0,08	0,09
Cracked concrete								
Displacement	δ_{N0}	[mm/(N/mm ²)]	¹⁾	0,07	0,07	0,06	¹⁾	¹⁾
Displacement	$\delta_{N\infty}$	[mm/(N/mm ²)]	¹⁾	0,11	0,11	0,11	¹⁾	¹⁾

¹⁾ No performance assessed

Table C5: Displacement under shear load

Threaded rod according to Annex A			M8	M10	M12	M16	M20	M24
Displacement	δ_{V0}	[mm/(N/mm ²)]	0,06	0,06	0,05	0,04	0,04	0,03
Displacement	$\delta_{V\infty}$	[mm/(N/mm ²)]	0,09	0,08	0,08	0,06	0,06	0,05

Injection system Hilti HIT-HY 170 with HAS-U

Performances
Displacements

Annex C3

Table C6: Essential characteristics for HAS..., HAS-U... and AM... under tension loads for seismic performance category C2

HAS..., HAS-U... and AM ...		M12	M16
Steel failure			
HAS 8.8 (HDG), HAS-U 8.8 (HDG), AM 8.8 (HDG)	$N_{Rk,s,seis}$ [kN]	67	126
Combined pullout and concrete cone failure			
Temperature range I: 24 °C / 40 °C	$\tau_{Rk,seis}$ [N/mm ²]	2,0	1,9
Temperature range II: 50 °C / 80 °C	$\tau_{Rk,seis}$ [N/mm ²]	1,4	1,3

Table C7: Essential characteristics for HAS..., HAS-U... and AM... under shear loads for seismic performance category C2

HAS..., HAS-U... and AM ...		M12	M16
Steel failure without lever arm with Hilti Filling Set			
HAS 8.8, HAS-U 8.8, AM 8.8	$V_{Rk,s,seis}$ [kN]	28	46
Steel failure without lever arm without Hilti Filling Set			
HAS 8.8, HAS-U 8.8, AM 8.8	$V_{Rk,s,seis}$ [kN]	24	40
HAS 8.8 HDG, HAS-U 8.8 HDG, AM 8.8 HDG	$V_{Rk,s,seis}$ [kN]	18	30

Table C8: Displacements under tension load for seismic performance category C2

HAS..., HAS-U... and AM ...		M12	M16
Displacement DLS	$\delta_{N,seis}(DLS)$ [mm]	0,2	0,2
Displacement ULS	$\delta_{N,seis}(ULS)$ [mm]	0,6	0,4

Table C9: Displacements under shear load for seismic performance category C2

HAS..., HAS-U... and AM ...		M12	M16
Installation with Hilti Filling Set			
Displacement DLS	$\delta_{V,seis}(DLS)$ [mm]	1,6	1,2
Displacement ULS	$\delta_{V,seis}(ULS)$ [mm]	4,5	3,2
Installation without Hilti Filling Set			
Displacement DLS: HAS 8.8, HAS-U 8.8, AM 8.8	$\delta_{V,seis}(DLS)$ [mm]	2,9	3,2
Displacement DLS: HAS 8.8 HDG, HAS-U 8.8 HDG, AM 8.8 HDG	$\delta_{V,seis}(DLS)$ [mm]	2,2	2,3
Displacement ULS: HAS 8.8, HAS-U 8.8, AM 8.8	$\delta_{V,seis}(ULS)$ [mm]	5,4	9,2
Displacement ULS: HAS 8.8, HAS-U 8.8 HDG, AM 8.8 HDG	$\delta_{V,seis}(ULS)$ [mm]	4,1	4,3

Injection system Hilti HIT-HY 170 with HAS-U

Performances

Essential characteristics for seismic performance category C2 and displacements.

Annex C4