

Approval body for construction products
and types of construction

Bautechnisches Prüfamt

An institution established by the Federal and
Laender Governments



European Technical Assessment

ETA-20/0475
of 28 August 2023

English translation prepared by DIBt - Original version in German language

General Part

Technical Assessment Body issuing the
European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

Connector Hilti HCC-K with Injectionmortar Hilti HIT-HY
200-A V3, Hilti HIT-HY 200-R V3, Hilti HIT-RE 500 V3 and
Hilti HIT-RE 500 V4

Product family
to which the construction product belongs

Connector for Strengthening of existing concrete
structures by concrete overlay

Manufacturer

Hilti Aktiengesellschaft
Feldkircherstrasse 100
9494 SCHAAN
FÜRSTENTUM LIECHTENSTEIN

Manufacturing plant

Hilti Werke

This European Technical Assessment
contains

25 pages including 3 annexes which form an integral part
of this assessment

This European Technical Assessment is
issued in accordance with Regulation (EU)
No 305/2011, on the basis of

332347-00-0601, Edition 09/2022

This version replaces

ETA-20/0475 issued on 15 June 2021

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

Specific Part

1 Technical description of the product

The Connector Hilti HCC-K is a headed fastener made of steel anchored with Injectionmortar Hilti HIT-HY 200-A V3, Hilti HIT-HY 200-R V3, Hilti HIT-RE 500 V3 or Hilti HIT-RE 500 V4 into a predrilled cylindrical drill hole in existing concrete. The Hilti HCC-K is connecting two layers of concrete cast at different times (existing concrete and concrete overlay). The side with the anchor head of Hilti HCC-K is finally embedded in the concrete overlay.

The product description is given in Annex A.

2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment

3.1 Mechanical resistance and stability (BWR 1)

Essential characteristic	Performance
Existing concrete: - resistances - edge distance and spacing	See Annex C 1 to C 5 See Annex B 3
Concrete overlay: - resistances - edge distance and spacing	See Annex C 6 See Annex B 3
Shear interface parameter under static and quasi-static and fatigue cyclic loading - material and geometric parameters - factor for fatigue cyclic loading	See Annex C 6 No performance assessed

3.2 Safety in case of fire (BWR 2)

Essential characteristic	Performance
Reaction to fire	Class A1

4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with European Assessment Document EAD No. 332347-00-0601 the applicable European legal act is: [96/582/EC].

The system to be applied is: 1

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited with Deutsches Institut für Bautechnik.

The following standards and documents are referred to in this European Technical Assessment:

- EN 1992-1-1:2004 + AC:2010 Eurocode 2: Design of concrete structures - Part 1-1: General rules and rules for buildings
- EN 206:2013 + A1:2016 Concrete - Specification, performance, production and conformity
- EOTA TR 066:2019 Design and requirements for construction works of post-installed shear connection for two concrete layers


Issued in Berlin on 28 August 2023 by Deutsches Institut für Bautechnik

Dipl.-Ing. Beatrix Wittstock
Head of Section

beglaubigt:
Tempel

Installed condition

Figure A1:
Connector Hilti HCC-K

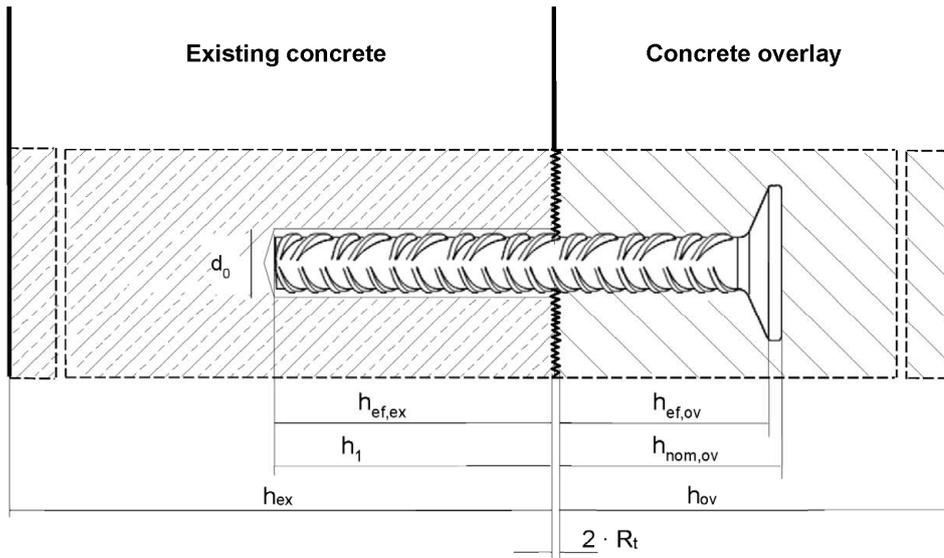

$h_{ef,ex}$ Effective embedment depth in existing concrete
 h_1 Drill hole depth
 h_{ex} Thickness of existing concrete
 R_t Roughness according to EOTA Technical Report TR 066

$h_{ef,ov}$ Effective embedment depth in concrete overlay
 $h_{nom,ov}$ Overall embedment depth in the concrete overlay
 h_{ov} Thickness of concrete overlay


Connector Hilti HCC-K

Product description
Installed condition

Annex A1

Product description: Connector and injection mortar

Steel element Hilti HCC-K, size 10, 12, 14, 16

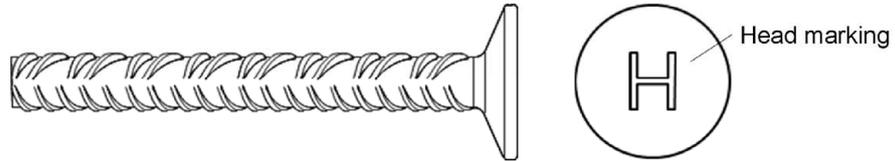

**Injection mortar Hilti HIT-HY 200-A V3 and HIT-HY 200-R V3: hybrid system with aggregate
330 ml and 500 ml**

Marking:
HILTI HIT
HY 200-A V3
Production time and production line
Expiry date mm/yyyy



Product name: "Hilti HIT-HY 200-A V3"

Marking:
HILTI HIT
HY 200-R V3
Production time and production line
Expiry date mm/yyyy



Product name: "Hilti HIT-HY 200-R V3"

Connector Hilti HCC-K

Product description
Steel element / Injection mortar

Annex A2

Injection mortar Hilti HIT-RE 500 V3: epoxy resin system with aggregate
330 ml, 500 ml and 1400 ml

Marking:
HILTI HIT
Product name
Production time and line
Expiry date mm/yyyy



Product name: "Hilti HIT-RE 500 V3"

Injection mortar Hilti HIT-RE 500 V4: epoxy resin system with aggregate
330 ml, 500 ml and 1400 ml

Marking:
HILTI HIT
Product name
Production time and line
Expiry date mm/yyyy



Product name: "Hilti HIT-RE 500 V4"

Static mixer Hilti HIT-E-M



Connector Hilti HCC-K

Product description
Injection mortar / Static mixer


Annex A3

Table A1: Materials

Designation	Material
HCC-K	Reinforcing bar B500B according to EN 1992-1-1, Annex C Strength: $f_{uk} \geq 550 \text{ N/mm}^2$, $f_{yk} \geq 500 \text{ N/mm}^2$ Strain at maximum force $\epsilon_{uk} \geq 5\%$

Table A2: Specification

Connector Hilti HCC-K			10	12	14	16
Rebar diameter	ϕ	[mm]	10	12	14	16
Overall length	L	[mm]	100 to 650	140 to 650	200 to 650	230 to 650
Diameter of the head	d_h	[mm]	30	36	42	48
Thickness of the head	t_h	[mm]	2	2	2	2

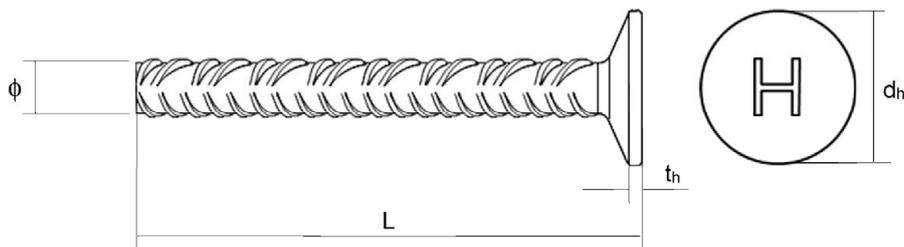

Connector Hilti HCC-K

Product description
Materials / Specification

Annex A4

Specifications of intended use

Anchorage subject to:

- static and quasi-static loading
 - surface roughness “very smooth” to “very rough” of the shear interface according to EOTA Technical Report TR 066.

Base material (existing concrete and concrete overlay):

- Compacted reinforced or unreinforced normal weight concrete without fibres according to EN 206.
- Strength classes C20/25 to C50/60 according to EN 206.
- Cracked and uncracked concrete.

Temperature in the base material (existing concrete):

For use with **HIT-HY 200-A V3** and **HIT-HY 200-R V3**

- **at installation:**
-10 °C to +40 °C for the standard variation of temperatures after installation
- **in-service:**
 - Temperature range I: -40 °C to +40 °C
(max. long term temperature +24 °C and max. short term temperature +40 °C)
 - Temperature range II: -40 °C to +80 °C
(max. long term temperature +50 °C and max. short term temperature +80 °C)
 - Temperature range III: -40 °C to +120 °C
(max. long term temperature +72 °C and max. short term temperature +120 °C)

For use with **HIT-RE 500 V3**

- **at installation:**
-5 °C to +40 °C for the standard variation of temperatures after installation
- **in-service:**
 - Temperature range I: -40 °C to +40 °C
(max. long term temperature +24 °C and max. short term temperature +40 °C)
 - Temperature range II: -40 °C to +70 °C
(max. long term temperature +43 °C and max. short term temperature +70 °C)

For use with **HIT-RE 500 V4**

- **at installation:**
-5 °C to +40 °C for the standard variation of temperatures after installation
- **in-service:**
 - Temperature range I: -40 °C to +40 °C
(max. long term temperature +24 °C and max. short term temperature +40 °C)
 - Temperature range II: -40 °C to +55 °C
(max. long term temperature +43 °C and max. short term temperature +55 °C)
 - Temperature range III: -40 °C to +75 °C
(max. long term temperature +55 °C and max. short term temperature +75 °C)

Connector Hilti HCC-K

Intended use
Specifications

Annex B1

Design:

- The design of an anchorage and the specification of the fastener is under the control of an engineer experienced in anchorages and concrete work.
- Post-installed shear connections are designed in accordance with EOTA Technical Report TR 066.
- For the concrete overlay following requirements on the mixture apply:
 - Concrete compressive strength of the new concrete shall be higher than the concrete compressive strength of the existing concrete.
 - Use of concrete with low shrinkage is recommended.
 - Slump of fresh concrete $f \geq 380$ mm, a slump value $f \geq 450$ mm is recommended, if applicable.

Installation:

- Use category (existing concrete):
 - dry or wet concrete condition: all injection mortars. HIT-HY 200-A V3 and HIT-HY 200-R V3, HIT-RE 500 V3 and HIT-RE 500 V4, HIT-HY 170.
 - water-filled drill holes:
 - HIT-RE 500 V3 and HIT-RE 500 V4: for hammer drilling only, for uncracked concrete only.
 - HIT-HY 200-A V3 and HIT-HY 200-R V3: for hammer drilling only, cracked and uncracked concrete.
- Installation direction in existing concrete is downward and horizontal and upwards (e.g. overhead) installation (D3).
- The fastener installation is executed by trained personnel, ensuring that the Installation instruction and the specifications by the engineer are observed.
- The requirements for construction works given in EOTA Technical Report TR 066 have to be considered.

Connector Hilti HCC-K	Annex B2
Intended use Specifications	


Table B1: Installation parameters of connector Hilti HCC-K in existing concrete

Connector Hilti HCC-K			10	12	14	16
Effective embedment depth and drill hole depth	$h_{ef,ex}$ $= h_1$	[mm]	60	70	75	80
			200	240	280	320
Nominal diameter of drill bit	d_0	[mm]	12 ¹⁾ 14 ¹⁾	14 ¹⁾ 16 ¹⁾	18	20
Minimum thickness of existing concrete	$h_{min,ex}$	[mm]	max (100; $h_{ef} + 30$, $h_{ef} + 2 \cdot d_0$)			
Minimum spacing	$s_{min,ex}$	[mm]	50	60	70	80
Minimum edge distance	$c_{min,ex}$	[mm]	45	45	50	50

1) Each of the two given values can be used.

Table B2: Installation parameters of connector Hilti HCC-K in concrete overlay

Connector Hilti HCC-K			10	12	14	16
Effective embedment depth	$\frac{\text{min. } h_{ef,ov}}{\text{max. } h_{ef,ov}}$	[mm]	40			
			$L - h_{nom,ex} - t_h - 2 \cdot R_t$ ¹⁾			
Overall embedment depth	$h_{nom,ov}$	[mm]	$h_{ef,ov} + t_h$			
Minimum thickness of concrete overlay	$h_{min,ov}$	[mm]	$h_{nom,ov} + c_{nom}$ ²⁾			
Minimum spacing	$s_{min,ov}$	[mm]	60	75	85	100
Minimum edge distance	$c_{min,ov}$	[mm]	$15 + c_{nom}$ ²⁾	$20 + c_{nom}$ ²⁾	$25 + c_{nom}$ ²⁾	$25 + c_{nom}$ ²⁾

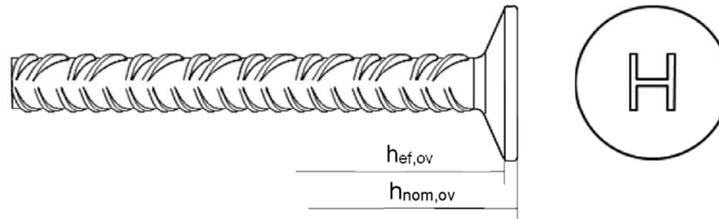

1) R_t : Roughness according to EOTA Technical Report TR 066

2) c_{nom} : Minimum concrete cover according EN 1992-1-1

Connector Hilti HCC-K

Intended use
Installation parameters

Annex B3

**Table B3: Working time and curing time for
Hilti HIT-HY 200-A V3 and Hilti HIT-HY 200-R V3**

Temperature in the base material T ¹⁾	HIT-HY 200-A V3		HIT-HY 200-R V3	
	Maximum working time t_{work}	Minimum curing time t_{cure}	Maximum working time t_{work}	Minimum curing time t_{cure}
-10 °C to -5 °C	1,5 hours	7 hours	3 hours	20 hours
> -5 °C to 0 °C	50 min	4 hours	1,5 hours	8 hours
> 0 °C to 5 °C	25 min	2 hours	45 min	4 hours
>5 °C to 10 °C	15 min	75 min	30 min	2,5 hours
>10 °C to 20 °C	7 min	45 min	15 min	1,5 hours
>20 °C to 30 °C	4 min	30 min	9 min	1 hours
>30 °C to 40 °C	3 min	30 min	6 min	1 hours

¹⁾ The minimum temperature of the foil pack is 0° C.

**Table B4: Working time and curing time for
Hilti HIT-RE 500 V3 and Hilti HIT-RE 500 V4 ¹⁾²⁾**

Temperature in the base material T	Maximum working time t_{work}	Minimum curing time t_{cure}
-5 °C to -1 °C	2 hours	168 hours
0 °C to 4 °C	2 hours	48 hours
5 °C to 9 °C	2 hours	24 hours
10 °C to 14 °C	1,5 hours	16 hours
15 °C to 19 °C	1 hour	16 hours
20 °C to 24 °C	30 min	7 hours
25 °C to 29 °C	20 min	6 hours
30 °C to 34 °C	15 min	5 hours
35 °C to 39 °C	12 min	4,5 hours
40 °C	10 min	4 hours

¹⁾ The curing time data are valid for dry base material only. In wet base material the curing times must be doubled.

²⁾ The minimum temperature of the foil pack is +5° C.

Connector Hilti HCC-K

Intended use
Working time and curing time

Annex B4

Table B5: Overview of installation options

Concrete condition	Drilling	Cleaning	HCC-K with ...		
			HIT-HY 200-A V3 HIT-HY 200-R V3	HIT-RE 500 V3	HIT-RE 500 V4
Dry / wet	Hammer drilling with hollow drill bit TE-CD or TE-YD 	Automatic	✓	✓	✓
	Hammer drilling 	Manual cleaning	✓	-	-
		Compressed air cleaning	✓	✓	✓
	Diamond coring with roughening tool TE-YRT 	Cleaning of diamond cored holes with roughening	✓	✓	✓
Diamond coring 	Cleaning of diamond cored holes	-	✓	✓	
Water-filled drill hole	Hammer drilling 	Cleaning for water-filled drill holes	✓	✓	✓

Table B6: Parameters of cleaning and setting tools

Elements	Drill and clean					Installation
	Hammer drilling		Diamond coring		Brush	
HCC-K		Hollow drill bit TE-CD, TE-YD ¹⁾		Roughening tool TE-YRT		Piston plug
						
size	d ₀ [mm]	d ₀ [mm]	d ₀ [mm]	d ₀ [mm]	HIT-RB	HIT-SZ
10	12	12	12	-	12	12
	14	14	14	-	14	14
12	14	14	14	-	14	14
	16	16	16	-	16	16
14	18	18	18	18	18	18
16	20	20	20	20	20	20

¹⁾ With vacuum cleaner Hilti VC 10/20/40 (automatic filter cleaning activated, eco mode off) or a vacuum cleaner providing equivalent cleaning performance in combination with the specified Hilti hollow drill bit TE-CD or TE-YD.

Connector Hilti HCC-K

Intended use

Overview of installation options / Parameters of cleaning and setting tools

Annex B5

Table B7: Cleaning alternatives

<p>Manual Cleaning (MC) for use with HIT-HY 200-R V3 only: Hilti hand pump for blowing out drill holes with diameters $d_0 \leq 20$ mm and drill hole depths $h_0 \leq 10 \cdot d$.</p>	
<p>Compressed air cleaning (CAC): Air nozzle with an orifice opening of minimum 3,5 mm in diameter.</p>	
<p>Automatic Cleaning (AC): Cleaning is performed during drilling with Hilti TE-CD and TE-YD drilling system including vacuum cleaner.</p>	

Table B8: Parameters for use of the Hilti Roughening tool TE-YRT

Associated components			
Diamond coring		Roughening tool TE-YRT	Wear gauge RTG...
			
d_0 [mm]		d_0 [mm]	size
nominal	measured		
18	17,9 to 18,2	18	18
20	19,9 to 20,2	20	20

Table B9: Installation parameters for use of the Hilti Roughening tool TE-YRT

	Roughening time t_{roughen}	Minimum blowing time t_{blowing}
$h_{\text{ef,ex}}$ [mm]	$t_{\text{roughen}} [\text{sec}] = h_{\text{ef,ex}} [\text{mm}] / 10$	$t_{\text{blowing}} [\text{sec}] = t_{\text{roughen}} [\text{sec}] + 20$
0 to 100	10	30
101 to 200	20	40
201 to 300	30	50
301 to 400	40	60

Table B10: Hilti Roughening tool TE-YRT and wear gauge RTG

TE-YRT	
RTG	

Connector Hilti HCC-K


Intended use
Cleaning alternatives / Parameters for use of roughening tool

Annex B6

Installation instruction


Hole drilling

a) Hammer drilling

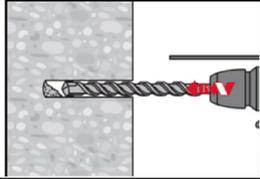


Drill hole to the required embedment depth with a hammer drill set in rotation-hammer mode using an appropriately sized carbide drill bit.

b) Hammer drilling with Hilti hollow drill bit

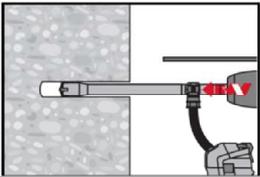


Drill hole to the required embedment depth with an appropriately sized Hilti TE-CD or TE-YD hollow drill bit with vacuum attachment following the requirements given in Table B6. This drilling system removes the dust and cleans the drill hole during drilling when used in accordance with the user's manual. After drilling is completed, proceed to the "injection preparation" step in the installation instruction.

c) Diamond coring with roughening with Hilti roughening tool TE-YRT:

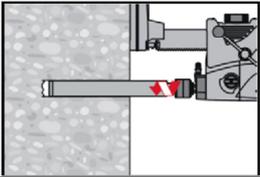


Diamond coring is permissible when suitable diamond core drilling machines and the corresponding core bits are used. For the use in combination with Hilti roughening tool TE-YRT see parameters in Table B8 and Table B9.

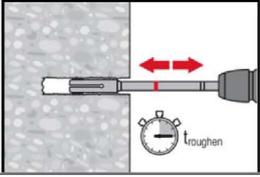

Before roughening water needs to be removed from the drill hole. Check usability of the roughening tool with the wear gauge RTG. Roughen the drill hole over the whole length to the required $h_{\text{ref,ex}}$.

d) Diamond coring: For dry and wet concrete only, for use with **HIT-RE 500 V3** and **HIT-RE 500 V4**

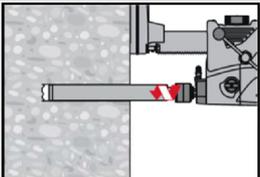


Diamond coring is permissible when suitable diamond core drilling machines and the corresponding core bits are used.

Drill hole cleaning

Just before setting an anchor, the drill hole must be free of dust and debris. Inadequate hole cleaning = poor load values.

Manual Cleaning (MC), for use with **HIT-HY 200-A V3** and **HIT-HY 200-R V3** only

Uncracked concrete only. For drill hole diameters $d_0 \leq 20$ mm and drill hole depths $h_0 \leq 10 \cdot d$.








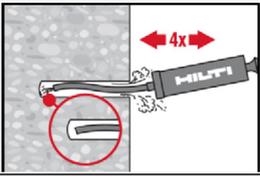


The Hilti hand pump may be used for blowing out drill holes up to diameters $d_0 \leq 20$ mm and drill hole depths $h_0 \leq 10 \cdot d$. Blow out at least 4 times from the back of the drill hole until return air stream is free of noticeable dust.

Connector Hilti HCC-K


Intended use
Installation instructions

Annex B7

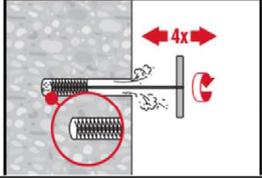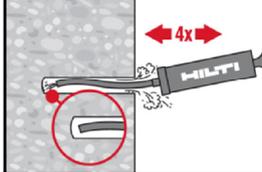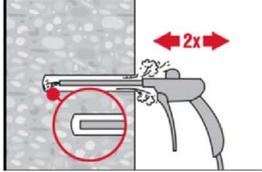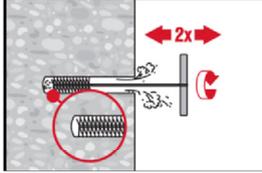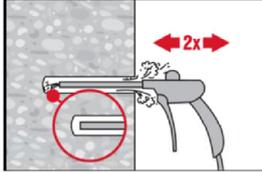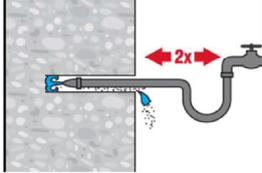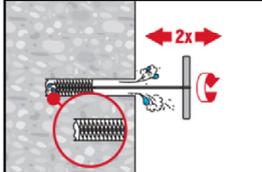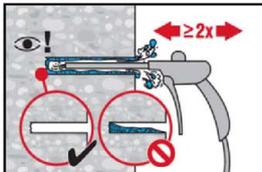
	<p>Brush 4 times with the specified brush (see Table B6) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the drill hole (brush $\varnothing \geq$ drill hole \varnothing) - if not the brush is too small and must be replaced with the proper brush diameter.</p>
	<p>Blow out again with the Hilti hand pump at least 4 times until return air stream is free of noticeable dust.</p>
<p>Compressed air cleaning (CAC) for all drill hole diameters d_0 and all drill hole depths h_0</p>	
	<p>Blow 2 times from the back of the hole (if needed with nozzle extension) over the hole length with oil-free compressed air (min. 6 bar at 6 m³/h) until return air stream is free of noticeable dust.</p>
	<p>Brush 2 times with the specified brush (see Table B6) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the drill hole (brush $\varnothing \geq$ drill hole \varnothing) - if not the brush is too small and must be replaced with the proper brush diameter.</p>
	<p>Blow again with compressed air 2 times until return air stream is free of noticeable dust.</p>
<p>Cleaning of diamond cored holes with roughening with Hilti roughening tool TE-YRT.</p>	
	<p>Flush 2 times by inserting a water hose (water-line pressure) to the back of the hole until water runs clear.</p>
	<p>Brush 2 times with the specified brush (see Table B6) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it. The brush must produce natural resistance as it enters the drill hole (brush $\varnothing \geq$ drill hole \varnothing) - if not the brush is too small and must be replaced with the proper brush diameter.</p>
	<p>Blow 2 times from the back of the hole (if needed with nozzle extension) over the whole length with oil-free compressed air (min. 6 bar at 6 m³/h) until return air stream is free of noticeable dust and water. Remove all water from the drill hole until drill hole is completely dried before mortar injection.</p>
<p>Connector Hilti HCC-K</p>	
<p>Intended use Installation instructions</p>	<p>Annex B8</p>

Cleaning and water removal of water filled holes drilled with hammer drilling, hammer drilling with Hilti hollow drill bit and diamond coring (check allowable mortars and drilling methods).


For all drill hole diameters d_0 and all drill hole depths h_0 .

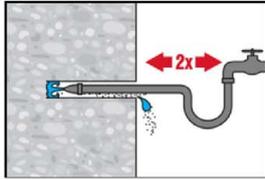


Flush 2 times by inserting a water hose (water-line pressure) to the back of the hole until water runs clear.

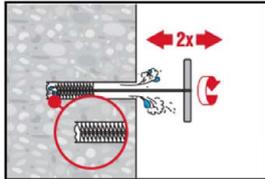


Brush 2 times with the specified brush (see Table B6) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it.
The brush must produce natural resistance as it enters the drill hole (brush $\varnothing \geq$ drill hole \varnothing) - if not the brush is too small and must be replaced with the proper brush diameter.

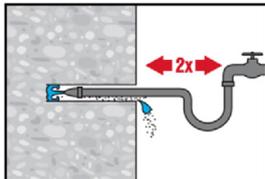


Flush 2 times by inserting a water hose (water-line pressure) to the back of the hole until water runs clear.

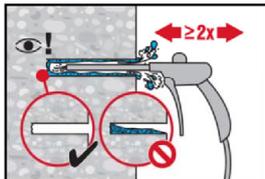

Blow 2 times from the back of the hole (if needed with nozzle extension) over the whole length with oil-free compressed air (min. 6 bar at 6 m³/h) until return air stream is free of noticeable dust and water.

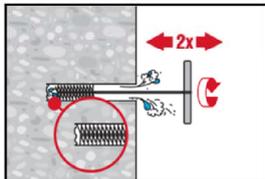

Brush 2 times with the specified brush size (brush $\varnothing \geq$ drill hole \varnothing , see Table B7) by inserting the steel brush Hilti HIT-RB to the back of the hole (if needed with extension) in a twisting motion and removing it.
The brush must produce natural resistance as it enters the drill hole – if not the brush is too small and must be replaced with the proper brush diameter.

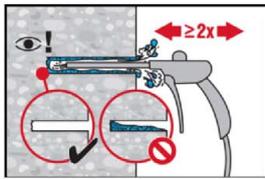


Blow again with compressed air 2 times until return air stream is free of noticeable dust and water.

Connector Hilti HCC-K


Intended use
Installation instructions

Annex B9

Injection preparation

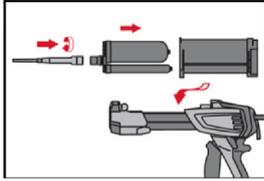

Tightly attach Hilti mixing nozzle HIT-RE-M to foil pack manifold. Do not modify the mixing nozzle.
Observe the instruction for use of the dispenser.
Check foil pack holder for proper function. Insert foil pack into foil pack holder and put holder into dispenser.

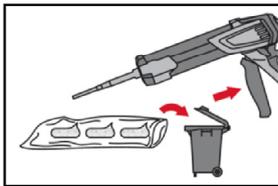

The foil pack opens automatically as dispensing is initiated. Depending on the size of the foil pack, an initial amount of adhesive has to be discarded. Discarded quantities are:

- for use with **HIT-HY 200-A V3** and **HIT-HY 200-R V3**:

2 strokes	for 330 ml foil pack,
3 strokes	for 500 ml foil pack,
4 strokes	for 500 ml foil pack ≤ 5 °C.


The minimum foil pack temperature is 0° C.

- for use with **HIT-RE 500 V3** and **HIT-RE 500 V4**:


3 strokes	for 330 ml foil pack,
4 strokes	for 500 ml foil pack,
65 ml	for 1400 ml foil pack

The minimum foil pack temperature is +5° C.


Inject adhesive from the back of the drill hole without forming air voids.

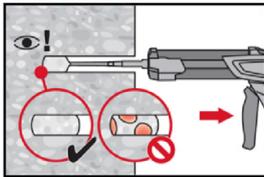

Inject the adhesive starting at the back of the hole, slowly withdrawing the mixer with each trigger pull.
Fill approximately 2/3 of the drill hole to ensure that the annular gap between the anchor and the concrete is completely filled with adhesive along the embedment length.
In water saturated concrete it is required to set the fastener immediately after cleaning the drill hole.

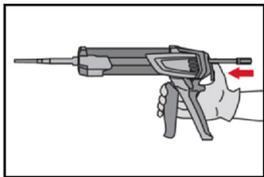

After injection is completed, depressurize the dispenser by pressing the release trigger. This will prevent further adhesive discharge from the mixer.

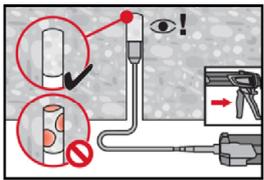


Overhead installation and/or installation with embedment depth $h_{ef,ex} > 250\text{mm}$.
For overhead installation the injection is only possible with the aid of extensions and piston plugs. Assemble HIT-RE-M mixer, extension(s) and appropriately sized piston plug (see Table B6). Insert piston plug to back of the hole and inject adhesive. During injection the piston plug will be naturally extruded out of the drill hole by the adhesive pressure.

Connector Hilti HCC-K


Intended use
Installation instructions

Annex B10


Setting the element

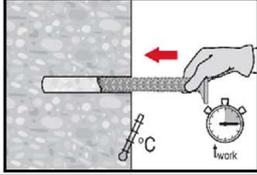

Before use, verify that the element is dry and free of oil and other contaminants. Mark and set element to the required embedment depth before working time t_{work} has elapsed. The working time t_{work} is given in Table B3 and Table B4.

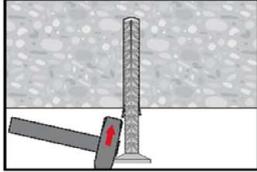

For overhead installation use piston plugs and fix embedded parts with e.g. wedges (Hilti HIT-OHW).

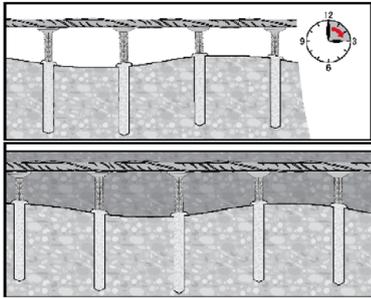

Observe the curing time t_{cure} , which varies according to temperature of base material (see Table B3 and Table B4). After t_{cure} has elapsed the concrete overlay can be concreted. Observe the required condition of the surface before concreting and the use of the correct concrete composition. For requirements on concrete composition see EOTA TR 066.

Connector Hilti HCC-K

Intended use
Installation instructions

Annex B11

Table C1: Essential characteristics of connector Hilti HCC-K in existing concrete

Connector Hilti HCC-K		10	12	14	16
Steel failure					
Characteristic resistance	$N_{Rk,s,ex}$ [kN]	43	62	85	111
Partial safety factor	$\gamma_{Ms,N,ex}$ [-]	1,4			
Concrete cone failure					
Factor for cracked concrete	$k_{Cr,N,ex}$ [-]	7,7			
Factor for uncracked concrete	$k_{ucr,N,ex}$ [-]	11,0			
Edge distance	$c_{Cr,N,ex}$ [mm]	$1,5 \cdot h_{ef,ex}$			
Spacing	$s_{Cr,N,ex}$ [mm]	$3,0 \cdot h_{ef,ex}$			
Splitting failure					
Edge distance $c_{Cr,sp,ex}$ [mm] for	$h / h_{ef,ex} \geq 2,0$	$1,0 \cdot h_{ef,ex}$			
	$2,0 > h / h_{ef,ex} > 1,3$	$4,6 \cdot h_{ef,ex} - 1,8 \cdot h$			
	$h / h_{ef,ex} \leq 1,3$	$2,26 \cdot h_{ef,ex}$			
Spacing	$s_{Cr,sp,ex}$ [mm]	$2,0 \cdot c_{Cr,sp,ex}$			

Connector Hilti HCC-K

Performance
Essential characteristics under tension load in existing concrete

Annex C1

Table C1 continued (1)

Connector Hilti HCC-K			10	12	14	16
Installation factor for HCC-K with HIT-HY 200-A V3 and HIT-HY 200-R V3						
For installation in dry or wet (water saturated) concrete						
Hammer drilling (HD)	γ_{inst}	[-]	1,0			
Hammer drilling with Hilti hollow drill bit TE-CD or TE-YD (HDB)	γ_{inst}	[-]	1,0			
Diamond coring with roughening with Hilti roughening tool TE-YRT (DD + RT)	γ_{inst}	[-]	1)	1,0		
For installation in water-filled drill holes (not sea water)						
Hammer drilling (HD)	γ_{inst}	[-]	1,4			
Hammer drilling with Hilti hollow drill bit TE-CD or TE-YD (HDB)	γ_{inst}	[-]	1,4			
Combined pullout and concrete cone failure for HCC-K with HIT-HY 200-A V3 and HIT-HY 200-R V3						
Characteristic bond resistance in cracked concrete C20/25 for installation in dry or wet (water saturated) concrete, all drilling methods (HD, HDB, DD + RT)						
Temperature range I:	24°C/40°C	$\tau_{Rk,cr}$ [N/mm ²]	5,0	7,0		
Temperature range II:	50°C/80°C	$\tau_{Rk,cr}$ [N/mm ²]	4,0	5,5		
Temperature range III:	72°C/120°C	$\tau_{Rk,cr}$ [N/mm ²]	3,5	5,0		
Characteristic bond resistance in uncracked concrete C20/25 for installation in dry or wet (water saturated) concrete, all drilling methods (HD, HDB, DD + RT)						
Temperature range I:	24°C/40°C	$\tau_{Rk,ucr}$ [N/mm ²]	12			
Temperature range II:	50°C/80°C	$\tau_{Rk,ucr}$ [N/mm ²]	10			
Temperature range III:	72°C/120°C	$\tau_{Rk,ucr}$ [N/mm ²]	8,5			
Characteristic bond resistance in cracked concrete C20/25 for installation in water-filled drill holes (not sea water), HD and HDB						
Temperature range I:	24°C/40°C	$\tau_{Rk,cr}$ [N/mm ²]	4,6	6,5		
Temperature range II:	50°C/80°C	$\tau_{Rk,cr}$ [N/mm ²]	3,7	5,2		
Temperature range III:	72°C/120°C	$\tau_{Rk,cr}$ [N/mm ²]	3,2	4,5		
Characteristic bond resistance in uncracked concrete C20/25 for installation in water-filled drill holes (not sea water), HD and HDB						
Temperature range I:	24°C/40°C	$\tau_{Rk,ucr}$ [N/mm ²]	11,4			
Temperature range II:	50°C/80°C	$\tau_{Rk,ucr}$ [N/mm ²]	9,3			
Temperature range III:	72°C/120°C	$\tau_{Rk,ucr}$ [N/mm ²]	8,1			
Influence factors ψ on bond resistance τ_{Rk} in cracked and uncracked concrete						
Influence of concrete strength class: $\tau_{Rk} = \tau_{Rk,(C20/25)} \cdot \psi_{c,ex}$						
Temperature range I to III :	$\psi_{c,ex}$	[-]	$(f_{ck}/20)^{0,1}$			
Sustained load factor						
Cracked and uncracked concrete	ψ_{sus}^0	24°C/40°C	0,74			
		50°C/80°C	0,89			
		72°C/120°C	0,72			

Connector Hilti HCC-K

Performance
Essential characteristics under tension load in existing concrete

Annex C2

Table C1 continued (2)

Connector Hilti HCC-K			10	12	14	16
Installation factor for HCC-K with HIT-RE 500 V3						
Hammer drilling (HD)	γ_{inst}	[-]	1,0			
Hammer drilling with Hilti hollow drill bit TE-CD or TE-YD (HDB)	γ_{inst}	[-]	1)	1,0		
Diamond coring (DD)	γ_{inst}	[-]	1,2			1,4
Diamond coring with roughening with Hilti roughening tool TE-YRT (DD + RT)	γ_{inst}	[-]	1)		1,0	
Hammer drilling in water-filled drill holes	γ_{inst}	[-]	1,4			
Combined pullout and concrete cone failure for HCC-K with HIT-RE 500 V3						
Characteristic bond resistance in cracked concrete C20/25 in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and diamond cored holes with roughening with Hilti roughening tool TE-YRT						
Temperature range I:	24 °C / 40 °C	$\tau_{RK,cr}$ [N/mm ²]	8,5	9,5	9,5	10
Temperature range II:	43 °C / 70 °C	$\tau_{RK,cr}$ [N/mm ²]	7,0	7,5	7,5	7,5
Characteristic bond resistance in uncracked concrete C20/25 in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and diamond cored holes with roughening with Hilti roughening tool TE-YRT						
Temperature range I:	24 °C / 40 °C	$\tau_{RK,ucr}$ [N/mm ²]	15			
Temperature range II:	43 °C / 70 °C	$\tau_{RK,ucr}$ [N/mm ²]	11			
Characteristic bond resistance in uncracked concrete C20/25 in diamond cored holes						
Temperature range I:	24 °C / 40 °C	$\tau_{RK,ucr}$ [N/mm ²]	9,0			
Temperature range II:	43 °C / 70 °C	$\tau_{RK,ucr}$ [N/mm ²]	6,5			
Characteristic bond resistance in uncracked concrete C20/25 in hammer drilled holes and installation in water-filled drill holes						
Temperature range I:	24 °C / 40 °C	$\tau_{RK,ucr}$ [N/mm ²]	12			
Temperature range II:	43 °C / 70 °C	$\tau_{RK,ucr}$ [N/mm ²]	9,5			
Influence factors ψ on bond resistance τ_{RK} in cracked and uncracked concrete						
Influence of concrete strength class: $\tau_{RK} = \tau_{RK,(C20/25)} \cdot \psi_{c,ex}$: temperature range I and II:						
In hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and diamond cored holes	$\psi_{c,ex}$	[-]	$(f_{ck}/20)^{0,1}$			
In diamond cored holes with roughening with Hilti roughening tool TE-YRT	$\psi_{c,ex}$	[-]	1,0			
Influence of sustained load						
In hammer drilled holes, hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and in diamond cored holes with roughening with Hilti Roughening tool TE-YRT	ψ_{sus}^0		24 °C / 40 °C	0,88		
			43 °C / 70 °C	0,70		

Connector Hilti HCC-K

Performance

Essential characteristics under tension load in existing concrete

Annex C3

Table C1 continued (3)

Connector Hilti HCC-K				10	12	14	16
Installation factor for HCC-K with HIT-RE 500 V4							
Hammer drilling	γ_{inst}	[-]		1,0			
Hammer drilling with Hilti hollow drill bit TE-CD or TE-YD	γ_{inst}	[-]	1)	1,0			
Diamond coring	γ_{inst}	[-]		1,2			1,4
Diamond coring with roughening with Hilti roughening tool TE-YRT	γ_{inst}	[-]	1)	1,0			
Hammer drilling in water-filled drill holes	γ_{inst}	[-]		1,4			
Combined pullout and concrete cone failure HCC-K with HIT-RE 500 V4							
Characteristic bond resistance in cracked concrete C20/25 in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and diamond cored holes with roughening with Hilti roughening tool TE-YRT							
Temperature range I:	24 °C / 40 °C	$\tau_{RK,cr}$	[N/mm ²]	10	12	12	12
Temperature range II:	43 °C / 55 °C	$\tau_{RK,cr}$	[N/mm ²]	8,5	10	10	10
Temperature range III:	55 °C / 75 °C	$\tau_{RK,cr}$	[N/mm ²]	4,0	4,0	5,0	5,0
Characteristic bond resistance in uncracked concrete C20/25 in hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and diamond cored holes with roughening with Hilti roughening tool TE-YRT							
Temperature range I:	24 °C / 40 °C	$\tau_{RK,ucr}$	[N/mm ²]	15	15	15	15
Temperature range II:	43 °C / 55 °C	$\tau_{RK,ucr}$	[N/mm ²]	13	12	12	12
Temperature range III:	55 °C / 75 °C	$\tau_{RK,ucr}$	[N/mm ²]	5,0	5,0	5,0	4,5
Characteristic bond resistance in uncracked concrete C20/25 in diamond cored holes							
Temperature range I:	24 °C / 40 °C	$\tau_{RK,ucr}$	[N/mm ²]	9,5	9,5	9,5	9,5
Temperature range II:	43 °C / 55 °C	$\tau_{RK,ucr}$	[N/mm ²]	7,5	7,5	8,0	8,0
Temperature range III:	55 °C / 75 °C	$\tau_{RK,ucr}$	[N/mm ²]	4,5	4,5	4,5	5,0
Characteristic bond resistance in uncracked concrete C20/25 in hammer drilled holes and installation in water-filled drill holes							
Temperature range I:	24 °C / 40 °C	$\tau_{RK,ucr}$	[N/mm ²]	13	13	13	12
Temperature range II:	43 °C / 55 °C	$\tau_{RK,ucr}$	[N/mm ²]	11	11	10	10
Temperature range III:	55 °C / 75 °C	$\tau_{RK,ucr}$	[N/mm ²]	4,0	4,0	4,0	4,0

Connector Hilti HCC-K

Performance

Essential characteristics under tension load in existing concrete

Annex C4

Table C1 continued (4)

Connector Hilti HCC-K		10	12	14	16
Influence factors ψ on bond resistance τ_{Rk} in cracked and uncracked concrete					
Influence of concrete strength class: $\tau_{Rk} = \tau_{Rk,(C20/25)} \cdot \psi_{c,ex}$, temperature range I to III :					
In hammer drilled holes and hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and diamond cored holes	$\psi_{c,ex}$	[-]	$(f_{ck}/20)^{0,1}$		
In diamond cored holes with roughening with Hilti roughening tool TE-YRT	$\psi_{c,ex}$	[-]	1,0		
Influence of sustained load					
In hammer drilled holes, hammer drilled holes with Hilti hollow drill bit TE-CD or TE-YD and in diamond cored holes with roughening with Hilti Roughening tool TE-YRT	ψ_{sus}^0	24 °C / 40 °C	0,88		
		43 °C / 55 °C	0,72		
		55 °C / 75 °C	0,69		
In diamond cored holes	ψ_{sus}^0	24 °C / 40 °C	0,89		
		43 °C / 55 °C	0,70		
		55 °C / 75 °C	0,62		

1) No performance assessed.

Connector Hilti HCC-K

Performance
Essential characteristics under tension load in existing concrete

Annex C5

Table C2: Essential characteristics of connector Hilti HCC-K under tension load in concrete overlay

Connector Hilti HCC-K			10	12	14	16
Steel failure						
Characteristic resistance	$N_{Rk,s,ov}$	[kN]	43	62	85	111
Partial safety factor	$\gamma_{Ms,N,ov}$	[-]	1,4			
Pullout failure for anchor heads						
Projected area of the head	A_h	[mm ²]	628	905	1232	1608
Thickness of the head	t_h	[mm]	2			
Concrete cone failure						
Effective embedment depth	min. $h_{ef,ov}$	[mm]	40			
	max. $h_{ef,ov}$	[mm]	$L - h_{nom,ex} - t_h - 2 \cdot R_t^{1)}$			
Factor for cracked concrete	$k_{cr,N,ov}$	[-]	8,9			
Factor for uncracked concrete	$k_{ucr,N,ov}$	[-]	12,7			
Edge distance	$c_{cr,N,ov}$	[mm]	$1,5 \cdot h_{ef,ov}$			
Spacing	$s_{cr,N,ov}$	[mm]	$3,0 \cdot h_{ef,ov}$			
Splitting failure						
Edge distance	$c_{cr,sp,ov}$	[mm]	$3,0 \cdot h_{ef,ov}$			
Spacing	$s_{cr,sp,ov}$	[mm]	$6,0 \cdot h_{ef,ov}$			
Blow-out failure						
Projected area of the head	A_h	[mm ²]	628	905	1232	1608
Factor for cracked concrete	$k_{5,cr}$	[-]	8,7			
Factor for uncracked concrete	$k_{5,ucr}$	[-]	12,2			

1) R_t : Roughness according to EOTA Technical Report TR 066

Table C3: Essential characteristics of connector Hilti HCC-K for the shear interface

Connector Hilti HCC-K			10	12	14	16
Characteristic yield strength	f_{yk}	[N/mm ²]	500			
Product specific factor for ductility	α_{k1}	[-]	1,0			
Relevant cross section in area of the interface	A_s	[mm ²]	78,5	113	154	201
Product specific factor for geometry	α_{k2}	[-]	1,0			

Connector Hilti HCC-K

Performance
Essential characteristics under tension load in concrete overlay
Essential characteristics for the shear interface

Annex C6