

Public-law institution jointly founded by the federal states and the Federation

European Technical Assessment Body
for construction products



European Technical Assessment

ETA-18/1160 of 23 December 2025

English translation prepared by DIBt - Original version in German language

General Part

Technical Assessment Body issuing the European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

HUS4 Bonded screw

Product family to which the construction product belongs

Bonded screw fastener for use in concrete

Manufacturer

HILTI Corporation
Feldkircherstraße 100
9494 SCHAAN
FÜRSTENTUM LIECHTENSTEIN

Manufacturing plant

Hilti Plants

This European Technical Assessment contains

27 pages including 3 annexes which form an integral part of this assessment

This European Technical Assessment is issued in accordance with Regulation (EU) No 305/2011, on the basis of

EAD 332795-01-0601

This version replaces

ETA-18/1160 issued on 16 January 2025

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

Specific Part

1 Technical description of the product

The HUS4 Bonded screw consists of a foil capsule HUS4-MAX and a steel element HUS4 according to Annex A1. The anchor made of galvanized or stainless steel is screwed into a predrilled cylindrical drill hole, filled with a mortar capsule HUS4-MAX. The special thread of the anchor cuts an internal thread into the member while setting. The anchorage is characterized by mechanical interlock in the special thread.

Product and product description are given in Annex A.

2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment

3.1 Mechanical resistance and stability (BWR 1)

Essential characteristic	Performance
Characteristic resistance to tension load (static and quasi-static loading)	See Annex B4, B5 and B6, Annex C1, C2 and C3
Characteristic resistance to shear load (static and quasi-static loading)	See Annex C4
Displacements (static and quasi-static loading)	See Annex C8 and C9
Characteristic resistance for seismic performance category C1	See Annex C5
Characteristic resistance and displacements for seismic performance category C2	See Annex C6 and C9

3.2 Safety in case of fire (BWR 2)

Essential characteristic	Performance
Reaction to fire	Class A1
Resistance to fire	See Annex C7

3.3 Aspects of durability linked with the basic works requirements

Essential characteristic	Performance
Durability	See Annex B1

4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with European Assessment Document EAD No. 332795-01-0601 the applicable European legal act is: [96/582/EC].

The system to be applied is: 1

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document


Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited at Deutsches Institut für Bautechnik.

Issued in Berlin on 23 December 2025 by Deutsches Institut für Bautechnik

Dipl.-Ing. Beatrix Wittstock
Head of Section

beglaubigt:
Tempel


Installed condition without adjustment

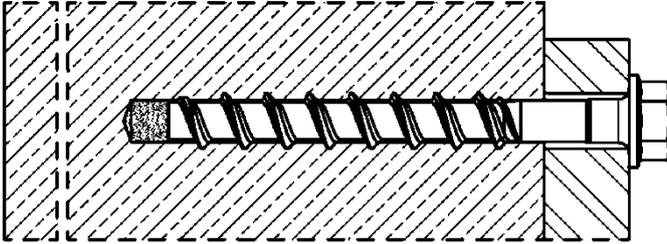

HUS4-H (hexagon head configuration sizes 10, 12, 14 and 16)


HUS4-HF (hexagon head configuration sizes 10, 12, 14 and 16)

HUS4-HR (hexagon head configuration sizes 10 and 14)

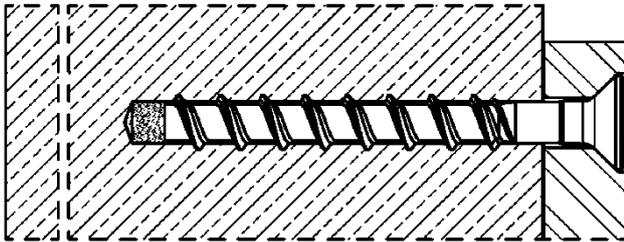

HUS4-C (countersunk head configuration size 10)


HUS4-CR (countersunk head configuration size 10)

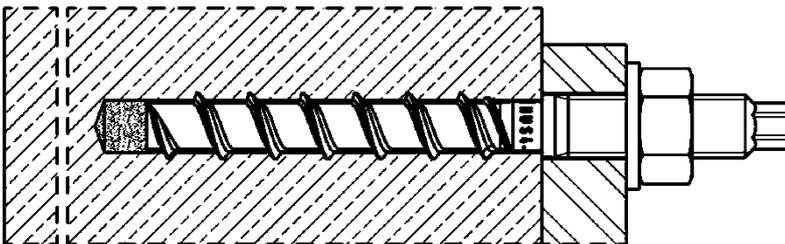

HUS4-A
(threaded rod connection
sizes 10 with M12 and 14 with M16)


HUS4-AF
(threaded rod connection
sizes 10 with M12 and 14 with M16)

Installed condition with adjustment

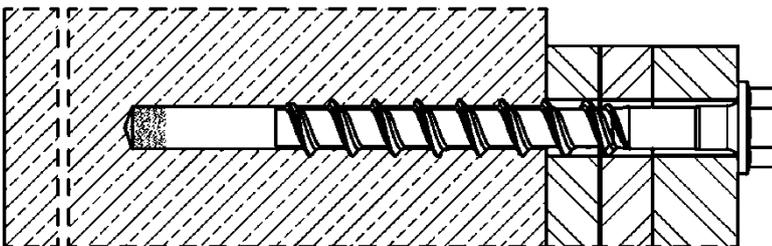

HUS4-H (hexagon head configuration sizes 10, 12, and 14 and 16 G02)

HUS4-HF (hexagon head configuration sizes 10, and 14)

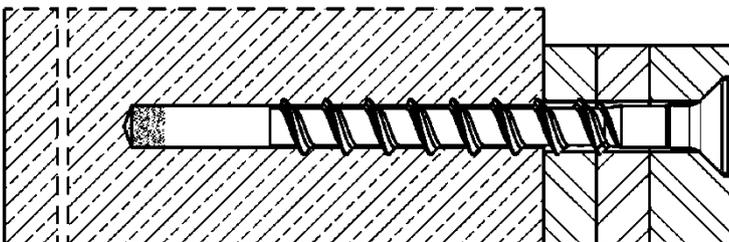

HUS4-C (countersunk head configuration size 10)

HUS4 Bonded screw

Product description
Installed condition

Annex A1

Product description: Foil capsule and steel elements

Foil capsule HUS4-MAX size 10 to 16: resin and hardener

Marking:
HUS4-MAX size
Expiry date mm/yyyy



Table A1: Screw types

<p>Hilti HUS4-H, sizes 10, 12, 14 and 16, hexagonal head configuration, galvanized Hilti HUS4-HF, sizes 10, 12, 14 and 16 (G02), hexagonal head configuration, multilayer coating</p>
<p>Hilti HUS4-HR, sizes 10 and 14 hexagonal head configuration, stainless steel</p>
<p>Hilti HUS4-C, size 10, countersunk head configuration, galvanized</p>
<p>Hilti HUS4-CR, size 10 countersunk head configuration, stainless steel</p>
<p>Hilti HUS4-A, size 10 with external thread M12 and size 14 with external thread M16, galvanized Hilti HUS4-AF, size 10 with external thread M12 and size 14 with external thread M16, multilayer coating</p>

HUS4 Bonded screw



Product description
Foil capsule / Steel elements


Annex A2

Table A2: Materials

Designation	Material
HUS4-H(F), HUS4-C and HUS4-A(F) screw anchor	Carbon steel, galvanized Rupture elongation $A_5 \leq 8\%$
HUS4-HR and HUS4-CR screw anchor	Stainless steel A4 according to EN 10088-1:2014 Rupture elongation $A_5 > 8\%$ Corrosion resistance class CRC III according to EN 1993-1-4:2006+A1:2015
Hilti Filling Set (carbon steel)	Carbon steel, galvanized
Hilti Filling Set A4 (stainless steel)	Stainless steel A4 according to EN 10088-1:2014 Corrosion resistance class CRC III according to EN 1993-1-4:2006+A1:2015
Injection Mortar (for filling set)	Injection Mortar Hilti HIT-HY... or Hilti HIT-RE... (with ETA)

Table A3: Geometry and compatibility of Hilti Filling set

Filling set size		M10	M12	M16	M20
Diameter of sealing washer	d_{vs} [mm]	42	44	52	60
Thickness of sealing washer	h_{vs} [mm]	5	5	6	6
Thickness of Hilti Filling Set	h_{fs} [mm]	9	10	11	13
Fastener size of HUS4 (T)-H (F, R)		8	10	12 + 14	16
Fastener size of HUS4-A (F)		-	10	14	-

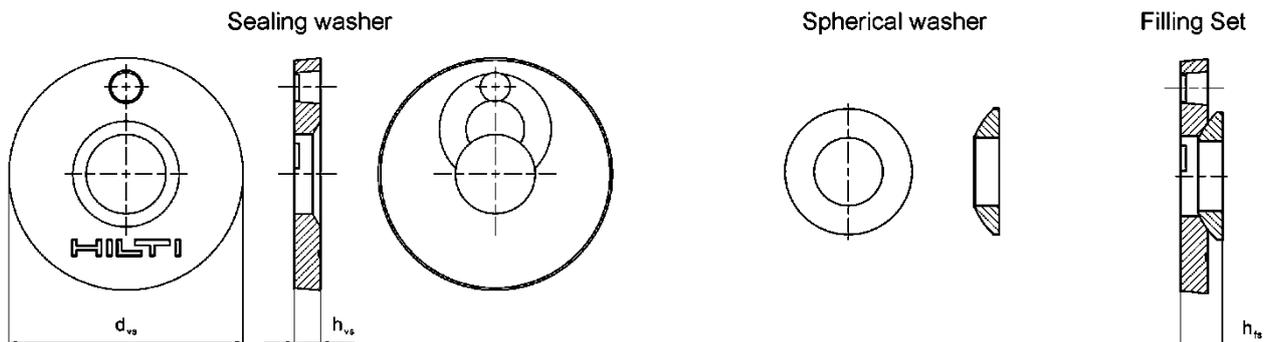

HUS4 Bonded screw

Product description
Materials

Annex A3

Table A4: Fastener dimensions and marking HUS4-H(F, R)

Fastener size HUS4-	H(F) 10	H(F) 12	H(F) 14	H(F) 16	H(F) 16 G02
Nominal fastener diameter d [mm]	10	12	14	16	16
Nominal embedment depth h_{nom} [mm]	85	100	115	130	130
Effective embedment depth h_{ef} [mm]	85	100	115	130	130
Pitch of the thread h_t [mm]	10	12	14	13,2	14,5
Length of screw (min / max) L [mm]	90 / 305	110 / 150	130 / 150	140 / 205	140 / 205

Fastener size HUS4-	HR 10	HR 14
Nominal fastener diameter d [mm]	10	14
Nominal embedment depth h_{nom} [mm]	90	110
Effective embedment depth h_{ef} [mm]	90	110
Pitch of the thread h_t [mm]	8	9,8
Length of screw (min / max) L [mm]	95 / 130	120 / 135

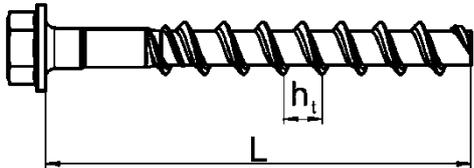
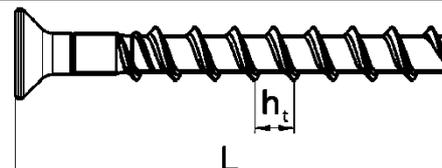
		<p>HUS4: Hilti Universal Screw 4th generation H: Hexagonal head, galvanized HF: Hexagonal head, multilayer coating HR: Hexagonal head, stainless steel 10: Nominal screw diameter d [mm] 100: Length of screw L [mm]</p>
-------------------------------------------------------------------------------------	-------------------------------------------------------------------------------------	--------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------

Table A5: Fastener dimensions and marking HUS4-C and HUS4-CR

Fastener size HUS4-	C 10	CR 10
Nominal fastener diameter d [mm]	10	10
Nominal embedment depth h_{nom} [mm]	85	90
Effective embedment depth h_{ef} [mm]	85	90
Pitch of the thread h_t [mm]	10	8
Length of screw (min / max) L [mm]	100 / 120	105

		<p>HUS4: Hilti Universal Screw 4th generation C: Countersunk head, galvanized CR: Countersunk head, stainless steel 10: Nominal screw diameter d [mm] 100: Length of screw L [mm]</p>
-------------------------------------------------------------------------------------	-------------------------------------------------------------------------------------	---------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------------


HUS4 Bonded screw

Product description
Fastener dimensions and markings

Annex A4

Table A6: Fastener dimensions and marking HUS4-A (AF)

Fastener size HUS4-		A(F) 10	A(F) 14
Nominal fastener diameter	d [mm]	10	14
Metric thread connection		M12	M16
Nominal embedment depth	h_{nom} [mm]	85	115
Effective embedment depth	h_{ef} [mm]	85	115
Pitch of the thread	h_t [mm]	10	14
Length of screw (min / max)	L [mm]	140 / 165	185 / 205

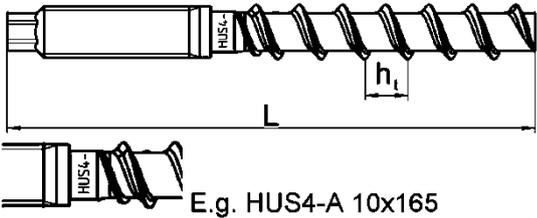 <p>E.g. HUS4-A 10x165</p>		<p>HUS4: Hilti Universal Screw 4th generation A: Thread connection, galvanized AF: Thread connection, multilayer coating 10: Nominal screw diameter d [mm] 165: Length of screw L [mm] 8: Carbon steel K: Length identification HUS4-A 10x165</p>			
		I	K	L	N
		10x140	10x165	14x185	14x205

HUS4 Bonded screw

Product description
Fastener dimensions and markings

Annex A5

Specifications of intended use

Anchorage subject to:

- Static and quasi static loading
- Seismic performance category C1 and C2 for carbon steel types
- Fire exposure for carbon steel types

Base material:

- Compacted reinforced or unreinforced normal weight concrete without fibres according to EN 206:2013 +A1:2016.
- Strength classes C20/25 to C50/60 according to EN 206-1:2010+A1:2016.
- Cracked or uncracked concrete.

Temperature in the base material:

- **at installation**
-10 °C to +40 °C
- **in-service**
Temperature range I: -40 °C to +120 °C
(max. long term temperature +72 °C and max. short term temperature +120 °C)

Use conditions (Environmental conditions):

- Anchorages subject to dry internal conditions: all screw types.
- For all other conditions corresponding to corrosion resistance classes CRC according to EN 1993-1-4:2006+A1:2015
 - Stainless steel according to Annex A3, Table A2, screw types HUS4-HR/-CR: CRC III

Design:

- Anchorages are designed under the responsibility of an engineer experienced in anchorages and concrete work.
- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the fastener is indicated on the design drawings (e. g. position of the fastener relative to reinforcement or to supports, etc.).
- The anchorages are designed in accordance with EN 1992-4:2018 and EOTA Technical Report TR 075, Edition 10/2020 (amended December 2024).
- In case of requirements to resistance to fire local spalling of the concrete cover must be avoided.

Installation:

- Concrete condition I1: installation in dry or wet (water saturated) concrete and use in service in dry concrete for carbon steel.
- Concrete condition I1: installation in dry or wet (water saturated) concrete and use in service in dry or wet concrete for stainless steel.
- Fastener installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site.
- In case of aborted hole: new drilling at a minimum distance away of twice the depth of the aborted hole or smaller distance if the aborted hole is filled with high strength mortar and if under shear or oblique tension load it is not the direction of the load application.
- After installation further turning of the fastener must not be possible.
- The head of the fastener (HUS4-H (F, R) and HUS4-C/CR) must be supported on the fixture and is not damaged.
- Hilti filling set is suitable for HUS4-H (F, R) and HUS4-A (F).

HUS4 Bonded screw

Intended Use
Specifications

Annex B1

Specifications of intended use: Drilling and cleaning for HUS4

Adjustment according to annex B8 and B9 is possible for HUS4 carbon steel sizes 10 to 14 and 16 G02.

Table B1: Static and quasi static loading

HUS4		H(F); C; A(F) carbon steel	HR; CR stainless steel
Cracked and uncracked concrete			
Hammer drilling (HD)	cleaned 	size 10 to 16	size 10 and 14
	not cleaned		
Hammer drilling with Hilti hollow drill bit TE-CD or TE-YD (HDB) 		sizes 12 to 16	-

Table B2: Seismic performance category C1

HUS4		H(F); C; A(F) carbon steel
Hammer drilling (HD)	cleaned 	sizes 10 to 14 and 16 G02
	not cleaned	
Hammer drilling with Hilti hollow drill bit TE-CD or TE-YD (HDB) 		sizes 12 and 14

Table B3: Seismic performance category C2

HUS4		H(F); C; A(F) carbon steel
Hammer drilling (HD)	cleaned 	sizes 10 to 14 and 16 G02
	not cleaned	

Table B4: Static and quasi static loading under fire exposure


HUS4		H(F); C; A(F) carbon steel
Hammer drilling (HD)	cleaned 	sizes 10 to 16
	not cleaned	
Hammer drilling with Hilti hollow drill bit TE-CD or TE-YD (HDB) 		sizes 12 to 16

HUS4 Bonded screw

**Intended Use
Specifications**

Annex B2

Installation parameters

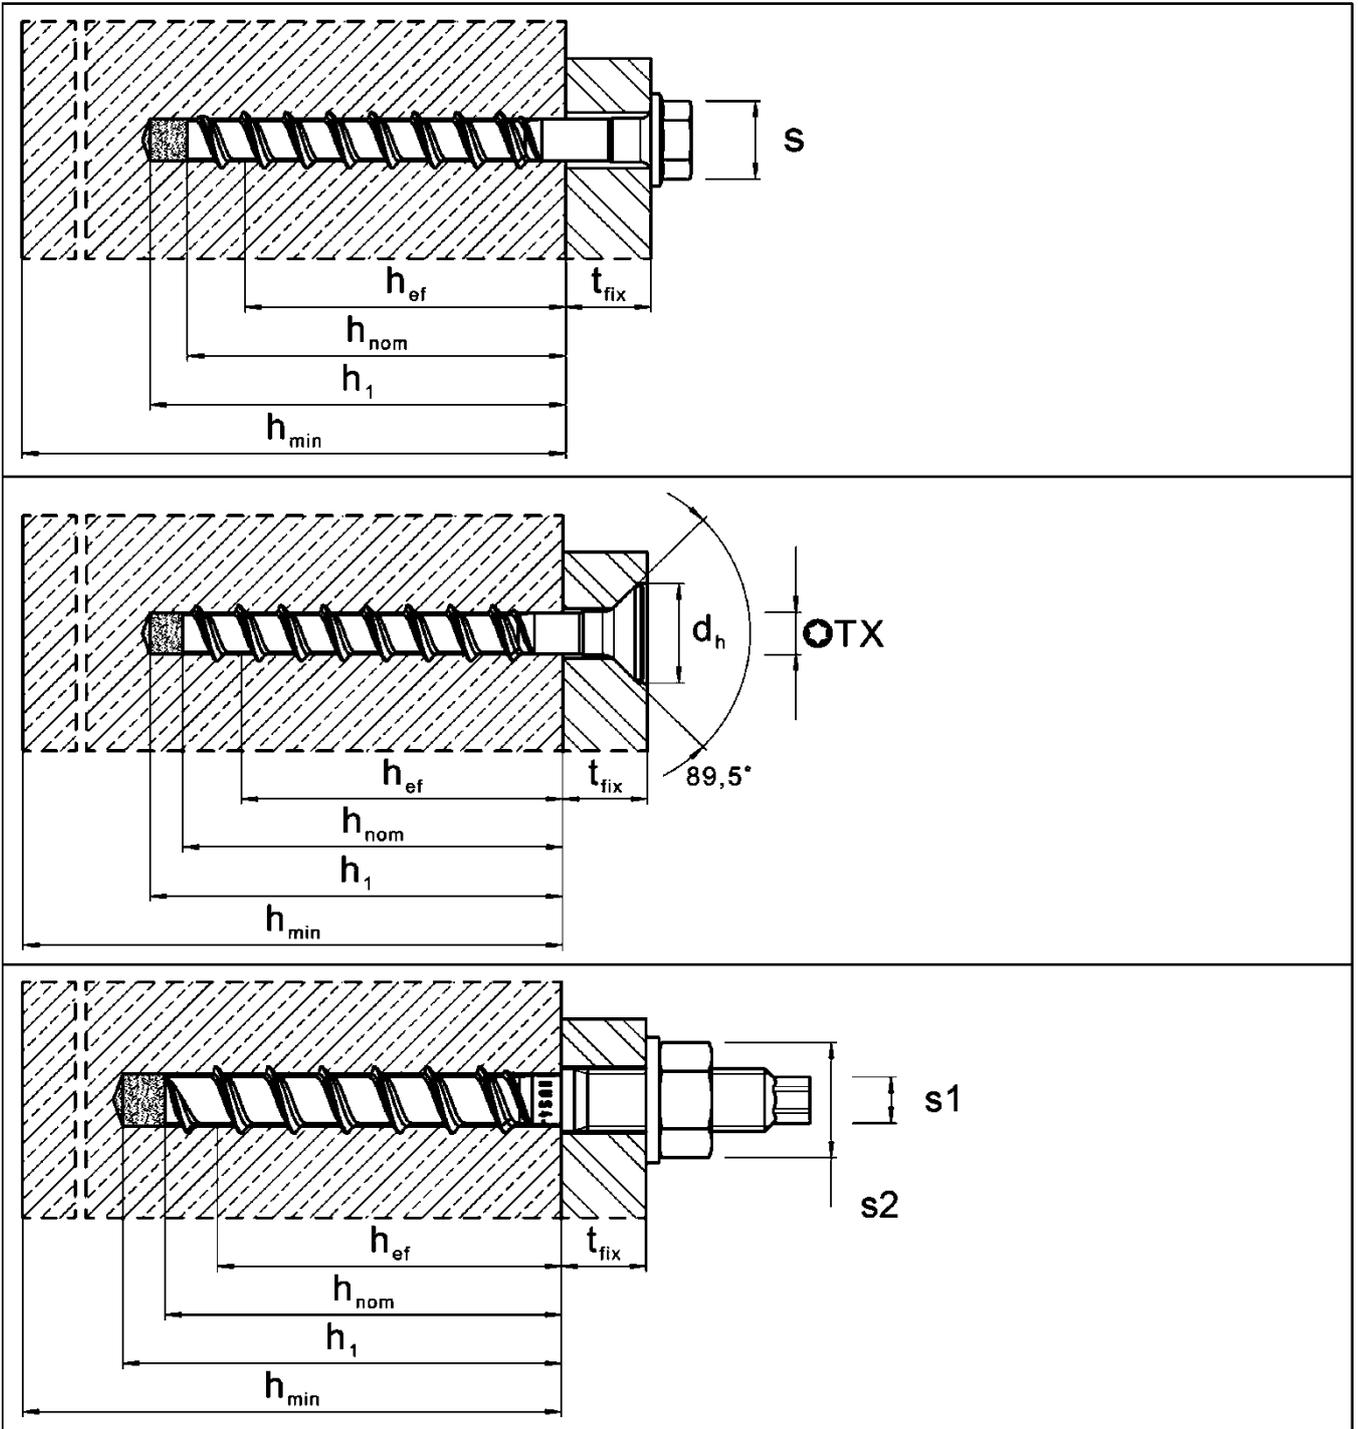

HUS4 Bonded screw

Intended Use
Installation parameters

Annex B3

Table B5: Installation parameters HUS4 Bonded screw carbon steel size 10 to 14

Fastener size HUS4			10	12	14
Type			H(F), C, A(F)	H(F)	H(F), A(F)
Nominal embedment depth	h_{nom}	[mm]	85	100	115
Nominal drill hole diameter	d_0	[mm]	10	12	14
Cutting diameter of drill bit	$d_{cut} \leq$	[mm]	10,45	12,50	14,50
Clearance hole diameter through setting	$d_f \frac{\min}{\max}$	[mm]	13	15	17
			14	16	18
Clearance hole diameter pre setting (A-type)	$d_f \leq$	[mm]	14	-	18
Wrench size (H, HF-type)	s	[mm]	15	17	21
Wrench size for hex head (A-type)	s1	[mm]	8	-	12
Wrench size (A-type)	s2	[mm]	19	-	24
Maximum torque (A-type)	$\max T_{inst}$	[Nm]	40	-	80
Torx size (C-type)	TX	-	50	-	-
Diameter of countersunk head	d_h	[mm]	21	-	-
Depth of drill hole for cleaned hole or for uncleaned hole when drilling upwards	$h_1 =$	[mm]	$h_{nom} + 10 \text{ mm}$		
			95	110	125
Depth of drill hole for uncleaned hole hammer drilling in wall and floor position	$h_1 =$	[mm]	$h_{nom} + 30$	$h_{nom} + 35$	$h_{nom} + 40$
			115	135	155
Depth of drill hole (with adjustability) cleaned hole or for uncleaned hole when drilling upwards	$h_1 =$	[mm]	$h_{nom} + 20 \text{ mm}$		
			105	120	135
Depth of drill hole (with adjustability) for uncleaned hole hammer drilling in wall and floor position	$h_1 =$	[mm]	$h_{nom} + 40$	$h_{nom} + 45$	$h_{nom} + 50$
			125	145	165
Minimum thickness of concrete member	$h_{min} \geq$	[mm]	$h_1 + 30 \text{ mm}$		
			140	160	200
Minimum spacing	$s_{min} \geq$	[mm]	40	50	60
Minimum edge distance	$c_{min} \geq$	[mm]	40	50	60
Hilti setting tool ¹⁾			SIW 6AT-A22 SIW 22T-A SIW 6(AT)-22 SIW 8-22 gear 1 SIW 9-A22 SI-AT-22 module optional	SIW 22T-A SIW 6-22 SIW 8(AT)-22 SIW 9-A22 SI-AT-22 module optional	

¹⁾ Installation with other impact wrench of equivalent power is possible.

HUS4 Bonded screw

Intended Use
Installation parameters

Annex B4

Table B6: Installation parameters HUS4 Bonded screw carbon steel size 16

Fastener size HUS4			16	16
Type			H(F)	H(F) G02
Nominal embedment depth	h_{nom}	[mm]	130	130
Nominal drill hole diameter	d_0	[mm]	16	16
Cutting diameter of drill bit	$d_{cut} \leq$	[mm]	16,50	16,50
Clearance hole diameter through setting	$d_f \leq$	[mm]	20	20
Wrench size (H, HF-type)	s	[mm]	24	24
Depth of drill hole for cleaned hole or for uncleaned hole when drilling upwards	$h_1 =$	[mm]	$h_{nom} + 10 \text{ mm}$	
			140	
Depth of drill hole for uncleaned hole hammer drilling in wall and floor position	$h_1 =$	[mm]	$h_{nom} + 40 \text{ mm}$	
			170	
Depth of drill hole (with adjustability) for cleaned hole hammer drilling, diamond coring or for uncleaned hole when drilling upwards	$h_1 \geq$	[mm]	-	$h_{nom} + 20 \text{ mm}$
			-	150
Depth of drill hole (with adjustability) for uncleaned hole hammer drilling in wall and floor position	$h_1 \geq$	[mm]	-	$h_{nom} + 50 \text{ mm}$
			-	180
Minimum thickness of concrete member	$h_{min} \geq$	[mm]	$h_1 + 35 \text{ mm}$	$h_1 + 35 \text{ mm}$
			200	200
Minimum spacing	$s_{min} \geq$	[mm]	90	70
Minimum edge distance	$c_{min} \geq$	[mm]	65	65
Hilti setting tool ¹⁾			SIW 22T-A SIW 6(AT)-22 SIW 8-22SIW 9-A22 SIW 10-22	SIW 22T-A SIW 6(AT)-22 SIW 8-22SIW 9-A22 SIW 10-22 SI-AT-22 module optional

¹⁾ Installation with other impact wrench of equivalent power is possible.

HUS4 Bonded screw	Annex B5
Intended Use Installation parameters	

Table B7: Installation parameters HUS4 Bonded screw stainless steel

Fastener size HUS4			10	14
Type			HR, CR	HR
Nominal embedment depth	h_{nom}	[mm]	90	110
Nominal drill hole diameter	d_0	[mm]	10	14
Cutting diameter of drill bit	$d_{cut} \leq$	[mm]	10,45	14,50
Clearance hole diameter	$d_f \leq$	[mm]	14	18
Wrench size (H-type)	s	[mm]	15	21
Torx size (C-type)	TX	-	50	-
Diameter of countersunk head (CR)	d_h	[mm]	21	-
Depth of drill hole for cleaned hole or for uncleaned hole when drilling upwards	h_1	[mm]	$h_{nom} + 10\text{mm}$	
			100	120
Depth of drill hole for uncleaned hole hammer drilling in wall and floor position	$h_1 =$	[mm]	$h_{nom} + 30\text{ mm}$	$h_{nom} + 40\text{ mm}$
			120	150
Minimum thickness of concrete member	$h_{min} \geq$	[mm]	$h_1 + 30\text{ mm}$	
			140	160
Minimum spacing	$s_{min} \geq$	[mm]	50	60
Minimum edge distance	$c_{min} \geq$	[mm]	50	60
Hilti setting tool ¹⁾			SIW 22T-A SIW 6AT-A22 SIW 4(AT)- 22 SIW 6(AT)-22 SI-AT-22 module optional	SIW 22T-A SIW 6(AT)-22 SIW 8-22 gear 1 SIW 9-A22 SI-AT-22 module optional

¹⁾ Installation with other impact wrench of equivalent power is possible.

HUS4 Bonded screw


Intended Use
Installation parameters

Annex B6


Installation

Hole drilling and cleaning


Hammer drilling (HD) all sizes for carbon and stainless steel screw types

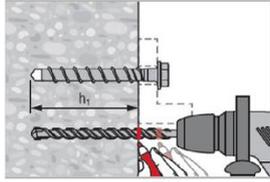

Mark drilling depth h_1 for drilling with or without fixture in place.
Details for drilling depth h_1 see table B5, B6 and B7.

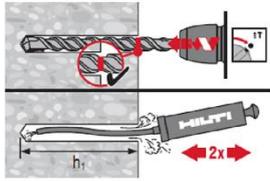


Cleaning needed in downward and horizontal installation direction with drill hole depth
 $h_1 = h_{nom} + 10 \text{ mm}$

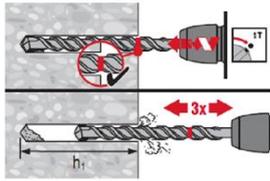


No cleaning is allowed in upward installation direction.
No cleaning is allowed in downward and horizontal installation direction when 3x ventilation¹⁾ after drilling is executed.
¹⁾ moving the drill bit in and out of the drill hole 3 times after the recommended drilling depth h_1 is achieved. This procedure shall be done with both revolution and hammer functions activated in the drilling machine. For more details read the relevant installation instruction (MPII).

Hammer drilling with Hilti hollow drill bit (HDB) TE-CD or TE-YD size 12 to 16 for carbon steel screw types

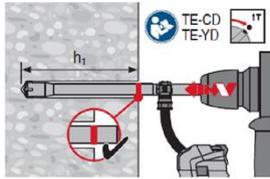

No cleaning needed
 $h_1 = h_{nom} + 10 \text{ mm}$

Insert of HUS4-MAX foil capsule




HUS4 Bonded screw

Intended Use
Installation instructions

Annex B7


Fastener setting without adjustment for carbon and stainless steel screw types

Setting by impact wrench

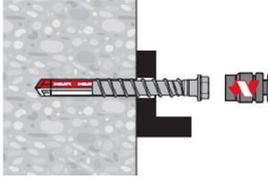


Setting parameters listed in Table B5, B6 and B7

Setting check

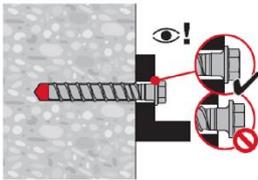


Fastener setting with adjustment for size 10 to size 14 for carbon steel screw types

Adjusting process 1

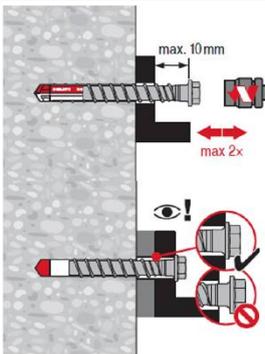

A screw can get adjusted maximum two times. The total allowed maximum thickness of shims added during the adjustment process is 10 mm. The final embedment depth after adjustment process must be larger or equal than h_{nom} .

Adjusting process 2

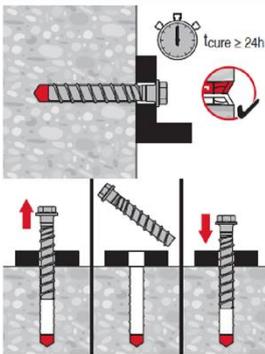


After minimum curing time of 24 h the HUS4 screw can screw out and in for 1 time.

HUS4 Bonded screw


Intended Use
Installation instructions

Annex B8

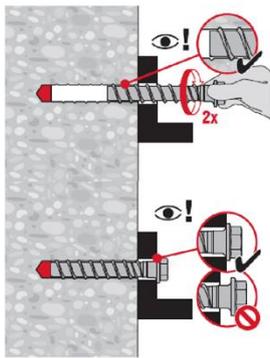


Find the thread in the drilled hole
The screw should be screw in 2 revolutions by hand and finish with the setting tool.


Overhead installation

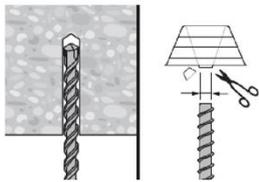


For upward installation direction use the overhead dripping cup
HIT-OHC.

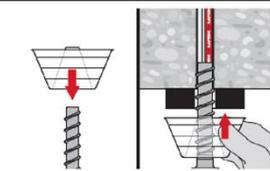

Fastener setting with Hilti filling set for carbon steel screw types

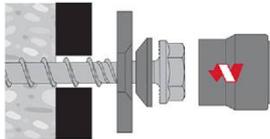

Injection of Hilti HIT mortar and curing time

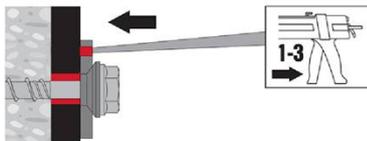

Fill the annular gap between screw and fixture with 1-3 strokes of a
Hilti injection mortar HIT-HY ... or HIT-RE ...
Follow the installation instructions supplied with the respective Hilti
injection mortar.
After required curing time t_{cure} the fastening can be loaded.

HUS4 Bonded screw

Intended Use
Installation instructions

Annex B9

Table C1: Essential characteristics for HUS4 Bonded screw carbon steel size 10 to 14 under tension load in case of static and quasi static loading

HUS4-MAX with HUS4 screw			10	12	14
			H(F); A(F); C	H(F)	H(F); A(F)
Nominal embedment depth	h_{nom}	[mm]	85	100	115
Installation factor	γ_{inst}	[-]	1,0		
Adjustment					
Total max. thickness of adjustment layers	t_{adj}	[mm]	10		
Max. number of adjustments	n_a	[-]	2		
Steel failure					
Characteristic resistance	$N_{RK,s}$	[kN]	55,0	79,0	101,5
Partial factor	$\gamma_{Ms,N}^{1)}$	[-]	1,5		
Combined pull-out and concrete failure³⁾					
Uncracked concrete, Temperature range I					
Concrete screw contribution	$N_{RK,p,CS,ucr}^0$	[kN]	$\geq N_{RK,c}^0$ ²⁾		
Bond material contribution	$N_{RK,p,B,ucr}^0$	[kN]	10,0	20,0	26,0
Increasing factor for $N_{RK,p,ucr} = N_{RK,p,ucr}(C20/25) * \psi_c$	ψ_c	[-]	$(f_{ck}/20)^{0,30}$		
Cracked concrete, Temperature range I:					
Concrete screw contribution	$N_{RK,p,CS,cr}^0$	[kN]	$\geq N_{RK,c}^0$ ²⁾		
Bond material contribution	$N_{RK,p,B,cr}^0$	[kN]	4,5	11,0	11,0
Increasing factor for $N_{RK,p,cr} = N_{RK,p,cr}(C20/25) * \psi_c$	ψ_c	[-]	$(f_{ck}/20)^{0,50}$		
Sustained load factor	ψ_{sus}^0	[-]	0,94		
Concrete cone failure					
Effective embedment depth	h_{ef}	[mm]	85	100	115
Factor for uncracked concrete	$k_{ucr,N}$	[-]	11,0		
Factor for cracked concrete	$k_{cr,N}$	[-]	7,7		
Increasing factor for $N_{RK,c} = N_{RK,c}(C20/25) * \psi_c$	ψ_c	[-]	$(f_{ck}/20)^{0,50}$		
Edge distance	$c_{cr,N}$	[mm]	1,5 h_{ef}		
Spacing	$s_{cr,N}$	[mm]	3 h_{ef}		
Splitting failure					
Characteristic resistance	$N_{RK,sp}^0$	[kN]	$= N_{RK,c}^0$ ⁴⁾		
Edge distance	$c_{cr,sp}$	[mm]	1,6 h_{ef}	1,7 h_{ef}	1,85 h_{ef}
Spacing	$s_{cr,sp}$	[mm]	3,2 h_{ef}	3,4 h_{ef}	3,7 h_{ef}

1) In absence of other national regulations

2) $N_{RK,c}^0$ is calculated according to EN1992-4:2018 with $h_{ef} = 0,85(h_{nom} - 0,5h_t)$

3) $N_{RK,p,CS,(u)cr}^0$ and $N_{RK,p,B,(u)cr}^0$ should be combined for the total bonded screw capacity $N_{RK,p,(u)cr}$ according to EOTA TR 075

4) $N_{RK,c}^0$ is calculated according to EN1992-4:2018 with h_{ef} according to annex C1

HUS4 Bonded screw

Performances

Essential characteristics under tension loads in case of static and quasi-static loading

Annex C1

Table C2: Essential characteristics for HUS4 Bonded screw carbon steel size 16 under tension load in case of static and quasi static loading

HUS4-MAX with HUS 4 screw			16 H(F)	16 G02 H(F)
Nominal embedment depth	h_{nom}	[mm]	130	130
Installation factor	γ_{inst}	[-]	1,0	
Adjustment				
Total max. thickness of adjustment layers	t_{adi}	[mm]	-	10
Max. number of adjustments	n_a	[-]	-	2
Steel failure				
Characteristic resistance	$N_{RK,s}$	[kN]	107,7	141,9
Partial factor	$\gamma_{Ms,N}^{1)}$	[-]	1,5	
Combined pull-out and concrete failure ³⁾				
Uncracked concrete, Temperature range I				
Concrete screw contribution	$N_{RK,p,CS,ucr}^0$	[kN]	46,0	$\geq N_{RK,c}^{2)}$
Bond material contribution	$N_{RK,p,B,ucr}^0$	[kN]	34,0	32,0
Increasing factor for $N_{RK,p,ucr} = N_{RK,p,ucr(C20/25)} * \psi_c$	ψ_c	[-]	$(f_{ck}/20)^{0,30}$	$(f_{ck}/20)^{0,50}$
Cracked concrete, Temperature range I:				
Concrete screw contribution	$N_{RK,p,CS,cr}^0$	[kN]	32,0	$\geq N_{RK,c}^{2)}$
Bond material contribution	$N_{RK,p,B,cr}^0$	[kN]	23,0	16,0
Increasing factor for $N_{RK,p,cr} = N_{RK,p,cr(C20/25)} * \psi_c$	ψ_c	[-]	$(f_{ck}/20)^{0,50}$	
Sustained load factor	ψ_{sus}^0	[-]	0,94	
Concrete cone failure				
Effective embedment depth	h_{ef}	[mm]	130	
Factor for uncracked concrete	$k_{ucr,N}$	[-]	11,0	
Factor for cracked concrete	$k_{cr,N}$	[-]	7,7	
Increasing factor for $N_{RK,c} = N_{RK,c(C20/25)} * \psi_c$	ψ_c	[-]	$(f_{ck}/20)^{0,50}$	
Edge distance	$c_{cr,N}$	[mm]	1,5 h_{ef}	
Spacing	$s_{cr,N}$	[mm]	3 h_{ef}	
Splitting failure				
Characteristic resistance	$N_{RK,sp}^0$	[kN]	$= N_{RK,c}^{4)}$	
Edge distance	$c_{cr,sp}$	[mm]	1,95 h_{ef}	
Spacing	$s_{cr,sp}$	[mm]	3,9 h_{ef}	

1) In absence of other national regulations.

2) $N_{RK,c}$ is calculated according to EN1992-4:2018 with $h_{ef} = 0,85(h_{nom} - 0,5h_t)$

3) $N_{RK,p,CS,(u)cr}^0$ and $N_{RK,p,B,(u)cr}^0$ should be combined for the total bonded screw capacity $N_{RK,p,(u)cr}$ according to EOTA TR 075

4) $N_{RK,c}$ is calculated according to EN1992-4:2018 with h_{ef} according to annex C2

HUS4 Bonded screw

Performances
Essential characteristics under tension loads in case of static and quasi-static loading

Annex C2

Table C3: Essential characteristics for HUS4 Bonded screw stainless steel under tension load in case of static and quasi static loading

HUS4-MAX with HUS4 screw			10 HR; CR	14 HR
Nominal embedment depth	h_{nom}	[mm]	90	110
Installation factor	γ_{inst}	[-]	1,0	
Steel failure				
Characteristic resistance	$N_{RK,s}$	[kN]	52,6	102,2
Partial factor	$\gamma_{Ms,N}^{1)}$	[-]	1,4	
Combined pull-out and concrete failure ³⁾				
Uncracked concrete, Temperature range I				
Concrete screw contribution	$N_{RK,p,CS,ucr}^0$	[kN]	25,0	$\geq N_{RK,c}^{2)}$
Bond material contribution	$N_{RK,p,B,ucr}^0$	[kN]	15,0	22,0
Increasing factor for $N_{RK,p,ucr} = N_{RK,p,ucr}(C20/25) * \psi_c$	ψ_c	[-]	$(f_{ck}/20)^{0,30}$	
Cracked concrete, Temperature range I				
Concrete screw contribution	$N_{RK,p,CS,cr}^0$	[kN]	16	25
Bond material contribution	$N_{RK,p,B,cr}^0$	[kN]	8	15
Increasing factor for $N_{RK,p,cr} = N_{RK,p,cr}(C20/25) * \psi_c$	ψ_c	[-]	$(f_{ck}/20)^{0,50}$	
Sustained load factor	ψ_{sus}^0	[-]	0,90	
Concrete cone failure				
Effective embedment depth	h_{ef}	[mm]	90	110
Factor for uncracked concrete	$k_{ucr,N}$	[-]	11,0	
Factor for cracked concrete	$k_{cr,N}$	[-]	7,7	
Increasing factor for $N_{RK,c} = N_{RK,c}(C20/25) * \psi_c$	ψ_c	[-]	$(f_{ck}/20)^{0,50}$	
Edge distance	$c_{cr,N}$	[mm]	1,5 h_{ef}	
Spacing	$s_{cr,N}$	[mm]	3 h_{ef}	
Splitting failure				
Characteristic resistance	$N_{RK,sp}^0$	[kN]	$= N_{RK,c}^{4)}$	
Edge distance	$c_{cr,sp}$	[mm]	1,95 h_{ef}	1,85 h_{ef}
Spacing	$s_{cr,sp}$	[mm]	3,9 h_{ef}	3,7 h_{ef}

1) In absence of other national regulations.

2) $N_{RK,c}^0$ is calculated according to EN1992-4:2018 with $h_{ef} = 0,85(h_{nom} - 0,5h_t)$

3) $N_{RK,p,CS,(u)cr}^0$ and $N_{RK,p,B,(u)cr}^0$ should be combined for the total bonded screw capacity $N_{RK,p,(u)cr}$ according to EOTA TR 075

4) $N_{RK,c}^0$ is calculated according to EN1992-4:2018 with h_{ef} according to annex C3

HUS4 Bonded screw

Performances

Essential characteristics under tension loads in case of static and quasi-static loading

Annex C3

Table C4: Essential characteristics for HUS4 Bonded screw carbon steel under shear load in case of static and quasi static loading

HUS4-MAX with HUS4 screw			10 H(F); A(F); C	12 H(F)	14 H(F); A(F)	16 H(F)	16 H(F) G02
Nominal embedment depth	h_{nom}	[mm]	85	100	115	130	
Steel failure for shear load							
Characteristic resistance	$V_{Rk,s}^0$	[kN]	32,0	44,9	62	73,1	82,9
Partial factor	$\gamma_{Ms,V}^{1)}$	[-]	1,25				
Ductility factor	k_7	[-]	0,8				
Characteristic resistance	$M_{Rk,s}^0$	[Nm]	64	120	186	240	350
Concrete pry-out failure							
Pry-out factor	k_8	[-]	2,0				
Concrete edge failure							
Effective length of fastener	l_f	[mm]	85	100	115	130	
Diameter of fastener	d	[mm]	10	12	14	16	

¹⁾ In absence of other national regulations.

Table C5: Essential characteristics for HUS4 Bonded screw stainless steel under shear load in case of static and quasi static loading

HUS4-MAX with HUS4 screw			10 HR; CR	14 HR
Nominal embedment depth	h_{nom}	[mm]	90	110
Steel failure for shear load				
Characteristic resistance	$V_{Rk,s}^0$	[kN]	33,0	77,0
Partial factor	$\gamma_{Ms,V}^{1)}$	[-]	1,5	
Ductility factor	k_7	[-]	1,0	
Characteristic resistance	$M_{Rk,s}^0$	[Nm]	66	193
Concrete pry-out failure				
Pry-out factor	k_8	[-]	2,0	
Concrete edge failure				
Effective length of fastener	l_f	[mm]	90	110
Diameter of fastener	d	[mm]	10	14

¹⁾ In absence of other national regulations.

HUS4 Bonded screw

Performances

Essential characteristics under shear load in case of static and quasi static loading

Annex C4

Table C6: Essential characteristics for HUS4 Bonded screw carbon steel seismic performance category C1 in concrete

HUS4-MAX with HUS4 screw			10 H(F); A(F); C	12 H(F)	14 H(F); A(F)	16 H(F) G02
Nominal embedment depth	h_{nom}	[mm]	85	100	115	130
Adjustment						
Total max. thickness of adjustment layers	t_{adj}	[mm]	10			
Max. number of adjustments	n_a	[-]	2			
Steel failure for tension and shear load						
Characteristic resistance	$N_{Rk,s,C1}$	[kN]	55,0	79,0	101,5	141,9
Partial factor	$\gamma_{Ms,N}^{1)}$	[-]	1,5			
Characteristic resistance	$V_{Rk,s,C1}$	[kN]	26,7	38,9	46,0	51,0
Partial factor	$\gamma_{Ms,V}^{1)}$	[-]	1,25			
Reduction factor acc. to EN 1992-4:2018 annular gap unfilled	α_{gap}	[-]	0,5			
Reduction factor acc. to EN 1992-4:2018 annular gap filled	α_{gap}	[-]	1,0			
Combined pullout and concrete cone failure Cracked concrete C20/25, Temperature range I³⁾						
Concrete screw contribution	$N_{Rk,p,CS,C1}^0$	[kN]	$\geq N_{Rk,c}^{0,2)}$			
Bond material contribution	$N_{Rk,p,B,C1}^0$	[kN]	4,5	11,0	11,0	16,0
Concrete cone failure						
Effective embedment depth	h_{ef}	[mm]	85	100	115	130
Edge distance	$c_{cr,N}$	[mm]	$1,5 h_{ef}$			
Spacing	$s_{cr,N}$	[mm]	$3 h_{ef}$			
Installation factor	γ_{inst}	[-]	1,0			
Concrete pry-out failure						
Pry-out factor	k_B	[-]	2,0			
Concrete edge failure						
Effective length of fastener	$l_f = h_{ef}$	[mm]	85	100	115	130
Outside diameter of fastener	d_{nom}	[mm]	10	12	14	16

¹⁾ In absence of other national regulations.

²⁾ $N_{Rk,c}^0$ is calculated according to EN1992-4:2018 with $h_{ef} = 0,85(h_{nom} - 0,5h_t)$

³⁾ $N_{Rk,p,CS,C1}^0$ and $N_{Rk,p,B,C1}^0$ should be combined for the total bonded screw capacity $N_{Rk,p,C1}$ according to EOTA TR 075

HUS4 Bonded screw

Performances

Essential characteristics for seismic performance category C1

Annex C5

Table C7: Essential characteristics for HUS4 Bonded screw carbon steel seismic performance category C2 in concrete

HUS4-MAX with HUS4 screw			10 H(F); A(F); C	12 H(F)	14 H(F); A(F)	16 H(F) G02
Nominal embedment depth	h_{nom}	[mm]	85	100	115	130
Adjustment						
Total max. thickness of adjustment layers	t_{adj}	[mm]	10			
Max. number of adjustments	n_a	[-]	2			
Steel failure for tension						
Characteristic resistance	$N_{Rk,s,C2}$	[kN]	55,0	79,0	101,5	141,9
Partial factor	$\gamma_{Ms,N}^{1)}$	[-]	1,5			
Steel failure shear load						
Partial factor	$\gamma_{Ms,V}^{1)}$	[-]	1,25			
Installation with Hilti filling set (HUS4-H and HUS4-A)						
Characteristic resistance	$V_{Rk,s,C2}$	[kN]	23,2	28,6	46,5	61,9
Reduction factor acc. to EN 1992-4:2018 annular gap filled	α_{gap}	[-]	1,0			
Installation without Hilti filling set						
Characteristic resistance	$V_{Rk,s,C2}$	[kN]	14,8	23,7	34,4	61,9
Reduction factor acc. to EN 1992-4:2018 annular gap unfilled	α_{gap}	[-]	0,5			
Combined pullout and concrete cone failure Cracked concrete C20/25, Temperature range I²⁾						
Concrete screw contribution	$N_{Rk,p,CS,C2}^0$	[kN]	5,4	11,4	17,7	25,8
Bond material contribution	$N_{Rk,p,B,C2}^0$	[kN]	5,3	5,8	0,5	2,7
Concrete cone failure						
Effective embedment depth	h_{ef}	[mm]	85	100	115	130
Edge distance	$c_{cr,N}$	[mm]	1,5 h_{ef}			
Spacing	$s_{cr,N}$	[mm]	3 h_{ef}			
Installation factor	γ_{inst}	[-]	1,0			
Concrete pry-out failure						
Pry-out factor	k_8	[-]	2,0			
Concrete edge failure						
Effective length of fastener	$l_f = h_{ef}$	[mm]	85	100	115	130
Outside diameter of fastener	d_{nom}	[mm]	10	12	14	16

¹⁾ In absence of other national regulations.

²⁾ $N_{Rk,p,CS,C2}^0$ and $N_{Rk,p,B,C2}^0$ should be combined for the total bonded screw capacity $N_{Rk,p,C2}$ according to EOTA TR 075

HUS4 Bonded screw

Performances
Essential characteristics for seismic performance category C2

Annex C6

Table C8: Essential characteristics under fire exposure in concrete for HUS4 Bonded screw carbon steel

HUS4-MAX with HUS4 screw			10			12		14		16	
			H(F)	C 10	A(F)	H(F)	H(F)	A(F)	H(F)	H(F) (G02)	
Nominal embedment depth	h_{nom}	[mm]	85	85	85	100	115	115	130	130	
Steel failure for tension and shear load ($F_{Rk,s,fi} = N_{Rk,s,fi} = V_{Rk,s,fi}$)											
Characteristic resistance	R30	$F_{Rk,s,fi}$	[kN]	4,2	1,0	4,2	7,7	10,5	8,4	10,7	
	R60	$F_{Rk,s,fi}$	[kN]	3,2	0,9	3,3	5,9	8,1	6,8	8,2	
	R90	$F_{Rk,s,fi}$	[kN]	2,4	0,7	2,5	4,1	5,8	5,1	5,9	
	R120	$F_{Rk,s,fi}$	[kN]	1,7	0,6	2,1	3,1	4,4	4,3	4,5	
	R30	$M^0_{Rk,s,fi}$	[Nm]	4,9	1,2	4,8	11,6	19,3	15,4	23,9	
	R60	$M^0_{Rk,s,fi}$	[Nm]	3,7	1,0	3,8	8,9	14,8	12,4	18,3	
	R90	$M^0_{Rk,s,fi}$	[Nm]	2,7	0,8	2,9	6,2	10,7	9,3	13,2	
	R120	$M^0_{Rk,s,fi}$	[Nm]	1,9	0,6	2,4	4,7	8,1	7,8	10,0	
Pull-out failure											
Characteristic resistance	R30	$N^0_{Rk,p,fi}$	[kN]				6,1	7,5	8,7	11,7	
	R60			4,7							
	R90						4,9	6,0	7,0	9,4	
	R120			3,7							
Edge distance											
R30 to R120	$c_{cr,fi}$	[mm]	2 h_{ef}								
In case of fire exposure from more than one side, the minimum edge distance shall be ≥ 300 mm.											
Fastener spacing											
R30 to R120	$s_{cr,fi}$	[mm]	2 $c_{cr,fi}$								
Concrete pry-out failure											
R30 to R120	k_8	[-]	2,0								
The anchorage depth shall be increased for wet concrete by at least 30 mm.											

HUS4 Bonded screw

Performances
Essential characteristics under fire exposure in concrete

Annex C7

Table C9: Displacements under tension load for HUS4 Bonded screw carbon steel in case of static and quasi static loading

HUS4-MAX with HUS4 screw		10 H(F); A(F); C		12 H(F)		
		Uncracked concrete	Cracked concrete	Uncracked concrete	Cracked concrete	
Temperature range I						
Displacement	N	[kN]	17,1	10,5	23,8	16,2
	δ_{N0}	[mm]	0,3	0,3	0,4	0,5
	$\delta_{N\infty}$	[mm]	0,6	0,6	0,6	0,6

Table C10: Displacements under tension load for HUS4 Bonded screw carbon steel in case of static and quasi static loading

HUS4-MAX with HUS4 screw		14 H(F); A(F)		16 H(F)		16 H(F) G02		
		Uncracked concrete	Cracked concrete	Uncracked concrete	Cracked concrete	Uncracked concrete	Cracked concrete	
Temperature range I								
Displacement	N	[kN]	31,0	18,1	38,1	26,2	34,7	24,3
	δ_{N0}	[mm]	0,5	0,6	0,6	0,8	0,1	0,2
	$\delta_{N\infty}$	[mm]	0,8	0,8	0,8	0,8	0,6	0,6

Table C11: Displacements under tension load for HUS4 Bonded screw stainless steel in case of static and quasi static loading

HUS4-MAX with HUS4 screw		10 HR; CR		14 HR		
		Uncracked concrete	Cracked concrete	Uncracked concrete	Cracked concrete	
Temperature range I						
Displacement	N	[kN]	19,0	11,4	31,0	19,0
	δ_{N0}	[mm]	0,3	0,5	0,5	0,8
	$\delta_{N\infty}$	[mm]	0,5	0,5	0,5	0,8

HUS4 Bonded screw

Performances
Displacements

Annex C8

Table C12: Displacements under shear load for HUS4 Bonded screw carbon steel in case of static and quasi static loading

HUS4-MAX with HUS4 screw		10 H(F); A(F); C	12 H(F)	14 H(F); A(F)	16 H(F)	16 H(F) G02	
Temperature range I							
Displacement	V	[kN]	18,3	25,7	35,4	41,8	44,5
	δ_{V0}	[mm]	1,0	0,9	4,0	1,8	3,5
	$\delta_{V\infty}$	[mm]	1,5	1,4	6,0	2,7	5,3

Table C13: Displacements under shear load for HUS4 Bonded screw stainless steel in case of static and quasi static loading

HUS4-MAX with HUS4 screw		10 HR; CR	14 HR	
Temperature range I				
Displacement	V	[kN]	15,7	27,3
	δ_{V0}	[mm]	1,7	3,9
	$\delta_{V\infty}$	[mm]	2,4	4,3

Table C14: Displacements under tension and shear load for HUS4 Bonded screw carbon steel for seismic category C2

HUS4-MAX with HUS4 screw		10 H(F); A(F); C	12 H(F)	14 H(F); A(F)	16 H(F) G02	
Temperature range I						
Tension load						
Displacement DLS	$\delta_{N,C2 (DLS)}$	[mm]	0,75	0,70	0,77	0,65
Displacement ULS	$\delta_{N,C2 (ULS)}$	[mm]	2,07	3,43	4,24	2,29
Shear load with Hilti filling set (HUS4-H and HUS4-A)						
Displacement DLS	$\delta_{V,C2 (DLS)}$	[mm]	1,72	1,73	2,52	5,84
Displacement ULS	$\delta_{V,C2 (ULS)}$	[mm]	6,88	5,62	6,79	11,04
Shear load without Hilti filling set (HUS4-H and HUS4-A)						
Displacement DLS	$\delta_{V,C2 (DLS)}$	[mm]	5,02	4,90	4,93	5,84
Displacement ULS	$\delta_{V,C2 (ULS)}$	[mm]	8,97	7,00	9,14	11,04

HUS4 Bonded screw

Performances
Displacements

Annex C9