

Public-law institution jointly founded by the  
federal states and the Federation

**European Technical Assessment Body  
for construction products**



## European Technical Assessment

**ETA-25/0105  
of 23 April 2025**

English translation prepared by DIBt - Original version in German language

### General Part

Technical Assessment Body issuing the  
European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

Clawbolt Pro EAW and EIW

Product family  
to which the construction product belongs

Mechanical fastener for use in concrete

Manufacturer

Hobson Engineering Co Pty Ltd  
10 Clay Place Eastern Creek NSW 2766  
AUSTRALIEN

Manufacturing plant

Plant 6

This European Technical Assessment  
contains

36 pages including 3 annexes which form an integral part  
of this assessment

This European Technical Assessment is  
issued in accordance with Regulation (EU)  
No 305/2011, on the basis of

EAD 330232-01-0601, Edition 05/2021

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 25(3) of Regulation (EU) No 305/2011.

## Specific Part

### 1 Technical description of the product

The Clawbolt Pro EAW and EIW is a fastener made of zinc plated steel, stainless steel or high corrosion resistant steel which is placed into a drilled hole and anchored by torque-controlled expansion. The following fastener types are covered:

- Anchor type Clawbolt Pro EAW with external thread, washer and hexagon nut, sizes M8 to M27,
- Anchor type Clawbolt Pro EIW-B with internal thread, hexagon head nut and washer B, sizes M6 to M12,
- Anchor type Clawbolt Pro EIW-K with internal thread, countersunk head screw and countersunk washer K, sizes M6 to M12,
- Anchor type Clawbolt Pro EIW-S with internal thread, hexagon nut and washer S, sizes M6 to M12.

The product description is given in Annex A.

### 2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the fastener is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the fastener of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

### 3 Performance of the product and references to the methods used for its assessment

#### 3.1 Mechanical resistance and stability (BWR 1)

| Essential characteristic   | Performance   |
|--|---|
| Characteristic resistance to tension load<br>(static and quasi-static loading)           | Clawbolt Pro EAW see Annex B4, B5, C1 to C4<br>Clawbolt Pro EIW see Annex B8, C11 and C12 |
| Characteristic resistance to shear load<br>(static and quasi-static loading)             | Clawbolt Pro EAW see Annex C5<br>Clawbolt Pro EIW see Annex C13                           |
| Displacements (static and quasi-static loading)  | Clawbolt Pro EAW see Annex C9 and C10<br>Clawbolt Pro EIW see Annex C15                   |
| Characteristic resistance and displacements for seismic performance categories C1 and C2 | Clawbolt Pro EAW see Annex C6, C9 and C10<br>Clawbolt Pro EIW No performance assessed     |

### 3.2 Safety in case of fire (BWR 2)

| Essential characteristic | Performance  |
|--------------------------|--|
| Reaction to fire         | Class A1   |
| Resistance to fire       | Clawbolt Pro EAW see Annex C7 and C8<br>Clawbolt Pro EIW see Annex C14 |

### 3.3 Aspects of durability

| Essential characteristic | Performance  |
|--------------------------|--------------|
| Durability               | See Annex B1 |

## 4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with the European Assessment Document EAD 330232-01-0601 the applicable European legal act is: [96/582/EC].

The system to be applied is: 1

## 5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited with Deutsches Institut für Bautechnik.

Issued in Berlin on 23 April 2025 by Deutsches Institut für Bautechnik

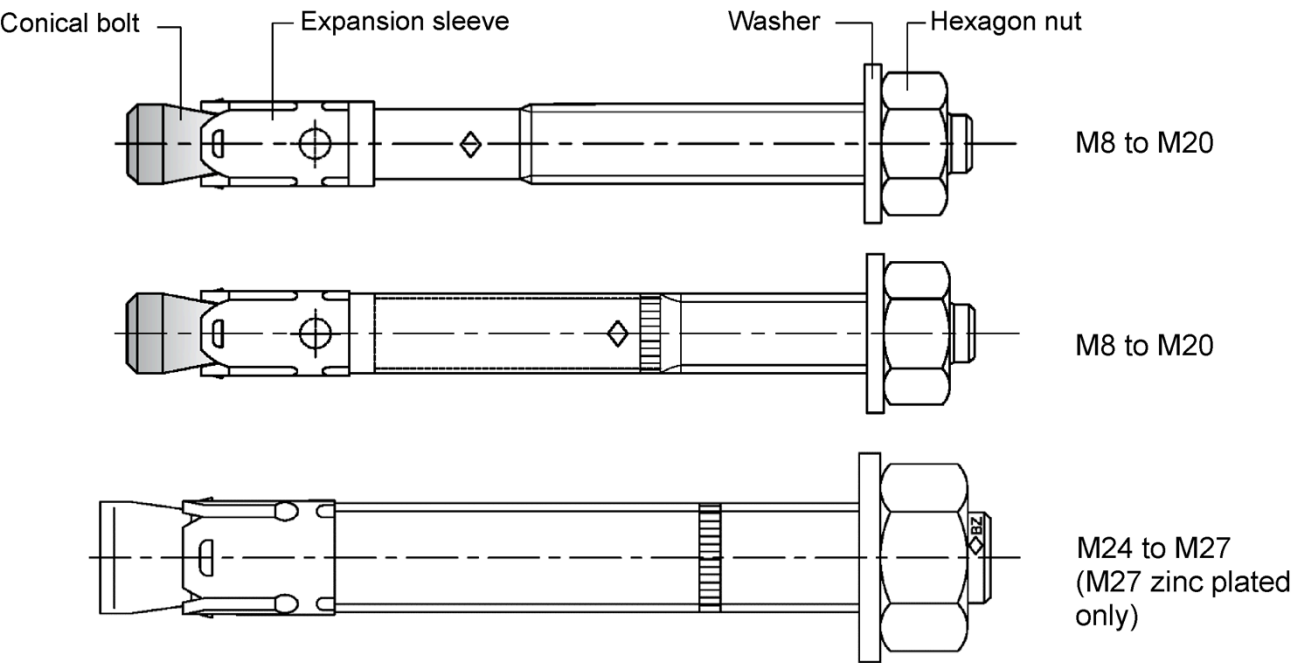
Dipl.-Ing. Beatrix Wittstock  
Head of Section

*beglaubigt:*  
Baderschneider

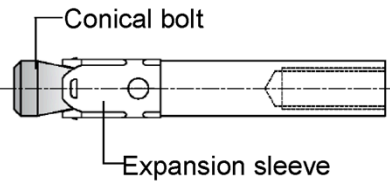









| Fastener version | Product description             | Intended use                                | Performance           |
|------------------|---------------------------------|---|-----------------------|
| Clawbolt Pro EAW | Annex A1 - Annex A4             | Annex B1 – Annex B7                         | Annex C1 – Annex C10  |
| Clawbolt Pro EIW | Annex A1<br>Annex A5 – Annex A7 | Annex B1 – Annex B2<br>Annex B8 – Annex B10 | Annex C11 – Annex C15 |

Clawbolt Pro EAW

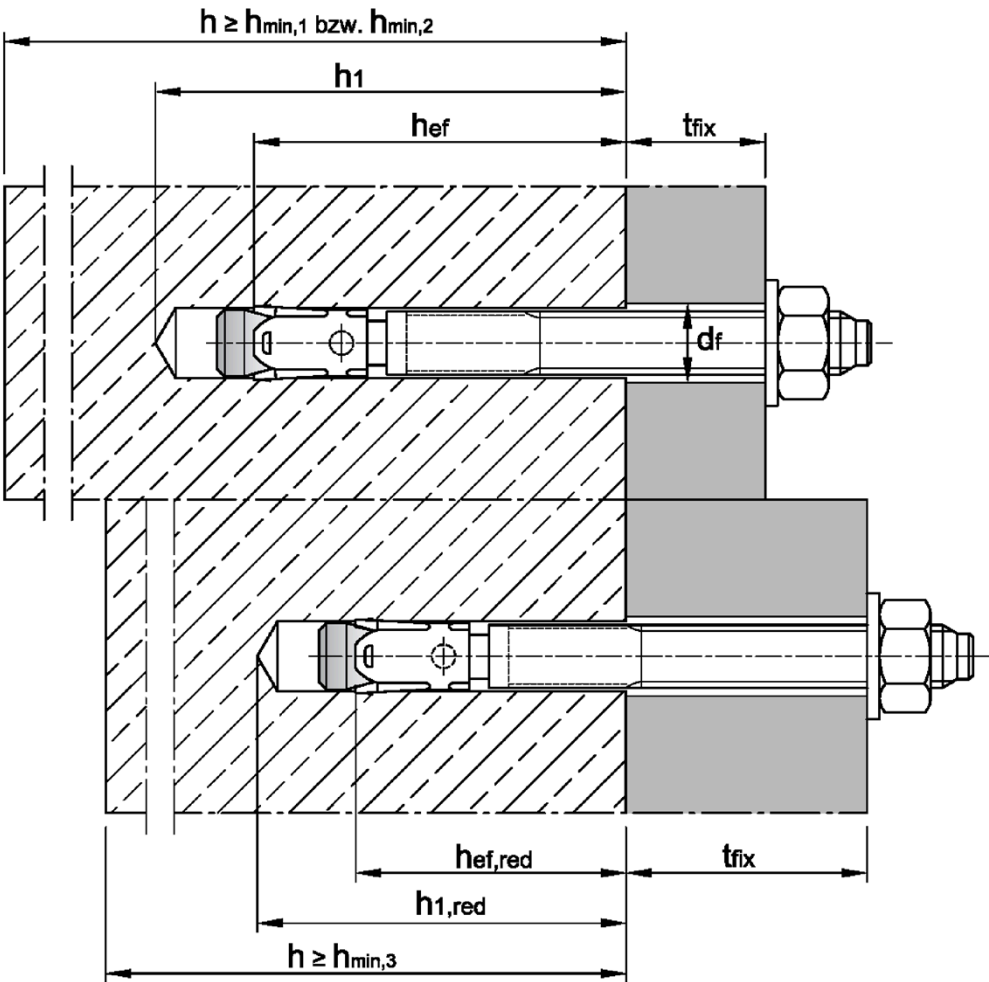


Clawbolt Pro EIW M6 to M12

| Fastener system    |   |   |   |
|--------------------|---|---|---|
| Clawbolt Pro EIW-B |  |  Washer  |  Hexagon head screw      |
| Clawbolt Pro EIW-K |   |  Countersunk washer  |  Countersunk head screw  |
| Clawbolt Pro EIW-S |   |  Washer  Hexagon nut |  Commercial standard rod |

| Clawbolt Pro EAW and EIW              |          |
|---------------------------------------|----------|
| Product description<br>Fastener types | Annex A1 |

Intended use Clawbolt Pro EAW




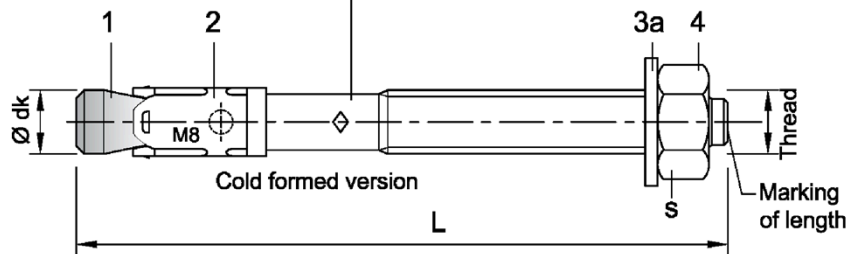
Clawbolt Pro EAW und EIW


Product description  
Installation situation **Clawbolt Pro EAW**


Annex A2

Fastener size Clawbolt Pro EAW M8 to M20:

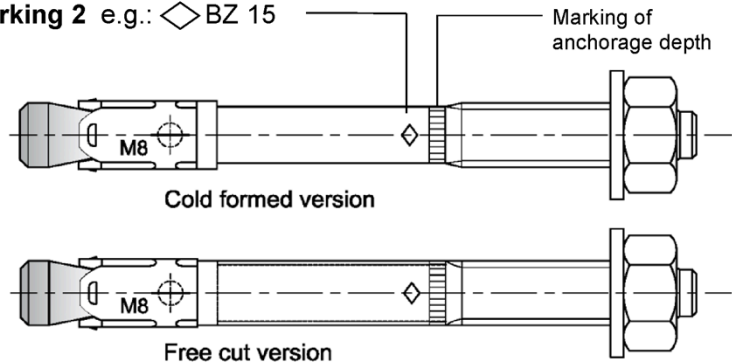
Marking 1 e.g.:  BZ 15/35





Marking 1 e.g.:  BZ 15/35

 identifying mark of manufacturing plant  
BZ fastener identity  
15 max. thickness of fixture for  $h_{ef}$   
35 max. thickness of fixture for  $h_{ef,red}$   
M8 thread diameter  
Additional marking:  
A4 stainless steel  
HCR high corrosion resistant steel

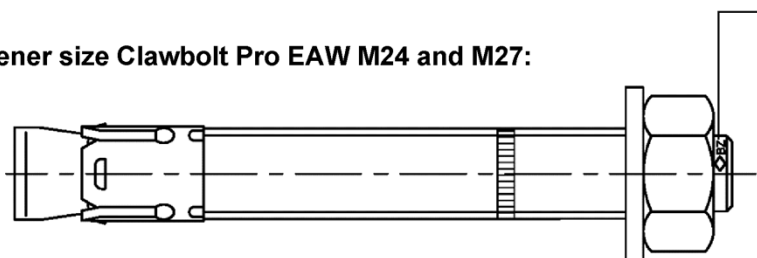
Marking 2 e.g.:  BZ 15





Marking 2 e.g.:  BZ 15

 identifying mark of manufacturing plant  
BZ fastener identity  
15 maximum thickness of fixture for  $h_{ef}$   
M8 thread diameter  
Additional marking:  
A4 stainless steel  
HCR high corrosion resistant steel

Fastener size Clawbolt Pro EAW M24 and M27:




Marking 3 e.g.:  BZ M24-30

 identifying mark of manufacturing plant  
BZ fastener identity  
M24 thread diameter  
30 maximum thickness of fixture  
Additional marking:  
A4 stainless steel  
HCR high corrosion resistant steel


| Marking of length             | C (c) | D (d) | E (e) | F (f) | G (g) | H (h) | I (i) | J (j) | K (k) | L (l) | M (m) | N (n) |
|-------------------------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| Length of fastener min $\geq$ | 63,5  | 76,2  | 88,9  | 101,6 | 114,3 | 127,0 | 139,7 | 152,4 | 165,1 | 177,8 | 190,5 | 203,2 |
| Length of fastener max $<$    | 76,2  | 88,9  | 101,6 | 114,3 | 127,0 | 139,7 | 152,4 | 165,1 | 177,8 | 190,5 | 203,2 | 215,9 |

| Marking of length             | O (o) | P (p) | Q (q) | R (r) | S (s) | T (t) | U (u) | V (v) | W (w) | X (x) | Y (y) | Z (z) |
|-------------------------------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|-------|
| Length of fastener min $\geq$ | 215,9 | 228,6 | 241,3 | 254,0 | 279,4 | 304,8 | 330,2 | 355,6 | 381,0 | 406,4 | 431,8 | 457,2 |
| Length of fastener max $<$    | 228,6 | 241,3 | 254,0 | 279,4 | 304,8 | 330,2 | 355,6 | 381,0 | 406,4 | 431,8 | 457,2 | 483,0 |

Filling washer and reducing adapter for filling the annular gap between fastener and fixture



Thickness of washer  
for diameter  
 $< M24$ :  $t = 5 \text{ mm}$   
 $\geq M24$ :  $t = 6 \text{ mm}$



Clawbolt Pro EAW und EIW

Product description  
Fastener sizes and marking

Annex A3

**Table A1: Fastener dimensions Clawbolt Pro EAW**

| Fastener size                    |                         |                      | M8                    | M10                   | M12                   | M16                  | M20                  | M24                  | M27                  |
|----------------------------------|-------------------------|----------------------|-----------------------|-----------------------|-----------------------|----------------------|----------------------|----------------------|----------------------|
| Conical bolt                     | Thread                  |                      | M8                    | M10                   | M12                   | M16                  | M20                  | M24                  | M27                  |
|                                  | Ø d <sub>k</sub> =      |                      | 7,9                   | 9,8                   | 12,0                  | 15,7                 | 19,7                 | 24                   | 28                   |
| Length of fastener <sup>1)</sup> | Steel, zinc plated      | L                    | 65 + t <sub>fix</sub> | 80 + t <sub>fix</sub> | 96,5+t <sub>fix</sub> | 118+t <sub>fix</sub> | 137+t <sub>fix</sub> | 161+t <sub>fix</sub> | 178+t <sub>fix</sub> |
|                                  | A4, HCR                 | L                    | 65 + t <sub>fix</sub> | 80 + t <sub>fix</sub> | 96,5+t <sub>fix</sub> | 118+t <sub>fix</sub> | 137+t <sub>fix</sub> | 168+t <sub>fix</sub> | -                    |
|                                  | reduced anchorage depth | L <sub>hef,red</sub> | 54 + t <sub>fix</sub> | 60 + t <sub>fix</sub> | 76,5+t <sub>fix</sub> | 98+t <sub>fix</sub>  | -                    | -                    | -                    |
| Thickness of filling washer      |                         | t [mm]               | 5                     | 5                     | 5                     | 5                    | 5                    | 6                    | 6                    |
| Hexagon nut                      |                         | s                    | 13                    | 17                    | 19                    | 24                   | 30                   | 36                   | 41                   |

<sup>1)</sup> With additional use of filling washer 3b the usable thickness of fixture is reduced by the thickness of filling washer t [mm]

Dimensions in mm

**Table A2: Materials Clawbolt Pro EAW**

| No. | Part             | EAWMS   |   | EAW16   | EAWHR   |
|-----|------------------|---|---|---|---|
|     |                  | Steel, zinc plated  |   | Stainless steel<br>A4<br>(CRC III)  | High corrosion<br>resistant steel HCR<br>(CRC V)  |
|     |                  | galvanized $\geq 5\mu\text{m}$  | sherardized $\geq 45\mu\text{m}$  |   |   |
| 1   | Conical bolt     | M8 to M20:<br>Cold formed or machined steel, galvanized, cone plastic coated                        | M8 to M20:<br>Cold formed or machined steel, sherardized, cone plastic coated                       | M8 to M20:<br>Stainless steel (e.g. 1.4401, 1.4404, 1.4578, 1.4571)<br>EN 10088:2014, cone plastic coated | M8 to M20:<br>High corrosion resistant steel 1.4529 or 1.4565, EN 10088:2014, cone plastic coated |
|     | Threaded bolt    | M24 and M27:<br>Steel, galvanized   | M24 and M27:<br>steel, sherardized  | M24:<br>Stainless steel (e.g. 1.4401, 1.4404)<br>EN 10088:2014  | M24:<br>High corrosion resistant steel 1.4529 or 1.4565, EN 10088:2014                            |
|     | Threaded cone    |   | M24 and M27:<br>Steel, galvanized   |   |   |
| 2   | Expansion sleeve | M8 to M20:<br>Steel (e.g. 1.4301 or 1.4401)<br>EN 10088:2014,<br>M24 and M27:<br>Steel, zinc plated | M8 to M20:<br>Steel (e.g. 1.4301 or 1.4401)<br>EN 10088:2014,<br>M24 and M27:<br>Steel, zinc plated | Stainless steel (e.g. 1.4401, 1.4404, 1.4571)<br>EN 10088:2014  | Stainless steel (e.g. 1.4401, 1.4404, 1.4571)<br>EN 10088:2014                                    |
| 3a  | Washer           | Steel, zinc plated  | Steel, zinc plated  | Stainless steel (e.g. 1.4401, 1.4571)<br>EN 10088:2014  | High corrosion resistant steel 1.4529 or 1.4565, EN 10088:2014                                    |
| 3b  | Filling washer   |   |   |   |   |
| 4   | Hexagon nut      | Steel, galvanized, coated   | Steel, zinc plated  | Stainless steel (e.g. 1.4401, 1.4571)<br>EN 10088:2014, coated  | High corrosion resistant steel 1.4529 or 1.4565, EN 10088:2014, coated                            |

**Clawbolt Pro EAW und EIW**

**Product description**  
Dimensions and materials

**Annex A4**


Intended use **Clawbolt Pro EIW**


| Pre-setting installation (V)   | Through-setting installation (D)   |
|--|--|
| Pre-set fastener body, the fixture bears on the screw or thread rod only | The fastener is set through the fixture, the fixture bears on the conical bolt EIW |
| <b>Clawbolt Pro EIW-B</b> consisting of EIW and -B                       |  |
|  |  |
| <b>Clawbolt Pro EIW-K</b> consisting of EIW and -K                       |  |
|  |  |
| <b>Clawbolt Pro EIW-S</b> consisting of EIW and -S                       |  |
|  |  |
| <b>Setting tool</b>  |  |
|  |  |
| EIW-AT M8 V, EIW-AT M10 V, EIW-AT M12 V oder EIW-AT M16 V                | EIW-AT M8 D, EIW-AT M10 D, EIW-AT M12 D oder EIW-AT M16 D                          |

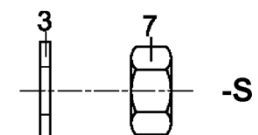
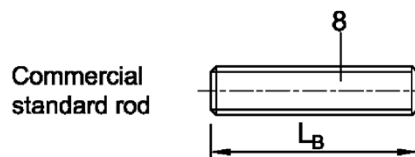
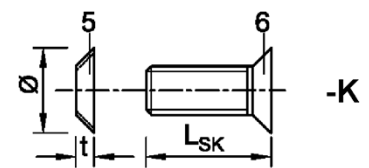
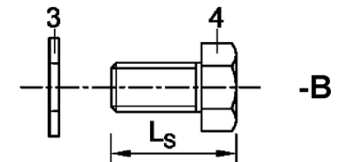
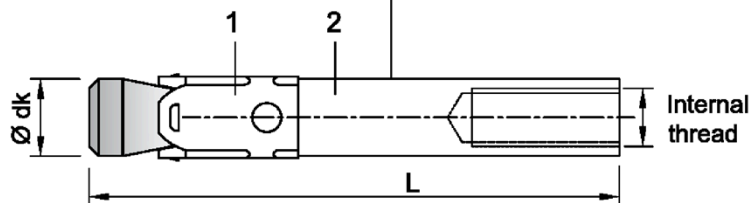
**Clawbolt Pro EAW und EIW**

**Product description**  
Installation situation **Clawbolt Pro EIW**

**Annex A5**

**Marking:**  identifying mark of manufacturing plant  
BZ fastener identity  
M6 size of internal thread  
10 max. thickness of fixture  
(only Through-setting installation)  
**Additional marking:**  
A4 stainless steel  
HCR high corrosion resistant steel

e.g.:  BZ M6-10 A4



**Table A3: Fastener dimensions Clawbolt Pro EIW**

| No. | Fastener size                         |                           | M6                            | M8   | M10                           | M12                           |
|-----|---------------------------------------|---------------------------|-------------------------------|--|-------------------------------|-------------------------------|
| 1   | Conical bolt with internal thread     | $\varnothing d_k$         | 7,9                           | 9,8  | 11,8                          | 15,7                          |
|     | Pre-setting installation              | L                         | 50                            | 62   | 70                            | 86                            |
|     | Through-setting installation          | L                         | 50 + t <sub>fix</sub>         | 62 + t <sub>fix</sub>  | 70 + t <sub>fix</sub>         | 86 + t <sub>fix</sub>         |
| 2   | Expansion sleeve                      |                           | see table A4                  |  |                               |                               |
| 3   | Washer                                |                           | see table A4                  |  |                               |                               |
| 4   | Hexagon head screw                    | width across flats        | 10                            | 13   | 17                            | 19                            |
|     | Pre-setting installation              | L <sub>s</sub>            | t <sub>fix</sub> + (13 to 21) | t <sub>fix</sub> + (17 to 23)                                  | t <sub>fix</sub> + (21 to 25) | t <sub>fix</sub> + (24 to 29) |
|     | Through-setting installation          | L <sub>s</sub>            | 14 to 20                      | 18 to 22   | 20 to 22                      | 25 to 28                      |
| 5   | Countersunk washer                    | $\varnothing$ countersunk | 17,3                          | 21,5   | 25,9                          | 30,9                          |
|     |                                       | t                         | 3,9                           | 5,0  | 5,7                           | 6,7                           |
| 6   | Countersunk head screw                | bit size                  | Torx T30                      | Torx T45 (Steel, zinc plated)<br>T40 (Stainless steel A4, HCR) | Hexagon socket 6 mm           | Hexagon socket 8 mm           |
|     | Pre-setting installation              | L <sub>sk</sub>           | t <sub>fix</sub> + (11 to 19) | t <sub>fix</sub> + (15 to 21)                                  | t <sub>fix</sub> + (19 to 23) | t <sub>fix</sub> + (21 to 27) |
|     | Through-setting installation          | L <sub>sk</sub>           | 16 to 20                      | 20 to 25   | 25                            | 30                            |
| 7   | Hexagon nut                           | width across flats        | 10                            | 13   | 17                            | 19                            |
| 8   | Commercial standard rod <sup>1)</sup> | type V                    | L <sub>B</sub> ≥              | t <sub>fix</sub> + 21  | t <sub>fix</sub> + 28         | t <sub>fix</sub> + 34         |
|     |                                       | type D                    | L <sub>B</sub> ≥              | 21   | 28                            | 34                            |

<sup>1)</sup> acc. to specifications (Table A4)

Dimensions in mm

### Clawbolt Pro EAW und EIW

**Product description**  
Fastener parts, marking and dimensions **Clawbolt Pro EIW**

**Annex A6**



**Table A4: Materials Clawbolt Pro EIW**

| No. | Part   | EIWMS   | EIW16  | EIWHR   |
|-----|--|---|--|---|
|     |  | Steel, galvanized $\geq 5 \mu\text{m}$<br>acc. to<br>EN ISO 4042:1999 | Stainless steel A4<br>(CRC III)  | High corrosion<br>resistant steel HCR<br>(CRC V)  |
| 1   | Conical bolt<br>Clawbolt Pro EIW<br>with internal thread | Machined steel,<br>Cone plastic coated                                | Stainless steel<br>(e.g. 1.4401, 1.4404,<br>1.4571)<br>EN 10088:2014,<br>Cone plastic coated         | High corrosion<br>resistant steel, 1.4529,<br>1.4565,<br>EN 10088:2014,<br>Cone plastic coated                    |
| 2   | Expansion sleeve<br>Clawbolt Pro EIW                     | Stainless steel<br>(e.g. 1.4301, 1.4401)<br>EN 10088:2014             | Stainless steel<br>(e.g. 1.4401, 1.4571)<br>EN 10088:2014  | Stainless steel<br>(e.g. 1.4401, 1.4571)<br>EN 10088:2014   |
| 3   | Washer<br>-B / -S  | Steel, galvanized   | Stainless steel<br>(e.g. 1.4401, 1.4571)<br>EN 10088:2014  | High corrosion<br>resistant steel,<br>1.4529, 1.4565,<br>EN 10088:2014  |
| 4   | Hexagon head screw<br>-B                                 | Steel, galvanized,<br>coated  | Stainless steel<br>(e.g. 1.4401, 1.4571)<br>EN 10088:2014,<br>coated                                 | High corrosion<br>resistant steel,<br>1.4529, 1.4565,<br>EN 10088:2014,<br>coated                                 |
| 5   | Countersunk washer<br>-K                                 | Steel, galvanized   | Stainless steel<br>(e.g. 1.4401, 1.4404,<br>1.4571)<br>EN 10088:2014,<br>zinc plated, coated         | High corrosion<br>resistant steel,<br>1.4529, 1.4565,<br>EN 10088:2014,<br>zinc plated, coated                    |
| 6   | Countersunk head<br>screw<br>-K                          | Steel, galvanized<br>coated   | Stainless steel<br>(e.g. 1.4401, 1.4571)<br>EN 10088:2014,<br>coated                                 | High corrosion<br>resistant steel,<br>1.4529, 1.4565,<br>EN 10088:2014,<br>coated                                 |
| 7   | Hexagon nut<br>-S  | Steel, galvanized<br>coated   | Stainless steel<br>(e.g. 1.4401, 1.4571)<br>EN 10088:2014,<br>coated                                 | High corrosion<br>resistant steel,<br>1.4529, 1.4565,<br>EN 10088:2014,<br>coated                                 |
| 8   | Commercial standard<br>rod                               | Property class 8.8,<br>EN ISO 898-1:2013<br>$A_5 > 8 \%$ ductile      | Stainless steel<br>(e.g. 1.4401, 1.4571)<br>EN 10088:2014,<br>property class 70,<br>EN ISO 3506:2009 | High corrosion<br>resistant steel,<br>1.4529, 1.4565,<br>EN 10088:2014,<br>property class 70,<br>EN ISO 3506:2009 |

**Clawbolt Pro EAW und EIW**

**Product description**  
Materials **Clawbolt Pro EIW**

**Annex A7**

## Specifications of intended use

| Clawbolt Pro EAW  |     |     |     |     |     |     |     |
|---|-----|-----|-----|-----|-----|-----|-----|
| Standard anchorage depth                                  | M8  | M10 | M12 | M16 | M20 | M24 | M27 |
| Steel, galvanized   | ✓   |     |     |     |     |     |     |
| Steel, sherardized  | ✓   |     |     |     |     |     |     |
| Stainless steel A4 and high corrosion resistant steel HCR | ✓   |     |     |     |     |     | _2) |
| Static or quasi-static action                             | ✓   |     |     |     |     |     |     |
| Fire exposure   | ✓   |     |     |     |     |     |     |
| Seismic action (C1 and C2) <sup>1)</sup>                  | ✓   |     |     |     |     | _2) | _2) |
| Reduced anchorage depth <sup>1)</sup>                     | M8  | M10 | M12 | M16 |     |     |     |
| Steel, galvanized   | ✓   |     |     |     |     |     |     |
| Steel, sherardized  | ✓   |     |     |     |     |     |     |
| Stainless steel A4 and high corrosion resistant steel HCR | ✓   |     |     |     |     |     |     |
| Static or quasi-static action                             | ✓   |     |     |     |     |     |     |
| Fire exposure   | ✓   |     |     |     |     |     |     |
| Seismic action (C1 and C2)                                | _2) |     |     |     |     |     |     |

¹) Only cold formed anchors acc. to Annex A3

²) No performance assessed

| Clawbolt Pro EIW  | M6 | M8 | M10 | M12 |
|---|----|----|-----|-----|
| Steel, galvanized   | ✓  |    |     |     |
| Stainless steel A4 and high corrosion resistant steel HCR | ✓  |    |     |     |
| Static or quasi-static action                             | ✓  |    |     |     |
| Fire exposure   | ✓  |    |     |     |
| Seismic action (C1 and C2)                                | ₁) |    |     |     |

¹) No performance assessed

### Base materials:

- Compacted, reinforced or unreinforced normal weight concrete (without fibers) according to EN 206:2013+A1:2016
- Strength classes C20/25 to C50/60 according to EN 206:2013+A1:2016
- Cracked or uncracked concrete

### Use conditions (Environmental conditions):

- Structures subject to dry internal conditions: all materials
- For all other conditions: Intended use of materials according to Annex A4, Table A2 or Annex A7, Table A4 corresponding corrosion resistance classes CRC according to EN 1993-1-4:2006+A1:2015

## Clawbolt Pro EAW und EIW

Intended use  
Specifications

Annex B1



Specifications of intended use

Design:

- Anchorages are designed under the responsibility of an engineer experienced in anchorages and concrete work
- Verifiable calculation notes and drawings are prepared taking account of the loads to be anchored. The position of the fastener is indicated on the design drawings (e.g. position of the fastener relative to reinforcement or to supports, etc.).
- Dimensioning of fasteners under static or quasi-static action, seismic action or fire exposure according to EN 1992-4:2018 in conjunction with Technical Report TR 055, Edition February 2018

Installation:

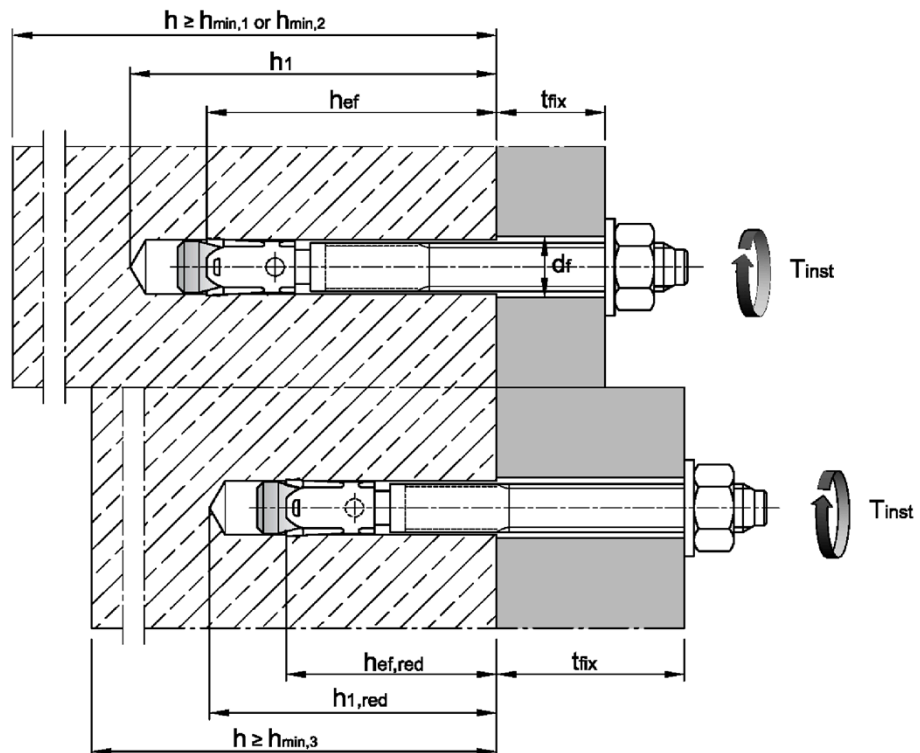
- Fastener installation carried out by appropriately qualified personnel and under the supervision of the person responsible for technical matters of the site
- Hole drilling by hammer drill bit or vacuum drill bit
- Use of the fastener only as supplied by the manufacturer without exchanging the components of the fastener
- Optionally, the annular gap between fixture and stud of the Clawbolt Pro EAW can be filled to reduce the hole. For this purpose, the filling washer (3b) must be used in addition to the supplied washer (3a). For filling use high-strength mortar with compressive strength  $\geq 40 \text{ N/mm}^2$ .
- In case of aborted hole: new drilling at a minimum distance away of twice the depth of the aborted hole or smaller distance if the aborted drill hole is filled with high strength mortar and if under shear or oblique tension load it is not in the direction of load application

|                                |          |
|--------------------------------|----------|
| Clawbolt Pro EAW und EIW       | Annex B2 |
| Intended use<br>Specifications |          |

**Table B1: Installation parameters, Clawbolt Pro EAW**

| Fastener size                             |                         |            | M8   | M10   | M12  | M16  | M20             | M24             | M27             |
|---|-------------------------|------------|------|-------|------|------|-----------------|-----------------|-----------------|
| Nominal drill hole diameter               | $d_0$                   | [mm]       | 8    | 10    | 12   | 16   | 20              | 24              | 28              |
| Cutting diameter of drill bit             | $d_{cut} \leq$          | [mm]       | 8,45 | 10,45 | 12,5 | 16,5 | 20,55           | 24,55           | 28,55           |
| Installation torque                       | Steel, galvanized       | $T_{inst}$ | [Nm] | 20    | 25   | 45   | 90              | 160             | 300             |
|   | Steel, sherardized      | $T_{inst}$ | [Nm] | 16    | 22   | 40   | 90              | 160             | 300             |
|   | Stainless steel A4, HCR | $T_{inst}$ | [Nm] | 20    | 35   | 50   | 110             | 290             | - <sup>1)</sup> |
| Diameter of clearance hole in the fixture | $d_f \leq$              | [mm]       | 9    | 12    | 14   | 18   | 22              | 26              | 30              |
| <b>Standard anchorage depth</b>           |                         |            |      |       |      |      |                 |                 |                 |
| Depth of drill hole                       | Steel, zinc plated      | $h_1 \geq$ | [mm] | 60    | 75   | 90   | 110             | 125             | 145             |
|   | Stainless steel A4, HCR | $h_1 \geq$ | [mm] | 60    | 75   | 90   | 110             | 125             | 155             |
| Effective anchorage depth                 | Steel, zinc plated      | $h_{ef}$   | [mm] | 46    | 60   | 70   | 85              | 100             | 115             |
|   | Stainless steel A4, HCR | $h_{ef}$   | [mm] | 46    | 60   | 70   | 85              | 100             | 125             |
| <b>Reduced anchorage depth</b>            |                         |            |      |       |      |      |                 |                 |                 |
| Depth of drill hole                       | $h_{1,red} \geq$        | [mm]       | 49   | 55    | 70   | 90   | - <sup>1)</sup> | - <sup>1)</sup> | - <sup>1)</sup> |
| Reduced effective anchorage depth         | $h_{ef,red}$            | [mm]       | 35   | 40    | 50   | 65   |                 |                 |                 |

<sup>1)</sup> No performance assessed



**Clawbolt Pro EAW und EIW**

**Intended use**  
Installation parameters

**Annex B3**

**Table B2: Minimum spacings and edge distances, standard anchorage depth,  
Clawbolt Pro EAW**

| Fastener size                              |              |      | M8                             | M10 | M12 | M16 | M20             | M24             | M27             |
|--|--------------|------|--------------------------------|-----|-----|-----|-----------------|-----------------|-----------------|
| Standard thickness of concrete member      |              |      |                                |     |     |     |                 |                 |                 |
| Steel zinc plated                          |              |      |                                |     |     |     |                 |                 |                 |
| Standard thickness of member               | $h_{min,1}$  | [mm] | 100                            | 120 | 140 | 170 | 200             | 230             | 250             |
| Cracked concrete                           |              |      |                                |     |     |     |                 |                 |                 |
| Minimum spacing                            | $s_{min}$    | [mm] | 40                             | 45  | 60  | 60  | 95              | 100             | 125             |
|  | für $c \geq$ | [mm] | 70                             | 70  | 100 | 100 | 150             | 180             | 300             |
| Minimum edge distance                      | $c_{min}$    | [mm] | 40                             | 45  | 60  | 60  | 95              | 100             | 180             |
|  | für $s \geq$ | [mm] | 80                             | 90  | 140 | 180 | 200             | 220             | 540             |
| Uncracked concrete                         |              |      |                                |     |     |     |                 |                 |                 |
| Minimum spacing                            | $s_{min}$    | [mm] | 40                             | 45  | 60  | 65  | 90              | 100             | 125             |
|  | für $c \geq$ | [mm] | 80                             | 70  | 120 | 120 | 180             | 180             | 300             |
| Minimum edge distance                      | $c_{min}$    | [mm] | 50                             | 50  | 75  | 80  | 130             | 100             | 180             |
|  | für $s \geq$ | [mm] | 100                            | 100 | 150 | 150 | 240             | 220             | 540             |
| Stainless steel A4, HCR                    |              |      |                                |     |     |     |                 |                 |                 |
| Standard thickness of member               | $h_{min,1}$  | [mm] | 100                            | 120 | 140 | 160 | 200             | 250             | - <sup>1)</sup> |
| Cracked concrete                           |              |      |                                |     |     |     |                 |                 |                 |
| Minimum spacing                            | $s_{min}$    | [mm] | 40                             | 50  | 60  | 60  | 95              | 125             | - <sup>1)</sup> |
|  | für $c \geq$ | [mm] | 70                             | 75  | 100 | 100 | 150             | 125             |                 |
| Minimum edge distance                      | $c_{min}$    | [mm] | 40                             | 55  | 60  | 60  | 95              | 125             |                 |
|  | für $s \geq$ | [mm] | 80                             | 90  | 140 | 180 | 200             | 125             |                 |
| Uncracked concrete                         |              |      |                                |     |     |     |                 |                 |                 |
| Minimum spacing                            | $s_{min}$    | [mm] | 40                             | 50  | 60  | 65  | 90              | 125             | - <sup>1)</sup> |
|  | für $c \geq$ | [mm] | 80                             | 75  | 120 | 120 | 180             | 125             |                 |
| Minimum edge distance                      | $c_{min}$    | [mm] | 50                             | 60  | 75  | 80  | 130             | 125             |                 |
|  | für $s \geq$ | [mm] | 100                            | 120 | 150 | 150 | 240             | 125             |                 |
| Minimum thickness of concrete member       |              |      |                                |     |     |     |                 |                 |                 |
| Steel zinc plated, stainless steel A4, HCR |              |      |                                |     |     |     |                 |                 |                 |
| Minimum thickness of member                | $h_{min,2}$  | [mm] | 80                             | 100 | 120 | 140 | - <sup>1)</sup> | - <sup>1)</sup> | - <sup>1)</sup> |
| Cracked concrete                           |              |      |                                |     |     |     |                 |                 |                 |
| Minimum spacing                            | $s_{min}$    | [mm] | 40                             | 45  | 60  | 70  | - <sup>1)</sup> | - <sup>1)</sup> | - <sup>1)</sup> |
|  | für $c \geq$ | [mm] | 70                             | 90  | 100 | 160 |                 |                 |                 |
| Minimum edge distance                      | $c_{min}$    | [mm] | 40                             | 50  | 60  | 80  |                 |                 |                 |
|  | für $s \geq$ | [mm] | 80                             | 115 | 140 | 180 |                 |                 |                 |
| Uncracked concrete                         |              |      |                                |     |     |     |                 |                 |                 |
| Minimum spacing                            | $s_{min}$    | [mm] | 40                             | 60  | 60  | 80  | - <sup>1)</sup> | - <sup>1)</sup> | - <sup>1)</sup> |
|  | für $c \geq$ | [mm] | 80                             | 140 | 120 | 180 |                 |                 |                 |
| Minimum edge distance                      | $c_{min}$    | [mm] | 50                             | 90  | 75  | 90  |                 |                 |                 |
|  | für $s \geq$ | [mm] | 100                            | 140 | 150 | 200 |                 |                 |                 |
| Fire exposure from one side                |              |      |                                |     |     |     |                 |                 |                 |
| Minimum spacing                            | $s_{min,fi}$ | [mm] | See normal ambient temperature |     |     |     |                 |                 |                 |
| Minimum edge distance                      | $c_{min,fi}$ | [mm] | See normal ambient temperature |     |     |     |                 |                 |                 |
| Fire exposure from more than one side      |              |      |                                |     |     |     |                 |                 |                 |
| Minimum spacing                            | $s_{min,fi}$ | [mm] | See normal ambient temperature |     |     |     |                 |                 |                 |
| Minimum edge distance                      | $c_{min,fi}$ | [mm] | $\geq 300$ mm                  |     |     |     |                 |                 |                 |

Intermediate values by linear interpolation.

<sup>1)</sup> No performance assessed

### Clawbolt Pro EAW und EIW

**Intended use**  
Minimum spacings and edge distances for standard anchorage depth

**Annex B4**

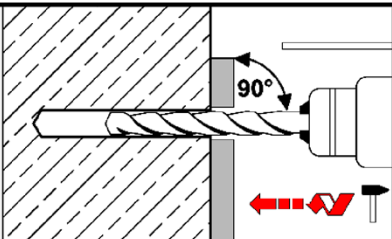
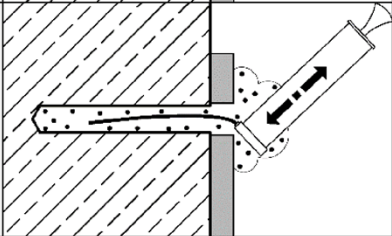
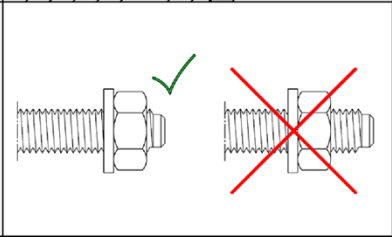
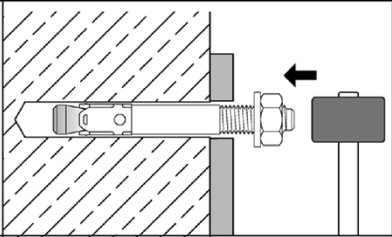
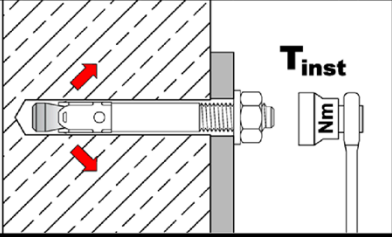
**Table B3: Minimum spacings and edge distances, reduced anchorage depth, Clawbolt Pro EAW**

| Fastener size                         |               |      | M8                             | M10 | M12 | M16 |
|---------------------------------------|---------------|------|--------------------------------|-----|-----|-----|
| Minimum thickness of concrete member  | $h_{\min,3}$  | [mm] | 80                             | 80  | 100 | 140 |
| Cracked concrete                      |               |      |                                |     |     |     |
| Minimum spacing                       | $s_{\min}$    | [mm] | 50                             | 50  | 50  | 65  |
|                                       | für $c \geq$  | [mm] | 60                             | 100 | 160 | 170 |
| Minimum edge distance                 | $c_{\min}$    | [mm] | 40                             | 65  | 65  | 100 |
|                                       | für $s \geq$  | [mm] | 185                            | 180 | 250 | 250 |
| Uncracked concrete                    |               |      |                                |     |     |     |
| Minimum spacing                       | $s_{\min}$    | [mm] | 50                             | 50  | 50  | 65  |
|                                       | für $c \geq$  | [mm] | 60                             | 100 | 160 | 170 |
| Minimum edge distance                 | $c_{\min}$    | [mm] | 40                             | 65  | 100 | 170 |
|                                       | für $s \geq$  | [mm] | 185                            | 180 | 185 | 65  |
| Fire exposure from one side           |               |      |                                |     |     |     |
| Minimum spacing                       | $s_{\min,fi}$ | [mm] | See normal ambient temperature |     |     |     |
| Minimum edge distance                 | $c_{\min,fi}$ | [mm] | See normal ambient temperature |     |     |     |
| Fire exposure from more than one side |               |      |                                |     |     |     |
| Minimum spacing                       | $s_{\min,fi}$ | [mm] | See normal ambient temperature |     |     |     |
| Minimum edge distance                 | $c_{\min,fi}$ | [mm] | $\geq 300\text{ mm}$           |     |     |     |

Intermediate values by linear interpolation.

|   |          |
|---|----------|
| Clawbolt Pro EAW und EIW  | Annex B5 |
| Intended use<br>Minimum spacings and edge distances for reduced anchorage depth |          |

Installation instructions Clawbolt Pro EAW

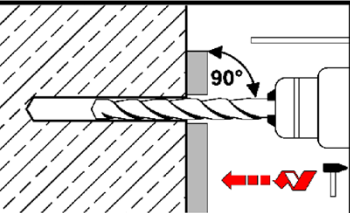
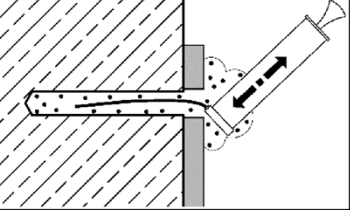
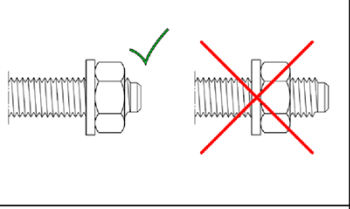
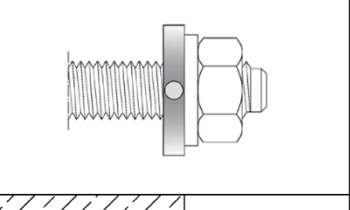
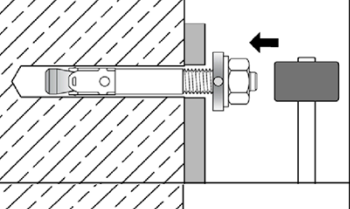
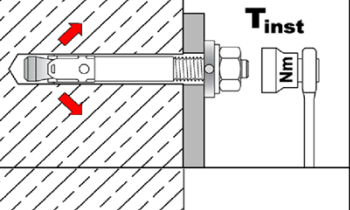
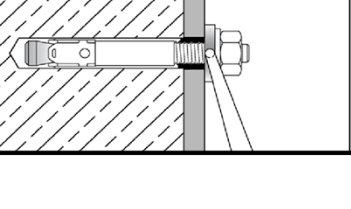
|   |   |  |
|---|---|--|
| 1 |    | Drill hole perpendicular to concrete surface.<br>If using a vacuum drill bit, proceed with step 3.   |
| 2 |    | Blow out dust. Alternatively vacuum clean down to the bottom of the hole.  |
| 3 |   | Check position of nut.   |
| 4 |  | Drive in fastener, such that $h_{ef}$ or $h_{ef,red}$ depth is met. This compliance is ensured, if the thickness of fixture is not greater than the maximum thickness of fixture marked on the fastener in accordance with Annex A3. |
| 5 |  | Installation torque $T_{inst}$ shall be applied by using calibrated torque wrench.   |

Clawbolt Pro EAW und EIW

Intended Use  
Installation instructions

Annex B6

## Installation instructions Clawbolt Pro EAW with filling of annular gap

|    |   |   |
|----|---|---|
| 1  |    | Drill hole perpendicular to concrete surface.<br>If using a vacuum drill bit, proceed with step 3a.   |
| 2  |    | Blow out dust. Alternatively vacuum clean down to the bottom of the hole.   |
| 3a |    | Check position of nut.  |
| 3b |  | Fit the filling washer to the fastener.<br>The thickness of the filling washer must be taken into account with $t_{fix}$ .  |
| 4  |  | Drive in fastener with filling washer, such that $h_{ef}$ or $h_{ef,red}$ depth is met.<br>This compliance is ensured, if the thickness of fixture is 5mm smaller (or 6mm when $\geq M24$ ) than the maximum thickness of fixture marked on the fastener in accordance with Annex A3.   |
| 5  |  | Installation torque $T_{inst}$ shall be applied by using calibrated torque wrench.  |
| 6  |  | Fill the annular gap between stud and fixture with high strength mortar with compressive strength $\geq 40 \text{ N/mm}^2$ .<br>Use enclosed reducing adapter. Observe the processing information of the mortar!<br>The annular gap is completely filled, when excess mortar seeps out. |

### Clawbolt Pro EAW und EIW

**Intended Use**  
Installation instructions with filling washer

**Annex B7**



**Table B4: Installation parameters Clawbolt Pro EIW**

| Fastener size                                   |                    |            | M6   | M8    | M10  | M12  |
|---|--------------------|------------|------|-------|------|------|
| Effective anchorage depth                       | $h_{ef}$           | [mm]       | 45   | 58    | 65   | 80   |
| Drill hole diameter                             | $d_0$              | [mm]       | 8    | 10    | 12   | 16   |
| Cutting diameter of drill bit                   | $d_{cut} \leq$     | [mm]       | 8,45 | 10,45 | 12,5 | 16,5 |
| Depth of drill hole                             | $h_1 \geq$         | [mm]       | 60   | 75    | 90   | 105  |
| Screwing depth of threaded rod                  | $L_{sd}^{2)} \geq$ | [mm]       | 9    | 12    | 15   | 18   |
| Installation torque,<br>steel zinc plated       | $T_{inst}$         | EIW-B [Nm] | 10   | 30    | 30   | 55   |
|   |                    | EIW-K [Nm] | 10   | 25    | 40   | 50   |
|   |                    | EIW-S [Nm] | 8    | 25    | 30   | 45   |
| Installation torque,<br>stainless steel A4, HCR | $T_{inst}$         | EIW-B [Nm] | 15   | 40    | 50   | 100  |
|   |                    | EIW-K [Nm] | 12   | 25    | 45   | 60   |
|   |                    | EIW-S [Nm] | 8    | 25    | 40   | 80   |
| <b>Pre-setting installation</b>                 |                    |            |      |       |      |      |
| Diameter of clearance hole in the fixture       | $d_f \leq$         | [mm]       | 7    | 9     | 12   | 14   |
| Minimum thickness of fixture                    | $t_{fix} \geq$     | EIW-B [mm] | 1    | 1     | 1    | 1    |
|   |                    | EIW-K [mm] | 5    | 7     | 8    | 9    |
|   |                    | EIW-S [mm] | 1    | 1     | 1    | 1    |
| <b>Through-setting installation</b>             |                    |            |      |       |      |      |
| Diameter of clearance hole in the fixture       | $d_f \leq$         | [mm]       | 9    | 12    | 14   | 18   |
| Minimum thickness of fixture <sup>1)</sup>      | $t_{fix} \geq$     | EIW-B [mm] | 5    | 7     | 8    | 9    |
|   |                    | EIW-K [mm] | 9    | 12    | 14   | 16   |
|   |                    | EIW-S [mm] | 5    | 7     | 8    | 9    |

<sup>1)</sup> The minimum thickness of fixture can be reduced to the value of pre-setting installation, if the shear load at steel failure is designed with lever arm.

<sup>2)</sup> see Annex A5

**Table B5: Minimum spacings and edge distances Clawbolt Pro EIW**

| Fastener size                         |               |      | M6                     | M8  | M10 | M12 |
|---------------------------------------|---------------|------|------------------------|-----|-----|-----|
| Minimum thickness of concrete member  | $h_{\min}$    | [mm] | 100                    | 120 | 130 | 160 |
| Cracked concrete                      |               |      |                        |     |     |     |
| Minimum spacing                       | $s_{\min}$    | [mm] | 50                     | 60  | 70  | 80  |
|                                       | für $c \geq$  | [mm] | 60                     | 80  | 100 | 120 |
| Minimum edge distance                 | $c_{\min}$    | [mm] | 50                     | 60  | 70  | 80  |
|                                       | für $s \geq$  | [mm] | 75                     | 100 | 100 | 120 |
| Uncracked concrete                    |               |      |                        |     |     |     |
| Minimum spacing                       | $s_{\min}$    | [mm] | 50                     | 60  | 65  | 80  |
|                                       | für $c \geq$  | [mm] | 80                     | 100 | 120 | 160 |
| Minimum edge distance                 | $c_{\min}$    | [mm] | 50                     | 60  | 70  | 100 |
|                                       | für $s \geq$  | [mm] | 115                    | 155 | 170 | 210 |
| Fire exposure from one side           |               |      |                        |     |     |     |
| Minimum spacing                       | $s_{\min,fi}$ | [mm] | See normal temperature |     |     |     |
| Minimum edge distance                 | $c_{\min,fi}$ | [mm] | See normal temperature |     |     |     |
| Fire exposure from more than one side |               |      |                        |     |     |     |
| Minimum spacing                       | $s_{\min,fi}$ | [mm] | See normal temperature |     |     |     |
| Minimum edge distance                 | $c_{\min,fi}$ | [mm] | $\geq 300$ mm          |     |     |     |

Intermediate values by linear interpolation.

**Clawbolt Pro EAW und EIW**

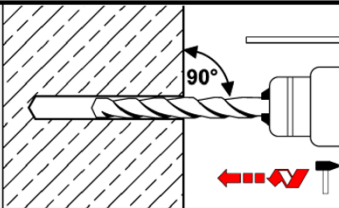
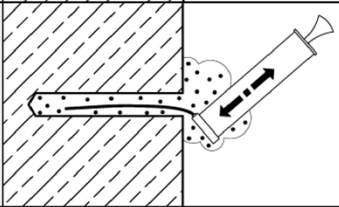
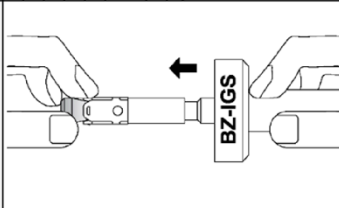
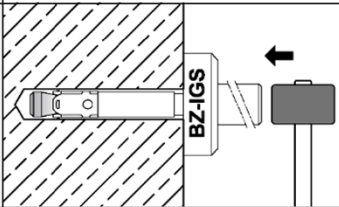
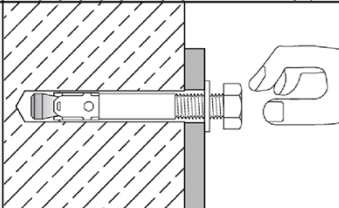
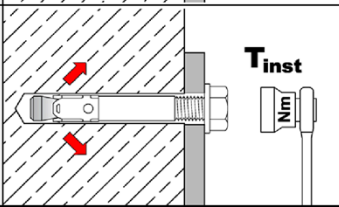
**Intended use**

Installation parameters, minimum spacings and edge distances **Clawbolt Pro EIW**

**Annex B8**

Installation instructions **Clawbolt Pro EIW**

Pre-setting installation

|   |   |  |
|---|---|--|
| 1 |    | Drill hole perpendicular to concrete surface.<br>If using vacuum drill bit, proceed with step 3. |
| 2 |    | Blow out dust. Alternatively vacuum clean down to the bottom of the hole.                        |
| 3 |   | Setting tool for <b>pre-setting installation</b> insert in fastener.                             |
| 4 |  | Drive in fastener with setting tool.   |
| 5 |  | Drive in screw.  |
| 6 |  | Installation torque $T_{inst}$ may be applied by using calibrated torque wrench.                 |

**Clawbolt Pro EAW und EIW**

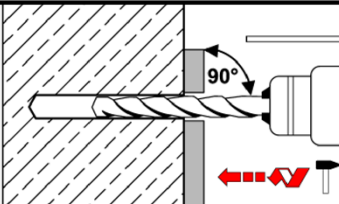
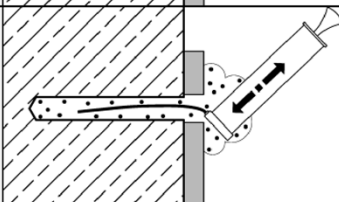
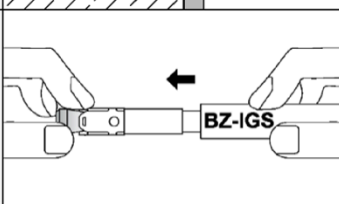
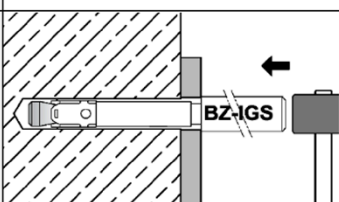
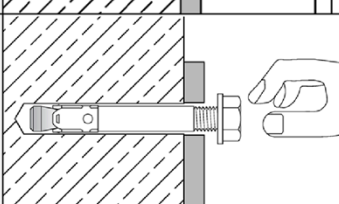
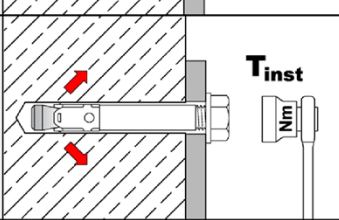
**Intended Use**  
Installation instructions for pre-setting installation **Clawbolt Pro EIW**

**Annex B9**



Installation instructions **Clawbolt Pro EIW**

Through-setting installation

|   |   |  |
|---|---|--|
| 1 |    | Drill hole perpendicular to concrete surface.<br>If using a vacuum drill bit, proceed with step 3. |
| 2 |    | Blow out dust. Alternatively vacuum clean down to the bottom of the hole.                          |
| 3 |   | Setting tool for <b>through-setting installation</b> insert in fastener.                           |
| 4 |  | Drive in fastener with setting tool.   |
| 5 |  | Drive in screw.  |
| 6 |  | Installation torque $T_{inst}$ may be applied by using calibrated torque wrench.                   |

**Clawbolt Pro EAW und EIW**

**Intended Use**  
Installation instructions for through-setting installation **Clawbolt Pro EIW**

**Annex B10**

**Table C1: Characteristic values for tension loads, Clawbolt Pro EAWMS (zinc plated), cracked concrete, static and quasi-static action**

| Fastener size   |                  |      | M8                                     | M10 | M12  | M16  | M20             | M24             | M27             |
|---|------------------|------|--|-----|------|------|-----------------|-----------------|-----------------|
| Installation factor   | $\gamma_{inst}$  | [-]  | 1,0                                    |     |      |      |                 |                 |                 |
| Steel failure   |                  |      |  |     |      |      |                 |                 |                 |
| Characteristic resistance   | $N_{Rk,s}$       | [kN] | 16                                     | 27  | 40   | 60   | 86              | 126             | 196             |
| Partial factor  | $\gamma_{Ms}$    | [-]  | 1,53                                   |     | 1,5  |      | 1,6             | 1,5             |                 |
| Pull-out  |                  |      |  |     |      |      |                 |                 |                 |
| Standard anchorage depth  |                  |      |  |     |      |      |                 |                 |                 |
| Characteristic resistance in cracked concrete C20/25              | $N_{Rk,p}$       | [kN] | 5                                      | 9   | 16   | 25   | 36              | 44,4            | 50,3            |
| Reduced anchorage depth   |                  |      |  |     |      |      |                 |                 |                 |
| Characteristic resistance in cracked concrete C20/25              | $N_{Rk,p}$       | [kN] | 5                                      | 7,5 | 12,7 | 18,9 | - <sup>1)</sup> | - <sup>1)</sup> | - <sup>1)</sup> |
| Increasing factor for $N_{Rk,p} = \psi_c \cdot N_{Rk,p}$ (C20/25) | $\psi_c$         | [-]  | $\left(\frac{f_{ck}}{20}\right)^{0,5}$ |     |      |      |                 |                 |                 |
| Concrete cone failure   |                  |      |  |     |      |      |                 |                 |                 |
| Effective anchorage depth   | $h_{ef}$         | [mm] | 46                                     | 60  | 70   | 85   | 100             | 115             | 125             |
| Reduced anchorage depth   | $h_{ef,red}$     | [mm] | 35 <sup>2)</sup>                       | 40  | 50   | 65   | - <sup>1)</sup> | - <sup>1)</sup> | - <sup>1)</sup> |
| Factor for cracked concrete                                       | $k_1 = k_{cr,N}$ | [-]  | 7,7                                    |     |      |      |                 |                 |                 |

<sup>1)</sup> No performance assessed

<sup>2)</sup> Restricted to the use of structural components with  $h_{ef} < 40\text{mm}$  which are statically indeterminate and subject to internal exposure conditions only

#### Clawbolt Pro EAW und EIW

#### Performance

Characteristic values for **tension loads**, Clawbolt Pro EAWMS (zinc plated), **cracked concrete**, static and quasi-static action

#### Annex C1

**Table C2: Characteristic values for tension loads, Clawbolt Pro EAW16 and EAWHR (A4 / HCR), cracked concrete, static and quasi-static action**

| Fastener size   |                 |      | M8                                     | M10 | M12  | M16  | M20             | M24             |
|---|-----------------|------|--|-----|------|------|-----------------|-----------------|
| Installation factor   | $\gamma_{inst}$ | [-]  | 1,0                                    |     |      |      |                 |                 |
| Steel failure   |                 |      |  |     |      |      |                 |                 |
| Characteristic resistance   | $N_{Rk,s}$      | [kN] | 16                                     | 27  | 40   | 64   | 108             | 110             |
| Partial factor  | $\gamma_{Ms}$   | [-]  | 1,5                                    |     |      |      | 1,68            | 1,5             |
| Pull-out  |                 |      |  |     |      |      |                 |                 |
| Standard anchorage depth  |                 |      |  |     |      |      |                 |                 |
| Characteristic resistance in cracked concrete C20/25              | $N_{Rk,p}$      | [kN] | 5                                      | 9   | 16   | 25   | 36              | 40              |
| Reduced anchorage depth   |                 |      |  |     |      |      |                 |                 |
| Characteristic resistance in cracked concrete C20/25              | $N_{Rk,p}$      | [kN] | 5                                      | 7,5 | 12,7 | 18,9 | - <sup>1)</sup> | - <sup>1)</sup> |
| Increasing factor for $N_{Rk,p} = \psi_c \cdot N_{Rk,p} (C20/25)$ | $\psi_c$        | [-]  | $\left(\frac{f_{ck}}{20}\right)^{0,5}$ |     |      |      |                 |                 |
| Concrete cone failure   |                 |      |  |     |      |      |                 |                 |
| Effective anchorage depth   | $h_{ef}$        | [mm] | 46                                     | 60  | 70   | 85   | 100             | 125             |
| Reduced anchorage depth   | $h_{ef,red}$    | [mm] | 35 <sup>2)</sup>                       | 40  | 50   | 65   | - <sup>1)</sup> | - <sup>1)</sup> |
| Factor for cracked concrete                                       | $k_{cr,N}$      | [-]  | 7,7                                    |     |      |      |                 |                 |

<sup>1)</sup> No performance assessed.

<sup>2)</sup> Restricted to the use of structural components with  $h_{ef} < 40\text{mm}$  which are statically indeterminate and subject to internal exposure conditions only

#### Clawbolt Pro EAW und EIW

##### Performance

Characteristic values for **tension loads**, Clawbolt Pro EAW16 and EAWHR (A4 / HCR), **cracked concrete**, static and quasi-static action

#### Annex C2

**Table C3: Characteristic values for tension loads, Clawbolt Pro EAWMS (zinc plated), uncracked concrete, static and quasi-static action**

| Fastener size  |                   |                 | M8               | M10                                    | M12  | M16  | M20             | M24             | M27             |
|--|-------------------|-----------------|------------------|--|------|------|-----------------|-----------------|-----------------|
| Installation factor  |                   | $\gamma_{Inst}$ | [-]              |  | 1,0  |      |                 |                 |                 |
| Steel failure  |                   |                 |                  |  |      |      |                 |                 |                 |
| Characteristic resistance  | $N_{Rk,s}$        | [kN]            | 16               | 27                                     | 40   | 60   | 86              | 126             | 196             |
| Partial factor   | $\gamma_{Ms}$     | [-]             | 1,53             |  | 1,5  |      | 1,6             | 1,5             |                 |
| Pull-out   |                   |                 |                  |  |      |      |                 |                 |                 |
| Standard anchorage depth   |                   |                 |                  |  |      |      |                 |                 |                 |
| Characteristic resistance in uncracked concrete C20/25   | $N_{Rk,p}$        | [kN]            | 12               | 16                                     | 25   | 35   | 51              | 62,9            | 71,3            |
| Reduced anchorage depth  |                   |                 |                  |  |      |      |                 |                 |                 |
| Characteristic resistance in uncracked concrete C20/25   | $N_{Rk,p}$        | [kN]            | 7,5              | 9                                      | 18   | 26,7 | — <sup>1)</sup> | — <sup>1)</sup> | — <sup>1)</sup> |
| Splitting  |                   |                 |                  |  |      |      |                 |                 |                 |
| Standard anchorage depth   |                   |                 |                  |  |      |      |                 |                 |                 |
| Splitting for <b>standard thickness of concrete member</b> (The higher resistance of case 1 and case 2 may be applied; $c_{cr,sp}$ may be linearly interpolated for the member thickness $h_{min,2} < h < h_{min,1}$ (Case 2); $\psi_{h,sp} = 1,0$ ) |                   |                 |                  |  |      |      |                 |                 |                 |
| Standard thickness of concrete   | $h_{min,1} \geq$  | [mm]            | 100              | 120                                    | 140  | 170  | 200             | 230             | 250             |
| Case 1   |                   |                 |                  |  |      |      |                 |                 |                 |
| Characteristic resistance in uncracked concrete C20/25   | $N^0_{Rk,sp}$     | [kN]            | 9                | 12                                     | 20   | 30   | 40              | 62,3            | 50              |
| Edge distance  | $c_{cr,sp}$       | [mm]            | 1,5 $h_{ef}$     |  |      |      |                 |                 |                 |
| Case 2   |                   |                 |                  |  |      |      |                 |                 |                 |
| Characteristic resistance in uncracked concrete C20/25   | $N^0_{Rk,sp}$     | [kN]            | 12               | 16                                     | 25   | 35   | 50,5            | 62,3            | 70,6            |
| Edge distance  | $c_{cr,sp}$       | [mm]            | 2 $h_{ef}$       |  |      |      | 2,2 $h_{ef}$    | 1,5 $h_{ef}$    | 2,5 $h_{ef}$    |
| Splitting for <b>minimum thickness of concrete member</b>  |                   |                 |                  |  |      |      |                 |                 |                 |
| Minimum thickness of concrete  | $h_{min,2} \geq$  | [mm]            | 80               | 100                                    | 120  | 140  | — <sup>1)</sup> | — <sup>1)</sup> | — <sup>1)</sup> |
| Characteristic resistance in uncracked concrete C20/25   | $N^0_{Rk,sp}$     | [kN]            | 12               | 16                                     | 25   | 35   |                 |                 |                 |
| Edge distance  | $c_{cr,sp}$       | [mm]            | 2,5 $h_{ef}$     |  |      |      |                 |                 |                 |
| Reduced anchorage depth  |                   |                 |                  |  |      |      |                 |                 |                 |
| Minimum thickness of concrete  | $h_{min,3} \geq$  | [mm]            | 80               | 80                                     | 100  | 140  | — <sup>1)</sup> | — <sup>1)</sup> | — <sup>1)</sup> |
| Characteristic resistance in uncracked concrete C20/25   | $N^0_{Rk,sp}$     | [kN]            | 7,5              | 9                                      | 17,9 | 26,5 |                 |                 |                 |
| Edge distance  | $c_{cr,sp}$       | [mm]            | 100              | 100                                    | 125  | 150  |                 |                 |                 |
| Increasing factor<br>$N_{Rk,p} = \psi_c \cdot N_{Rk,p}$ (C20/25)<br>$N^0_{Rk,sp} = \psi_c \cdot N^0_{Rk,sp}$ (C20/25)  |                   | $\psi_c$        | [-]              | $\left(\frac{f_{ck}}{20}\right)^{0,5}$ |      |      |                 |                 |                 |
| Concrete cone failure  |                   |                 |                  |  |      |      |                 |                 |                 |
| Effective anchorage depth  | $h_{ef}$          | [mm]            | 46               | 60                                     | 70   | 85   | 100             | 115             | 125             |
| Reduced anchorage depth  | $h_{ef,red}$      | [mm]            | 35 <sup>2)</sup> | 40                                     | 50   | 65   | — <sup>1)</sup> | — <sup>1)</sup> | — <sup>1)</sup> |
| Factor for uncracked concrete  | $k_1 = k_{ucr,N}$ | [-]             | 11,0             |  |      |      |                 |                 |                 |

<sup>1)</sup> No performance assessed.

<sup>2)</sup> Restricted to the use of structural components with  $h_{ef} < 40\text{mm}$  which are statically indeterminate and subject to internal

#### Clawbolt Pro EAW und EIW

#### Performance

Characteristic values for **tension loads, Clawbolt Pro EAWMS (zinc plated), uncracked concrete**, static and quasi-static action

#### Annex C3

**Table C4: Characteristic values for tension loads, Clawbolt Pro EAW16 and EAWHR (A4 / HCR), uncracked concrete, static and quasi-static action**

| Fastener size  |                   |      | M8                                     | M10 | M12  | M16  | M20             | M24             |                 |
|--|-------------------|------|--|-----|------|------|-----------------|-----------------|-----------------|
| Installation factor  | $\gamma_{inst}$   | [-]  | 1,0                                    |     |      |      |                 |                 |                 |
| Steel failure  |                   |      |  |     |      |      |                 |                 |                 |
| Characteristic resistance  | $N_{Rk,s}$        | [kN] | 16                                     | 27  | 40   | 64   | 108             | 110             |                 |
| Partial factor   | $\gamma_{Ms}$     | [-]  | 1,5                                    |     |      |      | 1,68            | 1,5             |                 |
| Pull-out   |                   |      |  |     |      |      |                 |                 |                 |
| Standard anchorage depth   |                   |      |  |     |      |      |                 |                 |                 |
| Characteristic resistance in uncracked concrete C20/25   | $N_{Rk,p}$        | [kN] | 12                                     | 16  | 25   | 35   | 51              | 71,3            |                 |
| Reduced anchorage depth  |                   |      |  |     |      |      |                 |                 |                 |
| Characteristic resistance in uncracked concrete C20/25   | $N_{Rk,p}$        | [kN] | 7,5                                    | 9   | 18   | 26,7 | - <sup>1)</sup> | - <sup>1)</sup> |                 |
| Splitting  |                   |      |  |     |      |      |                 |                 |                 |
| Standard anchorage depth   |                   |      |  |     |      |      |                 |                 |                 |
| Splitting for <b>standard thickness of concrete member</b> (The higher resistance of case 1 and case 2 may be applied; $C_{cr,sp}$ may be linearly interpolated for the member thickness $h_{min,2} < h < h_{min,1}$ (Case 2); $\psi_{h,sp} = 1,0$ ) |                   |      |  |     |      |      |                 |                 |                 |
| Standard thickness of concrete   | $h_{min,1} \geq$  | [mm] | 100                                    | 120 | 140  | 160  | 200             | 250             |                 |
| Case 1   |                   |      |  |     |      |      |                 |                 |                 |
| Characteristic resistance in uncracked concrete C20/25   | $N^0_{Rk,sp}$     | [kN] | 9                                      | 12  | 20   | 30   | 40              | - <sup>1)</sup> |                 |
| Edge distance  | $C_{cr,sp}$       | [mm] | 1,5 $h_{ef}$                           |     |      |      |                 |                 | - <sup>1)</sup> |
| Case 2   |                   |      |  |     |      |      |                 |                 |                 |
| Characteristic resistance in uncracked concrete C20/25   | $N^0_{Rk,sp}$     | [kN] | 12                                     | 16  | 25   | 35   | 50,5            | 70,6            |                 |
| Edge distance  | $C_{cr,sp}$       | [mm] | 115                                    | 125 | 140  | 200  | 220             | 250             |                 |
| Splitting for <b>minimum thickness of concrete member</b>  |                   |      |  |     |      |      |                 |                 |                 |
| Minimum thickness of concrete  | $h_{min,2} \geq$  | [mm] | 80                                     | 100 | 120  | 140  | - <sup>1)</sup> | - <sup>1)</sup> |                 |
| Characteristic resistance in uncracked concrete C20/25   | $N^0_{Rk,sp}$     | [kN] | 12                                     | 16  | 25   | 35   |                 |                 |                 |
| Edge distance  | $C_{cr,sp}$       | [mm] | 2,5 $h_{ef}$                           |     |      |      |                 |                 |                 |
| Reduced anchorage depth  |                   |      |  |     |      |      |                 |                 |                 |
| Minimum thickness of concrete  | $h_{min,3} \geq$  | [mm] | 80                                     | 80  | 100  | 140  | - <sup>1)</sup> | - <sup>1)</sup> |                 |
| Characteristic resistance in uncracked concrete C20/25   | $N^0_{Rk,sp}$     | [kN] | 7,5                                    | 9   | 17,9 | 26,5 |                 |                 |                 |
| Edge distance  | $C_{cr,sp}$       | [mm] | 100                                    | 100 | 125  | 150  |                 |                 |                 |
| Increasing factor<br>$N_{Rk,p} = \psi_c \cdot N_{Rk,p}$ (C20/25)<br>$N^0_{Rk,sp} = \psi_c \cdot N^0_{Rk,sp}$ (C20/25)  | $\psi_c$          | [-]  | $\left(\frac{f_{ck}}{20}\right)^{0,5}$ |     |      |      |                 |                 |                 |
| Concrete cone failure  |                   |      |  |     |      |      |                 |                 |                 |
| Effective anchorage depth  | $h_{ef}$          | [mm] | 46                                     | 60  | 70   | 85   | 100             | 125             |                 |
| Reduced anchorage depth  | $h_{ef,red}$      | [mm] | 35 <sup>2)</sup>                       | 40  | 50   | 65   | - <sup>1)</sup> | - <sup>1)</sup> |                 |
| Factor for uncracked concrete  | $k_1 = k_{ucr,N}$ | [-]  | 11,0                                   |     |      |      |                 |                 |                 |

<sup>1)</sup> No performance assessed.

<sup>2)</sup> Restricted to the use of structural components with  $h_{ef} < 40\text{mm}$  which are statically indeterminate and subject to internal

#### Clawbolt Pro EAW und EIW

#### Performance

Characteristic values for **tension loads**, Clawbolt Pro EAW16 and EAWHR (A4 / HCR), **uncracked concrete**, static and quasi-static action

#### Annex C4

**Table C5: Characteristic values for shear loads, Clawbolt Pro EAW, cracked and uncracked concrete, static or quasi static action**

| Fastener size   |                         |                 | M8   | M10              | M12  | M16 | M20  | M24             | M27             |                 |
|---|-------------------------|-----------------|------|------------------|------|-----|------|-----------------|-----------------|-----------------|
| Installation factor   |                         | $\gamma_{inst}$ | [-]  | 1,0              |      |     |      |                 |                 |                 |
| Steel failure without lever arm, Steel zinc plated              |                         |                 |      |                  |      |     |      |                 |                 |                 |
| Characteristic resistance                                       |                         | $V_{Rk,s}^0$    | [kN] | 12,2             | 20,1 | 30  | 55   | 69              | 114             | 169,4           |
| Ductility factor  |                         | $k_7$           | [-]  | 1,0              |      |     |      |                 |                 |                 |
| Partial factor  |                         | $\gamma_{Ms}$   | [-]  | 1,25             |      |     | 1,33 | 1,25            | 1,25            |                 |
| Steel failure without lever arm, Stainless steel A4, HCR        |                         |                 |      |                  |      |     |      |                 |                 |                 |
| Characteristic resistance                                       |                         | $V_{Rk,s}^0$    | [kN] | 13               | 20   | 30  | 55   | 86              | 123,6           | - <sup>1)</sup> |
| Ductility factor  |                         | $k_7$           | [-]  | 1,0              |      |     |      |                 |                 |                 |
| Partial factor  |                         | $\gamma_{Ms}$   | [-]  | 1,25             |      |     | 1,4  | 1,25            |                 |                 |
| Steel failure with lever arm, Steel zinc plated                 |                         |                 |      |                  |      |     |      |                 |                 |                 |
| Characteristic bending resistance                               |                         | $M_{Rk,s}^0$    | [Nm] | 23               | 47   | 82  | 216  | 363             | 898             | 1331,5          |
| Partial factor  |                         | $\gamma_{Ms}$   | [-]  | 1,25             |      |     | 1,33 | 1,25            | 1,25            |                 |
| Steel failure with lever arm, Stainless steel A4, HCR           |                         |                 |      |                  |      |     |      |                 |                 |                 |
| Characteristic bending resistance                               |                         | $M_{Rk,s}^0$    | [Nm] | 26               | 52   | 92  | 200  | 454             | 785,4           | - <sup>1)</sup> |
| Partial factor  |                         | $\gamma_{Ms}$   | [-]  | 1,25             |      |     | 1,4  | 1,25            |                 |                 |
| Concrete pry-out failure  |                         |                 |      |                  |      |     |      |                 |                 |                 |
| Pry-out factor  |                         | $k_8$           | [-]  | 2,4              |      |     | 2,8  |                 |                 |                 |
| Concrete edge failure   |                         |                 |      |                  |      |     |      |                 |                 |                 |
| Effective length of fastener in shear loading with $h_{ef}$     | Steel zinc plated       | $l_f$           | [mm] | 46               | 60   | 70  | 85   | 100             | 115             | 125             |
|   | Stainless steel A4, HCR | $l_f$           | [mm] | 46               | 60   | 70  | 85   | 100             | 125             | - <sup>1)</sup> |
| Effective length of fastener in shear loading with $h_{ef,red}$ | Steel zinc plated       | $l_{f,red}$     | [mm] | 35 <sup>2)</sup> | 40   | 50  | 65   | - <sup>1)</sup> | - <sup>1)</sup> | - <sup>1)</sup> |
|   | Stainless steel A4, HCR | $l_{f,red}$     | [mm] | 35 <sup>2)</sup> | 40   | 50  | 65   |                 |                 |                 |
| Outside diameter of fastener                                    |                         | $d_{nom}$       | [mm] | 8                | 10   | 12  | 16   | 20              | 24              | 27              |

<sup>1)</sup> No performance assessed.

<sup>2)</sup> Restricted to the use of structural components with  $h_{ef} < 40\text{mm}$  which are statically indeterminate and subject to internal exposure conditions only.

#### Clawbolt Pro EAW und EIW

#### Performance

Characteristic values for **shear loads**, Clawbolt Pro EAW, **cracked and uncracked concrete**, static or quasi static action

#### Annex C5



**Table C6: Characteristic resistance for seismic loading, Clawbolt Pro EAW, standard anchorage depth, performance category C1 and C2**

| Fastener size  |                                |                 | M8  | M10  | M12  | M16  | M20  |      |
|--|--------------------------------|-----------------|-----|------|------|------|------|------|
| Tension loads  |                                |                 |     |      |      |      |      |      |
| Installation factor                                      |                                | $\gamma_{inst}$ | [-] | 1,0  |      |      |      |      |
| Steel failure, Steel zinc plated                         |                                |                 |     |      |      |      |      |      |
| Characteristic resistance <b>C1</b>                      | $N_{Rk,s,eq,C1}$               | [kN]            | 16  | 27   | 40   | 60   | 86   |      |
| Characteristic resistance <b>C2</b>                      | $N_{Rk,s,eq,C2}$               | [kN]            | 16  | 27   | 40   | 60   | 86   |      |
| Partial factor   |                                | $\gamma_{Ms}$   | [-] | 1,53 |      | 1,5  |      | 1,6  |
| Steel failure, Stainless steel A4, HCR                   |                                |                 |     |      |      |      |      |      |
| Characteristic resistance <b>C1</b>                      | $N_{Rk,s,eq,C1}$               | [kN]            | 16  | 27   | 40   | 64   | 108  |      |
| Characteristic resistance <b>C2</b>                      | $N_{Rk,s,eq,C2}$               | [kN]            | 16  | 27   | 40   | 64   | 108  |      |
| Partial factor   |                                | $\gamma_{Ms}$   | [-] | 1,5  |      |      |      | 1,68 |
| Pull-out (steel zinc plated, stainless steel A4 and HCR) |                                |                 |     |      |      |      |      |      |
| Characteristic resistance <b>C1</b>                      | $N_{Rk,p,eq,C1}$               | [kN]            | 5   | 9    | 16   | 25   | 36   |      |
| Characteristic resistance <b>C2</b>                      | $N_{Rk,p,eq,C2}$               | [kN]            | 2,3 | 3,6  | 10,2 | 13,8 | 24,4 |      |
| Shear loads  |                                |                 |     |      |      |      |      |      |
| Steel failure without lever arm, Steel zinc plated       |                                |                 |     |      |      |      |      |      |
| Characteristic resistance <b>C1</b>                      | $V_{Rk,s,eq,C1}$               | [kN]            | 9,3 | 20   | 27   | 44   | 69   |      |
| Characteristic resistance <b>C2</b>                      | $V_{Rk,s,eq,C2}$               | [kN]            | 6,7 | 14   | 16,2 | 35,7 | 55,2 |      |
| Partial factor   |                                | $\gamma_{Ms}$   | [-] | 1,25 |      |      |      | 1,33 |
| Steel failure without lever arm, Stainless steel A4, HCR |                                |                 |     |      |      |      |      |      |
| Characteristic resistance <b>C1</b>                      | $V_{Rk,s,eq,C1}$               | [kN]            | 9,3 | 20   | 27   | 44   | 69   |      |
| Characteristic resistance <b>C2</b>                      | $V_{Rk,s,eq,C2}$               | [kN]            | 6,7 | 14   | 16,2 | 35,7 | 55,2 |      |
| Partial factor   |                                | $\gamma_{Ms}$   | [-] | 1,25 |      |      |      | 1,4  |
| Factor for annular gap                                   | without filling of annular gap | $\alpha_{gap}$  | [-] | 0,5  |      |      |      |      |
|  | with filling of annular gap    | $\alpha_{gap}$  | [-] | 1,0  |      |      |      |      |

**Clawbolt Pro EAW und EIW**

**Performance**  
Characteristic resistance for **seismic loading**, Clawbolt Pro EAW,  
**standard anchorage depth**, performance category **C1** and **C2**

**Annex C6**

**Table C7: Characteristic values for tension and shear load under fire exposure, Clawbolt Pro EAW, standard anchorage depth, cracked and uncracked concrete C20/25 to C50/60**

| Fastener size                   |      |                 | M8   | M10 | M12 | M16  | M20  | M24  | M27   |      |
|---------------------------------|------|-----------------|------|-----|-----|------|------|------|-------|------|
| Tension load                    |      |                 |      |     |     |      |      |      |       |      |
| Steel failure                   |      |                 |      |     |     |      |      |      |       |      |
| Steel, zinc plated              |      |                 |      |     |     |      |      |      |       |      |
| Characteristic resistance       | R30  | $N_{Rk,s,fi}$   | [kN] | 1,5 | 2,6 | 4,1  | 7,7  | 9,4  | 13,6  | 17,6 |
|                                 | R60  |                 |      | 1,1 | 1,9 | 3,0  | 5,6  | 8,2  | 11,8  | 15,3 |
|                                 | R90  |                 |      | 0,8 | 1,4 | 2,4  | 4,4  | 6,9  | 10,0  | 13,0 |
|                                 | R120 |                 |      | 0,7 | 1,2 | 2,2  | 4,0  | 6,3  | 9,1   | 11,8 |
| Stainless steel A4, HCR         |      |                 |      |     |     |      |      |      |       |      |
| Characteristic resistance       | R30  | $N_{Rk,s,fi}$   | [kN] | 3,8 | 6,9 | 12,7 | 23,7 | 33,5 | 48,2  | -1)  |
|                                 | R60  |                 |      | 2,9 | 5,3 | 9,4  | 17,6 | 25,0 | 35,9  |      |
|                                 | R90  |                 |      | 2,0 | 3,6 | 6,1  | 11,5 | 16,4 | 23,6  |      |
|                                 | R120 |                 |      | 1,6 | 2,8 | 4,5  | 8,4  | 12,1 | 17,4  |      |
| Shear load                      |      |                 |      |     |     |      |      |      |       |      |
| Steel failure without lever arm |      |                 |      |     |     |      |      |      |       |      |
| Steel, zinc plated              |      |                 |      |     |     |      |      |      |       |      |
| Characteristic resistance       | R30  | $V_{Rk,s,fi}$   | [kN] | 1,6 | 2,6 | 4,1  | 7,7  | 11   | 16    | 20,6 |
|                                 | R60  |                 |      | 1,5 | 2,5 | 3,6  | 6,8  | 11   | 15    | 19,8 |
|                                 | R90  |                 |      | 1,2 | 2,1 | 3,5  | 6,5  | 10   | 15    | 19,0 |
|                                 | R120 |                 |      | 1,0 | 2,0 | 3,4  | 6,4  | 10   | 14    | 18,6 |
| Stainless steel A4, HCR         |      |                 |      |     |     |      |      |      |       |      |
| Characteristic resistance       | R30  | $V_{Rk,s,fi}$   | [kN] | 3,8 | 6,9 | 12,7 | 23,7 | 33,5 | 48,2  | -1)  |
|                                 | R60  |                 |      | 2,9 | 5,3 | 9,4  | 17,6 | 25,0 | 35,9  |      |
|                                 | R90  |                 |      | 2,0 | 3,6 | 6,1  | 11,5 | 16,4 | 23,6  |      |
|                                 | R120 |                 |      | 1,6 | 2,8 | 4,5  | 8,4  | 12,1 | 17,4  |      |
| Steel failure with lever arm    |      |                 |      |     |     |      |      |      |       |      |
| Steel, zinc plated              |      |                 |      |     |     |      |      |      |       |      |
| Characteristic resistance       | R30  | $M^0_{Rk,s,fi}$ | [Nm] | 1,7 | 3,3 | 6,4  | 16,3 | 29   | 50    | 75   |
|                                 | R60  |                 |      | 1,6 | 3,2 | 5,6  | 14   | 28   | 48    | 72   |
|                                 | R90  |                 |      | 1,2 | 2,7 | 5,4  | 14   | 27   | 47    | 69   |
|                                 | R120 |                 |      | 1,1 | 2,5 | 5,3  | 13   | 26   | 46    | 68   |
| Stainless steel A4, HCR         |      |                 |      |     |     |      |      |      |       |      |
| Characteristic resistance       | R30  | $M^0_{Rk,s,fi}$ | [Nm] | 3,8 | 9,0 | 19,7 | 50,1 | 88,8 | 153,5 | -1)  |
|                                 | R60  |                 |      | 2,9 | 6,8 | 14,6 | 37,2 | 66,1 | 114,3 |      |
|                                 | R90  |                 |      | 2,1 | 4,7 | 9,5  | 24,2 | 43,4 | 75,1  |      |
|                                 | R120 |                 |      | 1,6 | 3,6 | 7,0  | 17,8 | 32,1 | 55,5  |      |

<sup>1)</sup> No performance assessed

## Clawbolt Pro EAW und EIW

### Performance

Characteristic values for tension and shear load under fire exposure, Clawbolt Pro EAW, standard anchorage depth, cracked and uncracked concrete C20/25 to C50/60

## Annex C7



**Table C8: Characteristic values for tension and shear load under fire exposure, Clawbolt Pro EAW, reduced anchorage depth, cracked and uncracked concrete C20/25 to C50/60**

| Fastener size                   |      |                                   |      | M8  | M10 | M12  | M16  |
|---------------------------------|------|-----------------------------------|------|-----|-----|------|------|
| Tension load                    |      |                                   |      |     |     |      |      |
| Steel failure                   |      |                                   |      |     |     |      |      |
| Steel, zinc plated              |      |                                   |      |     |     |      |      |
| Characteristic resistance       | R30  | N <sub>Rk,s,fi</sub>              | [kN] | 1,5 | 2,6 | 4,1  | 7,7  |
|                                 | R60  |                                   |      | 1,1 | 1,9 | 3,0  | 5,6  |
|                                 | R90  |                                   |      | 0,8 | 1,3 | 1,9  | 3,5  |
|                                 | R120 |                                   |      | 0,6 | 1,0 | 1,3  | 2,5  |
| Stainless steel A4, HCR         |      |                                   |      |     |     |      |      |
| Characteristic resistance       | R30  | N <sub>Rk,s,fi</sub>              | [kN] | 3,2 | 6,9 | 12,7 | 23,7 |
|                                 | R60  |                                   |      | 2,5 | 5,3 | 9,4  | 17,6 |
|                                 | R90  |                                   |      | 1,9 | 3,6 | 6,1  | 11,5 |
|                                 | R120 |                                   |      | 1,6 | 2,8 | 4,5  | 8,4  |
| Shear load                      |      |                                   |      |     |     |      |      |
| Steel failure without lever arm |      |                                   |      |     |     |      |      |
| Steel, zinc plated              |      |                                   |      |     |     |      |      |
| Characteristic resistance       | R30  | V <sub>Rk,s,fi</sub>              | [kN] | 1,5 | 2,6 | 4,1  | 7,7  |
|                                 | R60  |                                   |      | 1,1 | 1,9 | 3,0  | 5,6  |
|                                 | R90  |                                   |      | 0,8 | 1,3 | 1,9  | 3,5  |
|                                 | R120 |                                   |      | 0,6 | 1,0 | 1,3  | 2,5  |
| Stainless steel A4, HCR         |      |                                   |      |     |     |      |      |
| Characteristic resistance       | R30  | V <sub>Rk,s,fi</sub>              | [kN] | 3,2 | 6,9 | 12,7 | 23,7 |
|                                 | R60  |                                   |      | 2,5 | 5,3 | 9,4  | 17,6 |
|                                 | R90  |                                   |      | 1,9 | 3,6 | 6,1  | 11,5 |
|                                 | R120 |                                   |      | 1,6 | 2,8 | 4,5  | 8,4  |
| Steel failure with lever arm    |      |                                   |      |     |     |      |      |
| Steel, zinc plated              |      |                                   |      |     |     |      |      |
| Characteristic resistance       | R30  | M <sup>0</sup> <sub>Rk,s,fi</sub> | [Nm] | 1,5 | 3,3 | 6,4  | 16,3 |
|                                 | R60  |                                   |      | 1,2 | 2,5 | 4,7  | 11,9 |
|                                 | R90  |                                   |      | 0,8 | 1,7 | 3,0  | 7,5  |
|                                 | R120 |                                   |      | 0,6 | 1,2 | 2,1  | 5,3  |
| Stainless steel A4, HCR         |      |                                   |      |     |     |      |      |
| Characteristic resistance       | R30  | M <sup>0</sup> <sub>Rk,s,fi</sub> | [Nm] | 3,2 | 8,9 | 19,7 | 50,1 |
|                                 | R60  |                                   |      | 2,6 | 6,8 | 14,6 | 37,2 |
|                                 | R90  |                                   |      | 2,0 | 4,7 | 9,5  | 24,2 |
|                                 | R120 |                                   |      | 1,6 | 3,6 | 7,0  | 17,8 |

**Clawbolt Pro EAW und EIW**

**Performance**

Characteristic values for tension and shear load under fire exposure, Clawbolt Pro EAW, reduced anchorage depth, cracked and uncracked concrete C20/25 to C50/60

**Annex C8**

**Table C9: Displacements under tension load, Clawbolt Pro EAW**

| Fastener size                                       |                       |      | M8  | M10  | M12  | M16  | M20  | M24  | M27 |
|---|-----------------------|------|-----|------|------|------|------|------|-----|
| Standard anchorage depth                            |                       |      |     |      |      |      |      |      |     |
| Steel zinc plated                                   |                       |      |     |      |      |      |      |      |     |
| Tension load in cracked concrete                    | N                     | [kN] | 2,4 | 4,3  | 7,6  | 11,9 | 17,1 | 21,1 | 24  |
| Displacement  | $\delta_{N0}$         | [mm] | 0,6 | 1,0  | 0,4  | 1,0  | 0,9  | 0,7  | 0,9 |
|   | $\delta_{N\infty}$    | [mm] | 1,4 | 1,2  | 1,4  | 1,3  | 1,0  | 1,2  | 1,4 |
| Tension load in uncracked concrete                  | N                     | [kN] | 5,7 | 7,6  | 11,9 | 16,7 | 23,8 | 29,6 | 34  |
| Displacement  | $\delta_{N0}$         | [mm] | 0,4 | 0,5  | 0,7  | 0,3  | 0,4  | 0,5  | 0,3 |
|   | $\delta_{N\infty}$    | [mm] | 0,8 |      | 1,4  | 0,8  |      |      | 1,4 |
| Displacements under seismic tension loads <b>C2</b> |                       |      |     |      |      |      |      |      |     |
| Displacements for DLS                               | $\delta_{N,eq,(DLS)}$ | [mm] | 2,3 | 4,1  | 4,9  | 3,6  | 5,1  | _1)  | _1) |
| Displacements for ULS                               | $\delta_{N,eq,(ULS)}$ | [mm] | 8,2 | 13,8 | 15,7 | 9,5  | 15,2 |      |     |
| Stainless steel A4, HCR                             |                       |      |     |      |      |      |      |      |     |
| Tension load in cracked concrete                    | N                     | [kN] | 2,4 | 4,3  | 7,6  | 11,9 | 17,1 | 19,0 | _1) |
| Displacement  | $\delta_{N0}$         | [mm] | 0,7 | 1,8  | 0,4  | 0,7  | 0,9  | 0,5  |     |
|   | $\delta_{N\infty}$    | [mm] | 1,2 | 1,4  | 1,4  | 1,4  | 1,0  | 1,8  |     |
| Tension load in uncracked concrete                  | N                     | [kN] | 5,8 | 7,6  | 11,9 | 16,7 | 23,8 | 33,5 | _1) |
| Displacement  | $\delta_{N0}$         | [mm] | 0,6 | 0,5  | 0,7  | 0,2  | 0,4  | 0,5  |     |
|   | $\delta_{N\infty}$    | [mm] | 1,2 | 1,0  | 1,4  | 0,4  | 0,8  | 1,1  |     |
| Displacements under seismic tension loads <b>C2</b> |                       |      |     |      |      |      |      |      |     |
| Displacements for DLS                               | $\delta_{N,eq,(DLS)}$ | [mm] | 2,3 | 4,1  | 4,9  | 3,6  | 5,1  | _1)  | _1) |
| Displacements for ULS                               | $\delta_{N,eq,(ULS)}$ | [mm] | 8,2 | 13,8 | 15,7 | 9,5  | 15,2 |      |     |
| Reduced anchorage depth                             |                       |      |     |      |      |      |      |      |     |
| Steel zinc plated, stainless steel A4, HCR          |                       |      |     |      |      |      |      |      |     |
| Tension load in cracked concrete                    | N                     | [kN] | 2,4 | 3,6  | 6,1  | 9,0  | _1)  | _1)  | _1) |
| Displacement  | $\delta_{N0}$         | [mm] | 0,8 | 0,7  | 0,5  | 1,0  |      |      |     |
|   | $\delta_{N\infty}$    | [mm] | 1,2 | 1,0  | 0,8  | 1,1  |      |      |     |
| Tension load in uncracked concrete                  | N                     | [kN] | 3,7 | 4,3  | 8,5  | 12,6 | _1)  | _1)  | _1) |
| Displacement  | $\delta_{N0}$         | [mm] | 0,1 | 0,2  | 0,2  | 0,2  |      |      |     |
|   | $\delta_{N\infty}$    | [mm] | 0,7 | 0,7  | 0,7  | 0,7  |      |      |     |

<sup>1)</sup> No performance assessed

**Clawbolt Pro EAW und EIW**

**Performance**  
Displacements under tension load, Clawbolt Pro EAW

**Annex C9**

**Table C10: Displacements under shear load, Clawbolt Pro EAW**

| Fastener size                                |                      |      | M8  | M10  | M12  | M16  | M20  | M24  | M27  |
|--|----------------------|------|-----|------|------|------|------|------|------|
| Standard anchorage depth                     |                      |      |     |      |      |      |      |      |      |
| Steel zinc plated                            |                      |      |     |      |      |      |      |      |      |
| Shear load in cracked and uncracked concrete | V                    | [kN] | 6,9 | 11,4 | 17,1 | 31,4 | 36,8 | 64,9 | 96,8 |
| Displacement                                 | $\delta_{V0}$        | [mm] | 2,0 | 3,2  | 3,6  | 3,5  | 1,8  | 3,5  | 3,6  |
|  | $\delta_{V\infty}$   | [mm] | 3,0 | 4,7  | 5,5  | 5,3  | 2,7  | 5,3  | 5,4  |
| Displacements under seismic shear loads C2   |                      |      |     |      |      |      |      |      |      |
| Displacements for DLS                        | $\delta_{V,eq(DLS)}$ | [mm] | 3,0 | 2,7  | 3,5  | 4,3  | 4,7  | _1)  | _1)  |
| Displacements for ULS                        | $\delta_{V,eq(ULS)}$ | [mm] | 5,9 | 5,3  | 9,5  | 9,6  | 10,1 |      |      |
| Stainless steel A4, HCR                      |                      |      |     |      |      |      |      |      |      |
| Shear load in cracked and uncracked concrete | V                    | [kN] | 7,3 | 11,4 | 17,1 | 31,4 | 43,8 | 70,6 | _1)  |
| Displacement                                 | $\delta_{V0}$        | [mm] | 1,9 | 2,4  | 4,0  | 4,3  | 2,9  | 2,8  |      |
|  | $\delta_{V\infty}$   | [mm] | 2,9 | 3,6  | 5,9  | 6,4  | 4,3  | 4,2  |      |
| Displacements under seismic shear loads C2   |                      |      |     |      |      |      |      |      |      |
| Displacements for DLS                        | $\delta_{V,eq(DLS)}$ | [mm] | 3,0 | 2,7  | 3,5  | 4,3  | 4,7  | _1)  | _1)  |
| Displacements for ULS                        | $\delta_{V,eq(ULS)}$ | [mm] | 5,9 | 5,3  | 9,5  | 9,6  | 10,1 |      |      |
| Reduced anchorage depth                      |                      |      |     |      |      |      |      |      |      |
| Steel zinc plated                            |                      |      |     |      |      |      |      |      |      |
| Shear load in cracked and uncracked concrete | V                    | [kN] | 6,9 | 11,4 | 17,1 | 31,4 | _1)  | _1)  | _1)  |
| Displacement                                 | $\delta_{V0}$        | [mm] | 2,0 | 3,2  | 3,6  | 3,5  |      |      |      |
|  | $\delta_{V\infty}$   | [mm] | 3,0 | 4,7  | 5,5  | 5,3  |      |      |      |
| Stainless steel A4, HCR                      |                      |      |     |      |      |      |      |      |      |
| Shear load in cracked and uncracked concrete | V                    | [kN] | 7,3 | 11,4 | 17,1 | 31,4 | _1)  | _1)  | _1)  |
| Displacement                                 | $\delta_{V0}$        | [mm] | 1,9 | 2,4  | 4,0  | 4,3  |      |      |      |
|  | $\delta_{V\infty}$   | [mm] | 2,9 | 3,6  | 5,9  | 6,4  |      |      |      |

<sup>1)</sup> No performance assessed

**Clawbolt Pro EAW und EIW**

**Performance**  
Displacements under shear load, Clawbolt Pro EAW

**Annex C10**

**Table C11: Characteristic values for tension loads, Clawbolt Pro EIW, cracked concrete, static and quasi-static action**

| Fastener size  |                  |      | M6                                     | M8   | M10  | M12  |
|--|------------------|------|--|------|------|------|
| Installation factor  | $\gamma_{inst}$  | [-]  | 1,2                                    |      |      |      |
| Steel failure  |                  |      |  |      |      |      |
| Characteristic resistance,<br>steel zinc plated                      | $N_{Rk,s}$       | [kN] | 16,1                                   | 22,6 | 26,0 | 56,6 |
| Partial factor   | $\gamma_{Ms}$    | [-]  | 1,5                                    |      |      |      |
| Characteristic resistance,<br>stainless steel A4, HCR                | $N_{Rk,s}$       | [kN] | 14,1                                   | 25,6 | 35,8 | 59,0 |
|  | $\gamma_{Ms}$    | [-]  | 1,87                                   |      |      |      |
| Pull-out failure   |                  |      |  |      |      |      |
| Characteristic resistance in<br>cracked concrete C20/25              | $N_{Rk,p}$       | [kN] | 5                                      | 9    | 12   | 20   |
| Increasing factor for<br>$N_{Rk,p} = \psi_c \cdot N_{Rk,p}$ (C20/25) | $\psi_c$         | [-]  | $\left(\frac{f_{ck}}{20}\right)^{0,5}$ |      |      |      |
| Concrete cone failure  |                  |      |  |      |      |      |
| Effective anchorage depth  | $h_{ef}$         | [mm] | 45                                     | 58   | 65   | 80   |
| Factor for cracked concrete  | $k_1 = k_{cr,N}$ | [-]  | 7,7                                    |      |      |      |

**Clawbolt Pro EAW und EIW**

**Performance**

Characteristic values for tension loads, Clawbolt Pro EIW, cracked concrete, static and quasi-static action

**Annex C11**

**Table C12:** Characteristic values for **tension loads, Clawbolt Pro EIW, uncracked concrete**, static and quasi-static action

| Fastener size   |                   |      | M6                                     | M8   | M10  | M12  |
|---|-------------------|------|--|------|------|------|
| Installation factor   | $\gamma_{inst}$   | [-]  | 1,2                                    |      |      |      |
| Steel failure   |                   |      |  |      |      |      |
| Characteristic resistance,<br>steel zinc plated   | $N_{Rk,s}$        | [kN] | 16,1                                   | 22,6 | 26,0 | 56,6 |
| Partial factor  | $\gamma_{Ms}$     | [-]  | 1,5                                    |      |      |      |
| Characteristic resistance,<br>stainless steel A4, HCR   | $N_{Rk,s}$        | [kN] | 14,1                                   | 25,6 | 35,8 | 59,0 |
| Partial factor  | $\gamma_{Ms}$     | [-]  | 1,87                                   |      |      |      |
| Pull-out  |                   |      |  |      |      |      |
| Characteristic resistance in<br>uncracked concrete C20/25   | $N_{Rk,p}$        | [kN] | 12                                     | 16   | 20   | 30   |
| Splitting (the higher resistance of Case 1 and Case 2 may be applied)   |                   |      |  |      |      |      |
| Minimum thickness of concrete<br>member   | $h_{min}$         | [mm] | 100                                    | 120  | 130  | 160  |
| Case 1  |                   |      |  |      |      |      |
| Characteristic resistance in<br>uncracked concrete C20/25   | $N^0_{Rk,sp}$     | [kN] | 9                                      | 12   | 16   | 25   |
| Edge distance   | $c_{cr,sp}$       | [mm] | 1,5 $h_{ef}$                           |      |      |      |
| Case 2  |                   |      |  |      |      |      |
| Characteristic resistance in<br>uncracked concrete C20/25   | $N^0_{Rk,sp}$     | [kN] | 12                                     | 16   | 20   | 30   |
| Edge distance   | $c_{cr,sp}$       | [mm] | 2,5 $h_{ef}$                           |      |      |      |
| Increasing factor for<br>$N_{Rk,p} = \psi_c \cdot N_{Rk,p}$ (C20/25)<br>$N^0_{Rk,sp} = \psi_c \cdot N^0_{Rk,sp}$ (C20/25) | $\psi_c$          | [-]  | $\left(\frac{f_{ck}}{20}\right)^{0,5}$ |      |      |      |
| Concrete cone failure   |                   |      |  |      |      |      |
| Effective anchorage depth   | $h_{ef}$          | [mm] | 45                                     | 58   | 65   | 80   |
| Factor for uncracked concrete   | $k_1 = k_{ucr,N}$ | [-]  | 11,0                                   |      |      |      |

**Clawbolt Pro EAW und EIW**

**Performance**  
Characteristic values for **tension loads, Clawbolt Pro EIW, uncracked concrete**, static and quasi-static action

**Annex C12**

**Table C13: Characteristic values for shear loads, Clawbolt Pro EIW, cracked and uncracked concrete, static and quasi-static action**

| Fastener size   |                 |      | M6   | M8   | M10  | M12   |
|---|-----------------|------|------|------|------|-------|
| Installation factor   | $\gamma_{inst}$ | [-]  | 1,0  |      |      |       |
| Clawbolt Pro EIWMS, steel zinc plated                         |                 |      |      |      |      |       |
| Steel failure without lever arm, pre-setting installation     |                 |      |      |      |      |       |
| Characteristic resistance                                     | $V^0_{Rk,s}$    | [kN] | 5,8  | 6,9  | 10,4 | 25,8  |
| Steel failure without lever arm, through-setting installation |                 |      |      |      |      |       |
| Characteristic resistance                                     | $V^0_{Rk,s}$    | [kN] | 5,1  | 7,6  | 10,8 | 24,3  |
| Steel failure with lever arm, pre-setting installation        |                 |      |      |      |      |       |
| Characteristic bending resistance                             | $M^0_{Rk,s}$    | [Nm] | 12,2 | 30,0 | 59,8 | 104,6 |
| Steel failure with lever arm, through-setting installation    |                 |      |      |      |      |       |
| Characteristic bending resistance                             | $M^0_{Rk,s}$    | [Nm] | 36,0 | 53,2 | 76,0 | 207   |
| Partial factor for $V_{Rk,s}$ and $M^0_{Rk,s}$                | $\gamma_{Ms}$   | [-]  | 1,25 |      |      |       |
| Ductility factor  | $k_7$           | [-]  | 1,0  |      |      |       |
| Clawbolt Pro EIW16 and EIWHR, stainless steel A4, HCR         |                 |      |      |      |      |       |
| Steel failure without lever arm, pre-setting installation     |                 |      |      |      |      |       |
| Characteristic resistance                                     | $V^0_{Rk,s}$    | [kN] | 5,7  | 9,2  | 10,6 | 23,6  |
| Partial factor  | $\gamma_{Ms}$   | [-]  | 1,25 |      |      |       |
| Steel failure without lever arm, through-setting installation |                 |      |      |      |      |       |
| Characteristic resistance                                     | $V^0_{Rk,s}$    | [kN] | 7,3  | 7,6  | 9,7  | 29,6  |
| Partial factor  | $\gamma_{Ms}$   | [-]  | 1,25 |      |      |       |
| Steel failure with lever arm, pre-setting installation        |                 |      |      |      |      |       |
| Characteristic bending resistance                             | $M^0_{Rk,s}$    | [Nm] | 10,7 | 26,2 | 52,3 | 91,6  |
| Partial factor  | $\gamma_{Ms}$   | [-]  | 1,56 |      |      |       |
| Steel failure with lever arm, through-setting installation    |                 |      |      |      |      |       |
| Characteristic bending resistance                             | $M^0_{Rk,s}$    | [Nm] | 28,2 | 44,3 | 69,9 | 191,2 |
| Partial factor  | $\gamma_{Ms}$   | [-]  | 1,25 |      |      |       |
| Ductility factor  | $k_7$           | [-]  | 1,0  |      |      |       |
| Concrete pry-out failure                                      |                 |      |      |      |      |       |
| Pry-out factor  | $k_8$           | [-]  | 1,5  | 1,5  | 2,0  | 2,0   |
| Concrete edge failure   |                 |      |      |      |      |       |
| Effective length of fastener in shear loading                 | $l_f$           | [mm] | 45   | 58   | 65   | 80    |
| Effective diameter of fastener                                | $d_{nom}$       | [mm] | 8    | 10   | 12   | 16    |

**Clawbolt Pro EAW und EIW**

**Performance**  
Characteristic values for shear loads, Clawbolt Pro EIW,  
cracked and uncracked concrete, static and quasi-static action

**Annex C13**

**Table C14: Characteristic values for tension and shear load under fire exposure, Clawbolt Pro EIW, cracked and uncracked concrete C20/25 to C50/60**

| Fastener size                   |      |                 | M6   | M8  | M10 | M12  |      |
|---------------------------------|------|-----------------|------|-----|-----|------|------|
| Tension load                    |      |                 |      |     |     |      |      |
| Steel failure                   |      |                 |      |     |     |      |      |
| Steel zinc plated               |      |                 |      |     |     |      |      |
| Characteristic resistance       | R30  | $N_{Rk,s,fi}$   | [kN] | 0,7 | 1,4 | 2,5  | 3,7  |
|                                 | R60  |                 |      | 0,6 | 1,2 | 2,0  | 2,9  |
|                                 | R90  |                 |      | 0,5 | 0,9 | 1,5  | 2,2  |
|                                 | R120 |                 |      | 0,4 | 0,8 | 1,3  | 1,8  |
| Stainless steel A4, HCR         |      |                 |      |     |     |      |      |
| Characteristic resistance       | R30  | $N_{Rk,s,fi}$   | [kN] | 2,9 | 5,4 | 8,7  | 12,6 |
|                                 | R60  |                 |      | 1,9 | 3,8 | 6,3  | 9,2  |
|                                 | R90  |                 |      | 1,0 | 2,1 | 3,9  | 5,7  |
|                                 | R120 |                 |      | 0,5 | 1,3 | 2,7  | 4,0  |
| Shear load                      |      |                 |      |     |     |      |      |
| Steel failure without lever arm |      |                 |      |     |     |      |      |
| Steel zinc plated               |      |                 |      |     |     |      |      |
| Characteristic resistance       | R30  | $V_{Rk,s,fi}$   | [kN] | 0,7 | 1,4 | 2,5  | 3,7  |
|                                 | R60  |                 |      | 0,6 | 1,2 | 2,0  | 2,9  |
|                                 | R90  |                 |      | 0,5 | 0,9 | 1,5  | 2,2  |
|                                 | R120 |                 |      | 0,4 | 0,8 | 1,3  | 1,8  |
| Stainless steel A4, HCR         |      |                 |      |     |     |      |      |
| Characteristic resistance       | R30  | $V_{Rk,s,fi}$   | [kN] | 2,9 | 5,4 | 8,7  | 12,6 |
|                                 | R60  |                 |      | 1,9 | 3,8 | 6,3  | 9,2  |
|                                 | R90  |                 |      | 1,0 | 2,1 | 3,9  | 5,7  |
|                                 | R120 |                 |      | 0,5 | 1,3 | 2,7  | 4,0  |
| Steel failure with lever arm    |      |                 |      |     |     |      |      |
| Steel zinc plated               |      |                 |      |     |     |      |      |
| Characteristic resistance       | R30  | $M^0_{Rk,s,fi}$ | [Nm] | 0,5 | 1,4 | 3,3  | 5,7  |
|                                 | R60  |                 |      | 0,4 | 1,2 | 2,6  | 4,6  |
|                                 | R90  |                 |      | 0,4 | 0,9 | 2,0  | 3,4  |
|                                 | R120 |                 |      | 0,3 | 0,8 | 1,6  | 2,8  |
| Stainless steel A4, HCR         |      |                 |      |     |     |      |      |
| Characteristic resistance       | R30  | $M^0_{Rk,s,fi}$ | [Nm] | 2,2 | 5,5 | 11,2 | 19,6 |
|                                 | R60  |                 |      | 1,5 | 3,9 | 8,1  | 14,3 |
|                                 | R90  |                 |      | 0,7 | 2,2 | 5,1  | 8,9  |
|                                 | R120 |                 |      | 0,4 | 1,3 | 3,5  | 6,2  |

**Clawbolt Pro EAW und EIW**

**Performance**

Characteristic values for **tension** and **shear loads** under **fire exposure**,  
**Clawbolt Pro EIW**, cracked and uncracked concrete C20/25 to C50/60

**Annex C14**



**Table C15: Displacements under tension load, Clawbolt Pro EIW**

| Fastener size                      |                    |      | M6  | M8  | M10 | M12  |
|------------------------------------|--------------------|------|-----|-----|-----|------|
| Tension load in cracked concrete   | N                  | [kN] | 2,0 | 3,6 | 4,8 | 8,0  |
| Displacements                      | $\delta_{N0}$      | [mm] | 0,6 | 0,6 | 0,8 | 1,0  |
|                                    | $\delta_{N\infty}$ | [mm] | 0,8 | 0,8 | 1,2 | 1,4  |
| Tension load in uncracked concrete | N                  | [kN] | 4,8 | 6,4 | 8,0 | 12,0 |
| Displacements                      | $\delta_{N0}$      | [mm] | 0,4 | 0,5 | 0,7 | 0,8  |
|                                    | $\delta_{N\infty}$ | [mm] | 0,8 | 0,8 | 1,2 | 1,4  |

**Table C16: Displacements under shear load, Clawbolt Pro EIW**

| Fastener size                                |                    |      | M6  | M8  | M10 | M12  |
|--|--------------------|------|-----|-----|-----|------|
| Shear load in cracked and uncracked concrete | V                  | [kN] | 4,2 | 5,3 | 6,2 | 16,9 |
| Displacements                                | $\delta_{V0}$      | [mm] | 2,8 | 2,9 | 2,5 | 3,6  |
|  | $\delta_{V\infty}$ | [mm] | 4,2 | 4,4 | 3,8 | 5,3  |

**Clawbolt Pro EAW und EIW**

**Performance**

Displacements under tension load and under shear load, **Clawbolt Pro EIW**

**Annex C15**