

Public-law institution jointly founded by the federal states and the Federation

European Technical Assessment Body
for construction products



European Technical Assessment

ETA-21/0969
of 2 March 2026

English translation prepared by DIBt - Original version in German language

General Part

Technical Assessment Body issuing the European Technical Assessment:

Deutsches Institut für Bautechnik

Trade name of the construction product

Connector Hilti HUS4-H

Product family to which the construction product belongs

Connector for Strengthening of existing concrete structures by concrete overlay

Manufacturer

Hilti Aktiengesellschaft
Feldkircherstrasse 100
9494 SCHAAN
FÜRSTENTUM LIECHTENSTEIN

Manufacturing plant

Hilti Werke

This European Technical Assessment contains

19 pages including 3 annexes which form an integral part of this assessment

This European Technical Assessment is issued in accordance with Article 95(4) of Regulation (EU) No 2024/3110, on the basis of

EAD 332347-00-0601-v01

This version replaces

ETA-21/0969 issued on 16 May 2022

The European Technical Assessment is issued by the Technical Assessment Body in its official language. Translations of this European Technical Assessment in other languages shall fully correspond to the original issued document and shall be identified as such.

Communication of this European Technical Assessment, including transmission by electronic means, shall be in full. However, partial reproduction may only be made with the written consent of the issuing Technical Assessment Body. Any partial reproduction shall be identified as such.

This European Technical Assessment may be withdrawn by the issuing Technical Assessment Body, in particular pursuant to information by the Commission in accordance with Article 36(3) of Regulation (EU) No 2024/3110.

Specific Part

1 Technical description of the product

The Connector Hilti HUS4-H is a concrete screw made of galvanized steel anchored into a predrilled cylindrical drill hole in existing concrete. The special thread of the concrete screw cuts an internal thread into the member while setting. The Hilti HUS4-H is connecting two layers of concrete cast at different times (existing concrete and concrete overlay). The side with head of concrete screw is finally embedded in the concrete overlay.

The product description is given in Annex A.

2 Specification of the intended use in accordance with the applicable European Assessment Document

The performances given in Section 3 are only valid if the anchor is used in compliance with the specifications and conditions given in Annex B.

The verifications and assessment methods on which this European Technical Assessment is based lead to the assumption of a working life of the anchor of at least 50 years. The indications given on the working life cannot be interpreted as a guarantee given by the producer, but are to be regarded only as a means for choosing the right products in relation to the expected economically reasonable working life of the works.

3 Performance of the product and references to the methods used for its assessment

3.1 Mechanical resistance and stability (BWR 1)

Essential characteristic	Performance
Existing concrete, characteristic resistance to tension load (static and quasi-static loading): - resistances, robustness, edge distance to prevent splitting - minimum edge distance and spacing	See Annex C1, C2 and C3 See Annex B2, B3 and B4
Existing concrete, characteristic resistance for seismic performance categories C1 and C2	See Annex C5 and C6
Concrete overlay, characteristic resistance to tension load (static and quasi-static loading): - resistances, edge distance to prevent splitting - minimum edge distance and spacing	See Annex C4 See Annex B2, B3 and B4
Concrete overlay, characteristic resistance for seismic performance categories C1 and C2	See Annex C7
Shear interface parameter under static and quasi-static, fatigue and seismic cyclic loading - material and geometric parameters - factor for fatigue cyclic loading	See Annex C8 No performance assessed

3.2 Safety in case of fire (BWR 2)

Essential characteristic	Performance
Reaction to fire	Class A1

4 Assessment and verification of constancy of performance (AVCP) system applied, with reference to its legal base

In accordance with European Assessment Document EAD No. 332347-00-0601-v01 the applicable European legal act is: [96/582/EC].

The system to be applied is: 1

5 Technical details necessary for the implementation of the AVCP system, as provided for in the applicable European Assessment Document

Technical details necessary for the implementation of the AVCP system are laid down in the control plan deposited with Deutsches Institut für Bautechnik.

Issued in Berlin on 2 March 2026 by Deutsches Institut für Bautechnik

Dipl.-Ing. Beatrix Wittstock
Head of Section


beglaubigt:
Tempel

Installed condition

Connector Hilti HUS4-H

Existing concrete

Concrete overlay

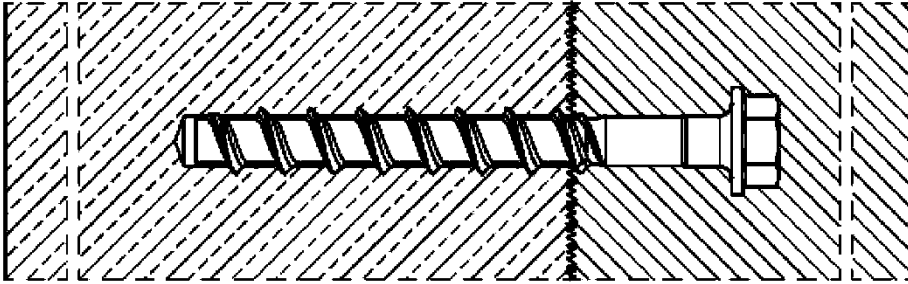

Connector Hilti HUS4-H

Product description
Installed condition

Annex A1

Product description: Connector


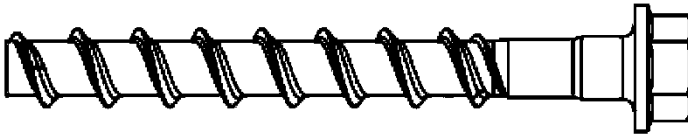


Table A1: Materials

Part	Material
Connector HUS4-H	Carbon steel Rupture elongation $A_5 \leq 8\%$

Table A2: Connector dimensions and marking HUS4-H

Connector HUS4-H	8			10			12			14			16		16 G02		
Nominal diameter d [mm]	8			10			12			14			16		16		
Nominal embedment depth h_{nom} [mm]	1	2	3	1	2	3	1	2	3	1	2	3	1	2	1	2	3
	40	60	70	55	75	85	60	80	100	65	85	115	85	130	85	110	130
Length of connector min / max L [mm]	100 / 150			100 / 305			100 / 150			130 / 150			140 / 205		140 / 205		
Thickness of head t_h [mm]	7,6			9,1			10,4			11,8			14,5		14,5		

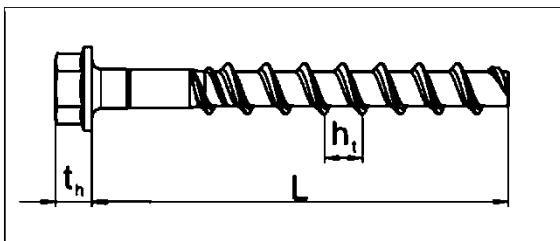

HUS4: Hilti Universal Screw 4th generation

H: Hexagonal head, galvanized

HF: Hexagonal head, multilayer coating

10: Nominal screw diameter d [mm]

100: Length of screw L [mm]

Connector Hilti HUS4-H

Annex A2

Product description
Materials and connector dimensions

Specifications of intended use

Anchorage subject to:

- Static and quasi-static loadings
- Seismic performance category C1 and C2
- Surface roughness “very smooth” to “very rough” of the shear interface acc. to EOTA Technical Report TR 066, Amendment November 2020

Base materials:

Connector for use to strengthen existing concrete by concrete overlay. Both concrete is compacted reinforced or unreinforced normal weight concrete without fibres with strength classes in the range C20/25 to C50/60 all in accordance with EN 206:2013 + A1:2016; cracked and uncracked concrete.


Design:

- The design of an anchorage and the specification of the fastener is under the control of an engineer experienced in anchorages and concrete work.
- Post-installed shear connections are designed in accordance with EOTA Technical Report TR 066, Amendment November 2020.
- For the concrete overlay following requirements on the mixture apply:
 - Concrete compressive strength of the new concrete shall be higher than the concrete compressive strength of the existing concrete.
 - Use of concrete with low shrinkage is recommended.
 - Slump of fresh concrete $f \geq 380$ mm, a slump value $f \geq 450$ mm is recommended, if applicable.

Installation:

- The fastener installation is executed by trained personnel, ensuring that the Installation instruction and the specifications are observed.
- Hammer drilling with cleaning for sizes 8 to 16.
- Hammer drilling with Hilti hollow drill bit TE-CD for sizes 12 and 14.
- Hammer drilling without cleaning for sizes 8 to 14.
- The requirements for construction works given in EOTA Technical Report TR 066, Amendment November 2020 have to be considered.

Installation parameters

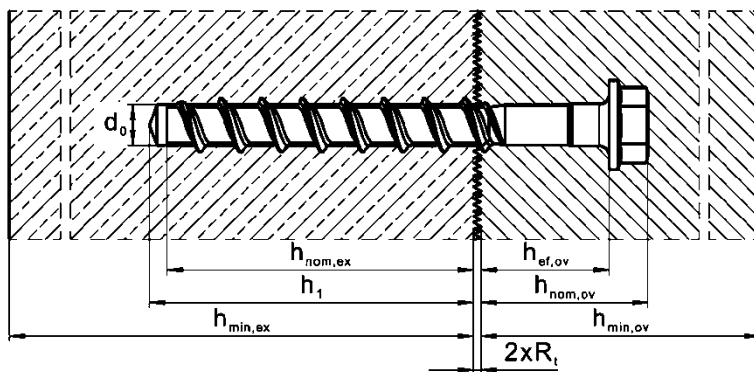

$h_{nom,ex}$ Nominal embedment depth in existing concrete
 h_1 Depth of drill hole
 h_{ex} Thickness of existing concrete
 R_t Roughness according EOTA Technical Report TR 066:2020-11

$h_{ef,ov}$ Effective embedment depth in concrete overlay
 $h_{nom,ov}$ Overall embedment depth in concrete overlay
 h_{ov} Thickness of concrete overlay

Connector Hilti HUS4-H

Intended Use
Specifications and Installation parameters

Annex B1

Table B1: Installation parameters HUS4-H size 8 and 10

Connector HUS4-H				8			10		
Existing concrete									
				h_{nom1}	h_{nom2}	h_{nom3}	h_{nom1}	h_{nom2}	h_{nom3}
Nominal embedment depth	$h_{nom,ex}$	[mm]		40	60	70	55	75	85
Nominal drill hole diameter	d_0	[mm]		8			10		
Cutting diameter of drill bit	$d_{cut} \leq$	[mm]		8,45			10,45		
Wrench size	s	[mm]		13			15		
Depth of drill hole for cleaned hole hammer drilling	$h_1 \geq$	[mm]		$h_{nom} + 10 \text{ mm}$					
				50	70	80	65	85	95
Depth of drill hole for uncleaned hole hammer drilling	$h_1 \geq$	[mm]		$h_{nom} + 25 \text{ mm}$			$h_{nom} + 30 \text{ mm}$		
				65	85	95	85	105	115
Minimum thickness of concrete member	$h_{min,ex} \geq$	[mm]		$h_1 + 30 \text{ mm}$					
				80	100	120	100	130	140
Minimum spacing	$s_{min,ex} \geq$	[mm]		35			40		
Minimum edge distance	$c_{min,ex} \geq$	[mm]		35			40		
Hilti Setting tool ¹⁾				SIW 4(AT)-22 SIW 6(AT)-A22 SIW 6(AT)-22 gear 1			SIW 6(AT)-22 SIW 22T-A SIW 8-22 gear 1 SIW 9-A22		
Concrete overlay									
Effective embedment depth	$\frac{\min}{\max}$	$h_{ef,ov}$	[mm]	40					
				$L - h_{nom,ex} - 2 \cdot R_t$ ²⁾					
Overall embedment depth		$h_{nom,ov}$	[mm]	$h_{ef,ov} + t_h$					
Min. thickness of concrete overlay		$h_{min,ov} \geq$	[mm]	$h_{nom,ov} + c_{nom}$ ³⁾					
Minimum spacing		$s_{min,ov} \geq$	[mm]	40			45		
Minimum edge distance		$c_{min,ov} \geq$	[mm]	$10 + c_{nom}$ ³⁾			$15 + c_{nom}$ ³⁾		

¹⁾ Installation with other impact screw driver of equivalent power is possible.

²⁾ "R_t" Roughness according to EOTA Technical Report TR 066:2020-11.

³⁾ "c_{nom}" Nominal concrete cover according to EN 1992-1-1:2004 + AC:2010

Connector Hilti HUS4-H

Intended use
Installation parameters

Annex B2

Table B2: Installation parameters HUS4-H size 12 and 14

Connector size HUS4-H			12			14		
Existing concrete								
			h_{nom1}	h_{nom2}	h_{nom3}	h_{nom1}	h_{nom2}	h_{nom3}
Nominal embedment depth	$h_{nom,ex}$	[mm]	60	80	100	65	85	115
Nominal drill hole diameter	d_0	[mm]	12			14		
Cutting diameter of drill bit	$d_{cut} \leq$	[mm]	12,5			14,5		
Wrench size	s	[mm]	17			21		
Depth of drill hole for cleaned hole hammer drilling	$h_1 \geq$	[mm]	$h_{nom} + 10 \text{ mm}$					
			70	90	110	75	95	125
Depth of drill hole for uncleaned hole hammer drilling	$h_1 \geq$	[mm]	$h_{nom} + 35$			$h_{nom} + 40$		
			95	115	135	105	125	155
Minimum thickness of concrete member	$h_{min,ex} \geq$	[mm]	$h_1 + 30 \text{ mm}$					
			110	130	150	120	160	200
Minimum spacing	$s_{min,ex} \geq$	[mm]	50			60		
Minimum edge distance	$c_{min,ex} \geq$	[mm]	50			60		
Hilti Setting tool ¹⁾			SIW 6(AT)-22 SIW 22T-A SIW 8-22 gear 1 SIW 9-A22			SIW 22T-A SIW 6(AT)-22 SIW 8-22 SIW 9-A22		
Concrete overlay								
Effective embedment depth	$\frac{\min}{\max}$	$h_{ef,ov}$	40					
		[mm]	$L - h_{nom,ex} - 2 \cdot R_t$ ²⁾					
Overall embedment depth	$h_{nom,ov}$	[mm]	$h_{ef,ov} + t_h$					
Min. thickness of concrete overlay	$h_{min,ov} \geq$	[mm]	$h_{nom,ov} + c_{nom}$ ³⁾					
Minimum spacing	$s_{min,ov} \geq$	[mm]	50			60		
Minimum edge distance	$c_{min,ov} \geq$	[mm]	$15 + c_{nom}$ ³⁾			$15 + c_{nom}$ ³⁾		

¹⁾ Installation with other impact screw driver of equivalent power is possible.

²⁾ "R_t" Roughness according to EOTA Technical Report TR 066:2020-11.

³⁾ "c_{nom}" Nominal concrete cover according to EN 1992-1-1:2004 + AC:2010

Connector Hilti HUS4-H

Intended use
Installation parameters

Annex B3

Table B3: Installation parameters HUS4-H size 16

Connector size HUS4-H			16		16 G02		
Existing concrete							
			h_{nom1}	h_{nom2}	h_{nom1}	h_{nom2}	h_{nom3}
Nominal embedment depth	$h_{nom,ex}$	[mm]	85	130	85	110	130
Nominal drill hole diameter	d_0	[mm]	16		16		
Cutting diameter of drill bit	$d_{cut} \leq$	[mm]	16,5		16,5		
Wrench size	s	[mm]	24		24		
Depth of drill hole for cleaned hole hammer drilling	$h_1 \geq$	[mm]	$h_{nom} + 10 \text{ mm}$				
			95	140	95	120	140
Depth of drill hole for uncleaned hole hammer drilling	$h_1 \geq$	[mm]	-		$h_{nom} + 40$		
			-	-	125	150	170
Minimum thickness of concrete member	$h_{min,ex} \geq$	[mm]	$h_1 + 35 \text{ mm}$				
			130	195	130	155	175
Minimum spacing	$s_{min,ex} \geq$	[mm]	90		70		
Minimum edge distance	$c_{min,ex} \geq$	[mm]	65		65		
Hilti Setting tool ¹⁾			SIW 22T-A SIW 6(AT)-22 SIW 8-22 SIW 9-A22 SIW 10-22		SIW 22T-A SIW 6(AT)-22 SIW 8-22 SIW 9-A22 SIW 10-22		
Concrete overlay							
Effective embedment depth	$\frac{\min}{\max}$	$h_{ef,ov}$	[mm]	40			
				$L - h_{nom,ex} - 2 \cdot R_t$ ²⁾			
Overall embedment depth		$h_{nom,ov}$	[mm]	$h_{ef,ov} + t_h$			
Min. thickness of concrete overlay		$h_{min,ov} \geq$	[mm]	$h_{nom,ov} + c_{nom}$ ³⁾			
Minimum spacing		$s_{min,ov} \geq$	[mm]	65			
Minimum edge distance		$c_{min,ov} \geq$	[mm]	$20 + c_{nom}$ ³⁾			

- 1) Installation with other impact screw driver of equivalent power is possible.
2) "R_t" Roughness according to EOTA Technical Report TR 066:2020-11.
3) "c_{nom}" Nominal concrete cover according to EN 1992-1-1:2004 + AC:2010

Connector Hilti HUS4-H


Intended use
Installation parameters

Annex B4


Installation instructions

Hole drilling and cleaning

Hammer drilling (HD) all sizes (size 16 with cleaning only)

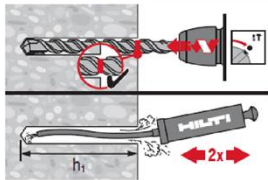


With cleaning
Drill hole depth h_1 according to Table B1 to B3.

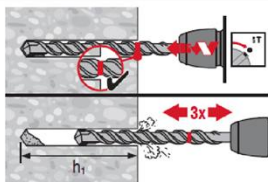


No cleaning is allowed when 3x ventilation¹⁾ after drilling is executed.
Drill hole depth $h_1 = h_{nom} + 10 \text{ mm} + 2 * d_0$ according to Table B1 to B3.
¹⁾ moving the drill bit in and out of the drill hole 3 times after the recommended drilling depth h_1 is achieved. This procedure shall be done with both revolution and hammer functions activated in the drilling machine. For more details read the relevant installation instruction (MPII).

Hammer drilling with Hilti hollow drill bit (HDB) TE-CD size 12 to 14.

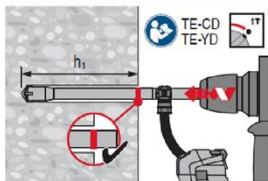


No cleaning needed.
Drill hole depth h_1 according to Table B1 to B3


Connector setting

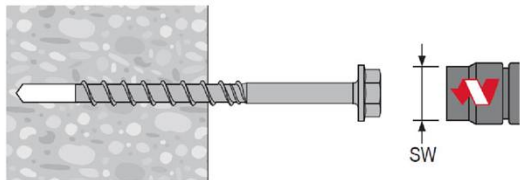


Install the screw anchor by impact screw driver.

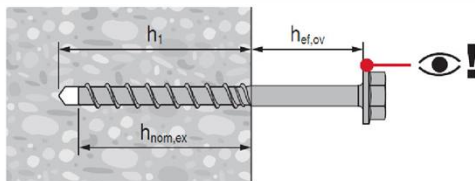

Set the HUS4-H to the desired anchoring embedment depth $h_{nom,ex}$ in existing concrete and ensure the desired embedment depth $h_{ef,ov}$ for concrete overlay.

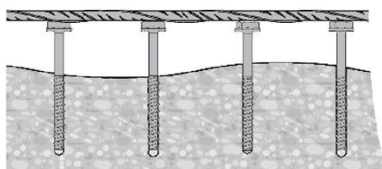

After connector installation, the rebar connections can be done to the connectors.

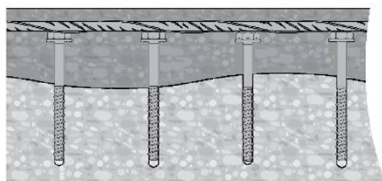

Observe the required condition of the surface before casting and the use of the correct concrete composition.

Connector Hilti HUS4-H

Intended use
Installation instructions

Annex B5

Table C1: Essential characteristics of connector Hilti HUS4-H sizes 8 and 10 in existing concrete under static and quasi-static tension load

Connector HUS4-H			8			10		
			h_{nom1}	h_{nom2}	h_{nom3}	h_{nom1}	h_{nom2}	h_{nom3}
Nominal embedment depth	$h_{nom,ex}$	[mm]	40	60	70	55	75	85
Steel failure								
Characteristic resistance	$N_{RK,s,ex}$	[kN]	36,0			55,0		
Partial factor	$\gamma_{Ms,N,ex}^{1)}$	[-]	1,5					
Pull-out failure								
Characteristic resistance in uncracked concrete C20/25	$N_{RK,p,ex}$	[kN]	$\geq N_{RK,c}^{0,2)}$			13	22	$\geq N_{RK,c}^{0,2)}$
Characteristic resistance in cracked concrete C20/25	$N_{RK,p,ex}$	[kN]	5,5	$\geq N_{RK,c}^{0,2)}$				
Increasing factor for $N_{RK,p} = N_{RK,p,ex(C20/25)} * \psi_{c,ex}$	$\psi_{c,ex}$	[-]	$(f_{ck}/20)^{0,5}$					
Concrete cone failure								
Effective embedment depth	$h_{ef,ex}$	[mm]	30,6	47,6	56,1	42,5	59,5	68,0
Factor for	uncracked concrete	$k_{ucr,N,ex}$	11,0					
	cracked concrete	$k_{cr,N,ex}$	7,7					
Concrete cone failure	Edge distance	$c_{cr,N,ex}$	$1,5 h_{ef}$					
	Spacing	$s_{cr,N,ex}$	$3 h_{ef}$					
Splitting failure	Edge distance	$c_{cr,sp,ex}$	$1,5 h_{ef}$			$1,65 h_{ef}$		
	Spacing	$s_{cr,sp,ex}$	$3 h_{ef}$			$3,3 h_{ef}$		
Installation factor	$\gamma_{inst,ex}$	[-]	1,0			1,2	1,0	

¹⁾ In absence of other national regulations.

²⁾ $N_{RK,c}$ according to EN 1992-4:2018

Connector Hilti HUS4-H

Performances
Essential characteristics in existing concrete under static and quasi-static tension load

Annex C1

Table C2: Essential characteristics of connector Hilti HUS4-H sizes 12 and 14 in existing concrete under static and quasi-static tension load

Connector HUS4-H			12			14		
			h_{nom1}	h_{nom2}	h_{nom3}	h_{nom1}	h_{nom2}	h_{nom3}
Nominal embedment depth	$h_{nom,ex}$	[mm]	60	80	100	65	85	115
Steel failure								
Characteristic resistance	$N_{Rk,s,ex}$	[kN]	79,0			101,5		
Partial factor	$\gamma_{Ms,N,ex}^{1)}$	[-]	1,5					
Pull-out failure								
Characteristic resistance in uncracked concrete C20/25	$N_{Rk,p,ex}$	[kN]	$\geq N_{Rk,c}^{2)}$					
Characteristic resistance in cracked concrete C20/25	$N_{Rk,p,ex}$	[kN]	10	$\geq N_{Rk,c}^{2)}$				
Increasing factor for $N_{Rk,p} = N_{Rk,p,ex(C20/25)} * \psi_{c,ex}$	$\psi_{c,ex}$	[-]	$(f_{ck}/20)^{0,5}$					
Concrete cone and splitting failure								
Effective embedment depth	$h_{ef,ex}$	[mm]	45,9	62,9	79,9	49,3	66,3	91,8
Factor for	uncracked concrete	$k_{ucr,N,ex}$	11,0					
	cracked concrete	$k_{cr,N,ex}$	7,7					
Concrete cone failure	Edge distance	$c_{cr,N,ex}$	$1,5 h_{ef}$					
	Spacing	$s_{cr,N,ex}$	$3 h_{ef}$					
Splitting failure	Edge distance	$c_{cr,sp,ex}$	$1,65 h_{ef}$			$1,60 h_{ef}$		
	Spacing	$s_{cr,sp,ex}$	$3,30 h_{ef}$			$3,20 h_{ef}$		
Installation factor	$\gamma_{inst,ex}$	[-]	1,0					

1) In absence of other national regulations.

2) $N_{Rk,c}$ according to EN 1992-4:2018

Connector Hilti HUS4-H

Performances

Essential characteristics in existing concrete under static and quasi-static tension load

Annex C2

Table C3: Essential characteristics of connector Hilti HUS4-H size 16 in existing concrete under static and quasi-static tension load

Connector HUS4-H			16		16 G02		
			h_{nom1}	h_{nom2}	h_{nom1}	h_{nom2}	h_{nom3}
Nominal embedment depth	$h_{nom,ex}$	[mm]	85	130	85	110	130
Steel failure							
Characteristic resistance	$N_{Rk,s,ex}$	[kN]	107,7		141,9		
Partial factor	$\gamma_{Ms,N,ex}^{1)}$	[-]	1,5				
Pull-out failure							
Characteristic resistance in uncracked concrete C20/25	$N_{Rk,p,ex}$	[kN]	22	46	$\geq N_{Rk,c}^{0,2)}$		
Characteristic resistance in cracked concrete C20/25	$N_{Rk,p,ex}$	[kN]	17	34	$\geq N_{Rk,c}^{0,2)}$		
Increasing factor for $N_{Rk,p} = N_{Rk,p,ex(C20/25)} * \psi_{c,ex}$	$\psi_{c,ex}$	[-]	$(f_{ck}/20)^{0,5}$				
Concrete cone and splitting failure							
Effective embedment depth	$h_{ef,ex}$	[mm]	66,6	104,9	66,1	87,3	104,3
Factor for	uncracked concrete	$k_{ucr,N,ex}$	11,0				
	cracked concrete	$k_{cr,N,ex}$	7,7				
Concrete cone failure	Edge distance	$c_{cr,N,ex}$	$1,5 h_{ef}$				
	Spacing	$s_{cr,N,ex}$	$3 h_{ef}$				
Required splitting area	$A_{sp,rqd}$	[mm]	-		$(N_{Rk,sp}^{0,2} + 2,81) / 0,000745$		
Splitting failure	Edge distance	$c_{cr,sp,ex}$	$1,60 h_{ef}$		$\min \left[\frac{A_{sp,rqd} + 0,8 \cdot (h_{min} - h_{ef})^2}{3,41 \cdot h_{min} - 0,59 \cdot h_{ef}} ; \frac{A_{sp,rqd}}{s_{min} \cdot \sqrt{8}} \right]$		
	Spacing	$s_{cr,sp,ex}$	$3,20 h_{ef}$		$\geq (1,50 \cdot h_{ef})$ $2,00 c_{cr,sp}$		
Installation factor	$\gamma_{inst,ex}$	[-]	1,0				

1) In absence of other national regulations.

2) $N_{Rk,c}^{0,2}$ according to EN 1992-4:2018

Connector Hilti HUS4-H

Performances

Essential characteristics in existing concrete under static and quasi-static tension load

Annex C3

Table C4: Essential characteristics of connector Hilti HUS4-H in concrete overlay under static and quasi-static tension load

Connector HUS4			8	10	12	14	16	16 G02
Steel failure								
Characteristic resistance	$N_{Rk,s,ov}$	[kN]	36,0	55,0	79,0	101,5	107,7	141,9
Partial factor	$\gamma_{Ms,N,ov}$	[-]	1,5					
Pull-out failure								
Projected area of the head	A_h	[mm ²]	187,1	249,1	320,5	510,9	637,3	584,7
Factor for	$\frac{\text{uncracked concrete}}{\text{cracked concrete}}$	k_2	10,5					
			7,5					
Concrete cone failure								
Effective embedment depth	$h_{ef,ov}$	min	40					
		max	$L - h_{nom,ex} - 2 \cdot R_t$ ¹⁾					
Factor for	$\frac{\text{uncracked concrete}}{\text{cracked concrete}}$	$k_{ucr,N,ov}$	12,7					
		$k_{cr,N,ov}$	8,9					
Edge distance	$c_{cr,N,ov}$	[mm]	1,5 h_{ef}					
Spacing	$s_{cr,N,ov}$	[mm]	3,0 h_{ef}					
Splitting failure								
Edge distance	$c_{cr,sp,ov}$	[mm]	3,0 h_{ef}					
Spacing	$s_{cr,sp,ov}$	[mm]	6,0 h_{ef}					
Blow-out failure								
Projected area of the head	A_h	[mm ²]	187,1	249,1	320,5	510,9	637,3	584,7
Factor for uncracked concrete	k_5	[-]	12,2					
Factor for cracked concrete		[-]	8,7					

¹⁾ "R_t" Roughness according to EOTA Technical Report TR 066:2020-11

Connector Hilti HUS4-H

Performances
Essential characteristics in concrete overlay under static and quasi-static tension load

Annex C4

Table C5: Essential characteristics of connector Hilti HUS4-H in existing concrete under seismic performance category C1

Connector HUS4-H	8		10		12		
	h_{nom2}	h_{nom3}	h_{nom2}	h_{nom3}	h_{nom1}	h_{nom2}	h_{nom3}
Nominal embedment depth $h_{nom,ex}$ [mm]	60	70	75	85	60	80	100
Steel failure for tension load							
Characteristic resistance $N_{RK,s,C1,ex}$ [kN]	36,0		55,0		79,0		
Partial factor $\gamma_{Ms,N}^{1)}$ [-]	1,5						
Pull-out failure							
Characteristic resistance in cracked concrete $N_{RK,p,C1,ex}$ [kN]	$\geq N_{RK,c}^{0,2)}$						

Connector HUS4-H	14			16		16 G02		
	h_{nom1}	h_{nom2}	h_{nom3}	h_{nom1}	h_{nom2}	h_{nom1}	h_{nom2}	h_{nom3}
Nominal embedment depth $h_{nom,ex}$ [mm]	65	85	115	85	130	85	110	130
Steel failure for tension load								
Characteristic resistance $N_{RK,s,C1,ex}$ [kN]	101,5			107,7		141,9		
Partial factor $\gamma_{Ms,N}^{1)}$ [-]	1,5							
Pull-out failure								
Characteristic resistance in cracked concrete $N_{RK,p,C1,ex}$ [kN]	$\geq N_{RK,c}^{0,2)}$			7,5	19,0	$\geq N_{RK,c}^{0,2)}$		

¹⁾ In absence of other national regulations.

²⁾ $N_{RK,c}^{0}$ according to EN 1992-4:2018

Connector Hilti HUS4-H

Performances

Essential characteristics in existing concrete under seismic performance category C1

Annex C5

Table C6: Essential characteristics of connector Hilti HUS4-H in existing concrete under seismic performance category C2

Connector HUS4-H		8		10		12		
		h_{nom2}	h_{nom3}	h_{nom2}	h_{nom3}	h_{nom1}	h_{nom2}	h_{nom3}
Nominal embedment depth	$h_{nom,ex}$ [mm]	60	70	75	85	60	80	100
Steel failure for tension load								
Characteristic resistance	$N_{RK,s,C2,ex}$ [kN]	36,0		55,0		79,0		
Partial factor	$\gamma_{Ms,N}^{1)}$ [-]	1,5						
Pull-out failure								
Characteristic resistance in cracked concrete	$N_{RK,p,C2,ex}$ [kN]	1,8	2,7	3,6	5,4	5,7	8,5	11,4

Connector HUS4-H		14			16 G02		
		h_{nom1}	h_{nom2}	h_{nom3}	h_{nom1}	h_{nom2}	h_{nom3}
Nominal embedment depth	$h_{nom,ex}$ [mm]	65	85	115	85	110	130
Steel failure for tension load							
Characteristic resistance	$N_{RK,s,C2,ex}$ [kN]	101,5			141,9		
Partial factor	$\gamma_{Ms,N}^{1)}$ [-]	1,5					
Pull-out failure							
Characteristic resistance in cracked concrete	$N_{RK,p,C2,ex}$ [kN]	5,4	8,9	17,7	10,8	18,5	25,3

¹⁾ In absence of other national regulations.

Connector Hilti HUS4-H

Annex C6

Performances

Essential characteristics in existing concrete under seismic performance category C2

Table C7: Essential characteristics of connector Hilti HUS4-H in concrete overlay under seismic performance category C1

Connector HUS4-H			8	10	12
Steel failure for tension load					
Characteristic resistance	$N_{Rk,s,C1,ov}$	[kN]	36,0	55,0	79,0
Partial factor	$\gamma_{Ms,N}^{1)}$	[-]	1,5		
Pull-out failure					
Characteristic resistance in cracked concrete	$N_{Rk,p,C1,ov}$	[kN]	$\geq N_{Rk,p,C1,ex}$		

Connector HUS4-H			14	16	16 G02
Steel failure for tension load					
Characteristic resistance	$N_{Rk,s,C1,ov}$	[kN]	101,5	107,7	141,9
Partial factor	$\gamma_{Ms,N}^{1)}$	[-]	1,5		
Pull-out failure					
Characteristic resistance in cracked concrete	$N_{Rk,p,C1,ov}$	[kN]	$\geq N_{Rk,p,C1,ex}$		

¹⁾ In absence of other national regulations.

Table C8: Essential characteristics of connector Hilti HUS4-H in concrete overlay under seismic performance category C2

Connector HUS4-H			8	10	12
Steel failure for tension load					
Characteristic resistance	$N_{Rk,s,C2,ov}$	[kN]	36,0	55,0	79,0
Partial factor	$\gamma_{Ms,N}^{1)}$	[-]	1,5		
Pull-out failure					
Characteristic resistance in cracked concrete	$N_{Rk,p,C2,ov}$	[kN]	$\geq N_{Rk,p,C1,ex}$		

Connector HUS4-H			14	16 G02
Steel failure for tension load				
Characteristic resistance	$N_{Rk,s,C2,ov}$	[kN]	101,5	141,9
Partial factor	$\gamma_{Ms,N}^{1)}$	[-]	1,5	
Pull-out failure				
Characteristic resistance in cracked concrete	$N_{Rk,p,C2,ov}$	[kN]	$\geq N_{Rk,p,C1,ex}$	

¹⁾ In absence of other national regulations.

Connector Hilti HUS4-H

Performances
Essential characteristics in concrete overlay under seismic performance category C1 and C2

Annex C7

Table C9: Essential characteristics of connector Hilti HUS4-H for the shear interface under static and quasi-static loading and seismic loading

Connector size HUS4-H			8	10	12			
Characteristic yield strength	f_{yk}	[N/mm ²]	606	639	613			
Product specific factor for ductility	α_{k1}	[-]	0,8					
Stressed cross section	A_s	[mm ²]	47,5	68,9	103,1			
Product specific factor for geometry	α_{k2}	[-]	1,0					
Factor for seismic cyclic loading and related minimum embedment depth in existing concrete and concrete overlay								
Nominal embedment depth	$h_{nom,ex} \geq$	[mm]	60	60	75	60	80	85
Effective embedment depth	$h_{ef,ov} \geq$	[mm]	40	40	40	40	40	60
Factor for seismic cyclic loading	α_{seis}	[-]	0,46	0,46	0,50	0,46	0,50	0,52

Connector size HUS4-H			14		16		16 G02		
Characteristic yield strength	f_{yk}	[N/mm ²]	582		494		608		
Product specific factor for ductility	α_{k1}	[-]	0,8						
Stressed cross section	A_s	[mm ²]	139,5		173,2		186,3		
Product specific factor for geometry	α_{k2}	[-]	1,0						
Factor for seismic cyclic loading and related minimum embedment depth in existing concrete and concrete overlay									
Nominal embedment depth	$h_{nom,ex} \geq$	[mm]	65	85	85	85	85	85	85
Effective embedment depth	$h_{ef,ov} \geq$	[mm]	40	40	60	40	60	40	60
Factor for seismic cyclic loading	α_{seis}	[-]	0,46	0,50	0,52	0,5	0,52	0,5	0,52

Connector Hilti HUS4-H

Performances
Essential characteristics for the shear interface under shear load

Annex C8